

Contractor's Report to the Board

Evaluation of Health Effects of Recycled Waste Tires in Playground and Track Products

Produced under contract by:



January 2007



STATE OF CALIFORNIA

Arnold Schwarzenegger
Governor

Linda S. Adams
Secretary, California Environmental Protection Agency

INTEGRATED WASTE MANAGEMENT BOARD

Margo Reid Brown
Board Chair

Wesley Chesbro
Board Member

Jeffrey Danzinger
Board Member

Rosalie Mulé
Board Member

Gary Petersen
Board Member

Vacant Position
Board Member

Mark Leary
Executive Director

For additional copies of this publication, contact:

Integrated Waste Management Board
Public Affairs Office, Publications Clearinghouse (MS-6)
1001 I Street
P.O. Box 4025
Sacramento, CA 95812-4025
www.ciwmb.ca.gov/Publications/
1-800-CA-WASTE (California only) or (916) 341-6306

Publication #622-06-013



Copies of this document originally provided by CIWMB were printed on recycled paper containing 100 percent postconsumer fiber.

Copyright © 2007 by the California Integrated Waste Management Board. All rights reserved. This publication, or parts thereof, may not be reproduced in any form without permission.

Prepared as part of contract number IWM-C2070, \$420,000

The California Integrated Waste Management Board (CIWMB) does not discriminate on the basis of disability in access to its programs. CIWMB publications are available in accessible formats upon request by calling the Public Affairs Office at (916) 341-6300. Persons with hearing impairments can reach the CIWMB through the California Relay Service, 1-800-735-2929.

Disclaimer: This report to the Board was produced under contract by the Office of Environmental Health Hazard Assessment of California Environmental Protection Agency. The statements and conclusions contained in this report are those of the contractor and not necessarily those of the California Integrated Waste Management Board, its employees, or the State of California and should not be cited or quoted as official Board policy or direction.

The State makes no warranty, expressed or implied, and assumes no liability for the information contained in the succeeding text. Any mention of commercial products or processes shall not be construed as an endorsement of such products or processes

Additional Resources: The CIWMB suggests that in order to make an informed decision as to whether rubberized products for your playground and track are best for your needs, you should review the ASTM standard F1292, "Standard Specification for Impact Attenuation of Surfacing Materials within the Use Zone of Playground Equipment," and the Handbook for Public Playground Safety, U.S. Consumer Product Safety Commission, Pub. No. 325, and ask your playground/track contractor and/or manufacturer about any safety concerns you may have.

Table of Contents

Page

List of Tables	ii
List of Figures	iv
Acknowledgments.....	v
Executive Summary	1
Chapter 1: Introduction	4
Chapter 2: Survey of CIWMB Playground Grantees 2001–2003: Playground Surface Types and Locations.....	6
Chapter 3: Substances Released by Recycled Tires: Values from the Published Literature	7
Chapter 4: Toxicity Reference Values for Substances Released by Recycled Tires	27
Chapter 5: Evaluation of Toxicity Due to Ingestion of Tire Shreds Based on the Existing Literature of Tire Leachate Studies.....	39
Chapter 6: Evaluation of Toxicity Due to Ingestion of Tire Shreds Based on OEHHA Gastric Digestion Simulation Study.....	53
Chapter 7: Evaluation of Toxicity Due to Chronic Hand-To-Mouth Behavior Based on OEHHA Wipe Sampling of Playground Surfaces.....	65
Chapter 8: A First-Step Evaluation of High School Running Tracks Containing Recycled Tire Rubber: Wipe Testing and Customer Satisfaction Survey.....	83
Chapter 9: Skin Sensitization Testing of Rubberized Playground Surfacing	86
Chapter 10: Ecotoxicity of Recycled Tires Including Yulupa Elementary School Tire Chips Fire	90
Chapter 11: Evaluating the Risk of Serious Head Injury Due to Falls on California Playground Surfaces Made of Recycled Tires	104
Abbreviations.....	129
Bibliography.....	131

All Appendices are included at the end of this report.

Appendix A: Raw Data From Gastric Digestion Experiment

Appendix B: Wipe Sampling Raw Data

Appendix C: Raw Data From Skin Sensitization Testing

List of Tables

Table 1. Substances released by whole tires or tire chips/shreds in laboratory and field studies	8
Table 2. Concentrations of metals leaching from tire shreds used in various civil engineering applications in the field or leaching in lab studies	16
Table 3. Concentrations of Volatile Organic Compounds (VOCs) released from tire shreds in various field applications and laboratory studies, and in ambient air samples	21
Table 4. Concentrations of Semi-Volatile Organic Compounds (sVOCs) released from tire shreds in various field applications and laboratory studies, and in some ambient environmental samples	24
Table 5. Concentrations of particulates in the air resulting from tire wear.....	26
Table 6: Metals: Oral route: Toxicity Values	28
Table 7: VOCs: Oral route: Toxicity Values	33
Table 8: sVOCs: Oral route: Toxicity Values.....	37
Table 9. Comparison of ingested dose to health-based screening level for an acute ingestion of tire-derived crumb/shreds by a child based on published studies of tire leachate: noncancer health effects. ...	41
Table 10. Average daily intakes of chemicals released by tires	47
Table 11. Hazard Quotients and Hazard Index for an Acute Ingestion of Chemicals Identified in Published Studies of Tire Leachate	49
Table 12. Increased cancer risk in a 3 year old following a one-time ingestion of 10 grams of shredded tires based on published tire leachate studies.....	51
Table 13. Composition of “Gastric Digestion” Solution	53
Table 14. Chemicals leaching from three shredded tire samples in “gastric digestion” experiment	54
Table 15. Hazard Quotients and Hazard Index for an Acute Ingestion of Chemicals Identified in OEHHA Gastric Digestion Simulation Experiment	56
Table 16. Comparison of ingested dose to health-based screening level for an acute ingestion of tire-derived shreds based on “gastric digestion” study: noncancer health effects.	58
Table 17. Increased cancer risk in a 3 year old following a one-time ingestion of 10 grams of shredded tires based on OEHHA “gastric digestion” study	63
Table 18. Chemicals detected by wipe sampling three rubberized playground surfaces.....	66
Table 19. Hand-to-floor contact rates for children.....	69
Table 20. Frequency of hand-to-mouth activity in children	69
Table 21. Factors considered in estimating dermal loading.....	70
Table 22. Time and/or frequency of playground use	71
Table 23. Dermal absorption rates of 20 chemicals found in published studies	72
Table 24. Estimated exposures from hand-to-mouth activity in a 15 kg three year old child at a playground where rubberized surfaces are present	73
Table 25. Playground-associated chemical exposures and associated noncancer screening values	74
Table 26. Estimated increased cancer risk from exposure to chrysene via hand-to-mouth activity in a child (ages 1-12) frequenting a playground with a rubberized surface.....	79
Table 27. Chemicals detected on a track surface made of recycled tires.....	83
Table 28. Track Coach Satisfaction Survey.....	84

Table 29. Soil analysis in the vicinity of recycled tires used in road/parking lot construction, a playground surface, or as a soil amendment.	92
Table 30. Groundwater analysis in the vicinity of recycled tires used in road and parking lot construction, and in underground test trenches.	96
Table 31. Toxicologic responses of sentinel organisms to recycled tire rubber and its leachate.....	98
Table 32. Advantages and disadvantages of different playground safety surfaces.....	106
Table 33. HIC standard compliance rates for playground surfaces: rubber vs wood	115
Table 34. Types of playground structures failing the HIC standard	115

List of Figures

Figure 1. Exposure model for children using rubberized playground surfaces	65
Figure 2: Triax2000 triaxial accelerometer.....	116
Figure 3: HIC as a function of G_{max}	117
Figure 4: HIC as a function of playground structure fall height.....	118
Figure 5: Percentages of playground structures on rubberized surfaces passing the HIC standard at increasing fall height.....	119
Figure 6: Numbers of failing structures (HIC > 1000) per rubberized playground surface.....	120
Figure 7: Percentages of playground structures with fall heights > 6 feet yielding HIC values < 1000 as a function of rubberized surface age.....	121
Figure 8. HIC as a function of surface age during the first two to three months following installation. .	122
Figure 9: Same as for Figure 8, except that for this playground the first measurement day was at four days after installation of the top layer.....	123
Figure 10: HIC values for four playground structures on a loose-fill surface of shredded tire rubber. ...	124
Figure 11: Temperature dependence of HIC measurements on a pour-in-place surface: cold to hot.	125
Figure 12: Temperature dependence of HIC measurements on a pour-in-place surface: hot to cold.	126
Figure 13: HIC as a function of fall height measured at two different surface temperatures: Playground I.	127
Figure 14: HIC as a function of fall height measured at two different surface temperatures: Playground II.	128

Acknowledgments

Project Director

Anna Fan, Ph.D.

Authors

Charles Vidair, Ph.D., Robert Haas, Ph.D. and Robert Schlag, M.Sc.

Reviewers

George Alexeeff, Ph.D., Robert Blaisdell, Ph.D., Linda Dickinson, B.Sc., Anna Fan, Ph.D., Poorni Iyer, Ph.D., Karen Randles, M.P.H., David Rice, Ph.D., Jim Sanborn, Ph.D., Todd Thalhamer, P.E., Roger Trent, Ph.D., Feng Tsai, Ph.D., and Barbara Washburn, Ph.D.

Administrative Support

Hermelinda Jimenez

We thank the following individuals for helping with this study: Amy Arcus, David Morry, Richard Sedman and Chuck Salocks of OEHHA; Linda Dickinson of the CIWMB; Myrto Petreas, Jarnail Garcha and Dinesh Chand of the DTSC; Andy of the Oakland Machine Works; Rolf Huber of the Canadian Playground Advisory Inc.; Paul Bamburak of Playground Clearing House, USA, Inc; Shirley Zhu of Berlex Inc.

Executive Summary

In response to the California Integrated Waste Management Board's (CIWMB) need to better understand the potential health risks to children using outdoor playground and track surfaces constructed from recycled waste tires, the Office of Environmental Health Hazard Assessment (OEHHA) conducted the following studies.

- The playground surfaces were evaluated for the release of chemicals that could cause toxicity in children following ingestion or dermal contact. Three routes of child exposure to chemicals in the rubber were considered: 1) ingestion of loose rubber tire shreds (acute exposure), 2) ingestion via hand-to-surface contact followed by hand-to-mouth contact (chronic exposure), and 3) skin sensitization via dermal contact (acute exposure).
- Playground surfaces constructed from recycled tires were tested for their ability to attenuate fall-related impacts.
- The potential of these rubberized surfaces to impact the local environment, including the local ecology, was also addressed through a discussion of the published literature.

Evaluation of toxicity due to ingestion of tire shreds based on the existing literature

OEHHA found 46 studies in the scientific literature that measured the release of chemicals by recycled tires in laboratory settings and in field studies where recycled tires were used in civil engineering applications: 49 chemicals were identified. Using the highest published levels of chemicals released by recycled tires, the likelihood for noncancer health effects was calculated for a one-time ingestion of ten grams of tire shreds by a typical three-year-old child; only exposure to zinc exceeded its health-based screening value (i.e., value promulgated by a regulatory agency such as OEHHA or U.S. EPA). Overall, we consider it unlikely that a one-time ingestion of tire shreds would produce adverse health effects. Seven of the chemicals leaching from tire shreds in published studies were carcinogens, yielding a 1.2×10^{-7} (1.2 in ten million) increased cancer risk for the one-time ingestion described above. This risk is well below the *di minimis* level of 1×10^{-6} (one in one million), generally considered an acceptable cancer risk due to its small magnitude compared to the overall cancer rate (OEHHA, 2006).

Evaluation of toxicity due to ingestion of tire shreds based on gastric digestion simulation

OEHHA conducted a gastric digestion experiment in which 22 chemicals were found to be released by tire shreds incubated for 21 hours at 37°C in a solution mimicking the gastric environment. OEHHA then compared the levels of released chemicals to their health-based screening values, assuming a young child ingested ten grams of tire shreds; all exposures were at or below the screening values suggesting a low risk of noncancer acute health effects. Five of the chemicals released by tire shreds in the gastric digestion experiment were carcinogens. If the released chemicals were ingested as a onetime event and averaged over a lifetime, the cancer risk would be 3.7×10^{-8} (3.7 in one hundred million). This risk is considerably below the *di minimis* risk level of 1×10^{-6} (one in one million), generally considered an acceptable cancer risk due to its small magnitude compared to the overall cancer rate (OEHHA, 2006). The assumption that the risk from a onetime exposure is equivalent to the risk from the same dose spread over a lifetime is uncertain, and may overestimate or underestimate the true risk.

Evaluation of toxicity due to chronic hand-to-surface-to-mouth activity

OEHHA performed wipe sampling of in-use playground surfaces containing recycled tire rubber; one metal (zinc) and four PAHs were measured at levels that were at least three times background. Assuming ingestion of the above five chemicals via chronic hand-to-mouth contact, exposures were below the corresponding chronic screening values, suggesting a low risk of

adverse noncancer health effects. From among the five chemicals identified by wipe sampling, the PAH chrysene is a carcinogen. Assuming playground use from 1 through 12 years of age, an increased cancer risk of 2.9×10^{-6} (2.9 in one million) was calculated due to the chronic ingestion of chrysene. This risk is slightly higher than the *de minimis* risk level of 1×10^{-6} (one in one million), generally considered an acceptable cancer risk due to its small magnitude compared to the overall cancer rate (OEHHA, 2006). Calculation of the 2.9×10^{-6} (2.9 in one million) value does not account for many uncertainties, some of which would decrease the risk while others would increase the risk.

Testing for skin sensitization by playground surfaces made of recycled tires

Since children commonly contact these rubberized surfaces with their hands and other body parts, and since natural rubber contains the proven skin sensitizer latex, OEHHA contracted a laboratory to perform skin sensitization testing of tire-derived surfacing. Skin sensitization testing in the guinea pig was performed by Product Safety Laboratories (Dayton, NJ) with tire-derived playground surfacing as well as with the synthetic rubber EPDM; no sensitization was observed, suggesting that these surfaces would not cause skin sensitization in children, nor would they be expected to elicit skin reactions in children already sensitized to latex.

Evaluating the potential for damage to the local environment and ecology

Following a fire in a playground surface made of chipped tires at the Yulupa Elementary School in Sonoma County, soil samples from under the playground contained levels of metals, VOCs, PAHs, dioxins and furans that were at or below background, suggesting a low risk to the local ecology. Also following the Yulupa fire, the air above the burn site was judged by U.S. EPA to pose no health risks to clean-up workers, and the soil/rubber mixture removed from the site was judged not to be hazardous waste, and could therefore be deposited in a designated class III waste facility.

Groundwater in contact with tire shreds contained elevated levels of many chemicals; however, those levels rapidly approached background a few feet outside of the tire trench. Additional published studies indicate that concentrated leachate produced in the laboratory from tire shreds, crumb rubber or whole tires was toxic in 19/31 studies to a variety of organisms including bacteria, algae, aquatic invertebrates, fish, frogs and plants; however, it is unlikely that the use of shredded tires in outdoor applications such as playground surfaces would result in the leaching during rain events of high enough concentrations of chemicals to cause such effects. Further, shredded tires used in applications above the ground water table, as is the case for playground surfaces, produced no toxicity in sentinel species.

Evaluation of potential injury from falls on playground surfaces made of recycled tires

Using an accelerometer to test impact attenuation by California playground surfaces made of recycled tires, OEHHA staff visited 32 rubberized playground surfaces, to determine if the state mandated (CCR sections 65700-65750) standard for head impact (Head Impact Criterion or HIC) of ≤ 1000 was being met. Only 31 percent of rubberized playground surfaces passed the HIC standard. This is compared to 100 percent for surfaces made of wood chips, although only five surfaces of wood chips were tested. As the fall heights of playground structures increased, the underlying rubberized playground surface was more likely to fail the HIC standard; however, even at fall heights of 9-12 feet, some rubberized surfaces passed the standard. HIC values were not affected by the age of the rubberized surface, either during the first 2-3 months following installation or during the first two years. HIC values of rubberized surfaces increased with increasing surface temperature; in one playground the HIC value measured at dawn increased almost 20 percent when measured again in the afternoon during the heat of the day. These data point out the importance of testing the impact attenuation of rubberized playground surfaces to ensure that they meet the safety standards already in place.

Unfortunately, our survey found a 69 percent failure rate for rubberized California playground surfaces using attenuation standards. Theoretically, failure and potential injuries could be prevented with better installation practices by contractors who had placed rubberized material too thin. Further, if the purchaser of the product would have sought certification of impact attenuation standards at the completion of the project, each playground's HIC value should have been assured. This represents a missed opportunity for prevention of playground fall injuries, which are estimated to be in the thousands and which include serious trauma such as brain injury.

Chapter 1: Introduction

Waste tires are being used increasingly as a primary component of children's playground surfaces and running tracks. In addition to the benefits of recycling, playground surfaces made from recycled tires have the potential to reduce child injury due to falls in the playground. CIWMB provides grant funds to schools and city recreation departments to construct outdoor playgrounds and tracks using recycled waste tires. To be thorough and diligent, and to assure no inadvertent adverse health consequences, CIWMB asked OEHHA to evaluate outdoor playground and track surfaces made of recycled tires for potential toxicity from chemical exposure and for injury from falls.

Recycled tires in playground surfaces take one of three forms:

1. As uncompressed tire shreds or crumb comprising a rakeable surface,
2. As rubber tire shreds that are poured-in-place along with a binder, hardening into a permanent surface,
3. As tiles molded in the factory from tire shreds and binder, which are then transported to the playground and locked or glued into place, forming a permanent surface.

Track applications use the method described in #2 above.

Studying the toxicology of recycled tires used in playground surfaces

The first part of this study addresses the toxicologic safety of rubber playground and track surfaces made of recycled tires. We examined whether such surfaces release toxicants capable of adversely affecting either children's health or the health of the local ecology. These issues are addressed in three ways:

1. Through a review of the literature covering what is known to be released by recycled tires in laboratory studies and in civil engineering projects that utilized tire shreds (e.g., roadways, parking lots, leachate fields).
2. By conducting studies to identify chemicals released by tire shreds in a laboratory setting and at actual rubber surfaces in use at selected playgrounds and a track within California.
3. By conducting a skin sensitization study of pieces of recycled tire rubber used in playground surfacing.

Once we identified the chemical substances to which a child could be exposed, we estimated exposure potential and compared those values to toxicologic reference values. This approach enabled us to quantify the risks to children's health. We took a similar approach in evaluating potential environmental risks from playground recycled tire leachate.

Studying impact attenuation and the prevention of fall injury by playground surfaces made of recycled tires

The second part of this study evaluates whether playground surfaces made of recycled tires are an effective means for reducing serious head injury due to falls. The US CDC (2005) estimates that it cost 1.2 billion dollars to treat playground-related injuries in the United States in 1995. If 10 percent of these injuries occurred in California, then approximately 120 million dollars were spent in this state. Since approximately 80 percent of these injuries resulted from falls (Tinsworth and McDonald, 2001), then reducing the injury rate from falls by only 10 percent has the potential to save almost 10 million dollars in California. An accompanying reduction in injury severity would save even more.

While preliminary laboratory data suggest that crumb rubber should be effective at reducing the incidence of injury to children that fall, the three types of rubber surfaces have never been intercompared for injury reduction, and only sparse data exist regarding the efficacy of rubber surfaces relative to more traditional impact-absorbing surfaces such as sand or wood chips. While standards for head impact attenuation by playground surfaces have been written into California law (CCR sections 65700-65750), the compliance rate has not been systematically monitored.

Thus, measurement of the compliance rate for playground surfaces made of recycled tire rubber was an important part of this study. In effect, we have measured parameters of impact attenuation by in use playground surfaces to determine whether these surfaces, as they are currently being installed in California, can be expected to protect children from serious head injury due to falls. This approach was chosen in consultation with members of the Injury Surveillance and Epidemiology Section of the California Department of Health Services, and the Department of Epidemiology in the UCLA School of Public Health. Those discussions failed to identify a set of injury data collected from playgrounds before and after installation of a rubberized surface, or any information on insurance savings that could be directly linked to decreased playground injuries. Thus, we found it necessary to generate our own set of data covering the impact attenuating properties of California playground surfaces, from which estimates of fall injury risk could be made.

Chapter 2: Survey of CIWMB playground grantees 2001–2003: playground surface types and locations

Background: Municipalities and school districts receiving CIWMB grants for installation of playground surfaces made of recycled tires were surveyed by telephone. The CIWMB allocated 90 playground surface grants in the 2000-2001 cycle and 59 grants in the 2001-2002 cycle. Contact persons were asked to provide information on the type of surface installed (pour-in-place, tiles or rakeable shreds/crumb), the composition of the surface and the name of the manufacturer/installer. Approximately one third of the grantees who were contacted provided this information. Below are the data on surface type and composition.

Nomenclature: The synthetic rubber called styrene-butadiene rubber is a major component of tires. Thus, the abbreviation SBR is often used as a designation for the shredded tire component of these surfaces. For pour-in-place surfaces, the SBR is mixed with a binder and poured at the playground site, where it hardens into a uniform surface. At this point, granules of synthetic rubber called ethylene propylene diene monomer (EPDM) are often mixed with a binder and poured into the playground to serve as a top layer. When this process is performed at a factory using molds, tiles of SBR with top layers of EPDM result. These tiles are put in the playground and locked in place, also forming a uniform surface. Both pour-in-place surfaces and surfaces of tiles can be constructed using SBR only. Lastly, shredded SBR can be used much like wood chips or gravel by simply transporting it to the playground site where it is raked into place.

Playground materials survey results

- **Pour-in-place SBR only:** no grantees installed surfaces of this material
- **Pour-in-place SBR with a pour-in-place top layer of EPDM:** 44 playground surfaces in Antioch, Bear Mountain, Belvedere, Cathedral City, Commerce, Conejo, Culver City, Downey, Duarte, El Cerrito, Eureka, Fair Oaks, Greater Vallejo Recreation District, Imperial, Kern County, King City, Lodi, Long Beach, Modesto, Monterey, Morongo Valley Community Service District, Napa, Pacheco, Pacifica Community Charter School (L.A. Unified School District), Paramount, Pico Rivera, Poway, Reef Sunset Unified, San Clemente, San Diego, San Francisco, San Luis Obispo, Santa Barbara, Saugas, Silverado-Modjeska, Sunrise, Union City, Wilsona School District
- **SBR tiles:** 2 playground surfaces in Gridley and Smith River
- **SBR tiles with top layer of EPDM:** 2 playgrounds in Long Beach and Bell
- **Rakeable rubber shreds:** 3 playgrounds in Horicon Elementary School District, Morongo Valley Community Service District and Salinas

Comment: Since the great majority of grantees (44/51) installed a pour-in-place surface consisting of a base layer of recycled SBR covered by an EPDM top layer, OEHHA focused its testing on both EPDM and SBR playground materials. These products were used to analyze the chemicals released by in-use playground surfaces and for conducting the skin sensitization test.

Chapter 3: Substances released by recycled tires: values from the published literature

Introduction

Table 1 lists the published studies that identified metals, compounds and particulates released by tires in laboratory and field settings. In some cases, whole tires were used, but more often tire shreds, chips or crumb was tested. The studies are approximately evenly distributed between field and laboratory studies. Field studies involved the use of tire pieces in road beds, road embankments, leachate fields, a parking lot, and as a component of turf. In addition, an application with whole tires in water was that of reef construction. No study was located identifying substances released by recycled tires in playground surfaces, although a single study tested for ecotoxicity by the water-soluble extracts from playground tire crumb (Birkholz et al., 2003). Therefore, until our gastric digestion and wipe sampling studies, the data shown here were the only information available for making predictions about the behavior of tire pieces in playground surfaces. Using these surrogate data to assess risks from rubberized playground and track surfaces introduces a variety of uncertainties due to the following:

1. Waste tire processing for playground and track surfaces includes a step to remove the metal belts and metal beads, and the rubber end product is generally washed, while the shredded tires used in these published studies still contained the metallic components, and the end product was not necessarily washed; therefore, the shredded tires used in these published studies represent a potentially greater source of leaching chemicals compared to the tire shreds and crumb rubber used in playground surfaces,
2. Most playground and track surfaces made of the recycled tire rubber also use a chemical binder such as polyurethane to hold the rubber pieces in place, while the shredded tires used in these published studies did not include a binder; therefore, chemicals leaching from the binder cannot be identified from these published studies,
3. Playground and track surfaces are continually exposed to changing climatic conditions including sunlight, precipitation, and variations in temperature, as well as to volatile chemicals in the ambient atmosphere,
4. The laboratory studies collected from the literature generally consisted of day, week, or month-long incubations of tire shreds in aqueous solutions in closed tanks or other reaction vessels; these laboratory conditions do not replicate the predicted routes of child exposure to recycled tire rubber in playground surfaces, such as through hand-to-surface-to-mouth contact or ingestion of tire shreds.

Table 1. Substances released by whole tires or tire chips/shreds in laboratory and field studies

Authors	Type of study	VOCs	sVOCs	Metals	Other
Al-Tabbaa and Aravinthan, 1998	Lab			Cu, Ni	
Anthony et al., 1995	Tire shred leachate in lab	Nitro compounds, hydrophilic compounds	Morpholino-thio-benzothiazole	Iron, manganese, nickel, zinc	
Anthony and Latawiec, 1993	Whole tire leachates in lab	An olefinic hydrocarbon, an alkoxy ether/alcohol, series of nitro-aliphatic ethers	Morpholino-thio-benzothiazole		
BAS Inc., 1993	MSDS for crumb rubber				Fine particles
Boniak et al., 2001	Tire crumb in field test			Zn	
Chien et al., 2003	Tire shredding factory-particulates in air		Amines, aniline, quinoline, amides, benzothiazole all in particulates		Respirable particulates
Edil et al., 2003	Tire chip leachate in field	Methyl isobutyl ketone			
Exponent, 2003	Tire shred leachate in field	Acetone, 1,1-dichloroethane, cis-1,2-dichloroethene, chloroethane, benzene, trichloroethene, toluene	Aniline, N-Nitrosodimethylamine, N-Nitrosodiphenylamine	Manganese, iron	
Florida Community College, 1999	Leachate from crumb rubber in the field and soil measurements	Toluene		Fe, Zn, Ba, Na, Cr, Pb, Cu, Sb	
Florida Dept. of Envir. Protect., 1999	Lab study conducted by the Virginia DOT			Cd, Cr, Pb, Al, Cu, Fe, Ni, Zn	

Authors	Type of study	VOCs	sVOCs	Metals	Other
Florida Dept. of Envir. Protect., 1999	Field study conducted in Idaho			Zn	
Fukuzaki et al., 1986	Field				5-24 ng/m ³ tire dust
Gaultieri et al., 2005	Lab			Zn	
Gunter et al., undated	Tire chip leachate in lab	Acetone, benzene, trichloroethylene, methyl ethyl ketone, methyl isobutyl ketone		Iron, lead, manganese	
Hartwell et al., 1998	Tire shred leachate in lab	Naphthalene, 2 Methyl naphthalene	Morpholiniothio-benzothiazole, bis(2-ethylhexyl)phthalate	Al, Ba, Cd, Cr, Co, Cu, Mn, Ni, Zn, Fe	
Hildemann et al., 1991	Field + lab				Fine particulate organic C (105 µg/m ² /day)
Horner, 1996	Tire chip leachate in lab and soil near tire dump			Cadmium, zinc, lead	
Humphrey, 1999	Tire chip leachate in field	None detected	None detected	Barium, iron, manganese, zinc	Chloride, sulfate
Humphrey and Katz, 2000	Tire shred leachate in field	1,1-dichloroethane, 4-methyl-2-pentanone (MIBK)	2-(4-morpholinyl)-benzothiazole	Iron, manganese	
Humphrey and Katz, 2001	Tire shred leachate in field	1,1-dichloroethane, 4-methyl-2-pentanone (MIBK), acetone, benzene, cis-1,2-dichloroethene	Aniline, m+p cresol	Iron, manganese, zinc	

Authors	Type of study	VOCs	sVOCs	Metals	Other
Johnson et al., 2002	Tire chip leachate in lab			Zinc	
Kim et al., 1990	Suspended particulate matter in urban air				Tire tread particles
Kumata et al., 1996	Street dust, river sediment, air		2-(4-morpholinyl)benzothiazole		
Kumata et al., 2002	Highway runoff, river sediment		2-(4-morpholinyl)-benzothiazole, N-cyclohexyl-2-benzothiazolamine		
Liu et al., 1998	Tire shred leachate in field			Iron, manganese	Latex allergens
Miguel et al., 1996	Air samples and guardrail swipes near freeway				Particulates with latex allergens
Miller and Chadik, 1993	Tire shred leachate in field and laboratory	Methyl isobutyl ketone, 1,3,5-trimethylbenzene, benzene	aniline	Arsenic, zinc	
Minn. DOT, 1995	Tire chip leachate in lab	Isophorone, 2,6-dinitrotoluene		Mercury, zinc	
Minn. Pollution Control Agency, 1990	Tire chip leachate in lab	Total petroleum hydrocarbons, PAHs		Aluminum, barium, cadmium, chromium, iron, selenium, zinc, lead	

Authors	Type of study	VOCs	sVOCs	Metals	Other
Nelson et al., 1994	Whole tire and tire plug leachates in lab			Zinc copper, cadmium lead	
Ontario Ministry of Environment and Energy, 1994	Lab		Benzothiazole, 4-(phenylamino)-phenol, 2-(4-morpholinyl)benzothiazole, 24 other organic compounds at lower levels	Zn	
O'Shaughnessy and Garga, 2000	Lab		Benzothiazole, 2(3H)-benzothiazolone, (1,1-diethylethyl)-2-methoxyphenol, 4-(2-benzothiazolythio)-morpholine	Al, Fe, Mn, Zn	
Park et al., 2003	Tire shred leachate in lab			Zinc, barium and lead in precipitates	
Pierce and Blackwell, 2003	Lab	VOCs absorbed by ground tire rubber added to slurry cutoff wall backfill material			
Radian Corp., 1989	Tire chip leachate in lab	Phenol		Barium, chromium, lead, mercury, selenium	
Reddy and Quinn, 1997	Field + lab		Benzothiazole, 2-hydroxybenzothiazole, 2-(4-morpholinyl)-benzothiazole		
Rogge et al., 1993	Tire dust generated in lab	Alkanes, PAHs	alkanoic acids, natural resins, benzothiazole		

Authors	Type of study	VOCs	sVOCs	Metals	Other
Schauer et al., 2002	Field				Fine particulate organic C (1 µg /m ³) [total part.=2µg]
Scrap Tire Management Council, 1991	Tire chip leachate in lab	Methyl ethyl ketone, toluene	phenol	Barium, chromium, lead, mercury	Carbon disulfide
Sengupta and Miller, 1999	Tire shred leachate in lab			Iron, aluminum, zinc, copper	Chloride
Shieh, 2001	Tire chip leachate in lab	Methyl ethyl ketone, toluene	Phenol	Arsenic, lead	Carbon disulfide
Spies et al., 1987	SF bay sediment		Benzthiazole, 2-(4-morpholinyl)-benzthiazole		
Stephensen et al., 2003	Lab	PAHs, aromatic nitrogen compounds			
Tatlisož et al., 1996	Field and lab	Benzene, toluene	Phenol	As, Ba, Cd, Cr, Pb, Fe, Mn, Se, Hg, Zn	
Williams et al., 1995	Air near freeway				Rubber particles with latex allergens
Yoon et al., 2005	Tire shred leachate in the field			As, Ba, Cd, Cr, Se	

VOC = volatile organic compound; sVOC = semi-volatile organic compound

Substances released by tires

Tables 2 through 5 show the concentrations of substances released by recycled tires (or “in use” tires in the case of airborne particulates) for the studies listed in Table 1. The substances released comprise four groups consisting of 15 metals (Table 2), 20 volatile organic compounds (VOCs, Table 3), 14 semi-volatile organic compounds (sVOCs, Table 4), and particulates in air resulting from tire wear (Table 5). Where possible, the data are reported as amount of chemical released per gram of tire. This facilitated the use of these data to predict how much of each chemical would be released were a child to intentionally ingest a specific amount of tire shreds.

Metals

From among the 15 metals listed in Table 2, zinc (21 instances) and iron (sixteen instances) were detected most frequently and at the highest levels. Iron is a component of the steel belts and beads, while zinc oxide is used as an activator in the vulcanization process (CIWMB, 1996). Manganese was the next most frequently detected (ten instances). Like iron, it probably originated from the steel belts and beads. Today, the production of crumb rubber from tires typically includes a step to remove 99 percent of the steel belting and bead material. This would be expected to greatly reduce the release of iron and manganese from the recycled tire material. Barium was the next most commonly detected metal (nine instances), possibly as a result of its use to catalyze the synthesis of polybutadiene rubber (Halasa et al., 2003).

Lead was also identified in eight instances, possibly due to its former use as an activator of the vulcanization process, in the form of lead oxide (CIWMB, 1996). Chromium detection in seven instances may have resulted from its use in steel production. If this is the case, removal of the steel wire from recycled tires should also markedly reduce the release of this metal. Unfortunately, none of the studies determined whether the chromium was in the +6 or +3 oxidation state, since the former ion is highly carcinogenic (by inhalation) while the latter is not. The remaining nine metals (cadmium, copper, aluminum, antimony, mercury, nickel, arsenic, selenium, cobalt) were detected in five or fewer instances.

While the presence of metals at levels above background is noteworthy, the toxicologic significance depends upon the concentrations and magnitude of exposure. As shown in Table 2, both zinc and iron were detected in tire chip leachate at levels indicating that milligram amounts of these metals were released per gram of tire. These studies were conducted in the laboratory under controlled conditions. Similar laboratory studies indicate that microgram amounts of manganese, aluminum, barium and copper were released per gram of tire, while only nanogram amounts of lead, cadmium, chromium, nickel, arsenic, selenium and cobalt were released (Table 2).

To assess the toxicologic significance of these findings, these levels will first be used to estimate child exposure by the oral route. Exposures will then be compared to corresponding oral reference toxicity values, such as a public health goal (PHG), reference concentration (RfC), minimal risk level (MRL), or reference exposure level (REL). These values have been developed by various authoritative bodies including OEHHA, U.S. EPA, the Centers for Disease Control (CDC), and the Agency for Toxic Substances and Disease Registry (ATSDR). The calculations will determine whether exposures are likely to cause adverse health effects.

VOCs

Tire shreds released lower concentrations of volatile organic compounds (VOCs) than metals (Table 3). A total of 20 compounds were identified, including three classes of compounds (polycyclic aromatic hydrocarbons, aromatic nitrogen-containing, total petroleum hydrocarbons). Other than the unidentified ether compound whose level was estimated in the laboratory study by Anthony and Latawiec (1993), the highest values were for the solvent methyl isobutyl ketone (1,151 ng released per gram of tire; Gunter et al., undated) and for naphthalene (1,100 ng released per gram of tire; Hartwell et al., 1998). The presence of methyl isobutyl ketone may be the result of its use in the production of rubber antioxidants (U.S. EPA, 2003b), while naphthalene may originate from carbon black.

Seven compounds or groups of compounds were released in ng amounts per gram of tire: acetone, toluene, benzene, total petroleum hydrocarbons, polycyclic aromatic hydrocarbons, methyl ethyl ketone and 2-methyl naphthalene. All these compounds except for the last may result from the use of petroleum oils (the source of carbon black) and coal tar fractions in tire production, which serve as softeners and extenders (Sullivan et al., 1992). These findings were from studies performed in the laboratory, where the volatile organic compounds were released into aqueous solutions.

A clue towards how these volatile compounds might behave when tire shreds are used in playground surfaces, and the compounds are released directly into the air, may be provided by the study of Chang et al. (1999). In that study of rubberized athletic tracks, the emission of volatile organic compounds decreased with time, so that after about two years the levels at breathing heights were near background. Unfortunately, since recycled tire rubber was most likely not used in the construction of these tracks, it is problematic to use these data to draw firm conclusions about the release of VOCs from playground surfaces made of recycled tires. Chapter 8 presents wipe sampling data from a running track containing recycled tires as well as a discussion of the safety benefits of such a surface.

sVOCs

A total of 14 sVOCs are listed in Table 4. This includes five different benzothiazoles, three of which were released at μg amounts per gram of tire. These benzothiazole contaminants have been proposed as environmental markers for tire-derived material (Kumata et al., 2002). Benzothiazoles are used in tire production to accelerate the vulcanization process (Kumata et al., 2002), as antioxidants (Spies et al., 1987), and to help bond the metal wire and metal belts to the tire rubber (CIWMB, 1996). Aniline, phenol, 4-(phenylamino)-phenol, phenoxazine, and 2(3H)-benzothiazolone were released in ng amounts per gram of tire. Aniline is added to tires to inhibit rubber degradation (CIWMB, 1996).

Detection of phenol (and cresol) may be due to the use of petroleum oils and/or coal tar fractions as softeners and extenders in tire production. In addition, treatment of the steel cords and fabrics comprising the belts with phenol/formaldehyde improves their adhesion to the rubber (Sullivan et al., 1992). Lastly, two nitrosoamines (diphenyl and dimethyl) were detected in the same study; this could be the result of their use to inhibit both the vulcanization process during tire production, and the decomposition of rubber in the finished product (CIWMB, 1996).

Particulates

Particles of tire-derived rubber have been measured in the air in a number of studies (Table 5). Three studies measured from 1-7 $\mu\text{g}/\text{m}^3$ in ambient air (Kim et al., 1990; Miguel et al., 1996; Schauer et al., 2002). This demonstrates that any measurements of rubber particulates above a rubber playground surface must take into account the ambient, background level. Two of the studies in Table 5 (Williams et al, 1995; Miguel et al., 1996) identified latex as a component of the airborne particulate matter. Such airborne particles containing latex allergens have been suggested as potential inducers of both latex sensitization and asthma (Miguel et al., 1996; Williams et al., 1995).

Table 2. Concentrations of metals leaching from tire shreds used in various civil engineering applications in the field or leaching in lab studies

Metal	Study Type	Concentration
Aluminum (Al)	Lab leachate study (Minn Poll Cntrl Agency, 1990)	2,000 ng released (per g tire)
	Lab leachate study (Hartwell et al., 1998)	1200 ng released (per g of tire)
	Lab study (Florida Dept. Environ. Protection, 1999)	420 ng released (per g of tire)
	Lab leachate study (Sengupta and Miller, 1999)	790 ppb in leachate
	Lab leachate study (O'Shaughnessy and Garga, 2000)	550 ppb in leachate
Antimony	Field leachate study (FCC at Jacksonville, 1999)	489 ppb in soil
Arsenic (As)	Lab leachate studies (Miller and Chadik, 1993)	130 ng released (per g tire)
	Field leachate study (Yoon et al., 2005)	19 ppb in leachate
Barium (Ba)	Lab leachate study (Minn Poll Cntrl Agency, 1990)	1,000 ng released (per g tire)
	Lab leachate study (Scrap Tire Man Cncl, 1991)	590 ppb in leachate
	Lab leachate studies (Tatlisoiz et al., 1996)	100 to 1000 ng released (per g tire)
	Lab leachate study (Hartwell et al., 1998)	1700 ng released (per g of tire)
	Field leachate study (Humphrey, 1999)	21 ppb in leachate
	Field leachate study (FCC at Jacksonville, 1999)	1,230 ppb in surface water
	Field leachate study (FCC at Jacksonville, 1999)	10,000 ppb in soil
	Lab leachate study (Park et al., 2003)	340 ng released (per g of tire)
	Field leachate study (Yoon et al., 2005)	113 ppb in leachate
Cadmium (Cd)	Lab leachate study (Minn Poll Cntr Agency, 1990)	270 ng released (per g of tire)
	Lab leachate study (Hartwell et al., 1998)	270 ng released (per g of tire)

Metal	Study Type	Concentration
	Lab study (Florida Dept. Environ. Protection, 1999)	4 ng released (per g of tire)
	Field leachate study (Yoon et al., 2005)	1.1 ppb in leachate
Chromium (Cr) with oxidation state (Cr ⁺³ or Cr ⁺⁶) not determined	Lab leachate study (Minn Poll Cntrl Agency, 1990)	500 ng released (per g tire)
	Lab leachate study (Scrap Tire Man Cncl, 1991)	48 ppb in leachate
	Lab leachate studies (Tatlisoz et al., 1996)	8 to 500 ng released (per g of tire)
	Lab leachate study (Hartwell et al., 1998)	100 ng released (per g of tire)
	Field leachate study (FCC at Jacksonville, 1999)	2 ppb in surface water
	Field leachate study (FCC at Jacksonville, 1999)	4 ppb in ground water
	Lab study (Florida Dept. Environ. Protection, 1999)	8 ng released (per g of tire)
	Field leachate study (Yoon et al., 2005)	55 ppb in leachate
Cobalt (Co)	Lab leachate study (Hartwell et al., 1998)	100 ng released (per g of tire)
Copper (Cu)	Lab leachate study (Al-Tabbaa and Aravinthan, 1998)	360 to 4880 ng released (per g of tire)
	Lab leachate study (Hartwell et al., 1998)	320 ng released (per g of tire)
	Field leaching study (FCC at Jacksonville, 1999)	2,300 ppb in leachate
	Lab study (Florida Dept. Environ. Protection, 1999)	235 ng released (per g of tire)
	Lab leachate study (Sengupta and Miller, 1999)	2,400 ppb in leachate
Iron (Fe)	Lab leachate study (Gunter et al., undated)	13,000 ng released (per g of tire)
	Lab leachate study (Minn. Poll. Cntr. Agency, 1990)	1,100,000 ng released (per g of tire)
	Lab leachate study (Anthony et al., 1995)	26,000 ng released (per g of tire)

Metal	Study Type	Concentration
	Lab leachate studies (Tatlisoiz et al., 1996)	1,150 to 1,100,000 ng released (per g tire)
	Field leachate study (Liu et al., 1998)	55,000 ppb in leachate
	Lab leachate study (Hartwell et al., 1998)	27,000 ng released (per g of tire)
	Lab study (Florida Dept. Environ. Protection, 1999)	341,000 ng released (per g of tire)
	Field leachate study (Humphrey et al., 1999)	30,000 ppb in leachate
	Field leachate study (FCC at Jacksonville, 1999)	1,500 ppb in ground water
	Field leachate study (FCC at Jacksonville, 1999)	210 ppb in surface water
	Field leachate study (FCC at Jacksonville, 1999)	960,000 ppb in soil
	Field leachate study (Humphrey 1999)	22,000 ppb in leachate
	Lab leachate study (Sengupta and Miller, 1999)	18,000 ppb in leachate
	Lab leachate study (O'Shaughnessy and Garga, 2000)	700 ppb in leachate
	Field leachate study (Humphrey et al., 2001)	33,000 ppb in leachate
	Field leachate study (Exponent, 2003)	80,000 ppb in leachate
Lead (Pb)	Lab leachate study (Gunter et al., undated)	12 ng released (per g of tire)
	Lab leachate study (Minn. Poll. Cntr. Agency, 1990)	920 ng released (per g of tire)
	Lab leachate study (Scrap Tire Man. Cncl., 1991)	30 ppb in leachate
	Lab leachate studies (Tatlisoiz et al., 1996)	3 to 920 ng released (per g tire)
	Field leachate study (FCC at Jacksonville, 1999)	6 ppb in surface water
	Lab study (Florida Dept. Environ. Protection, 1999)	56 ng released (per g tire)
	Field leachate study (FCC at Jacksonville, 1999)	13,300 ppb in soil

Metal	Study Type	Concentration
	Lab leachate study (Park et al., 2003)	120 ng released (per g of tire)
Manganese (Mn)	Lab leachate study (Gunter et al, undated)	1,040 ng released (per g tire)
	Lab leachate study (Anthony et al., 1995)	5800 ng released (per g tire)
	Lab leachate studies (Tatlisoiz et al., 1996)	1,500 ng released (per g of tire)
	Field leachate study (Liu et al., 1998)	3,000 ppb in leachate
	Lab leachate study (Hartwell et al., 1998)	5800 ng released (per g of tire)
	Field leachate study (Humphrey, 1999)	2,500 ppb in leachate
	Lab leachate study (O'Shaughnessy and Garga, 2000)	180 ppb in leachate
	Field leachate study (Humphrey and Katz, 2000)	22,000 ppb in leachate
	Field leachate study (Humphrey and Katz, 2001)	1,300 ppb in leachate
	Field leachate study (Exponent, 2003)	910 ppb in leachate
Mercury (Hg)	Lab leachate study (Scrap Tire Man Cncl, 1991)	0.4 ppb in leachate
	Lab leachate study (Minn Dept Trans, 1995)	0.4 ppb in leachate
	Lab leachate studies (Tatlisoiz et al., 1996)	0.07 ng released (per g tire)
Nickel (Ni)	Lab leachate study (Anthony et al., 1995)	80 ng released (per g of tire)
	Lab leachate study (Hartwell et al., 1998)	120 ng released (per g of tire)
	Lab leachate study (Al-Tabbaa and Aravinthan, 1998)	5-12 µg released (per g of tire)
	Lab study (Florida Dept. Environ. Protection, 1999)	113 ng released (per g of tire)
Selenium (Se) (elemental)	Lab leachate study (Minn Poll Cntrl Agency, 1990)	440 ng released (per g tire)
	Lab leachate studies (Tatlisoiz et al., 1996)	50 to 440 ng released (per g tire)

Metal	Study Type	Concentration
	Field leachate study (Yoon et al., 2005)	23 ppb in leachate
Zinc (Zn)	Lab leachate study (Minn. Poll Cntrl Agency, 1990)	50,000 ng released (per g tire)
	Lab leachate study (Scrap Tire Man. Council., 1991)	500 ppb in leachate
	Lab leachate study (Miller and Chadik, 1993)	3,200 ng released (per g of tire)
	Lab leachate study (Nelson et al., 1994)	4,200 ng released (per g tire)
	Lab leachate study (Ontario Ministry of Environment and Energy, 1994)	1,000 ng released (per g of tire)
	Lab leachate study (Minn. Dept. Trans., 1995)	2,950 ppb in leachate
	Lab leachate study (Horner, 1996)	2,320,000 ng released (per g tire)
	Lab leachate studies (Tatlisoiz et al., 1996)	1,130 to 50,000 ng released (per g tire)
	Lab leachate study (Hartwell et al., 1998)	68,000 ng released (per g of tire)
	Field leachate study (FCC at Jacksonville, 1999)	45,000 ppb in soil
	Field leachate study (Humphrey, 1999)	140 ppb in leachate
	Field leachate study (FCC at Jacksonville, 1999)	103 ppb in surface water
	Field study (Florida Dept. Environ. Protection, 1999)	618 ppb in leachate
	Lab study (Florida Dept. Environ. Protection, 1999)	30,000 ng released (per g of tire)
	Field leachate study (Humphrey and Katz, 2000)	26 ppb in leachate
	Lab leachate study (O'Shaughnessy and Garga, 2000)	590 ppb in leachate
	Field leaching study (Boniak et al., 2001)	310 ppb in soil
	Lab leachate study (Johnson et al., 2002)	2,950 ppb in leachate

Metal	Study Type	Concentration
	Lab leachate study (Park et al., 2003)	1100 ng released (per g of tire)
	Lab leachate study (Birkholz et al., 2003)	68,000 ng released (per g of tire)
	Lab leachate study (Gualtieri et al., 2005)	890,000 ng released (per g tire rubber)

Table 3. Concentrations of Volatile Organic Compounds (VOCs) released from tire shreds in various field applications and laboratory studies, and in ambient air samples

Compound	Study Type	Concentration
1,1-dichloroethane	Field leachate study (Humphrey and Katz, 2000)	Trace (<5 ppb) in leachate
2,6-dinitrotoluene	Lab leaching study (Minn Dept Trans, 1995)	45 ppb in leachate
2-Methyl naphthalene	Lab leaching study (Hartwell et al., 1998)	540 ng released (per g of tire)
1,3,5-trimethylbenzene	Field leaching study (Miller and Chadik, 1993)	4 ppb in leachate
Acetone	Lab leachate study (Gunter et al., undated)	115 ng released (per g of tire)
	Leachate in field (Humphrey and Katz, 2001)	28 ppb in leachate
	Leachate in field (Exponent, 2003)	27 ppb in leachate
Benzene	Lab leachate study (Gunter et al., undated)	0.9 ng released (per g of tire)
	Leaching study in lab (Miller and Chadik, 1993)	218 ng released (per g of tire)
	Field leachate study (Humphrey and Katz, 2001)	4 ppb in leachate
	Field leachate study (Exponent, 2003)	1.35 ppb in leachate
Chloroethane	Field leaching study (Exponent, 2003)	2 ppb in leachate
Cis-1,2-dichloroethene	Field leachate study (Humphrey and Katz, 2001)	24 ppb in leachate
Isophorone	Lab leaching study (Minn Dept Trans, 1995)	2 ppb in leachate

Compound	Study Type	Concentration
Methyl ethyl ketone	Lab leachate study (Gunter et al., undated)	17 ng released (per g of tire)
	Lab leachate study (Scrap Tire Manag Concl, 1991)	21 ppb in leachate
Methyl isobutyl ketone	Lab leachate study (Gunter et al., undated)	1151 ng released (per g of tire)
	Field leachate study (Miller and Chadik, 1993)	3 ppb in leachate
	Field leachate study (Humphrey and Katz, 2000)	Trace (<5 ppb) in leachate
	Field leachate study (Humphrey and Katz, 2001)	58 ppb in leachate
	Field leachate study (Edil et al., 2003)	69 ppb in leachate
Naphthalene	Lab leaching study (Hartwell et al., 1998)	1,100 ng released (per g of tire)
A nitro-aliphatic ether compound	Lab leaching study (Anthony and Latawiec, 1993)	5000 to 25000 ppb in leachate
n-pentatriacontane	Air sampling study (Schauer et al., 2002)	3 ng/m ³
n-tetraatriacontane	Air sampling study (Schauer et al., 2002)	3 ng/m ³
Polycyclic aromatic hydrocarbons (PAHs)	Lab leaching study (Minn Poll Cntr Agency, 1990)	140 ng released (per g of tire)
Toluene	Lab leaching study (Scrap Tire Man Cncl, 1991)	190 ppb in leachate
	Lab leaching studies (Tatlisoiz et al., 1996)	34 to 280 ng released (per g of tire)
	Field leaching study (FCC at Jacksonville, 1999)	63 ppb in soil
	Field leaching study (Exponent, 2003)	2.6 ppb in leachate
Total petroleum hydrocarbons	Lab leaching study (Minn Poll Cntr Agency, 1990)	140 ng released (per g of tire)
	Lab leaching study (Stephensen et al., 2003)	Up to 450 ng/g fish bile fluid
Trichloroethene	Field leaching study (Exponent, 2003)	0.8 ppb in leachate

Compound	Study Type	Concentration
Trichloroethylene	Lab leachate study (Gunter et al., undated)	0.8 ng released (per g of tire)
	Field leachate study (Humphrey and Katz, 2001)	6 ppb in leachate
	Field leachate study (Exponent, 2003)	2 ppb in leachate
	Field leachate study (Exponent, 2003)	16 ppb in leachate

Table 4. Concentrations of Semi-Volatile Organic Compounds (sVOCs) released from tire shreds in various field applications and laboratory studies, and in some ambient environmental samples

Compound	Study Type	Concentration
(1,1-diethylethyl)-2-methoxyphenol	Lab leachate study (O'Shaughnessy and Garga, 2000)	330 ppb in leachate
2(3H)-benzothiazolone	Lab leachate (Ontario Ministry of Environment and Energy, 1994)	170 ng released (per g of tire)
	Lab leachate study (O'Shaughnessy and Garga, 2000)	640 ppb in leachate
2-hydroxybenzothiazole	Lab leachate study (Reddy and Quinn, 1997)	36,000 ng released (per g crumb rubber)
	Urban runoff (Reddy and Quinn, 1997)	7.0 ppb in urban runoff
2-(4-morpholinyl)benzothiazole	S.F. bay sediment (Spies et al., 1987)	360 ppb in sediment
	Lab leachate (Ontario Ministry of Environment and Energy, 1994)	260 ng released (per g of tire)
	Background air sample (Kumata et al., 1996)	5.9 pg/m ³
	Lab leachate study (Reddy and Quinn, 1997)	2,000 ng released (per g crumb rubber)
	Urban runoff (Reddy and Quinn, 1997)	0.28 ppb in runoff
	Lab leachate study (Hartwell et al., 1998)	Not quantifiable
	Lab leachate study (O'Shaughnessy and Garga, 2000)	340 ppb in leachate
	River sediment (Kumata et al., 2002)	9 ppb in sediment
	Highway runoff (Kumata et al., 2002)	0.417 ppb in runoff
4-(phenylamino)-phenol	Lab leachate (Ontario Ministry of Environment and Energy, 1994)	340 ng released (per g of tire)
aniline	Lab leachate study (Miller and Chadik, 1993)	742 ng released (per g tire)
	Lab leachate (Ontario Ministry of Environment and Energy,	129 ng released (per g tire)

Compound	Study Type	Concentration
	1994)	
	Field leachate study (Humphrey and Katz, 2001)	71 ppb in leachate
	Field leachate study (Exponent, 2003)	100 ppb in leachate
benzothiazole	Lab leachate (Ontario Ministry of Environment and Energy, 1994)	430 ng released (per g of tire)
	Urban runoff (Reddy and Quinn, 1997)	1.3 ppb in urban runoff
	Lab leachate study (Reddy and Quinn, 1997)	100,000 ng released (per g crumb rubber)
	Lab leachate study (O'Shaughnessy and Garga, 2000)	900 ppb in leachate
Bis(2-ethylhexyl)phthalate	Lab leachate study (Hartwell et al., 1998)	Not quantifiable
m + p cresol	Field leachate study (Humphrey and Katz, 2001)	39 ppb in leachate
N-cyclohexyl-2-benzothiazolamine	Highway runoff (Kumata et al., 2002)	0.508 ppb in runoff
	River sediment (Kumata et al., 2002)	17 ppb in sediment
N-nitrosodimethylamine	Field leachate study (Exponent, 2003)	7 ppb in leachate
N-nitrosodiphenylamine	Field leachate study (Exponent, 2003)	7 ppb in leachate
phenol	Lab leachate study (Scrap Tire Man Concl, 1991)	50 ppb in leachate
	Lab leachate study (Tatlisoiz et al., 1996)	10 ng released (per g of tire)
phenoxazine	Lab leachate (Ontario Ministry of Environment and Energy, 1994)	220 ng released (per g of tire)

Table 5. Concentrations of particulates in the air resulting from tire wear

Substance	Study Type	Concentration
Rubber particulates (<10 microns) containing latex	Air sampling and guardrail swipes near freeway (Miguel et al., 1996)	1 µg/m ³
Rubber particles (59%<10 microns) with latex	Air sampling near freeway (Williams et al., 1995)	3800-6900 particles/m ³
Rubber particulates	Air sampling in urban area (Kim et al., 1990)	Up to 7 µg/m ³
Fine particulate organic carbon due to tire wear	Emissions into air in urban area (Hildemann et al., 1991)	105 µg /m ² of urban surface area/day
Fine particulate organic carbon from tires	Air sampling (Schauer et al., 2002)	1 µg/m ³
Airborne dust from tire tread	Air sampling near busy urban road (Fukuzaki et al., 1986)	24 ng/m ³

Chapter 4: Toxicity reference values for substances released by recycled tires

To determine if an environmental contaminant poses a threat to human health, its environmental concentration is used to estimate human exposure, which is then compared to reference toxicity values. Such reference values (i.e., RfD = reference dose, MRL = minimal risk level, PHG = public health goal, REL = reference exposure level) are often derived from data determined experimentally in studies with laboratory animals. Alternatively, human epidemiologic data can be used. This section lists the reference toxicity values for most of the substances identified in the previous section. The tables are arranged according to type of toxicant (metal, VOC, sVOC, particulate) and are for the oral route of exposure. Reference values were collected for acute (single), subchronic (up to 90 days) and chronic (one year or more) exposures. When available, OEHHA values were used. Information was also included regarding carcinogenicity and whether children represent a sensitive subgroup relative to the adult population.

Table 6: Metals: Oral route: Toxicity Values

<p>Aluminum (noncarcinogenic, the data do not suggest an increased susceptibility of infants or children; OEHHA, 2001a; ATSDR, 1999a)</p>
<p>Acute: not acutely toxic in healthy adults based on widespread exposure via food, water and antacid tablets (OEHHA, 2001a)</p>
<p>Subchronic: minimal risk level (MRL) = 2.0 mg/kg-d based on a NOAEL of 62 mg/kg-day in mice fed for 6 weeks and exhibiting decreased activity (uncertainty factors of 3 for interspecies and 10 for intraspecies variability; ATSDR, 1999a)</p>
<p>Chronic: a public health goal (PHG) for aluminum in drinking water was developed using a chronic oral screening value of 0.018 mg/kg-d derived from a human study in which volunteers fed the metal for 20 days exhibited a significant increase in serum aluminum (NOAEL/LOAEL = 125 mg/d, UF = 10 for intrahuman variability and 10 for subchronic to chronic extrapolation; OEHHA, 2001a)</p>
<p>Antimony (no data were located on carcinogenicity by the oral route or whether children represent a sensitive subpopulation)</p>
<p>Acute: no screening level identified</p>
<p>Subchronic: no screening level identified</p>
<p>Chronic: An LOAEL of 0.43 mg/kg-day was based on minor clinical signs and a slight decrease in longevity in a chronic rat study, yielding a chronic screening level of 1.4 µg/kg-day (UFs of 3 for LOAEL to NOAEL extrapolation, and 100 for intra- and interspecies extrapolation) (OEHHA, 1997c)</p>
<p>Arsenic (considered a group A human carcinogen; IRIS, 1998a) (no evidence that the young are more sensitive than adults)</p>
<p>Acute: an acute Minimal Risk Level (MRL) of 5 µg/kg-d was developed based on a 2-3 week exposure in humans which produced nausea, vomiting, diarrhea, occult blood in feces and duodenal juice (UF = 10 for LOAEL to NOAEL extrapolation; ATSDR, 2000a)</p>
<p>Subchronic: no screening level identified</p>
<p>Chronic: a 1×10^{-6} excess risk of lung and bladder cancer was calculated for a chronic oral intake by humans of 1.1×10^{-4} µg/kg-d (OEHHA, 2004a)</p>
<p>Barium (Dog and rat pharmacokinetic studies (Taylor et al., 1962; Cuddihy and Griffith, 1974) suggest that gastrointestinal absorption of barium may be higher in young animals than in older animals; IRIS, 1999) (not carcinogenic; OEHHA, 2003b)</p>

Acute: LD ₅₀ in weanling and adult rats of 220 and 132 mg/kg, respectively (OEHHA, 2003b); fatal dose of barium carbonate suggested to be about 800 mg (OEHHA, 2003b)
Subchronic: NOAEL of 0.21 mg/kg-day in adult humans exposed for four weeks (OEHHA, 2003b)
Chronic: 0.07 mg/kg-day in adult humans based on the absence of cardiovascular effects (NOAEL = 0.21 mg/kg-day) and an uncertainty factor (human variability) of 3 (OEHHA, 2003b)
Cadmium (considered a potential human carcinogen by the oral route; OEHHA, 1999a) (following ingestion, absorption was higher in young rats and guinea pigs compared to adults, suggesting that young humans may also absorb more ingested cadmium than adults; ATSDR, 1999b)
Acute: a single dose of 25 mg/kg was lethal in a human suicide (ATSDR, 1999b); a single dose LD ₅₀ of 29 mg/kg was measured in 2 week old rats (ATSDR, 1999b)
Subchronic: no screening level identified
Chronic: a Reference Exposure Level (REL) of 0.5 µg/kg-day was calculated based on proteinuria in an exposed human population (UFs = 10 for intraspecies variation; OEHHA, 2000a); an RfD of 0.5 µg/kg-day for cadmium intake in water was calculated based on the same critical study and UF listed above for the REL (IRIS, 1994a); Minimal Risk Level (MRL) = 0.21 µg/kg-day based on kidney effects in an exposed human population (UF = 10 for intraspecies variability; ATSDR, 1999b); a dose of 2.6 ng/kg-day yielded a <i>de minimis</i> excess lifetime cancer risk of 1x10 ⁻⁶ (OEHHA, 1999a)
Chromium (hexavalent) (no data to indicate children more susceptible; listed as a carcinogen by inhalation, OEHHA, 2004b)
Acute: no screening level identified
Subchronic: no screening level identified
Chronic: RfD = 3 µg/kg-day in rats based on the absence of toxicity at the highest dose tested (2.5 mg/kg-d) (uncertainty factors of 10 each for intraspecies and interspecies variability and 3 for subchronic to chronic extrapolation; IRIS, 1998b); the RDA for total chromium for a 1-3 year old child is 11 µg/day (USDA, 2006)
Cobalt (no data were located on carcinogenicity by the oral route or whether children represent a sensitive subpopulation)
Acute: no screening level identified
Subchronic: an MRL of 10 µg/kg-day was developed based on a 25 day study in which exposed humans exhibited polycythemia (UFs of 10 for LOAEL to NOAEL extrapolation and 10 for intrahuman variability) (ATSDR, 2004b)

Chronic: no screening level identified
Copper (infants and children may be more susceptible; OEHHA, 1997a) [Carcinogenicity classification -- D; not classified basis -- There are no human data, inadequate animal data from assays of copper compounds, and equivocal mutagenicity data (IRIS, 1991a)]
Acute: 5.3 mg (76 µg/kg) ingested by human adults caused gastrointestinal distress, headaches and dizziness (OEHHA, 1997a)
Subchronic: in adults a NOAEL of 0.0538 mg/kg-day (over two weeks) for gastrointestinal effects was divided by an UF = 3 (for human variability) to give an MRL (minimal risk level) of 0.02 mg/kg-day (ATSDR, 2002)
Chronic the RDA (recommended daily allowance) is 13 µg /kg-day (ATSDR, 2002) for an adult and 23 µg /kg-day for a 1-3 year old child weighing 15 kg (USDA, 2006).
Iron
Acute: 0.5 grams can be lethal if ingested by a child (Goyer, 1996; Spivey and Rader, 1988); acute ingestion of 20 mg/kg by adults was associated with gastrointestinal irritation (Institute of Medicine, 2002).
Subchronic: LOAEL = 70 mg/day (1 mg/kg/day in 70 kg adult) for 4 weeks of ingestion by adults resulting in GI effects, UL = LOAEL/1.5 (UF) = 45 mg/day (Institute of Medicine, 2002)
Chronic: Upper intake level = 40 mg/day for ingestion by infants and small children (Institute of Medicine, 2002); the RDA for a 1-3 year old child is 7 mg/day (USDA, 2006).
Lead (children may be most sensitive group, possibly due to greater absorption; OEHHA, 1997b) [B2; probable human carcinogen (IRIS, 1993a); determined to be carcinogenic by the oral route (OEHHA, 2004b)]
Acute: colic would be expected in a child following ingestion of approximately 80 µg /kg bodyweight (approximately 60 µg /dL blood level; ATSDR, 1999c) and dividing by UFs of 10 for intrahuman variability and 3 for LOAEL to NOAEL extrapolation gives an acute screening level = 2.7 µg /kg
Subchronic: no screening level identified
Chronic: intake of 29 µg/day by children associated with decreased IQ and other neurological effects, then, applying an UF = 3 results in a screening value of 10 µg/day or 0.67 µg /kg-day for a 15 kg child (OEHHA, 1997b); NSRL = 15 µg/day, MADL = 0.5 µg/day (OEHHA, 2004b); a dose of 0.18 µg/kg-day yielded an excess lifetime cancer risk of 1×10^{-6} (OEHHA, 1997b)

Manganese (neonates may absorb and retain more manganese than adults)
Acute: acute LD ₅₀ in rats = 200-300 mg/kg/day (ATSDR, 2000b)
Subchronic: no screening level identified
Chronic: RfD = 3 mg/day for non-food sources of manganese in adults (IRIS, 1996a); the RDA for a 1-3 year old child is 1.2 mg/day (USDA, 2006)
Mercury (inorganic) (not on Proposition 65 list as chemical known to the state to cause cancer; OEHHA, 2004b; listed as a Group C possible human carcinogen by the IRIS, 1995b) (suckling rats absorbed inorganic mercury from ingested food at a 30 to 40-fold higher rate than adults; ATSDR, 1999d)
Acute: Ingestion of 0.5 g can be lethal in humans, while LD ₅₀ s in rats ranged from 30 to 77 mg/kg (OEHHA, 1999b)
Subchronic: a subchronic screening value of 1.6 µg/kg-d was based on decreased weight gain and increased kidney weights in rats (UFs = 10 for intrahuman variability and 10 for interspecies extrapolation; OEHHA, 1999b)
Chronic: a screening value of 0.16 µg/kg-d was calculated based on decreased weight gain and increased kidney weights in rats (UFs = 10 for intrahuman variability, 10 for interspecies extrapolation, 10 for subchronic to chronic extrapolation; OEHHA, 1999b)
Molybdenum (no data located on carcinogenicity or whether children represent a sensitive subpopulation)
Acute: no screening level identified
Subchronic: no screening level identified
Chronic: an RfD of 5 µg/kg-day was developed based on increased serum uric acid levels in a chronically exposed human population (a UF of 3 was applied for intrahuman variability and 10 for LOAEL to NOAEL extrapolation; IRIS, 1993c)
Nickel (water soluble) (not a known oral carcinogen) (no data were located indicating that the young are more susceptible than adults)
Acute: adult humans became sick (nausea, abdominal cramps, diarrhea, vomiting) after ingesting water contaminated with nickel at dose levels ranging from 7 to 36 mg nickel/kg (OEHHA, 2001b) and dividing by UFs of 10 for intrahuman variability and 3 for LOAEL to NOAEL extrapolation gives an acute screening level = 233 µg/kg
Subchronic: no screening level identified

<p>Chronic: a chronic screening level of 1.12 µg/kg-d was calculated based on increased pup mortality in rat reproductive toxicity studies (UFs = 10 for intrahuman variability, 10 for interspecies extrapolation, 10 for potential carcinogenicity of soluble nickel by the oral route; OEHHA, 2001b); an RfD of 20 µg/kg-d was calculated based on decreased body and organ weights in rats fed nickel (UFs = 10 for intrahuman variability, 10 for interspecies extrapolation, 3 for inadequacies in the reproductive toxicity studies; IRIS, 1996b)</p>
<p>Selenium (designated a class D carcinogen: not classifiable as to carcinogenicity in humans; IRIS, 1993b) (no data to indicate that children are more sensitive than adults; ATSDR, 2003a)</p>
<p>Acute: no screening level identified</p>
<p>Subchronic: use chronic REL</p>
<p>Chronic: a chronic oral reference exposure level (REL) of 0.005 mg/kg-day was developed based on a human epidemiological study of lifetime exposures (3-fold UF for intrahuman variability; OEHHA, 2003a); the recommended daily allowance is 1.07 to 1.53 µg/kg-day for children (IRIS, 1993b)</p>
<p>Vanadium (no data were located on carcinogenicity by the oral route or whether children represent a sensitive subpopulation)</p>
<p>Acute: no screening level identified</p>
<p>Subchronic: An intermediate MRL of 3 µg/kg-day was developed based on a 3 month study in the rat producing hemorrhagic foci in the renal system (UFs of 10 for interspecies and 10 for intrahuman variability) (ATSDR, 1992c)</p>
<p>Chronic: an RfD of 9 µg/kg-day was developed based on decreased hair cystine in chronically exposed rats (an UF of 10 was applied for interspecies extrapolation and 10 for intrahuman variability; IRIS, 1996c).</p>
<p>Zinc (no evidence to suggest children more sensitive than adults)</p>
<p>Acute: LOAEL approx. 2-8 mg/kg based on gastrointestinal distress in adults after single-dose ingestion (ATSDR, 2003b)</p>
<p>Subchronic: subchronic MRL = 0.3 mg/kg-day based on decreased erythrocyte SOD activity, hematocrit and serum ferritin in human females (composite UF = 3; ATSDR, 2003b)</p>
<p>Chronic: RfD = 0.3 mg/kg-day based on same subchronic study cited above (IRIS, 1992); Recommended Dietary Allowance of 3 mg/day and a Tolerable Upper Intake Level of 7 mg/day in 1-3 year olds (The National Academies, 2001)</p>

Table 7: VOCs: Oral route: Toxicity Values

1,1-Dichloroethane (carcinogenic based on rodent studies, no evidence of enhanced sensitivity of infants or children; OEHHA, 2003c; ATSDR, 1990)
Acute: no screening level identified
Subchronic: no screening level identified
Chronic: lifetime oral consumption of 0.171 µg/kg-d yielded an excess individual cancer risk of 10 ⁻⁶ (OEHHA, 2003c); no significant risk level (NSRL) = 100 µg/day (yields an excess individual cancer risk of 10 ⁻⁵ for a 70 year exposure; OEHHA, 2004b)
1,2-Dichloroethene (no carcinogenicity studies were located, ATSDR, 1996; IRIS, 1995a; no evidence of increased sensitivity of infants or children, ATSDR, 1996)
Acute: minimal risk level (MRL) = 1.0 mg/kg-d based on decreased hematocrit and erythrocytes in female rats treated by single-dose oral gavage (NOAEL = 97 mg/kg-day, UFs of 10 for intraspecies and 10 for interspecies variability, ATSDR, 1996)
Subchronic: minimal risk levels (MRL) = 0.3 mg/kg-day based on decreased hematocrit in male rats dosed by gavage for 90 days with the cis isomer (NOAEL = 32 mg/kg-day, UFs 10 for intraspecies and 10 for interspecies variability, ATSDR, 1996); MRL = 0.2 mg/kg-day based on increased serum alkaline phosphatase and increased relative liver weight in male mice fed the trans isomer via the drinking water for 90 days (NOAEL = 17 mg/kg-day, UFs of 10 for intraspecies and 10 for interspecies variability, ATSDR, 1996)
Chronic: no screening level identified
Acetone (minimal evidence that young or pregnant rats more sensitive than nonpregnant adults; ATSDR, 1994) (data inadequate for assessment of human carcinogenic potential; IRIS, 2003c)
Acute: no screening level identified
Subchronic: Minimal Risk Level (MRL) = 2 mg/kg-day based on a 13 week study in rats identifying mild macrocytic anemia (UFs of 10 for intraspecies and 10 for interspecies extrapolation; ATSDR 1994)
Chronic: RfD = 0.9 mg/kg-day based on same subchronic rat drinking water study as above producing nephropathy (NOAEL = 900 mg/kg-day, UF = 10 for intraspecies, 10 ^{1/2} for interspecies, 10 ^{1/2} for subchronic to chronic extrapolation, 10 for data base deficiencies; IRIS, 2003c)
Benzene (classified as a human carcinogen; IRIS, 2000; OEHHA, 2001c; no data to indicate that infants or children are more susceptible than adults to the carcinogenic effects)

Acute: a single oral dose of 125 mg/kg is estimated to be lethal in humans (OEHHA, 2001c); as little as 50 mg/kg has caused death in humans (ATSDR, 2004)
Subchronic: no screening level identified
Chronic: a noncancer screening value of 9 µg/kg-day was based on hematological effects in workers exposed for up to 21 years (UF = 10 for intrahuman variability; OEHHA, 2001c); a <i>de minimis</i> excess individual cancer risk of 10 ⁻⁶ was associated with a lifetime exposure of 0.01 µg/kg-d (OEHHA, 2001c); a No Significant Risk Level (NSRL) of 7 µg/day for a cancer risk of 10 ⁻⁵ (equivalent to 0.01 µg/kg-d at a cancer risk level of 10 ⁻⁶ ; OEHHA, 2004b); MADL = 0.34 µg/kg-day (OEHHA, 2004b)
Benzo[b]fluoranthene (classified as a group B2 probable human carcinogen by IRIS, 1994d)
Acute: no data located
Subchronic: no data located
Chronic: a No Significant Risk Level (NSRL) of 0.096 µg/day (equivalent to 0.16 ng/kg-d at the 10 ⁻⁶ cancer risk level; OEHHA, 2004b)
Chrysene (classified as a group B2 probable human carcinogen by IRIS, 1994e)
Acute: no data located
Subchronic: no data located
Chronic: a No Significant Risk Level (NSRL) of 0.36 µg/day (equivalent to 0.58 ng/kg-d at the 10 ⁻⁶ cancer risk level; OEHHA, 2004b)
Fluoranthene (classified as a group D carcinogen [not classifiable as to human carcinogenicity] by IRIS, 1990b)
Acute: no data located
Subchronic: see chronic study below
Chronic: an oral RfD of 40 µg/kg-d was developed based on a 13 week subchronic study in which mice developed nephropathy, increased liver weights, hematological changes and clinical signs (UFs of 10 for intraspecies extrapolation, 10 for interspecies extrapolation, and 30 for both subchronic to chronic extrapolation and the absence of reproductive/developmental data and data from a second animal species; IRIS, 1990b)
Methyl ethyl ketone (data judged inadequate for determination of carcinogenicity in humans; IRIS, 2003a) (no data on whether the young are more susceptible)
Acute: mild renal tubular necrosis in rats after a single oral dose of 1080 mg (ATSDR, 1992a)
Subchronic: no screening level identified

Chronic: RfD of 0.6 mg/kg-day based on decreased rat pup weight in a repro study, UF = 1000 (10 for interspecies, 10 for intraspecies, 10 for deficiencies in data base) (IRIS, 2003a)
Methyl Isobutyl Ketone (listed as food additive by FDA)
Acute: no screening level identified
Subchronic: NOAEL = 250 mg/kg-day based on a variety of mild effects at 1000 mg/kg-day in rats gavaged for 13 weeks (IRIS, 2003b); applying UF = 100 gives a subchronic screening level = 10 mg/kg-day
Chronic: using above subchronic study and applying another UF = 10 for subchronic to chronic extrapolation gives chronic screening level = 1 mg/kg-day (IRIS thought data insufficient for derivation of a chronic RfD)
Phenanthrene (classified as a group D carcinogen [not classifiable as to human carcinogenicity] by IRIS, 1990c)
Acute: no data located
Subchronic: no data located
Chronic: no data located
Pyrene (classified as a group D carcinogen [not classifiable as to human carcinogenicity] by IRIS, 1991b)
Acute: no data located
Subchronic: see chronic study below
Chronic: an oral RfD of 30 µg/kg-d was developed based on a 13 week subchronic study in which mice developed kidney effects (UFs of 10 for interspecies extrapolation, 10 for intraspecies extrapolation, 10 for subchronic to chronic extrapolation, and 3 for the absence of developmental/reproductive data and data from a second animal species; IRIS, 1991b)
Styrene (no evidence for increased sensitivity of the young; listed as a group 2B possible human carcinogen by IARC [1994] with inadequate evidence in humans and limited evidence in animals)
Acute: no screening level identified
Subchronic: Minimal Risk Level (MRL) = 0.2 mg/kg-day based on a 100 day study in rats identifying changes in hepatic enzymes (UFs of 10 for interspecies, 10 for intraspecies, and 10 for use of a LOAEL; ATSDR, 1992b)
Chronic: RfD = 2 mg/kg-day for effects in rbcs and livers of dogs (UF = 100 for intra and interspecies variability, they also included 10 for subchronic to chronic extrapolation which I have dropped since the study ran for 560 days; IRIS, 1990a)
Toluene (carcinogenicity judged not classifiable [Group D] due to absence of human data and inadequate animal data; IRIS, 1994b) (only minimal data indicating that neonatal humans may be more sensitive than adults)

<p>Acute: Minimal Risk Level (MRL) = 0.8 mg/kg-day based on neurological changes (altered visual information processing) in rats following single-dose oral gavage (UFs of 10 for human variability, 10 for interspecies extrapolation, and 3 for use of a minimally adverse LOAEL; ATSDR, 2000c)</p>
<p>Subchronic: Minimal Risk Level (MRL) = 0.02 mg/kg-day based on a 28 day drinking water study in mice identifying increased brain norepinephrine and dopamine (UFs of 10 for human variability, 10 for interspecies extrapolation, and 3 for use of a minimally adverse LOAEL; ATSDR, 2000c)</p>
<p>Chronic: a chronic screening value of .022 mg/kg-day was identified from a subchronic mouse drinking water study producing immunological toxicity (UFs of 10 for interspecies, 10 for intraspecies, and 10 for subchronic to chronic extrapolation; OEHHA, 1999c); an RfD = 0.2 mg/kg-day was based on a subchronic rat gavage study which detected changes in liver and kidney weights (UF = 1000 for intraspecies and interspecies extrapolation, subchronic to chronic extrapolation, and limited developmental and reproductive toxicity data; IRIS, 1994b); maximum allowable dose level (MADL) = 7.0 mg/day (OEHHA, 2004b)</p>
<p>Trichloroethylene (IARC considers the evidence for carcinogenicity to be sufficient in animals and limited in humans; OEHHA, 1999d) (no data were located showing that the young are more sensitive than adults)</p>
<p>Acute: single-dose oral LD₅₀s were 2400 mg/kg-d in mice and 7200 mg/kg-d in rats (ATSDR, 1997b)</p>
<p>Subchronic: no screening level identified</p>
<p>Chronic: a chronic screening level of 0.5 mg/kg-day was based on kidney nephropathy in rats (UFs of 10 for interspecies and 10 for intrahuman variability; OEHHA, 1999d); an excess individual cancer risk of 10⁻⁶ was associated with a lifetime exposure of 0.077 µg/kg-d (OEHHA, 1999d)</p>

Table 8: sVOCs: Oral route: Toxicity Values

1H-isoindole-1,3(2H)-dione (a.k.a. captan) (no data were located on the carcinogenicity of 1H-isoindole-1,3(2H)-dione or whether children represent a sensitive subpopulation)
Acute: no screening level identified
Subchronic: no screening level identified
Chronic: an RfD of 130 µg/kg-d was developed based on decreased bodyweight in the rat (an UF of 10 was applied for interspecies and 10 for intrahuman extrapolation; IRIS, 1989)
Aniline (classified as a B2 probable human carcinogen by IRIS, 1994c)
Acute: Methemoglobinemia is the principle mechanism of acute aniline toxicity in man (Hazardous Substances Data Bank, 2004); a dose-dependent increase in methemoglobin resulted from single oral doses of aniline of 25-65 mg/person (Jenkins et al., 1972; IARC, 1982) with a NOEL at 15 mg (approximately 0.21 mg/kg); applying an UF of 10 for intrahuman variability yields an acute screening level of 0.021 mg/kg-day.
Subchronic: no screening level identified
Chronic: an excess cancer risk of 10 ⁻⁶ was calculated for a daily exposure of 0.175 µg/kg-d based on a two year feeding study in rats (IRIS, 1994c)
Benzothiazole (no data located on carcinogenicity or susceptibility of children) (used as a flavoring in foods at up to 0.5 ppm, listed as a GRAS substance ["generally recognized as safe"]; NTP, 2004)
Acute: Oral LD ₅₀ s: rat = 380-479 mg/kg, mouse = 900 mg/kg (NTP, 2004)
Subchronic: no screening level identified
Chronic: no screening level identified
Cyclohexanone (no data were located on the carcinogenicity of cyclohexanone or whether children represent a sensitive subpopulation)
Acute: no screening level identified
Subchronic: no screening level identified
Chronic: an RfD of 5.0 mg/kg-d was developed based on decreased bodyweight gain in the rat (an UF of 10 was applied for interspecies and 10 for intrahuman extrapolation; IRIS, 1987)

Phenol (data considered insufficient to determine if children are more sensitive than adults; ATSDR, 1998) (data considered inadequate for carcinogenicity assessment in humans; IRIS, 2002)

Acute: no screening level identified

Subchronic: The chronic RfD of 0.3 mg/kg-d (see below) could be applied to subchronic exposures, since it is based on a developmental study with an exposure duration of 10 days

Chronic: an RfD of 0.3 mg/kg-d was developed based on decreased maternal weight gain in a rat developmental study (UFs = 10 for interspecies variability, 10 for intrahuman variability, and 3 for immunological and hematological effects noted in a 28 day mouse drinking water study; IRIS, 2002)

Chapter 5: Evaluation of Toxicity Due to Ingestion of Tire Shreds Based on the Existing Literature of Tire Leachate Studies

Table 9 lists 27 chemicals and the highest amount of each that leached per gram of tire, as found in the published literature, along with leaching conditions. Measurements were made in laboratory settings under a variety of different conditions. Aqueous solutions containing various salts and/or buffers were used, with the pH ranging from 2.1 to 12.1 across the studies, or not controlled. Perhaps even more problematic was the variable leaching times, ranging from 17 hours to six months. These studies also utilized different starting material: whole tires, tire shreds, chips and crumb.

The different brands of tires used in the different studies almost certainly contributed to the variable levels of chemicals released (Tables 2-4), since tire components, as well as the tire manufacturing process itself, vary across the industry. Keeping these uncertainties in mind, the highest leaching value for each chemical was chosen for calculating the dose. In this respect, the calculations represent worst-case scenarios. Using the laboratory leaching values in this way assumes that the same amounts of these chemicals would leach following ingestion of tire-derived shreds or crumb by a child. All such leaching chemicals were also assumed to be 100 percent bioavailable, representing another worst-case assumption.

The doses calculated in Table 9 are based on a one-time (acute) ingestion of 10 grams of tire shreds or crumb rubber by a 15 kg child. The value of 10 grams has been recommended for acute risk assessment for children who ingest large amounts of soil on 1-2 days out of the year (U.S. EPA, 2002; OEHHA, 2000c). This is not a typical behavior pattern observed in most children, but rather a poorly characterized behavior seen in a subset of young children (U.S. EPA, 2002). It seems reasonable to assume that a child ingesting 10 grams of soil in a single episode would also be capable of ingesting 10 grams of crumb rubber. A bodyweight of 15 kg is the 50th percentile value for both male and female children that are three years old (U.S. EPA, 2002).

As discussed earlier in this report, toxicity reference values from authoritative bodies were collected for acute, subchronic and chronic oral exposures to the substances released by tires. The acronyms for these reference values, together with their meanings and issuing bodies, are listed at the end of Table 9. These can be used as screening levels and compared to the estimated dose a child might ingest, to predict whether adverse noncancer health effects would occur. If the estimated dose were less than the screening level, then acute health effects would not be expected. Toxicity reference values for use as screening levels have not been developed for every chemical listed in Table 9; therefore, in some cases screening levels were calculated where adequate toxicity data were located in the published literature (toxicity data cited by chemical in Tables 6-8).

Since the exposure scenario being considered here is an acute, single-dose exposure, acute health effects are expected, and acute screening levels are most appropriate for use in risk calculations. However, Table 9 shows that an acute screening level was usually not available. In such cases, a subchronic screening level was used, and if this was also unavailable, a chronic screening level was used. The following reasoning was applied in these latter two cases; if the estimated dose was lower than the subchronic or chronic

screening level, then acute health effects were considered unlikely. When available, OEHHA values were used as screening levels. Conclusions reached from this comparison of screening level with estimated dose are listed in Table 9 for each chemical.

The dose levels of ingested chemicals presented in Table 9 are due to ingestion of tire shreds. For comparison, Table 10 shows the average daily intakes resulting from the presence of these chemicals in food, water and air. In many cases these average daily intakes are rough estimates. Nonetheless, it is useful to compare the tire-derived levels to the average daily intakes. Average daily intakes were located for 17 of the chemicals listed in Table 9. For 12, the average daily intakes equal or exceed the tire-derived exposures. In many cases the exposure due to ingestion of tire shreds is much lower than the average daily intake. Only for arsenic, iron, lead, nickel and zinc does the tire-derived exposure exceed the average daily intake. This indicates that particular care should be taken when comparing the tire-derived exposures to these chemicals to their corresponding health-based screening levels.

Table 9. Comparison of ingested dose to health-based screening level for an acute ingestion of tire-derived crumb/shreds by a child based on published studies of tire leachate: noncancer health effects.

Chemical	Highest amount released per g of tire and leaching conditions¹	Dose²	Screening level³
Metals			
Aluminum	2.0 µg released per g of tire for slices of tire incubated in an aqueous solution at pH 3.5, 20-40°C for 24 h with agitation	1.3 µg/kg	Not acutely toxic in humans based on widespread presence in antacids, water and food; a 20 day human study was used to develop a chronic screening level of 18 µg/kg-d (OEHHA, 2001a)
<i>Conclusion</i>	<i>No acute screening level was identified. However, the estimated dose is 14-fold lower than the chronic screening level, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		
Arsenic	0.13 µg released per g of tire for shredded tires incubated in an aqueous solution whose pH ranged from 2.1 to 5.5 over 38 days	0.087 µg/kg	Acute MRL = 5 µg/kg-day (ATSDR, 2000a)
<i>Conclusion</i>	<i>The estimated dose is over 50-fold lower than the acute MRL, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		
Barium	1.7 µg released per g of tire shreds shaken for seven days in an aqueous solutions of 0-25 percent salinity	1.13 µg/kg	Subchronic screening level = 21 µg/kg-day (OEHHA, 2003b in Table 6)
<i>Conclusion</i>	<i>No acute screening level was identified. However, the estimated dose is 19-fold lower than the subchronic screening level, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		
Cadmium	0.27 µg released per g of tire (leaching conditions as for Al)	0.18 µg/kg	Chronic REL in adults = 0.5 µg/kg-day (OEHHA, 1999a)
<i>Conclusion</i>	<i>No acute or subchronic screening levels were identified. However, the estimated dose is 2.8-fold lower than the chronic REL, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		
Cobalt	0.1 µg released per g of tire (leaching conditions as for barium)	0.07 µg/kg	Intermediate MRL = 10 µg/kg-day (ATSDR, 2004b)
<i>Conclusion</i>	<i>The estimated dose is 143-fold lower than the intermediate MRL, suggesting a low risk of adverse effects from a one-time ingestion.</i>		

Chemical	Highest amount released per g of tire and leaching conditions¹	Dose²	Screening level³
Copper	4.88 µg released per g of tire for shredded tires shaken for 17 h in an aqueous solution, pH = 4.9	3.25 µg/kg	The recommended daily allowance (RDA) for a 1-3 year old child is 23 µg/kg-day (USDA, 2006)
<i>Conclusion</i>	<i>Since the estimated dose is below the recommended daily allowance, adverse health effects are not expected.</i>		
Chromium	0.5 µg (fractions as trivalent and hexavalent not determined) released per g of tire (leaching conditions as for Al)	0.33 µg/kg	Chronic RfD (hexavalent) = 3.0 µg/kg-day (IRIS, 1998b)
<i>Conclusion</i>	<i>No acute or subchronic screening levels were identified. However, the estimated dose is 9-fold lower than the chronic RfD, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		
Iron	1.1 mg released per g of tire (leaching conditions as for Al)	0.73 mg/kg	Upper intake level = 2.7 mg/kg-day for a 15 kg child (Institute of Medicine, 2002)
<i>Conclusion</i>	<i>The estimated dose is 3.7-fold lower than the upper intake level, suggesting a low risk of adverse health effects from a one-time exposure</i>		
Lead	0.92 µg released per g of tire (leaching conditions as for Al)	0.61 µg/kg	Acute screening level = 2.7 µg/kg (ATSDR, 1999c in Table 6); chronic screening level = 0.67 µg/kg-day (OEHHA, 1997b in Table 6)
<i>Conclusion</i>	<i>The estimated dose is 4.4-fold lower than the acute screening level in children. It is also below the chronic screening level. This suggests a low risk of adverse health effects from a one-time ingestion.</i>		
Manganese	5.8 µg released per g of tire for tire shreds shaken for 7 days in an aqueous solution at pH 6-7 and 25 parts per thousand salinity	3.9 µg/kg	Chronic RfD for nonfood sources of Mn in adults = 43 µg/kg-day (IRIS, 1996a in Table 6)
<i>Conclusion</i>	<i>No acute or subchronic screening levels were identified. However, the estimated dose is 11-fold lower than the chronic RfD, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		

Chemical	Highest amount released per g of tire and leaching conditions¹	Dose²	Screening level³
Mercury	0.07 ng released per g of tire for ground tires shaken in aqueous solutions ranging in pH from 2.9 to 4.9 and for times ranging from 18 to 24 hours	0.05 ng/kg	Subchronic screening value of 1.6 µg/kg-day (OEHHA, 1999b)
<i>Conclusion</i>	<i>No acute screening level was identified. However, the estimated dose is 32,000-fold lower than the subchronic screening level, suggesting a low risk of adverse health effects from a one-time oral exposure.</i>		
Nickel	12 µg released per g of tire (leaching conditions as for Cu)	8.0 µg/kg	Acute screening level = 233 µg/kg (OEHHA, 2001b in Table 6)
<i>Conclusion</i>	<i>The estimated dose is 29-fold below the acute screening level, suggesting a low risk of adverse health effects from a one-time oral exposure.</i>		
Selenium (elemental)	0.44 µg released per g of tire (leaching conditions as for Al)	0.29µg/kg	Chronic REL = 5 µg/kg-day (OEHHA, 2003a)
<i>Conclusion</i>	<i>The estimated dose is 17-fold below the chronic REL, suggesting a low risk of adverse health effects.</i>		
Zinc	2.32 mg released per g of tire chips shaken for 67 h in an aqueous solution at pH 2.5	1.55 mg/kg	Subchronic MRL = 0.3 mg/kg-day (ATSDR, 2003b)
<i>Conclusion</i>	<i>The estimated dose is 5.1-fold higher than the subchronic MRL, so adverse health effects are possible, but unlikely from an acute ingestion of tire shreds</i>		
Volatile Organic Compounds			
Acetone	0.115 µg released per g of tire chips incubated in water for at least 6 months prior to sampling	0.077 µg/kg	Subchronic MRL = 2.0 mg/kg-day (ATSDR, 1994)
<i>Conclusion</i>	<i>No acute screening level was identified. However, the estimated dose is over 25,000-fold lower than the subchronic MRL, suggesting a low risk of adverse health effects from a one-time oral exposure.</i>		
Benzene	0.218 µg released per g of shredded tires incubated for 38 days in an aqueous solution, where the pH varied from 2.1 to 4.7	0.145 µg/kg	MADL = 0.34 µg/kg-day (OEHHA, 2004b)

Chemical	Highest amount released per g of tire and leaching conditions¹	Dose²	Screening level³
<i>Conclusion</i>	<i>No acute or subchronic screening levels were identified. However, the estimated dose is 2.3-fold lower than the chronic MADL, suggesting a low risk of adverse health effects from a one-time oral exposure.</i>		
Methyl ethyl ketone	0.017 µg released per g of tire chips (leaching conditions as for Acetone)	0.011 µg/kg	Chronic RfD = 0.6 mg/kg-day (IRIS, 2003a)
<i>Conclusion</i>	<i>No acute or subchronic screening levels were identified. However, the estimated dose is over 50,000-fold lower than the chronic RfD, suggesting a low risk of adverse health effects from a one-time exposure.</i>		
Methyl isobutyl ketone	1.15 µg released per g of tire chips (leaching conditions as for Acetone)	0.77 µg/kg	Subchronic screening level = 10 mg/kg-day (IRIS, 2003b in Table 6)
<i>Conclusion</i>	<i>No acute screening level was identified. However, the estimated dose is more than 10,000-fold lower than the subchronic screening level, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		
Toluene	0.28 µg released per g of tire shreds (leaching conditions as for benzene)	0.187 µg/kg	Acute MRL = 0.8 mg/kg (ATSDR, 2000c)
<i>Conclusion</i>	<i>The estimated dose is over 4,000-fold lower than the acute MRL, suggesting a low risk of adverse health effects from a one-time oral exposure.</i>		
Naphthalene	1.1 µg released per g of tire shreds (leaching conditions as for barium)	0.73 µg/kg	Acute oral MRL = 600 µg/kg-day (ATSDR, 2005)
<i>Conclusion</i>	<i>The estimated dose is over 800-fold lower than the acute MRL, suggesting a low risk of health effects from a one-time ingestion.</i>		
2-Methyl naphthalene	0.54 µg released per g of tire shreds (leaching conditions as for barium)	0.36 µg/kg	Chronic oral MRL = 40 µg/kg-day (ATSDR, 2005)
<i>Conclusion</i>	<i>The estimated dose is 111-fold lower than the chronic MRL, suggesting a low risk of health effects from a one-time ingestion.</i>		
Trichloroethylene	0.8 ng released per g of tire chips (leaching conditions as for acetone)	0.53 ng/kg	Chronic screening level = 0.5 mg/kg-day (OEHHA, 1999d)

Chemical	Highest amount released per g of tire and leaching conditions¹	Dose²	Screening level³
<i>Conclusion</i>	<i>No acute or subchronic screening levels were identified. The estimated dose is 900,000-fold lower than the chronic screening level, suggesting a low risk of adverse health effects from a one-time ingestion</i>		
Semi-volatile Organic Compounds			
aniline	0.74 µg released per g of tire shreds incubated for 38 days in an aqueous solution, pH 12.0-12.1	0.5 µg/kg	Acute screening level = 0.021 mg/kg-day (Jenkins et al., 1972 and IARC, 1982 in Table 6)
<i>Conclusion</i>	<i>The estimated dose is 42-fold lower than the acute screening level, suggesting a low risk of adverse health effects from a one-time oral ingestion.</i>		
Benzothiazole	100 µg released per g of tire crumb shaken in water at 25°C for 5 days	67 µg/kg	On GRAS list; oral LD ₅₀ in rats = 380-479 mg/kg (NTP, 2004)
<i>Conclusion</i>	<i>Inadequate screening level data.</i>		
2(3H)-Benzothiazolone	0.17 µg released per g of whole tire submerged in water for 2 weeks with aeration	0.11 µg/kg	No data located
<i>Conclusion</i>	<i>Inadequate screening level data.</i>		
2-Hydroxy-benzothiazole	36 µg released per g of tire crumb (leaching conditions as for Benzothiazole)	24 µg/kg	No data located
<i>Conclusion</i>	<i>Inadequate screening level data.</i>		
2-(4-Morpholin-yl)benzothiazole	2.0 µg released per g of tire crumb (leaching conditions as for Benzothiazole)	1.33 µg/kg	No data located
<i>Conclusion</i>	<i>Inadequate screening level data.</i>		
Phenol	0.01 µg released per g of ground tire incubated in aqueous solutions ranging in pH from 2.9 to 4.9 and for times ranging from 18 to 24 hours		

0.0

Chemical	Highest amount released per g of tire and leaching conditions¹	Dose²	Screening level³
<i>Conclusion</i>	<i>No acute or subchronic screening levels were identified. However, the estimated dose is over 42,000-fold lower than the chronic RfD, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		
Phenoxazine	0.22 µg released per g of whole tire (leaching conditions as for 2(3H)-Benzothiazolone)		0.
<i>Conclusion</i>	<i>Inadequate screening level data.</i>		
4-(Phenyl-amino)-phenol	0.34 µg released per g of whole tire (leaching conditions as for 2(3H)-Benzothiazolone)		0.
<i>Conclusion</i>	<i>Inadequate screening level data.</i>		

¹ See Table 2 for references.

²The dose is the amount of chemical assumed to leach from 10 grams of tire crumb/shreds following ingestion by a 15 kg child.

³ See Tables 6, 7 and 8 for references associated with the screening levels covering metals, volatile organic compounds and semi-volatile organic compounds, respectively.

MRL = minimal risk level (ATSDR)

NSRL = no significant risk level (OEHHA)

REL = reference exposure level (OEHHA)

RfD = reference dose (U.S. EPA)

MADL = maximum allowable dose level (OEHHA)

GRAS = generally recognized as safe (FDA)

RDA = recommended daily allowance (NAS/NRC)

UL = upper intake level (Institute of Medicine)

Table 10. Average daily intakes of chemicals released by tires¹

Chemical	Source	Ave. daily intake in µg/kg	Reference
<i>Metals</i>			
Aluminum	Total diet	13-270	OEHHA, 2001d
Antimony	Food and water	0.061	OEHHA, 1997c
Arsenic	Food and water	0.013	OEHHA, 2004a
Barium	Food and water	9-24	ATSDR, 2005b
Cadmium	Food and water	0.08-1.17	OEHHA, 1999a
Chromium (total)	Total diet	1.0	ATSDR, 2000d
Cobalt	Food	0.07-0.53	ATSDR, 2004b
Copper	Total diet	39	OEHHA, 1997a
Iron	All sources	120-230	HSDB, 2006a
Lead	Total diet	0.23	ATSDR, 2005c
Manganese	Food	100	HSDB, 2006b
Mercury (inorganic)	Food	0.06	OEHHA, 1999b
Nickel	Total diet	2.2	OEHHA, 2001b
Selenium	Total diet	1.5	ATSDR, 2003a
Vanadium	Total diet	A few tenths of µg	ATSDR, 1992c
Zinc	All sources	67-213	ATSDR, 2005d
<i>Organics</i>			
1H-isoindole-1,3(2H)dione (a.k.a. captan)	All sources	0.007-0.014	HSDB, 2006c
Benzene	Air	0.1	OEHHA, 2001c
Chrysene	Total diet	0.007	HSDB, 2006d
Fluoranthene	Air	0.00006	HSDB, 2006e
Naphthalene	All sources	0.27	HSDB, 2006f
Phenanthrene	Air and water	0.0007-0.0054	HSDB, 2006g
Pyrene	All sources	0.00001	HSDB, 2006h
Toluene	Air	0.27	HSDB, 2006i
Trichloroethylene	Air and water	186-757	ATSDR, 1997b
Total Polycyclic Aromatic Hydrocarbons	Food	0.023-0.23	ATSDR, 1995

¹ Intakes were normalized to bodyweights of 70 kg for adult data and 15 kg for data from 2 year old children

Comparison of ingested dose to screening levels: noncancer effects

Comparison performed using the data from Table 9:

$\mu\text{g chemical released/gram tire shreds} \times 10 \text{ grams tire shreds ingested}/15 \text{ kg child} =$

$\mu\text{g chemical ingested} \times 10/15 \text{ kg child} \rightarrow \text{does dose exceed screening value?}$

Zn

Addressing acute health effects, only the estimated dose of leachable zinc (1.55 mg/kg) exceeded its associated screening level: in this case 5.1-fold above a subchronic MRL of 0.3 mg/kg-day based on decreased erythrocyte SOD activity, hematocrit and serum ferritin in human females dosed daily for 10 weeks. These effects were probably due to zinc-induced changes in the copper and iron balance, causing the above-mentioned hematological effects to develop towards the end of the study (IRIS, 1992). Thus, zinc supplementation acted as an inducer of copper and iron deficiency.

Since nutritional deficiencies and their related health effects develop over extended periods of time, these effects are unlikely to occur in response to an acute ingestion of zinc. In addition, zinc is an essential element with a Recommended Dietary Allowance of 3 mg/day and a Tolerable Upper Intake Level of 7 mg/day for a 3-year-old child (National Academies, 2001). These considerations make it unlikely that an acute, oral ingestion of 1.55 mg/kg of zinc by a child would result in adverse health effects, other than the gastrointestinal distress observed in adults ingesting 2-8 mg/kg acutely (Table 6).

An additional area of uncertainty in the zinc risk calculations relates to the range of zinc leaching values listed in Table 2. The highest value (2.3 mg leached per gram of tire) was selected for use in the risk calculation described in Table 9. However, this value is from 2.6- to 2,300-fold higher than other zinc measurements listed in Table 2, and 18-fold higher than the value measured in the gastric digestion simulation experiment shown below in Table 16. Thus, using most zinc leaching values other than the maximum value in Table 9 would result in an estimated dose that was below the subchronic screening level for zinc. This underscores the importance of accurate leaching data.

Other chemicals

Six of the chemicals listed in Table 9 could not be evaluated due to the absence of screening levels. In addition, 11 of the VOCs and sVOCs identified in Tables 3 and 4 as leaching from tires could not be evaluated due to the absence of information on the amount of tire rubber that was used to produce each leachate. Therefore, the acute risks from these chemicals remain uncharacterized. Other than for naphthalene and 2-methyl naphthalene, the data on polycyclic aromatic hydrocarbons (PAHs) and total petroleum hydrocarbons could not be evaluated since leaching data were not presented for individual compounds (Table 3).

It has become common practice to perform calculations to determine whether health effects are expected from exposures to complex mixtures of toxicants. The leachate from tires represents such a complex mixture. One methodology (CIWMB, 2004) is to calculate a Hazard Quotient for each individual toxicant by dividing the dose by the

associated health-based screening level, and then add all values together to give a Hazard Index (Table 11). A Hazard Index less than one suggests that health effects are unlikely, while an Index greater than one suggests that health effects are more likely. This approach is most meaningful when applied to chemicals that cause similar effects on the same target organ. Such is not the case here. It should also be noted that for most chemicals listed in Table 9 an acute screening level was not available, so that subchronic or chronic values were used instead. This undoubtedly led to higher individual Hazard Quotients than would have been calculated if acute screening values were available. On the other hand, for some chemicals there were no screening level data, so that a Hazard Quotient could not be calculated.

Nonetheless, the Hazard Index approach was used as a first tier screening procedure to estimate whether cumulative impacts would be expected from all the chemicals released by tire shreds. The Hazard Index based on all chemicals except zinc is 1.8, while that including zinc is 6.9. As discussed above, since zinc-induced copper or iron deficiencies develop over a period of weeks in which zinc is ingested daily, we believe it unlikely that zinc released from a one-time ingestion of tire shreds would cause health effects other than gastrointestinal distress. Since the Hazard Index for all chemicals other than zinc is close to one, this first tier screening suggests that this complex mixture of chemicals does not represent a serious health hazard.

Table 11. Hazard Quotients and Hazard Index for an Acute Ingestion of Chemicals Identified in Published Studies of Tire Leachate

Chemical	Dose ¹ /screening value ¹	Hazard quotient ²
Metals		
aluminum	1.3/18	0.072
arsenic	0.087/5	0.017
barium	1.13/21	0.054
cadmium	0.18/0.5	0.360
cobalt	0.07/10	0.007
copper	3.25/23 (RDA)	Not calculated
chromium (hexavalent)	0.33/3	0.110
iron	730/2700	0.27
lead	0.61/2.7	0.226
manganese	3.9/43	0.091
mercury	0.00005/1.6	0.00003
nickel	8/233	0.034
selenium (elemental)	0.29/5	0.058
zinc	1550/300	5.167

Chemical	Dose ¹ /screening value ¹	Hazard quotient ²
Volatile Organic Compounds		
acetone	0.077/2000	0.00004
benzene	0.145/0.34	0.426
methyl ethyl ketone	0.011/600	0.00002
methyl isobutyl ketone	0.77/10,000	0.00008
toluene	0.187/800	0.0002
naphthalene	0.73/600	0.001
2-methyl naphthalene	0.36/40	0.009
trichloroethylene	0.00053/500	1.1 x 10 ⁻⁶
Semi-volatile Organic Compounds		
aniline	0.5/21	0.024
phenol	0.007/300	0.00002
HAZARD INDEX (-) ZINC		1.8
HAZARD INDEX (+) ZINC		6.9

¹from Table 9, both in µg/kg ²calculated from second column of this table

In summary, serious noncancer health effects are not expected following a one-time ingestion of tire-derived shreds or crumb by a child. Gastrointestinal distress might occur as has been observed in adults ingesting high amounts of zinc (Table 6); however, the variable levels of zinc that leached from tire-derived material (Table 2 and the gastric digestion simulation experiment shown in Table 16) suggest that the amount leaching from ingested rubber would be significantly lower than that used in the calculation in Table 9, so that acute effects would not be expected. Chronic effects are also not expected due to the single-dose nature of the exposure (chronic health effects are examined more closely in a Chapter 7 dealing with chronic exposures via hand-to-mouth activity). Should a child ingest ten grams of tire shreds on more than one occasion, the methodology followed here would yield a proportional increase in ingested dose that could exceed some of the acute screening values listed in Table 9. Whether a child ingests ten grams of tire shreds often enough for such exposures to qualify as subchronic or chronic is unknown.

Estimating the increased cancer risk

From among the chemicals listed in Table 9, seven (arsenic, cadmium, lead, benzene, trichloroethylene, aniline, naphthalene) are currently listed as oral carcinogens by the State of California (OEHHA, 2005). In general, data are lacking as to whether a one-time ingestion of most carcinogens is sufficient to cause cancer. Nonetheless, Table 10 calculates the increased cancer risk to a three year old assuming that a one-time ingestion of these seven chemicals is sufficient, however, the true risk may be greater or less than the calculated risk. The calculations were performed according to draft methodology recommended by the U.S. EPA (2003c). Following this methodology, the dose from

Table 9 was averaged over a 70-year lifetime, multiplied by the Cancer Slope Factor, and multiplied by a factor of three to cover the increased sensitivity of a three-year-old child to some carcinogens:

$\text{ingested dose}/(70)(365) \times \text{oral cancer slope factor} \times (3) =$ $\text{increased cancer risk in a three-year-old}$

The increased cancer risk from exposure to each of seven chemicals (arsenic, cadmium, lead, benzene, trichloroethylene, aniline, naphthalene) is low, while the total increased risk is 1.2×10^{-7} . This is 3-fold higher than the increased cancer risk of 3.7×10^{-8} based on a “gastric digestion” experiment carried out by OEHHA (see Table 17). Thus, ingestion of tire-derived shreds by a three-year-old child is associated with a low cancer risk. The same U.S. EPA draft methodology that recommends the use of a safety factor of three for calculating the cancer risk to children between the ages of 2 and 15, also recommends the use of a safety factor of ten for children below the age of two (U.S. EPA, 2003c). Thus, multiplying the above total increased risk by 3.3 yields an increased risk of 3.6×10^{-7} .

Therefore, should a child below the age of two ingest ten grams of shredded tire rubber, the cancer risk would still be below the *de minimis* risk level of 1×10^{-6} , generally considered an acceptable cancer risk due to its small magnitude compared to the overall cancer rate (OEHHA, 2006). As for the noncancer health effects discussed above, calculating the increased cancer risk assumes a one-time ingestion of ten grams of tire shreds. Should this behavior be repeated in the same child, the risk would increase proportionately. However, lacking data as to whether ingestion of ten grams of tire shreds is a behavior that is repeated in some children, we have not calculated the increased cancer risk for other than a one-time ingestion.

Table 12. Increased cancer risk in a 3 year old following a one-time ingestion of 10 grams of shredded tires based on published tire leachate studies

Carcinogen	Dose ingested by a 3 year old in mg/kg ⁽¹⁾	Ingested dose averaged over 70 x 365 days in mg/kg-d	Oral Cancer Slope Factor in (mg/kg-d) ⁻¹⁽²⁾	Increased cancer risk in a 3 year old ⁽³⁾
Arsenic	8.7×10^{-5}	3.4×10^{-9}	9.45	9.6×10^{-8}
Cadmium	1.8×10^{-4}	7.0×10^{-9}	0.38	8.0×10^{-9}
Lead	6.1×10^{-4}	2.3×10^{-8}	0.0085	6.1×10^{-10}
Benzene	1.45×10^{-4}	5.7×10^{-9}	0.1	1.7×10^{-9}
Trichloroethylene	5.3×10^{-7}	2.1×10^{-11}	0.013	8.2×10^{-13}
Aniline	5.0×10^{-4}	2.0×10^{-8}	0.0057	3.4×10^{-10}
Naphthalene	7.3×10^{-4}	2.9×10^{-8}	0.12	1.0×10^{-8}

Calculated thus: $\text{ingested dose}/(70)(365) \times \text{oral cancer slope factor} \times (3) = \text{increased cancer risk in a three-year-old}$

⁽¹⁾ From Table 9.

⁽²⁾ From the OEHHA Toxicity Criteria Database, available at www.oehha.ca.gov

⁽³⁾ Calculated by multiplying the Cancer Slope Factor in column four by the averaged dose in column three, and then multiplying by a factor of three for the increased sensitivity of 3 year old children to carcinogens released by tires (U.S. EPA, 2003c).

Chronic ingestion of excess zinc is not considered to be carcinogenic by the ATSDR (2003b), while IRIS (1992) classifies zinc into Group D: not classifiable as to human carcinogenicity.

Chapter 6: Evaluation of Toxicity Due to Ingestion of Tire Shreds Based on OEHHA Gastric Digestion Simulation Study

Measuring the chemicals released from tire-derived shreds

To estimate the kinds and amounts of chemicals that could potentially be extracted in a child's gastrointestinal tract, we performed the following gastric digestion simulation experiment. Three samples of shredded tire rubber were obtained from three recyclers; two located in California and one in Ohio. Forty grams of shredded tire rubber were added to each of three glass flasks. A fourth control flask received no rubber. Then 200 mls of a solution were added to simulate the environment of the human stomach. The chart below lists the components of this gastric digestion solution along with references. A citric acid-sodium citrate buffer was added to help maintain a constant pH.

Table 13. Composition of "Gastric Digestion" Solution (Guyton and Hall, 2000; Semple et al., 2001)

Compound	Concentration
Citric acid (buffer)	20.0 mM
Sodium citrate (buffer)	0.5 mM
Potassium chloride	15.0 mM
Sodium chloride	3.0 mM
Pepsin	1.0 mg/ml
All in distilled water with pH = 2.3	

Following addition of shredded tires and solution, each flask was sealed with parafilm, placed in a temperature-controlled rotary shaker, and gently shaken at 37°C for 21 hours. Each solution was then filtered through Whatman filter paper into a glass sample jar. Samples were immediately refrigerated, followed by transport to the analyzing laboratory (Sequoia Analytical, Morgan Hill, CA). Metals were analyzed by EPA Method 6020 and sVOCs (including sixteen PAHs) by EPA Method 8270C.

Table 14 lists the metals and sVOCs that were identified in the extract. The tire leachates contained 13 metals and 9 sVOCs that were present at lower levels or not at all in the control. No PAHs were detected. The control sample contained two sVOCs that were not detected in any tire samples. Unfortunately, these measurements give no information on bioavailability, which was assumed to be 100 percent for all chemicals.

All 13 metals were higher in the three rubber samples than in the control. Three sVOCs were also present in all three rubber samples but not in the control: benzothiazole, 2(3H)-benzothiazolone and aniline. Comparing the results of the digestion experiment to the studies gathered from the literature and listed in Tables 2-4, our digestion experiment

identified three metals and five sVOCs not previously identified as leaching from tire rubber: antimony, molybdenum, vanadium, cyclohexanamine N-cyclohexyl, cyclohexanone, formamide, N-cyclohexyl, 1H-isoindole-1,3(2H)dione and o-cyanobenzoic acid. In addition, two other metals and three other sVOCs leached at higher levels in the digestion experiment compared to the literature values: barium, copper, aniline, 2(3H)-benzothiazolone and phenol. Importantly, the amount of zinc released per gram of rubber was 18-fold lower in the digestion experiment compared to the highest value found in the literature and used in Table 9. Thus, our value for leaching zinc as well as the majority of zinc values gathered from the literature (Table 2), suggest that the value used in Table 9 overestimates the dose.

Table 14. Chemicals leaching from three shredded tire samples in “gastric digestion” experiment (all units are µg/l, ND = below reporting limit)¹

Chemical	Reporting limit	Tire sample “G”	Tire sample “S”	Tire sample “O”	Control
Metals					
Antimony	0.50	110	42	1.7	ND
Arsenic	1.0	6.1	5.4	4.7	ND
Barium	1.0	130	110	870	4.2
Cadmium	0.25	2.2	2.8	1.1	0.44
Chromium (total)	2.0	41	57	35	16
Cobalt	0.50	45	50	33	ND
Copper	0.5-50	1500	960	1600	8.3
Lead	0.50	140	120	48	4.6
Molybdenum	1.0	11	18	8.5	ND
Nickel	1.0	27	27	22	1.1
Selenium	1.0	18	10	7.1	3.0
Vanadium	1.0	9.0	9.5	5.8	3.3
Zinc	5.0-500	17000	26000	13000	16
Organics					
o-cyanobenzoic acid	36-190	990	ND	910	ND
Cyclohexanamine, N-cyclohexyl-	190	190	410	ND	ND
Benzothiazole	36-190	320	450	390	ND
2(3H)-Benzothiazolone	36-190	640	450	480	ND

Chemical	Reporting limit	Tire sample "G"	Tire sample "S"	Tire sample "O"	Control
1H-isoindole-1,3 (2H)-dione	190	ND	490	ND	ND
Cyclohexanone	36	ND	ND	48	ND
Formamide, N- Cyclohexyl-	36	ND	ND	110	ND
Benzaldehyde, 3- Hydroxyl-4-methoxy-	19	ND	ND	ND	25
Hexanedioic acid, bis(2-ethylhexyl)	19	ND	ND	ND	28
Aniline	190-360	2800	3000	6700	ND
Phenol	19-360	190	ND	ND	ND

¹ Data reported in Appendix A in Work Order MOC0103. Ranges of reporting limits for some chemicals indicate that different reporting limits were associated with different samples.

COMPARISON OF CHEMICAL EXPOSURE DUE TO INGESTION OF TIRE SHREDS TO SCREENING LEVELS: NONCANCER EFFECTS

Comparison performed using the data from Table 14:

$$\mu\text{g chemical released/gram tire shreds} \times 10 \text{ grams tire shreds ingested/15 kg child} =$$

$$\mu\text{g chemical ingested} \times 10/15 \text{ kg child} \rightarrow \text{does dose exceed screening value?}$$

Exposure doses were calculated for chemicals that were detected in at least one rubber sample at a level that was either: 1) at least three times the control, or, if the control was a nondetect, at a level that was 2) at least three times one-half the reporting limit for that chemical. Multiplying the reporting limit by a factor of three has been recommended for setting the minimum level of quantitation (US EPA, 2004). In order to represent a worst case scenario, the highest value from among the three rubber samples was used in Table 16 for calculating exposure doses.

Chemicals released were assumed to be 100 percent bioavailable. It was also assumed that a 15 kg child might acutely ingest 10 grams of shredded rubber at one time, similar to the upper limit of soil ingestion recommended for estimating acute exposures in children (US EPA, 2002; OEHHA, 2000c). This kind of soil ingestion is not a typical behavior pattern observed in most children, but rather a poorly characterized behavior seen in a subset of young children (US EPA, 2002).

Estimated doses were calculated for each contaminant and compared to the corresponding screening value cited in Tables 6-8. Table 16 shows this comparison for noncancer health effects. As discussed in the previous section, acute screening levels were often lacking, so subchronic or chronic screening levels were used instead. The reasoning was that if the estimated dose was lower than the subchronic or chronic screening level, then acute health effects were unlikely. When available, OEHHA screening values were used.

The dose levels of ingested chemicals presented in Table 16 are due to ingestion of tire shreds. For comparison, Table 10 shows the average daily intakes resulting from the presence of these chemicals in food, water and air. In many cases these average daily intakes are rough estimates. Nonetheless, it is useful to compare the tire-derived levels to the average daily intakes. Average daily intakes were located for thirteen of the chemicals listed in Table 16. For nine, the average daily intake equals or exceeds the tire-derived exposure. In many cases the exposure due to ingestion of tire shreds is much lower than the average daily intake. Only for antimony, arsenic, lead and captan does the tire-derived exposure exceed the average daily intake. This indicates that particular care should be taken when comparing the tire-derived exposures to these chemicals to their corresponding health-based screening levels.

From among the 20 chemicals listed in Table 16, 15 yielded ingested dose levels that fell at or below the corresponding screening level. The remaining five chemicals had no associated screening levels, so that the risk of health effects could not be estimated. Thus, our measurements of chemicals that leach from tire rubber, under conditions approximating those in a child's stomach, suggest that acute health effects would not occur following ingestion of ten grams of shredded rubber by a 15 kg child. Should a child ingest ten grams of tire shreds on more than one occasion, the methodology followed here would yield a proportional increase in ingested dose that could exceed some of the acute screening values listed in Table 9. Whether a child ingests ten grams of tire shreds often enough for such exposures to qualify as subchronic or chronic is unknown.

As in Chapter 5, the Hazard Index approach was again used as a first tier screening procedure to estimate whether cumulative impacts would be expected from all the chemicals released by tire shreds in the gastric digestion study (Table 15). The Hazard Index based on all chemicals is 2.2. Since the Hazard Index is close to one, this first tier screening suggests that this complex mixture of chemicals does not represent a serious health hazard.

Table 15. Hazard Quotients and Hazard Index for an Acute Ingestion of Chemicals Identified in OEHA Gastric Digestion Simulation Experiment

Chemical	Dose ¹ /screening value ¹	Hazard quotient ²
Metals		
antimony	0.37/1.4	0.26
arsenic	0.02/5	0.004
barium	2.9/21	0.138
cadmium	0.009/0.5	0.180
chromium (hexavalent)	0.19/3	0.063
cobalt	0.17/10	0.017
copper	5.3/23 (RDA)	Not calculated
lead	0.47/2.7	0.174
molybdenum	0.06/5	0.012

Chemical	Dose¹/screening value¹	Hazard quotient²
nickel	0.09/233	0.0004
selenium	0.06/5	0.012
vanadium	0.032/3	0.011
zinc	87/300	0.29
Semi-volatile organic compounds		
aniline	22.3/21	1.062
1H-isoindole-1,3(2H)-dione	1.6/130	0.012
HAZARD INDEX		2.2

¹from Table 16, both in µg/kg ²calculated from second column of this table

Table 16. Comparison of ingested dose to health-based screening level for an acute ingestion of tire-derived shreds based on “gastric digestion” study: noncancer health effects.

Chemical	Highest amount released per g of tire (from among the three shredded tire samples subjected to “gastric digestion” in Table 14)	Dose¹	Screening level
Metals			
Antimony	0.55 µg	0.37 µg/kg	Chronic screening level = 1.4 µg/kg-day (OEHHA, 1997c)
<i>Conclusion</i>	<i>No acute or subchronic screening levels were identified. However, the estimated dose is 26% of the chronic screening level, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		
Arsenic	0.031 µg	0.02 µg/kg	Acute MRL = 5 µg/kg-day (ATSDR, 2000a)
<i>Conclusion</i>	<i>The estimated dose is 250-fold lower than the acute MRL, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		
Barium	4.35 µg	2.9 µg/kg	Subchronic screening level = 21 µg/kg-day (OEHHA, 2003b in Table 6)
<i>Conclusion</i>	<i>No acute screening level was identified. However, the estimated dose is 7-fold lower than the subchronic screening level, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		
Cadmium	0.014 µg	0.009 µg/kg	Chronic REL in adults = 0.5 µg/kg-day (OEHHA, 1999a)
<i>Conclusion</i>	<i>No acute or subchronic screening levels were identified. However, the estimated dose is 56-fold lower than the chronic REL, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		

Chemical	Highest amount released per g of tire (from among the three shredded tire samples subjected to “gastric digestion” in Table 14)	Dose¹	Screening level
Chromium	0.285 µg (fractions of trivalent and hexavalent not determined)	0.19 µg/kg	Chronic RfD (hexavalent) = 3.0 µg/kg-day (IRIS, 1998b)
<i>Conclusion</i>	<i>No acute or subchronic screening levels were identified. However, the estimated dose is 16-fold lower than the chronic RfD, suggesting that health effects are unlikely from an acute ingestion.</i>		
Cobalt	0.25 µg	0.17 µg/kg	Intermediate MRL = 10 µg/kg-day (ATSDR, 2004b)
<i>Conclusion</i>	<i>No acute screening level was identified. However, the estimated dose is 59-fold lower than the intermediate MRL, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		
Copper	8.0 µg	5.3 µg/kg	The recommended daily allowance (RDA) for a 1-3 year old is 23 µg/kg-day (USDA, 2006)
<i>Conclusion</i>	<i>Since the estimated dose is below the recommended daily allowance, adverse health effects are not expected.</i>		
Lead	0.7 µg	0.47 µg/kg	Acute screening level = 2.7 µg/kg (ATSDR, 1999c in Table 6); chronic screening level = 0.67 µg/kg-day (OEHHA, 1997b in Table 6)
<i>Conclusion</i>	<i>The estimated dose is 5.7-fold lower than the acute screening level in children. It is also below the chronic screening level. This suggests a low risk of adverse health effects from a one-time ingestion.</i>		
Molybdenum	0.09 µg	0.06 µg/kg	Chronic RfD = 5 µg/kg-day (IRIS, 1993c)
<i>Conclusion</i>	<i>No acute or subchronic screening levels were identified. However, the estimated dose is 83-fold lower than the chronic RfD, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		

Chemical	Highest amount released per g of tire (from among the three shredded tire samples subjected to “gastric digestion” in Table 14)	Dose¹	Screening level
Nickel	0.135 µg	0.09 µg/kg	Acute screening level = 233 µg/kg (OEHHA, 2001b in Table 6)
<i>Conclusion</i>	<i>The estimated dose is more than 2,500-fold below the acute screening level, suggesting a low risk of adverse health effects from a one-time oral exposure.</i>		
Selenium	0.09 µg	0.06 µg/kg	Chronic REL = 5 µg/kg-day (OEHHA, 2003a)
<i>Conclusion</i>	<i>The estimated dose is 83-fold below the chronic REL, suggesting a low risk of adverse health effects.</i>		
Vanadium	0.048 µg	0.032 µg/kg	Intermediate MRL = 3.0 µg/kg-day (ATSDR, 1992c)
<i>Conclusion</i>	<i>The estimated dose is 94-fold lower than the intermediate MRL, suggesting a low risk of adverse health effects from a one-time oral ingestion.</i>		
Zinc	130 µg	87 µg /kg	Subchronic MRL = 300 µg/kg-day (ATSDR, 2003b)
<i>Conclusion</i>	<i>The estimated dose is 3.4-fold lower than the subchronic MRL, suggesting a low risk of adverse health effects..</i>		
Semi-volatile Organic Compounds			
Aniline	33.5 µg	22.3 µg/kg	Acute screening level = 21 µg/kg-day (IARC, 1982 and Jenkins et al., 1972 in Table 10)
<i>Conclusion</i>	<i>The estimated dose is almost identical to the acute screening level, suggesting a low risk of adverse health effects from a one-time oral ingestion.</i>		

Chemical	Highest amount released per g of tire (from among the three shredded tire samples subjected to “gastric digestion” in Table 14)	Dose¹	Screening level
Benzothiazole	2.25 µg	1.5 µg/kg	On GRAS list; oral LD ₅₀ in rats = 380-479 mg/kg (NTP, 2004)
<i>Conclusion</i>	<i>Inadequate screening level data.</i>		
2(3H)-Benzothiazolone	3.2 µg	2.1 µg/kg	No data located
<i>Conclusion</i>	<i>Inadequate screening level data.</i>		
Cyclohexanamine,N-cyclohexyl-	2.1 µg	1.4 µg/kg	No data located
<i>Conclusion</i>	<i>Inadequate screening level data.</i>		
Formamide, N-cyclohexyl	0.55	0.37 µg/kg	No data located
<i>Conclusion</i>	<i>Inadequate screening level data.</i>		
1H-isoindole-1,3(2H)-dione (a.k.a. captan)	2.45 µg	1.6 µg/kg	Chronic RfD = 130 µg/kg-day (IRIS, 1989)
<i>Conclusion</i>	<i>No acute or subchronic screening levels were identified. However, the estimated dose is 81-fold lower than the chronic RfD, suggesting a low risk of adverse health effects from a one-time ingestion.</i>		
o-Cyanobenzoic acid	4.95 µg	3.3 µg/kg	No data located
<i>Conclusion</i>	<i>Inadequate screening level data.</i>		

¹The dose is the amount of chemical assumed to leach from 10 grams of tire crumb/shreds following ingestion by a 15 kg child, based on the results listed in the second column of the table.

MRL = minimal risk level (ATSDR)

NSRL = no significant risk level (OEHHA)

REL = reference exposure level (OEHHA)

RfD = reference dose (US EPA)

MADL = maximum allowable dose level (OEHHA)

GRAS = generally recognized as safe (FDA)

RDA = recommended daily allowance (NAS/NRC)

UL = upper intake level (Institute of Medicine)

ESTIMATING THE INCREASED CANCER RISK

From among the chemicals listed in Table 16, five (arsenic, cadmium, cobalt, lead, aniline) are currently listed as oral carcinogens by the State of California (OEHHA, 2005). However, data are lacking as to whether a one-time ingestion of these carcinogens is sufficient to cause cancer. Nonetheless, Table 17 calculates the increased cancer risk to a three year old assuming that a one-time ingestion is sufficient.

To do this, the dose from Table 16 was averaged over a 70 year lifetime, multiplied by the Cancer Slope Factor, and multiplied by a factor of three to cover the increased sensitivity of a three year old child to some carcinogens (US EPA, 2003c). These calculations could not be performed for cobalt, due to the absence of a Cancer Slope Factor. The increased cancer risk from exposure to each of four chemicals (arsenic, cadmium, lead, aniline) is low, while the total increased risk is 3.7×10^{-8} . This is 3-fold lower than the total increased cancer risk of 1.2×10^{-7} calculated above using published studies of chemicals that leached from tire shreds (see previous section).

The same US EPA draft methodology that recommends the use of a safety factor of three for calculating the cancer risk to children between the ages of two and fifteen, also recommends the use of a safety factor of ten for children below the age of two (US EPA, 2003c). Thus, multiplying the above total increased risk by 3.3 yields an increased risk of 1.2×10^{-7} . Therefore, should a child below the age of two ingest ten grams of shredded tire rubber, the increased cancer risk would still be below the *di minimis* risk level of 1×10^{-6} , generally considered an acceptable cancer risk due to its small magnitude compared to the overall cancer rate (OEHHA, 2006).

Table 17. Increased cancer risk in a 3 year old following a one-time ingestion of 10 grams of shredded tires based on OEHHA “gastric digestion” study

Carcinogen	Dose ingested by a 3 year old in mg/kg ⁽¹⁾	Ingested dose averaged over 70 x 365 days in mg/kg-d	Oral Cancer Slope Factor in (mg/kg-d) ⁻¹ (2)	Increased cancer risk in a 3 year old (3)
Arsenic	2×10^{-5}	7.8×10^{-10}	9.45	2.2×10^{-8}
Cadmium	9×10^{-6}	3.5×10^{-10}	0.38	4.0×10^{-10}
Cobalt	1.7×10^{-4}	6.6×10^{-9}	Unavailable	-
Lead	4.7×10^{-4}	1.8×10^{-8}	0.0085	4.6×10^{-10}
Aniline	2.2×10^{-2}	8.6×10^{-7}	0.0057	1.5×10^{-8}

Calculated thus: ingested dose/(70)(365) x oral cancer slope factor x (3) = increased cancer risk in a three-year-old

(1) From Table 16.

(2) From the OEHHA Toxicity Criteria Database, available at www.oehha.ca.gov

(3) Calculated by multiplying the Cancer Slope Factor in column four by the averaged dose in column three, and then multiplying by a factor of three for the increased sensitivity of 3 year old children to carcinogens released by tire shreds (US EPA, 2003c).

Conclusions


- Our gastric digestion experiment identified 22 chemicals released from tire shreds during a 21 hour incubation at 37°C in a solution that mimicked the gastric environment; these data were used to estimate the amounts of chemicals released following ingestion of 10 grams of tire shreds by a 15 kg child.
- All calculated exposure doses were at or below the corresponding screening value, suggesting a low risk of adverse noncancer health effects.
- Five of the leaching chemicals are currently listed by the State of California (OEHHA, 2005b) as carcinogens by the oral route.
- The acute ingestion of 10 grams of tire rubber by a 15 kg three year old child is associated with a 3.7×10^{-8} increased risk of cancer, based on the experimental results reported here; this is below the *di minimis* risk level of 1×10^{-6} , generally considered an acceptable cancer risk due to its small magnitude compared to the overall cancer rate (OEHHA, 2006).

Chapter 7: Evaluation of Toxicity Due to Chronic Hand-To-Mouth Behavior Based on OEHHA Wipe Sampling of Playground Surfaces

Exposure model

Figure 1 shows our model for estimating child exposure to toxicants released by unitary playground surfaces made of recycled tires. As discussed earlier in this report, unitary surfaces are solid surfaces that cannot be put into the mouth and ingested, unlike tire shreds. This eliminates the route of intentional ingestion (not shown in Figure 1). Since the playgrounds that are the subjects of this report are outdoors, we considered that any VOCs and sVOCs volatilizing from the rubber surfaces or fine particles becoming resuspended would enter the atmosphere and quickly disperse, precluding the inhalation of significant amounts by children. Thus, we did not consider the inhalation route in estimating exposure, nor did we measure VOCs released by these rubberized surfaces. Dermal uptake was estimated to be much less than incidental ingestion (hand-to-mouth), for reasons discussed in detail below. This left the route of incidental ingestion (hand-to-mouth) as the relevant route of exposure. This route is discussed in detail below.

Figure 1. Exposure model for children using rubberized playground surfaces

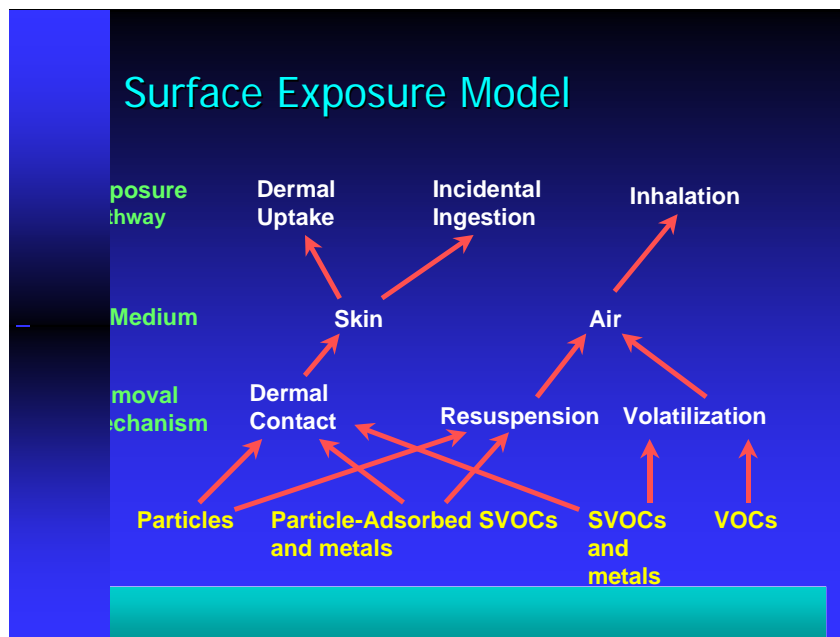

(courtesy of Chuck Salocks of OEHHA).

Measuring the concentration of dislodgeable toxicants on the playground surface

To measure the chemicals that might be transferred to a child's hand through contact with a unitary playground surface made of recycled waste tires, the following wipe sampling study was performed by OEHHA. The protocol is modified from the US EPA (2003a) protocol used to wipe sample arsenic from CCA-treated wood. Polyester wipes (catalogue #TX1009) were purchased from ITW Texwipe (Upper Saddle River, New Jersey). These wipes are 9 inches by 9 inches and weigh approximately 8.3 grams. Prior to sampling, each wipe was put into a clean glass jar with 23 mls of distilled water (for metals or sVOCs) or isopropyl alcohol (for PAHs).

A cylindrical steel weight was kindly provided by Oakland Machine Works (Oakland, CA). It weighed 1.1 kg and had a surface at each end that was 8.26 cm in diameter. For each sample, the weight was wrapped in a clean disposable plastic bag and then wrapped with the wetted wipe. The weight was then dragged for twelve feet (366 cm) along a tape measure laid on the rubber or control surface. Dragging was then reversed without rotating the weight, and finally the dragging was done once more for a total of three passes along the same twelve foot path. The area wiped was 3021 cm². The wipe was then returned to its glass jar. Clean nitrile gloves were used for each sample. Playground surfaces were sampled in duplicate per analyte class (metals, mercury, sVOCs, PAHs). Single field control wipes were performed on nearby sections of cement sidewalk. Two pour-in-place playground surfaces with bottom layers of recycled tires and top layers of EPDM were wipe tested. A single playground surface consisting of tiles made of 100% recycled tire rubber held together with a binder was also wipe sampled.

Samples were transported to Sequoia Analytical (Morgan Hill, CA) for analysis. The following methods were followed: calcium, iron, potassium and magnesium by EPA 6010B; mercury by EPA 7471A; all other metals by EPA 6020; sVOCs by EPA 8270C; PAHs by GCMS-SIM. Table 18 shows the chemicals that were detected in the wipe samples. Ten metals and six PAHs were detected. Another twelve metals and nine PAHs were not detected in any sample. In addition, no sVOCs were detected in any wipe sample.

Table 18. Chemicals detected by wipe sampling three rubberized playground surfaces (A,B,C)¹

Chemical	Reporting limit	A	A (field control)	B	B (field control)	C	C (field control)
aluminum	2.0	91	75	-	-	370	330
antimony	1.0	2.8	4.2	155	220	170	170
barium	5.0	ND	ND	6.5	19	ND	ND
calcium	12	425	240	ND	ND	405	1300
copper	5.0	ND	ND	ND	6.3	ND	ND
iron	5.0	180	170	ND	ND	685	670
magnesium	2.5	78	58	ND	ND	210	220
mercury	0.005	ND	ND	ND	0.012	ND	ND

Chemical	Reporting limit	A	A (field control)	B	B (field control)	C	C (field control)
potassium	100	85	ND	ND	ND	145	120
zinc	10	ND	ND	73	66	105	26
benzo(b)-fluoranthene	0.10	0.13	ND	ND	ND	ND	ND
chrysene	0.10	0.25	ND	ND	ND	ND	ND
fluoranthene	0.10	0.25	ND	0.14	ND	0.1	ND
naphthalene	0.10	0.10	ND	ND	0.11	0.12	0.11
phenanthrene	0.10	0.14	0.10	ND	ND	0.25	ND
pyrene	0.10	0.39	0.10	0.28	ND	0.36	0.11

[†] All values are in µg/wipe. Playground surface values are averages of two duplicate wipes. Field control values are from single wipes. Surfaces A and B were pour-in-place with a top layer of EPDM. Surface C consisted of tiles that were 100% recycled tire rubber. ND = not detected.

Surface A data reported in Appendix B in Work Orders MOF0403 (rubber wipe samples A, B, D, E, G, H, J, K; background wipe samples C, F, I, L) and MOI0327 (rubber wipe samples UC1, UC2; background wipe sample UC3).

Surface B data reported in Appendix B in Work Orders MOF0623 (rubber wipe samples A, B, D, E, G, H, J, K; background wipe samples C, F, I, L) and MOI0327 (rubber wipe samples EC1, EC2; background wipe sample EC3).

Surface C data reported in Appendix B in Work Order MOF0858 (rubber wipe samples A, B, D, E, G, H, J, K; background wipe samples C, F, I, L) and MOI0327 (rubber wipe samples GR1, GR2; background wipe sample GR3).

Results

Five chemicals in the above table were detected at levels that were at least three times the field control, or if the field control was a nondetect (ND), at least three times one-half the reporting limit. Multiplying the reporting limit by a factor of three has been recommended for setting the minimum level of quantitation (US EPA, 2004). One metal (zinc) and four PAHs (chrysene, fluoranthene, phenanthrene, pyrene) fell into these two categories. Therefore, the potential toxicity of these chemicals was evaluated.

The duplicate wipes of playground surface C gave an average zinc value of 105 µg/wipe, that was at least 3-fold higher than the field control wipe (26 µg/wipe). This surface was made of tiles composed of 100% shredded tire rubber held together with a binder. Zinc was not detected on pour-in-place surface A, and was only slightly above the field control for pour-in-place surface B. Both surfaces A and B had top layers of EPDM above a bottom layer of recycled tire rubber. A possible explanation for these findings is that the EPDM layer acted as a barrier to tire-derived zinc. This finding of zinc by wipe testing the tiles made of 100% recycled tire rubber is in good agreement with the results of the gastric digestion experiment. Digestion of shredded tire rubber identified zinc as the chemical released in the highest amount: 130 µg of zinc per gram of tire rubber (Table 14). Thus, it may not be surprising that zinc was identified by wipe sampling. As

discussed earlier, zinc oxide is used as an activator in the rubber vulcanization process (CIWMB, 1996).

From among the four PAHs that were evaluated, chrysene and fluoranthene were detected on playground surface A, phenanthrene on playground surface C, and pyrene on all three playground surfaces. These PAHs are all products of combustion, and are present in the exhaust from gasoline and diesel engines, as well as on barbecued foods. We were not able to determine whether the PAHs detected on the wipes originated from the rubber playground surface itself, or from automobile/truck exhaust fumes followed by atmospheric deposition onto the playground.

This toxicity evaluation uses the wipe values as surrogates for the amounts of chemicals a child would pick up on its hands after touching the playground surface. Therefore, since the wipe procedure sampled an area of playground surface equal to 3,021 cm², then the dislodgeable chemicals that can be transferred to a child's hands are estimated to be:

- Zinc = 105 µg/3021 cm² = 34.8 ng/cm²
- Chrysene = 0.25 µg/3021 cm² = 0.0828 ng/cm²
- Fluoranthene = 0.25 µg/3021 cm² = 0.0828 ng/cm²
- Phenanthrene = 0.25 µg/3021 cm² = 0.0828 ng/cm²
- Pyrene = 0.39 µg/3021 cm² = 0.129 ng/cm²

Estimating the child's body surface area that contacts the playground surface and from which toxicants can be transferred to the mouth

Since unitary rubber playground surfaces are solid surfaces that cannot be picked up by a child and put into its mouth, hands touching the surface and then put into the mouth is considered the pertinent route by which dislodgeable residues could be ingested. Hand-to-mouth activity, a subset of the category often called nondietary or incidental ingestion, is an important route of child exposure to environmental contaminants (Hubal et al., 2000; Zartarian et al., 2000). The surface area of a three year old child's hands is approximately 400 cm² (50th percentile value), comprising approximately six percent of the total body surface area (US EPA, 2002).

However, less than 100 percent of the hand's surface area would be expected to contact the rubber surface. A maximum value of 50 percent was estimated to be the fraction of the hand's surface area that is available to pick up a toxicant from a contaminated surface (Zartarian et al., 2000). However, using modeling techniques this same study found that less of a child's hand (5 to 30 percent corresponding to 10 to 60 cm²) contacts the mouth per mouthing event. The US EPA (2001) recommends the use of 20 cm² per mouthing event, which falls within the range specified in the Zartarian et al. (2000) study. Therefore, this toxicity evaluation uses a value of 20 cm² as the area of the child's hand that transfers dislodgeable toxicants from a playground surface to the child's mouth.

Estimating the frequency of hand-to-playground surface contact

No data were found on the frequency of child hand-to-playground surface contact, and only limited data were located on the frequency of hand-to-floor contact. The data in Table 19 below show that the hand-to-floor data come primarily from children engaged in indoor activities. However, playground behavior encompasses outdoor activities. Unfortunately, there is poor agreement between the two studies that observed children

outdoors, with AuYeung et al. (2004a) reporting a hand-to-floor contact rate of 27/hour and Freeman et al. (2005) reporting a rate of 3/hr. Due to the dearth of data on hand-to-floor contact rates, the four values from the studies shown in the bottom three rows of Table 19 were averaged (40 + 21 + 3 + 27) to give 23 contacts per hour. The data from Freeman et al. (2001) were not included since only a single child was observed per age group. Therefore, this toxicity evaluation will use 23 hand-to-playground surface contacts per hour for a three year old.

Table 19. Hand-to-floor contact rates for children

Study	Age and number of children (n)	Child mobility and setting	Hand-to-floor contacts
Freeman et al. (2001)	6 year old female (n=1)	Walker, indoors	5/hr
	8 year old female (n=1)	Walker, indoors	1/hr
Beamer et al. (2004)	6 and 24 months (n=11)	Walkers, mostly indoors	Mean = 40/hr
Freeman et al. (2005)	7-53 months (n=68)	Infants + toddlers, indoors	Median = 21/hr
		Infants + toddlers, outdoors	Median = 3/hr
AuYeung et al. (2004a)	1-6 years (n=38)	Mostly outdoors	Median = 27

Estimating the frequency of hand-to-mouth activity

To estimate the frequency at which a child might transfer a dislodgeable toxicant from a rubber playground surface to its mouth, studies were located on the rate of hand-to-mouth activity. Such studies used direct observation or videotape analysis of children engaged in various activities, both indoors and outdoors. Table 20 shows the results of those studies.

Table 20. Frequency of hand-to-mouth activity in children

Study	Age and setting	Hourly hand-to-mouth contacts
US EPA, 2002	24-72 months, mostly indoors	Mean = 9
Tulve et al., 2002	10-60 months, indoors	Median = 11
AuYeung et al., 2004b	14-82 months, outdoors	Median = 8
Black et al., 2004	7-53 months, outdoors	Median = 5

The US EPA, in their Child-Specific Exposure Factors Handbook (US EPA, 2002), recommends the use of 9 contacts per hour for the frequency of hand-to-mouth activity in children age 24 to 72 months. This value is based mostly on data from children observed indoors. However, the playground is an outdoor environment, and children playing outdoors exhibited 2 to 3-fold less hand-to-mouth behavior than those playing indoors (AuYeung et al., 2004b; Black et al., 2004). Two recent studies in Table 20 provide

hand-to-mouth frequency data for children in outdoor environments: AuYeung et al (2004b) and Black et al. (2004). Using these two studies OEHHA calculates that 7 hand-to-mouth contacts per hour $[(5 + 8) \div 2 = 7]$ represents the best available value for a three year old child playing outdoors. Therefore, we have used the value of 7 hand-to-mouth contacts per hour in the following calculations.

Estimating the efficiency of transfer of toxicants from the child's hand to the mouth

Measurements of transfer efficiency (a.k.a. saliva removal efficiency) have been made for the transfer of pesticides and soil from the hands of children to their mouths. Maximum transfer efficiencies of 50 percent and 16 percent were measured for pesticides and soil, respectively (Zartarian et al., 2000). The lower value for soil may be related to a lower propensity of a child to extensively suck dirty hands compared to hands bearing a relatively tasteless and invisible chemical. In a more recent study the transfer of riboflavin from the hand to the mouth was measured in college-age volunteers (Cohen Hubal et al., 2005). The highest rate of transfer for a single mouthing event was 34 percent; however, the measured values were highly variable and often much lower. US EPA (2001) uses a standard value of 50 percent for hand-to-mouth transfer efficiency. Therefore, considering these data, this toxicity evaluation uses the value of 50 percent for the efficiency by which dislodgeable toxicants might be transferred from a child's hand to its mouth, thereby becoming ingested.

Estimating dermal loading

The amount of toxicant accumulating on a child's hand as a result of touching a contaminated surface has been termed dermal loading, and is a prerequisite for estimating the amount of a toxicant that can be ingested through hand-to-surface-to-mouth activity. Dermal loading in this situation depends on how often the child touches the playground surface, how often it touches its mouth, the amount of a toxicant that is transferred from the surface to the hand at each contact, and the amount transferred to the mouth at each contact. Table 21 shows these parameters, all of which were discussed above.

Table 21. Factors considered in estimating dermal loading

Parameter	Variable measured	Value	Reference
Hand-to-surface	Frequency	23/hr	Beamer et al., 2004; Freeman et al. 2005; AuYeung et al. 2004a
Hand-to-mouth	Frequency	7/hr	AuYeung et al., 2004b; Black et al., 2004
Surface-to-hand	Amount of toxicant transferred	Wipe measurements in Table 15	This study
Hand-to-mouth	Transfer efficiency	50%	US EPA, 2001
Length of playground visit	time	2 hr (see below)	Gallup Organization (2003)

Assuming that 3 (23/7) hand-to-playground surface contacts occur between each hand-to-mouth contact, and 50 percent of the toxicant transfers from the hand to the mouth at each contact, then the amount of dermal loading per cm² occurring between each hand-to-mouth contact approaches 6 times the wipe value; i.e., where x is the amount of chemical detected by wipe sampling per cm², then dermal loading at each successive hand-to-mouth contact would be 3x, 4.5x, 5.25x, 5.625x, 5.8125x, etc. (this calculation also assumes that the efficiency of loading does not change with sequential playground surface contacts). Thus, a three year old is estimated to load each chemical on its hands to the following levels:

- Zinc = 34.8 ng/cm² X 6 = 209 ng/cm²
- Chrysene = 0.0828 ng/cm² X 6 = 0.5 ng/cm²
- Fluoranthene = 0.0828 ng/cm² X 6 = 0.5 ng/cm²
- Phenanthrene = 0.0828 ng/cm² X 6 = 0.5 ng/cm²
- Pyrene = 0.129 ng/cm² X 6 = 0.77 ng/cm²

Estimating the time and frequency of playground use

Three studies were located that measured the time and/or frequency that children spent in the playground. Table 22 lists those studies and their findings.

Table 22. Time and/or frequency of playground use

Study	Age	Time and/or frequency of playground use
Bjorklid-Chu, 1977	1 to 15 years	“practically every day” for 56% of those surveyed
Air Resources Board, 1991	Under 12 years	An average of 49 minutes per day for those surveyed
Gallup Organization, 2003	3-12 years	1)Daily or several times a week for 29% of those surveyed. 2)At least 1-2 hours per visit for 52% of those surveyed.

Data on the frequency of playground use by American children are sparse. The study by Bjorklid-Chu (1977) was conducted in a modern housing development in Sweden. The other two studies were performed in the United States, with the Air Resources Board (1991) study being performed in California and the Gallup study being a national survey. While the frequency of playground use and time spent in the playground per visit are hard to know with precision given the above data, it is clear that a significant fraction of children visit a playground daily or multiple times per week, and a large fraction of those visits last on the order of one or more hours.

Thus, it seems justified to consider child exposure to potential playground surface contaminants as a chronic exposure scenario. More specifically, the data in the table suggest that a significant subset of users visits a playground daily, for at least two hours per visit. Therefore, these are the values we use in the subsequent calculations. US EPA

(2005) recently completed an exposure assessment for children contacting chromated copper arsenate(CCA)-treated wooden playsets, in which two hours/day was considered the mean time that children used these playsets, either in public playgrounds or at home.

Estimating exposure due to dermal absorption

Some chemicals that become deposited on human skin are able to enter the body by passing through the skin. This rate of dermal absorption varies greatly, depending upon the chemical and body part. While hands are the body parts which participate in hand-to-mouth transfer of environmental contaminants, dermal absorption can potentially occur at any place on the body. Considering children using the playground, we believe that hands are the body parts likely to come into repeated contact with the rubberized surface. The amount of dermal loading on the hands is discussed above. It is also estimated above that 50 percent of a toxicant picked up on a child's hands would transfer to the mouth every 8.6 minutes (7 times per hour).

Thus, for dermal absorption from the hands to make a significant contribution to the amount of a toxicant entering a child's body, its rate should not be much less than this 50 percent/8.6 minutes value. Table 23 below shows dermal absorption rates for 20 chemicals, covering a wide range of molecular weights and structures. For example, 0.02 percent of the applied dermal dose of zinc was absorbed in 8.6 minutes. All rates of dermal absorption were less than 1 percent/8.6 minutes except for 4,4'-methylene dianiline, which was 3.9 percent/8.6 minutes. Therefore, based on this survey of dermal absorption rates, we believe it unlikely that dermal absorption from the hands would contribute significantly to the amount of toxicant entering a child's body, due to the much higher rate of ingestion resulting from hand-to-mouth activity. Therefore, we will not calculate exposure via dermal absorption.

Table 23. Dermal absorption rates of 20 chemicals found in published studies¹

Study	Species	Chemical	Dermal absorption ²
Aoyama et al., 1986	human	tobramycin	0.21
Shah et al., 1987	rat	carbofuran	0.04
Agren, 1990	human	zinc	0.02
Agren et al., 1991	rat	zinc	0.02
Koizumi, 1991	rat	hexachlorobenzene	0.02
VanRooij et al., 1993	human	pyrene (a PAH)	0.57
Brunmark et al., 1995	human	4,4'-methylene dianiline	3.9
Moody et al., 1995	human	Benzo[a]pyrene	0.1
Timchalk et al., 1998	human	ortho-phenylphenol	0.74
Flarend et al., 2001	human	aluminum	<0.025
Qiao and Riviere, 2002	pig	pentachlorophenol	0.04
Meuling et al., 2004	human	chlorpyrifos	0.12
US EPA, 1992	pig	Caffeine	0.06

Study	Species	Chemical	Dermal absorption ²
"	"	Benzoic acid	0.06
"	"	N,N-dimethyl-m-toluamide	0.02
"	"	Fluocinolone acetonide	0.01
"	"	Malathion	0.01
"	"	Parathion	0.04
"	"	Testosterone	0.01
"	"	Lindane	0.02
"	"	Progesterone	0.02

¹ All studies were performed *in vivo* except for the US EPA study which was performed *ex vivo*.

² Percent of applied dose entering the skin per 8.6 minutes.

Calculating exposure via hand-to-mouth activity

Using zinc as an example, the mass of ingested zinc was calculated as follows:

hand loaded zinc concentration ($\mu\text{g}/\text{cm}^2$) **X** hand surface area transferring zinc to mouth ($\text{cm}^2/\text{hand-to-mouth event}$) **X** total events (hand-to-mouth events/day) **X** hand-to-mouth transfer efficiency (dimensionless) =

$$0.209 \mu\text{g}/\text{cm}^2 \text{ X } 20 \text{ cm}^2/\text{event} \text{ X } 14 \text{ events}/\text{day} \text{ X } 0.5 = 29.3 \mu\text{g}/\text{day}$$

For a 15 kg child the ingested zinc dose would be 1.95 $\mu\text{g}/\text{kg}\text{-day}$

Table 24. Estimated exposures from hand-to-mouth activity in a 15 kg three year old child at a playground where rubberized surfaces are present

Chemical	Exposures
Zinc	1.95 $\mu\text{g}/\text{kg}\text{-d}$
Chrysene	0.005 $\mu\text{g}/\text{kg}\text{-d}$
Fluoranthene	0.005 $\mu\text{g}/\text{kg}\text{-d}$
Phenanthrene	0.005 $\mu\text{g}/\text{kg}\text{-d}$
Pyrene	0.007 $\mu\text{g}/\text{kg}\text{-d}$

The dose levels of ingested chemicals presented in Table 24 are due to contact with tire-derived playground surfaces. For comparison, Table 10 shows the average daily intakes resulting from the presence of these chemicals in food, water and air. In many cases these average daily intakes are rough estimates. Nonetheless, it is useful to compare the tire-derived levels in Table 24 to the average daily intakes. Average daily intakes were located for all five chemicals listed in Table 24. For zinc, chrysene and phenanthrene the average daily intake equals or exceeds the tire-derived exposure. Only for fluoranthene and pyrene does the tire-derived exposure exceed the average daily intake. This indicates

that particular care should be taken when comparing the tire-derived exposures to these chemicals to their corresponding health-based screening levels.

Comparison of playground chemical exposure to screening levels: noncarcinogenic effects

Table 25 below shows a comparison of the zinc exposure value for children using playground surfaces to screening values for subchronic and chronic zinc ingestion, and to its recommended daily dietary allowance (RDA). Chronic screening values were also located for the two PAHs, fluoranthene and pyrene, so that comparisons could be made to the chronic exposure values.

Zinc

The subchronic and chronic zinc screening values are based on the same study by Yadrick et al. (1989) in which healthy adult females were given zinc to supplement their normal diets for a period of ten weeks. The lowest observed adverse effects level (LOAEL, 0.83 mg/kg-day) was based on decreased red blood cell superoxide dismutase, hematocrit and serum ferritin. There was no NOAEL. Application of an uncertainty factor of 3 (for use of a minimal LOAEL and intrahuman variability) to the LOAEL yielded a subchronic MRL (ATSDR, 2003b) and a chronic RfD (IRIS, 1992) of 0.3 mg/kg-day. Since the zinc exposure is less than the MRL and RfD, subchronic and chronic health effects are not expected. This conclusion is supported by the RDA for zinc, also shown in Table 25. The RDA was developed for children 1-3 years old. It is slightly lower than the MRL and RfD, reflecting the importance of zinc in the human diet. The RDA is 100-fold greater than the exposure due to contact with the playground surface, suggesting that adverse health effects would not occur.

Fluoranthene and pyrene

In the case of fluoranthene, the exposure value is 8,000-fold lower than the RfD, which is based on nephropathy, increased liver weights, hematological changes and clinical signs in mice (Table 7). The calculated exposure to pyrene is 4,286-fold lower than the RfD, based on kidney effects in mice (Table 7). Thus, adverse health effects are not expected due to exposure to fluoranthene and pyrene. The absence of screening values for chrysene and phenanthrene makes it difficult to draw conclusions about those exposures, although the large margins of safety for the structurally related PAHs fluoranthene and pyrene suggest that exposure to similar dose levels of chrysene and phenanthrene would also be without health effects.

Table 25. Playground-associated chemical exposures and associated noncancer screening values

Chemical	Calculated ingested dose ¹	Noncancer screening value
Zinc	1.95 µg/kg-day	Intermediate MRL = 300 µg/kg-day (ATSDR, 2003b)
“	“	Chronic RfD = 300 µg/kg-day (IRIS, 1992)
“	“	RDA* = 200 µg/kg-day (The National Academies, 2001)

Chemical	Calculated ingested dose¹	Noncancer screening value
Chrysene	0.005 µg/kg-day	None located
Fluoranthene	0.005 µg/kg-day	Chronic RfD = 40 µg/kg-d (IRIS, 1990b)
Phenanthrene	0.005 µg/kg-day	None located
Pyrene	0.007 µg/kg-day	Chronic RfD = 30 µg/kg-day (IRIS, 1991b)

¹ From Table 24

* Normalized for a 15 kg child

MRL = minimal risk level; RfD = reference dose; RDA = recommended dietary allowance

Risk characterization for noncancer effects

Uncertainties that would increase exposure

- Eating in the playground would tend to increase the transfer of toxicants from the surface of the hands to the food and into the mouth (Cohen Hubal et al., 2000; Black et al., 2004).
- Going barefoot in the playground would increase non-dietary ingestion in those children that exhibit toes-to-mouth activity (Freeman et al., 2001).
- Toxicants loaded onto the hands would be subject to hand-to-mouth transfer after the child had left the playground, unless its hands were washed.
- Objects that contact the playground surface and then are put into the child's mouth would increase non-dietary ingestion.

Uncertainties that would decrease exposure

- The transfer efficiency from a surface to the hand decreased with increasing number of hand-to-surface contacts (Cohen Hubal et al, 2005), and the loading of Cr, Cu and As onto children's hands did not increase with time (Hamula et al., 2006), both suggesting a saturation for loading.
- Hand-to-mouth events are often clustered, with few or no intervening hand-to-floor events (Ross, 2005). This suggests that hands become "fully loaded" for only a fraction of the total hand-to-mouth contacts.
- Some toxicants may be transferred from the child's hand to surfaces other than the child's mouth, such as playground equipment or clothes. This would decrease the amount transferred into the mouth.
- The duration of mouthing at each hand-to-mouth contact may decrease with increasing child age, leading to less toxicant transfer from the hands to the mouth (Cohen Hubal et al., 2000); however, at least one study suggests that mouthing times do not decrease between 1-3 months and 5 years of age (Dept. of Trade and Industry (UK), 2002).

- A bioavailability of 100 percent has been assumed for each chemical. It is likely that the true values are less, but this assumption represents a public health upper bound in the absence of empirical data.
- For the two hours per day a child is estimated to spend in the playground, it would be on the rubber surface for only a fraction of the total time.

Zinc

In the Table 25 above, both the subchronic MRL and chronic RfD of 0.3 mg/kg-day for zinc were based on the same study by Yadrick et al. (1989), showing decreased red cell superoxide dismutase (SOD) activity (a copper-requiring enzyme), hematocrit and serum ferritin in human females dosed daily for 10 weeks. These effects were probably due to zinc-induced changes in the copper and iron balance, causing the above-mentioned hematological effects to develop towards the end of the study (IRIS, 1992). Thus, zinc supplementation acted as an inducer of copper and iron deficiency.

Similar hematological changes have been observed in subchronic studies performed in the rat, mouse, rabbit, cow and ferret, in which the animals' diets were supplemented with zinc either via the food or water (ATSDR, 2003b). Also, another subchronic study in humans identified a LOAEL based on reduced red cell SOD (Fischer et al., 1984). Lastly, a chronic study of zinc supplementation in the elderly identified a LOAEL based on reduced red blood cells (Hale et al., 1988). Thus, in a range of mammalian species, excess zinc caused hematological changes consistent with iron and copper deficiency, as might result from a competition between zinc and these cations. Therefore, these findings support the use of the MRL/RfD of 300 µg/kg-day for evaluating whether zinc-induced health effects would occur in children contacting rubberized playground surfaces.

Chronic ingestion of excess zinc is not considered to be carcinogenic by the ATSDR (2003b), while IRIS (1992) classifies zinc into Group D: not classifiable as to human carcinogenicity. Therefore, the zinc subchronic MRL and chronic RfD are the appropriate reference values for evaluating chronic oral exposures.

Fluoranthene

The chronic RfD for fluoranthene is based on a 13 week study in mice gavaged daily with 0, 125, 250 or 500 mg/kg-d (IRIS, 1990b). At the two highest dose levels the animals exhibited a variety of adverse effects including increased serum alanine transaminase, kidney and liver pathology, increased clinical signs and hematological changes. Therefore, the NOAEL was 125 mg/kg-d. The following uncertainty factors were selected by IRIS: 10 for interspecies extrapolation, 10 for intraspecies variability and 30 for both subchronic to chronic extrapolation and a lack of reproductive/developmental data. Applying these uncertainty factors to the NOAEL yielded a chronic RfD of 40 µg/kg-d.

Carcinogenicity studies of fluoranthene (mostly via the dermal route) have also been performed in mice. Most have been negative with regard to tumor induction (IRIS, 1990b). However, these data were judged inadequate for determining the carcinogenicity. In addition, most studies in both mammalian cells and bacteria found that fluoranthene was not mutagenic (IRIS, 1990b). Thus, the RfD for fluoranthene shown in the table is the appropriate screening value for evaluating its long-term health effects.

Pyrene

The chronic RfD for pyrene is based on a 13 week study in mice gavaged daily with 0, 75, 125 or 250 mg/kg-d (IRIS, 1991b). At the two highest dose levels the animals exhibited mild kidney lesions and reduced kidney weights. Therefore, the NOAEL was 75 mg/kg-d. The following uncertainty factors were chosen by IRIS: 10 for interspecies extrapolation, 10 for intraspecies variability, 10 for subchronic to chronic extrapolation, and 3 for both the lack of data from other species and the lack of reproductive/developmental data. Applying the uncertainty factors to the NOAEL yielded a chronic RfD of 30 µg/kg-d.

Pyrene did not induce tumors in mouse studies (intraperitoneal injection and dermal routes), however, the data were considered inadequate for judging this chemical's carcinogenicity (IRIS, 1991b). Most studies in mammalian cells and bacteria indicated that pyrene was not mutagenic (IRIS, 1991b). Thus, the RfD for pyrene shown in the table is the appropriate screening value for evaluating its long-term health effects.

Estimating the increased cancer risk

From among the five chemicals identified by wipe sampling rubber playground surfaces, chrysene is currently listed as an oral carcinogen by the State of California (OEHHA, 2005). US EPA (2003c) draft methodology was followed to quantify the increased cancer risk to a child using these surfaces.

As discussed above in the section entitled "Estimating the frequency of playground use", survey data support the assumption that a significant percentage of children use playgrounds daily, although the data do not provide information as to how many years a child can be expected to use playgrounds. Thus, in order to calculate the cancer risk, estimates must be made as to when a child starts and stops using playgrounds. We believe it is reasonable to assume children start to use playgrounds with impact-attenuating surfaces at the time they begin to walk.

Prior to the walking stage, it is unlikely that a crawling child could access the equipment found in playgrounds such as rockers, slides, swings and climbers. It is well established that most children begin walking between the ages of 12 and 18 months (Bayley, 1936; Cratty, 1979; Bottos et al., 1989; Adolph et al., 1998). Therefore, we will consider 12 months as the age at which some children begin using these playgrounds. However, it should be kept in mind that should a child in the crawling stage have access to one of these surfaces, its exposure could be much higher due to a much higher hand-to-playground surface contact rate in crawlers compared to walkers.

The age at which most children stop using playgrounds is not well defined. We have not located any data addressing this question. Therefore, we will use the age of twelve years, which corresponds to the age when most children enter junior high school, where the playgrounds of elementary school are replaced by basketball courts, tennis courts, etc. This age range of 1 to 12 years is similar to the range of 1 to 13 years recently used as one of the target populations in an exposure assessment for children using playsets and decks made of CCA-treated wood (US EPA, 2005).

In the section above entitled "Estimating the frequency of playground use", it was concluded that a significant fraction of children use playgrounds daily. However, this is different from saying that a child uses a playground every day of the year. Obviously, on many days the weather could prevent playground use. Also, a child would not be expected to use the playground when sick. Recently, it was estimated that children

between the ages of one and six use public playgrounds an average of 185 days out of the year (US EPA, 2005). Therefore, this value has been applied to children between the ages of one and twelve in the cancer risk calculations presented below.

Table 26 below shows the values used to estimate the increased cancer risk to a child resulting from eleven years of hand-to-mouth activity in playgrounds with rubberized surfaces. The calculations follow the US EPA (2003c) draft methodology for assessing the cancer risk from exposures in childhood. The total increased risk of 2.9×10^{-6} is above the benchmark value of 1×10^{-6} , usually considered the maximum acceptable value for increased cancer risk.

Table 26. Estimated increased cancer risk from exposure to chrysene via hand-to-mouth activity in a child (ages 1-12) frequenting a playground with a rubberized surface

Age	Dose ⁽¹⁾ in mg/kg-d	Cancer Slope Factor ⁽²⁾ in (mg/kg-d) ⁻¹	Duration of use normalized to 70 yr lifetime ⁽³⁾	Days of playground use per year ⁽⁴⁾	Safety Factor ⁽⁵⁾	Increased cancer risk ⁽⁶⁾
1-2 years	5 x 10 ⁻⁶	2.0	1 yr/70 yrs	185 days/ 365 days	10	0.7 x 10 ⁻⁶
2-12 years	5 x 10 ⁻⁶	2.0	10 yrs/70 yrs	185 days/ 365 days	3	2.2 x 10 ⁻⁶
Total increased cancer risk ⁽⁷⁾						2.9 x 10 ⁻⁶

⁽¹⁾From Table 24.

⁽²⁾Available at www.oehha.ca.gov/prop65/law/pdf_zip/6pahnsr162104.pdf

⁽³⁾Estimated durations of playground use normalized to 70 year lifetime.

⁽⁴⁾Days in the year that included “public playset time” (US EPA, 2005).

⁽⁵⁾Safety factor for the increased sensitivity of a 0-2 year old (SF = 10) or 2-15 year old (SF = 3) child to some carcinogens (US EPA, 2003c).

⁽⁶⁾Calculated by multiplying columns 2, 3, 4, 5 and 6 according to US EPA (2003c) draft methodology.

⁽⁷⁾Calculated by adding the two individual increased cancer risks for the two age groups (US EPA, 2003c).

Discussion of the increased cancer risk

Uncertainties that would increase exposure

- Were a child in the crawling stage to use these surfaces, its exposure from hand-to-floor-to-mouth activity would be greater than that of a child of walking age.
- Use of the rubberized playground surfaces may continue past the age of 12.
- Eating in the playground would tend to increase the transfer of toxicants from the surface of the hands to the food and into the mouth (Cohen Hubal et al., 2000; Black et al., 2004).
- Going barefoot in the playground would increase non-dietary ingestion in those children that exhibit toes-to-mouth activity (Freeman et al., 2001).
- Toxicants loaded onto the hands would be subject to hand-to-mouth transfer after the child had left the playground, unless its hands were washed.
- Objects that contact the playground surface and then are put into the child’s mouth would increase non-dietary ingestion.

Uncertainties that would decrease exposure

- The data on hand-to-floor contact rates presented in Table 19 above suggest that this rate decreases as the child grows older. While this toxicity evaluation uses a rate of 23 hand-to-floor contacts per 2 hours for a three year old child, it is likely that this rate is substantially less for at least the age range six through twelve. This would lead to a substantially decreased transfer of toxicants from the playground surface to the child's mouth during the second half of the proposed exposure period.
- Almost no data were located on the hand-to-mouth contact rates for adults, or for children older than six. Common experience tells us that this rate decreases as the child grows older, as discussed above for the hand-to-floor contact rate. Consequently, the transfer of toxicants from the playground surface to the mouth is most likely substantially less during the second half of the proposed exposure period, from ages six to twelve.
- The transfer efficiency from a surface to the hand decreased with increasing number of hand-to-surface contacts (Cohen Hubal et al, 2005), and the loading of Cr, Cu and As onto children's hands did not increase with time (Hamula et al., 2006), both suggesting a saturation for loading.
- Hand-to-mouth events are often clustered, with few or no intervening hand-to-floor events (Ross, 2005). This suggests that hands become "fully loaded" for only a fraction of the total hand-to-mouth contacts.
- Some toxicants may be transferred from the child's hand to surfaces other than the child's mouth, such as playground equipment or clothes. This would decrease the amount transferred into the mouth.
- The duration of mouthing at each hand-to-mouth contact may decrease with increasing child age, leading to less toxicant transfer from the hands to the mouth (Cohen Hubal et al., 2000); however, at least one study suggests that mouthing times do not decrease between 1-3 months and 5 years of age (Dept. of Trade and Industry (UK), 2002).
- A bioavailability of 100 percent has been assumed for each chemical. It is likely that the true values are less, but this assumption represents a public health upper bound in the absence of empirical data.
- For the two hours per day a child is estimated to spend in the playground, it would be on the rubber surface for only a fraction of the total time.

As enumerated above, there are many uncertainties associated with the exposure calculations. Some tend to increase the dose and therefore risk levels, while others decrease it. Another area of uncertainty to be considered is whether the chrysene measured on the surface of playground A originated from the rubber surface or resulted from atmospheric deposition. Referring to Table 18, two of three playground surfaces yielded chrysene values that were indistinguishable from field control wipes (all below the reporting limit).

These results, coupled with the finding that playground surface A yielded a wipe value for chrysene that was only 2.5 times the reporting limit (Table 18), indicate that more wipe tests should be performed on additional rubberized surfaces to determine if these surfaces consistently yield elevated levels of dislodgeable chrysene relative to field

controls. Seen in this light, the data collected from these playground surfaces suggest that if chrysene is elevated on these surfaces, regardless of its origin, the magnitude of the increase over background is small, and may occur only in a minority of playgrounds. In this regard, the wipes of the rubberized surfaces were always much dirtier than the control wipes performed on adjacent sidewalks, suggesting that the rubberized surfaces trap dirt more efficiently than concrete. If they also trap PAHs more efficiently, this might explain the increased PAH levels on wipes of the rubber surfaces.

The Cancer Slope Factor for chrysene shown in Table 26 was developed from intraperitoneal injection studies in neonatal mice, using an oral equivalent potency approach (OEHHA, 2004c). This approach first calculates the ratio of the potency of benzo[a]pyrene determined in the adult mouse by the oral route to that determined in the neonatal mouse by the intraperitoneal injection route. Then this ratio is applied to the neonatal intraperitoneal injection potency of chrysene, yielding the adult oral potency for chrysene used here.

Thus, it should be kept in mind that the Cancer Slope Factor for chrysene used here has its basis in intraperitoneal injection studies with neonatal mice. Those studies were performed with chrysene dissolved in DMSO, due to its very low solubility in water. Thus, its absorption from the intraperitoneal space in the carcinogenicity studies may differ from its absorption following ingestion due to hand-to-mouth activity in children (where DMSO is not used as a vehicle). These factors must be considered sources of uncertainty in applying the adult oral Cancer Slope Factor for chrysene to exposures in the playground.

Considering the uncertainty associated with both the exposure value and the Cancer Slope Factor for chrysene, the 2.9×10^{-6} -fold increased cancer risk calculated here could be either higher or lower than the true value. In addition, this relatively small increased cancer risk should be weighed against the beneficial impact-mitigating properties of rubberized surfaces, discussed elsewhere in this report.

Conclusions

- Wipe sampling of tire-derived playground surfaces was performed to measure the amounts of dislodgeable chemicals subject to ingestion through child hand-to-surface-to-mouth activity.
- Ten metals and six PAHs were identified, with five at levels that were at least 3-fold above background: zinc, chrysene, fluoranthene, phenanthrene and pyrene.
- Chronic exposure assessment was performed for the five chemicals using published values for child hand surface area, hand-to-floor contact rate, hand-to-mouth contact rate, saliva removal efficiency, and frequency of playground use; this exposure assessment was associated with large degrees of uncertainty, some of which could increase exposure and some decrease exposure.
- The exposure values were then compared to the corresponding chronic health-based screening values; all exposures were below the corresponding screening levels, suggesting a low risk of adverse noncancer health effects.
- Chrysene was the only chemical from among the five listed above that was identified as a carcinogen by the State of California (OEHHA, 2005b).

- Assuming playground use from ages one through twelve, a total increased cancer risk of 2.9×10^{-6} was calculated due to the chronic ingestion of chrysene via hand-to-surface-to-mouth activity on rubberized playground surfaces. This risk is slightly higher than the benchmark of 1×10^{-6} , generally considered an acceptable cancer risk due to its small magnitude compared to the overall cancer rate (OEHHA, 2006).
- The calculation of cancer risk due to chrysene was associated with additional areas of uncertainty, regarding both the years of playground use during childhood, and whether the low levels of PAHs (including chrysene) on playground surfaces originate from the rubber surface itself or from atmospheric deposition.

Chapter 8: A First-Step Evaluation of High School Running Tracks Containing Recycled Tire Rubber: Wipe Testing and Customer Satisfaction Survey

Introduction and Methods

In addition to playgrounds, the CIWMB also provides funds for the installation of running tracks made of recycled tires. One method of track construction follows that used for playground surfaces; a bottom layer primarily (80%) of recycled tire shreds is poured together with a chemical binder. After the bottom layer hardens, a top layer of synthetic rubber particles called EPDM is poured together with more binder. To determine if such tracks release chemicals following dermal contact, one such track at a northern California high school (funded by the CIWMB) was wipe sampled according to the methodology described above for sampling playground surfaces. Wipe sampling was performed twice, on two separate days. The field control wipes were performed on a concrete apron surrounding the track. Wipes were analyzed for metals, sVOCs and PAHs.

To obtain a first impression of how these rubberized track surfaces are performing, a customer satisfaction survey was taken among the track coaches at high schools awarded CIWMB grants. From among some twenty high schools contacted, six track or cross country coaches were kind enough to discuss their thoughts on track performance, with special attention paid to injury rates and athletic performance.

Wipe testing results and discussion

Table 27 shows the results of wipe sampling a high school track made of recycled tires. Metals from wipes of the track surface were below the values of the field control wipes. No sVOCs were detected. Five PAHs were detected at higher levels on the track compared to the field control (chrysene, fluoranthene, naphthalene, phenanthrene, pyrene). Pyrene was detected at the highest levels, with good agreement between the two sampling days (4.5 and 3.1 $\mu\text{g/wipe}$); however, the background field control wipes for pyrene varied almost 7-fold over the two sampling days. The PAH fluorene was detected on the field control wipe but not on the track wipes.

Table 27. Chemicals detected on a track surface made of recycled tires.

Date	Chemical	Reporting limit ¹	Track wipe ^{1,2}	Field control wipe ^{1,3}
6/27/05	Phenanthrene	0.82	1.7	ND
6/27/05	Pyrene	0.82	4.5	1.8
9/6/05	Chrysene	0.10	0.27	ND
9/6/05	Fluoranthene	0.10	0.43	0.11
9/6/05	Fluorene	0.10	ND	0.22

Date	Chemical	Reporting limit ¹	Track wipe ^{1,2}	Field control wipe ^{1,3}
9/6/05	Naphthalene	0.10	0.12	0.10
9/6/05	Phenanthrene	0.10	1.0	0.15
9/6/05	Pyrene	0.10	3.1	0.26

¹ All values in µg/wipe.

² Each value is an average of two wipe samples.

³ Each value represents a single wipe sample.

Data reported in Appendix B in Work Order MOF0960 (track wipe samples A, B, D, E, G, H, J, K; background wipe samples C, F, I, L) and Work Order MOI0327 (track wipe samples SM1, SM2; background wipe sample SM3).

In the preceding section, toxicity evaluations were performed for chemicals that were at least 3-fold higher in playground surface wipes compared to field control wipes (with one-half the reporting limit used for nondetects). Four PAHs from the above Table 27 fall into this category: chrysene, fluoranthene, phenanthrene and pyrene; however, it should be noted that while pyrene from track wipes exceeded the control wipe by almost 12-fold on 9/6/05, the margin was only 2.5-fold on 6/27/05. The reasons for this variability are unknown. On both days the samples were collected early in the morning when the skies were overcast with the typical morning fog. One possible explanation is that the PAHs detected on the track and cement apron resulted from atmospheric deposition, rather than from the material comprising the surfaces. Numerous studies have shown that the soil concentrations of various PAHs are increased in the vicinity of busy roads.

A comparison of exposure to health-based screening values was not performed for the high school students using this track surface, since their exposure to these chemicals was considered minimal for the following reasons: 1) hand-to-surface activity followed by hand-to-mouth activity was not considered an important route of exposure for these teenagers, 2) unlike the use of playgrounds by children, the use of this high school track by teenagers was considered a seasonal rather than daily activity.

Customer satisfaction survey

The six high school track and cross country coaches that comprise this survey were uniformly complimentary in their opinions of the new rubberized track surfaces compared to the old surfaces of cinders, dirt, or crushed stone. Most coaches felt their athletes suffered fewer injuries on the rubberized surfaces, with improved athletic performance. In addition, the coaches saw increased student participation on track teams, most likely due to the attractiveness and comfort of the rubberized surfaces. Community use of the tracks also increased. Lastly, some coaches mentioned the superior performance of the rubberized surfaces in foul weather compared to traditional track materials, leading to more training days per school year.

Table 28. Track Coach Satisfaction Survey

Track #1
Date Installed: unknown

Previous Surface: dirt
Injury Effects: unknown
Athletic Performance: more students have joined the track team-in the opinion of the coach, this is in large part due to the attractiveness of the new rubberized track
Track #2
Date Installed: in 2005
Previous Surface: clay and dirt
Injury Effects: fewer injuries in general compared to old track, fewer shin splints in particular
Athletic Performance: better athletic performance, including faster times; they can now train in foul weather; greater community use of the track
Track #3
Date Installed: October, 2003
Previous Surface: dirt and “granite fines”
Injury Effects: reduced shin splints especially in female distance runners
Athletic Performance: more students have joined the track team-in the opinion of the coach, this is in large part due to the attractiveness of the new rubberized track; the athletes can train harder and more often; there is increased usage of the track by people living in the neighborhood
Track #4
Date Installed: 2003
Previous Surface: crushed brick
Injury Effects: fewer injuries in general, fewer shin splints in particular
Athletic Performance: greatly improved times in the highly technical events, such as high hurdles
Track #5
Date Installed: 2004
Previous Surface: cinder, granite and sand
Injury Effects: dramatic decrease in shin splints and “runner’s knee”
Athletic Performance: the softer rubberized surface allows the cross country team to train on the track, with more interval training-as a result, times for the distance events have decreased
Track #6
Date Installed: 2005
Previous Surface: unknown
Injury Effects: unknown but coach expects fewer injuries
Athletic Performance: unknown but coach expects more students will participate on the track team

Chapter 9: Skin Sensitization Testing of Rubberized Playground Surfacing

Introduction

Tires contain varying amounts of natural rubber, in addition to the more prevalent synthetic rubber called styrene-butadiene. Natural rubber contains latex, which can form allergenic proteins leading to hypersensitization in susceptible individuals. Sensitized individuals become extremely sensitive to subsequent contact with material carrying latex allergens. These latex complexes have caused mild to severe allergic responses from dermal contact and through inhalation. This purpose of this study was to determine the potential of the recycled tire product in playground surfaces to cause skin sensitization in a laboratory animal model.

No data were located on either the latex allergen content of tires, or skin sensitization by vulcanized tire rubber in dermally exposed humans or laboratory animals. More importantly for this contract, data are also lacking for playground surfaces made from recycled tires. Such surfaces could potentially cause contact skin sensitization via latex allergens, or other unidentified allergens. Therefore, to quantitatively assess the skin sensitization endpoint, a laboratory study was performed in which guinea pigs were dermally exposed to pieces of playground surfaces made from recycled tires. The guinea pig has served as an effective animal model for identifying human contact skin sensitizers (Robinson et al., 1989), including latex (Sugiura et al., 2002).

As mentioned above, the major type of rubber in tires is the synthetic polymer styrene-butadiene. Manufacturers often refer to a playground surface made of tire pieces as SBR (styrene-butadiene rubber). Most schools and towns in California that install playground surfaces of SBR choose to add a top layer of virgin, synthetic rubber called EPDM, which contains no latex allergens. The EPDM layer is installed over the SBR layer, either in the factory (tiles) or directly in the playground itself (pour-in-place), and provides an attractive, weather-resistant surface. A survey of CIWMB grantees (see above) showed that 86 percent of responders installed a pour-in-place SBR base layer covered by a pour-in-place EPDM top layer. A few installed rakeable crumb rubber (SBR only), tiles of SBR only, or tiles of SBR constructed with an EPDM top layer. Therefore, we performed skin sensitization testing using tiles of SBR, EPDM, and loose crumb rubber (SBR).

Materials and Methods

Delayed skin sensitization testing was carried out by a modified Buehler method for solid materials according to testing guidelines (US EPA, 1998) and in accordance with Good Laboratory Practices at Product Safety Laboratories (Dayton, NJ). Guinea pigs were the test animals. The test samples were SBR tiles (Unity Surfacing, Hicksville, NY), EPDM tiles (All About Play, Sacramento, CA) and loose SBR crumb (West Coast Rubber Recycling, Gilroy, CA). All SBR was from recycled tires.

Skin sensitization testing consisted of three 6 hr induction exposures, each exposure separated by one week from the preceding exposure. All test samples were applied to the animals' skin. Then, after an additional two weeks, the animals were challenged with the test sample for 6 hrs and examined after 24 and 48 hours for signs of erythema (skin reddening). The negative control substance was high density polyethylene sheeting (TOLAS Health Care, Feasterville, PA), often used in medical packaging for its very low

incidence of allergic reaction. The positive control substance was alpha-Hexylcinnamaldehyde (HCA), a standard skin sensitizer. Additional controls included exposing animals to high density polyethylene for the induction exposure only, followed by challenge exposure to SBR or EPDM. The nine treatment groups are shown below:

<u>Group</u>	<u>Induction</u>	<u>Challenge</u>	<u># of animals</u>
1	HD polyethylene	HD polyethylene	10
2	HD polyethylene	SBR crumb	10
3	SBR crumb	SBR crumb	10
4	HD polyethylene	SBR tile	10
5	SBR tile	SBR tile	10
6	HD polyethylene	EPDM tile	10
7	EPDM tile	EPDM tile	10
8	HCA ¹	HCA	10
9	none	HCA	5

¹ alpha-Hexylcinnamaldehyde (positive control)

Initially, the animals in the positive control group (#8) failed to exhibit skin sensitization reactions following the challenge exposure. No animals in any other group showed sensitization reactions either. Therefore, all animals were re-challenged seven days after the first challenge, in exactly the same manner with the same samples. The results of this re-challenge are shown below in the Results section.

The scoring system for characterizing skin reactions was as follows:

0	no reaction
0.5	very faint erythema, usually non-confluent ¹
1	faint erythema, usually confluent
2	moderate erythema
3	severe erythema with or without reaction
¹	not considered a positive reaction

Results

A single animal in group #4 was euthanized for humane reasons on the second day of the test. There was no reason to believe that the morbidity observed in this animal was treatment related. All other animals displayed normal clinical signs, food consumption and weight gain for the duration of the test. No animal showed a positive skin reaction (skin score 1, 2 or 3) following any of the three induction doses. However, no positive reactions were observed after the challenge dose, including the positive control group. This made it necessary to re-challenge the animals seven days later. The need to re-challenge is common with this protocol (Buehler, 1994).

The skin reaction results from the re-challenge exposure are shown below. Fifty percent of the animals (5/10) in the positive control group (#8) showed positive skin reactions (skin score of 1, 2 or 3) at 24 hours after re-challenge, indicating that skin sensitization had occurred. These positive skin reactions persisted to 48 hrs after re-challenge in four of the five animals. Persistent skin reactions are hallmarks of skin sensitization (Buehler, 1994). No other treatment group contained any animal with a positive response. Thus,

the SBR tiles, SBR crumb and EPDM tiles were considered not to be contact skin sensitizers.

Numbers of animals showing positive skin reactions (skin score of 1, 2 or 3) following re-challenge¹

Group	<u>24 hrs after re-challenge</u>	<u>48 hrs after re-challenge</u>
1	0	0
2	0	0
3	0	0
4	0	0
5	0	0
6	0	0
7	0	0
8	5/10	4/10
9	0	0

¹ Data reported in Appendix C.

Discussion

Tires contain some natural rubber, and natural rubber contains latex allergens. Following dermal contact, latex allergens can induce skin sensitization in susceptible individuals. It is also possible that tire rubber contains allergens other than latex. Children using playgrounds with surfaces made of recycled tires can be exposed to substances on those surfaces through dermal contact. Hands would probably be the most common points of contact, while children playing without shoes or socks would have multiple contacts through their feet. Thus, it is prudent to determine whether such dermal exposures lead to skin sensitization.

The protocol used here to test for skin sensitization is a standard protocol for identifying contact sensitizers (US EPA, 1998). The test animal of choice is the guinea pig. Of the 85 animals used in the current study, one animal became sick early on and was euthanized. All other animals remained healthy throughout the testing period, as demonstrated by their normal clinical signs and weight gain. The only animals showing sensitization were those in the positive control group that had been exposed to an induction and re-challenge dose of the skin sensitizer alpha-Hexylcinnamaldehyde.

Five of ten animals in this group exhibited positive skin reactions at 24 hours after re-challenge, with four of ten also exhibiting positive skin reactions at 48 hours. No animals in any other group displayed positive skin reactions. Thus, the validity of this test to detect skin sensitization was demonstrated, and no playground surface sample caused sensitization. The SBR tile and SBR crumb samples contained some natural rubber, and therefore they also contained some latex allergens. However, the allergens may have become denatured during the vulcanization process, thereby losing the ability to cause skin sensitization. EPDM does not contain latex allergens. Nonetheless, it was tested and did not elicit skin sensitization.

These results suggest that recycled tires (SBR) used in playground surfaces do not cause skin sensitization in children. In addition, skin sensitization was not induced by EPDM, the material that is often used as a top layer to cover a bottom layer of SBR.

In performing risk assessment for potential skin sensitizers in humans, it has been recommended that human skin testing should follow testing in the guinea pig (Robinson et al., 1989). Nonetheless, negative results in the guinea pig, as found in our tests of SBR and EPDM, have been accurate predictors of negative results in humans (Robinson et al., 1989). Thus, these test results stand as evidence that playground surfaces made of recycled tires do not constitute a skin sensitization risk to children.

Conclusions

- Skin sensitization testing was performed with the guinea pig as test animal.
- Three materials used in rubberized playground surfaces were tested: 1) loose crumb rubber made from recycled tires, 2) tiles molded from tire shreds mixed with a binder, 3) tiles molded from particles of the synthetic rubber EPDM mixed with a binder.
- None of the components of rubberized playground surfaces caused any skin sensitization, while the positive control substance (alpha-Hexylcinnamaldehyde) produced positive reactions in 40-50 percent of the animals.
- These data suggest that playground surfaces made of recycled tires do not constitute a skin sensitization risk to children.

Chapter 10: Ecotoxicity of recycled tires including Yulupa Elementary School tire chips fire

Introduction

This section addresses the potential of recycled tires as a source of soil or groundwater contamination, and if so, whether the contamination is sufficiently high to constitute a hazard to the ecology. In addition, the results of toxicity testing in sentinel organisms are presented as an indication of the potential of recycled tires to adversely impact the animals and plants that compose many local ecologies.

Soil Contamination

Five studies contained measurements of metals and chemicals in soil either containing or within a few feet of recycled tire applications (Table 29). These applications were in a playground surface (CIWMB, 2004), in roadbed construction (Minnesota Pollution Control Agency, 1990), as cover for school parking lots and roadways (FCCJNC, 1999), as a rootzone amendment for the cultivation of turf grass (Boniak et al., 2001) and in a septic tank field (Amoozengar and Robarge, undated). A study by Newman et al. (1997) added ground tires to the potting medium used to grow hot-house flowers, while in a laboratory study by Smolders and Degryse (2002), fine tire debris was mixed with soil, allowed to weather, and filtered with water to measure the leaching of zinc.

Neither the playground study nor the roadbed study detected significant increases in metals or chemicals in the soil near the recycled tires (compared to background). For the turf grass application, the maximum increase in soil zinc was to 31 ppm: a level within the range of most agricultural soils in southern Illinois (Boniak et al., 2001). Soil zinc also increased in the laboratory study by Smolders and Degryse (2002), while both zinc and copper increased in the potting medium used to grow geraniums in a hot-house (Newman et al., 1997).

The parking lot study (FCCJNC, 1999) measured increases that correlated with the presence of recycled tire chips as cover for road surfaces: however, only the increase in iron appears to be significant based on the data presented in the report. As discussed previously in this report, the iron most likely originates from the steel belts and beads used in tire construction. At least 99 percent of this steel material is removed when tires are processed into crumb rubber for use in playground construction. Lastly, while the soil within 5 cm of rubber/gravel trenches of a septic field contained elevated levels of Zn, Se, Cr and Ni, the levels of the first three fell to background between 5 and 20 cm (Amoozengar and Robarge, undated).

None of the soil levels of metals or toluene measured in these studies exceeded either the U.S. EPA Region 9 Preliminary Remedial Goals for soil (U.S. EPA, 2003d), the screening values for soil-bound chemicals recently proposed by OEHHA (2005b), or the California Regional Water Quality Control Board Environmental Screening Levels (2003). Therefore, this limited data suggests that recycled tires do not leach sufficient chemicals into the surrounding soil so as to present a risk to human health.

Ecological toxicity

With regard to ecological toxicity, the screening levels set by the California Regional Water Quality Control Board (2003) also address risks to the flora and fauna. None of the levels reported in Table 29 exceed those screening levels; thus, risks to the health of the non-human organisms are not expected by those criteria. However, another set of Preliminary Remediation Goals for Ecological Endpoints (Efroymson et al., 1997) include soil values for zinc (8.5 ppm) and selenium (210 ppb) that are exceeded by the corresponding values in the table. In the case of selenium, the screening value is based on toxicity in the White-footed mouse, while the screening value for zinc is based on toxicity in the American woodcock.

Thus, ecological effects from contaminated soil cannot be ruled out based on these Preliminary Remediation Goals, although the selenium level in the soil was only marginally higher than the PRG and the zinc levels were close to the normal background levels. It should be added that these PRGs (Efroymson et al., 1997) assume widespread soil contamination and unlimited access of the wildlife to the contaminated soil. Since the soil values in the table reflect measurements made no more than a few feet away from the tire rubber, it is quite possible that any detected contamination did not extend more than a few feet. In the case of the only playground for which soil data exist (CIWMB, 2004 in Table 29) this was the case, since only background levels of metals and chemicals were present where the soil was sampled at 1.5 feet below the rubber chip layer.

Table 29. Soil analysis in the vicinity of recycled tires used in road/parking lot construction, a playground surface, or as a soil amendment.

Citation	Methods	Findings
Amoozegar and Robarge, undated	Chipped tires mixed with gravel and used to fill trenches of a septic system	Soil within 5 cm of trenches was at least 3-fold above background for Zn, Se, Cr (total) and Ni; levels of all but Ni fell to background between 5 and 20 cm of trenches
Boniak et al., 2001	Crumb rubber mixed with soil for use as a rootzone mix at 20, 30 or 40% rubber/g soil; grass was planted and soil analyzed approximately one year later	Soil zinc content increased 7- to 16-fold to 31 ppm (but still within range of most soil in southern Illinois), soil phosphorous and potassium increased up to 2-fold
CIWMB, 2004	3-24 inches of tire chips used as playground surface for 5 years; soil sampled 1.5 feet below tire layer	Metals, VOCs, PAHs, dioxins and furans all at or below background levels
FCCJNC, 1999	Ground rubber used to cover dirt parking areas and internal roadways of a community college; soil sampled from directly beneath tire layer over 2.5 years	Toluene 63 ppb, antimony 500 ppb, copper 2.3 ppm, iron 960 ppm, lead 13 ppm, zinc 45 ppm, barium 10 ppm, selenium 253 ppb, all elevated compared to pre-installation baselines (largest increase was for iron, at least 50-fold); all levels of contamination were below state soil cleanup goals
Minnesota Pollution Control Agency, 1990	Shredded tires used in roadbed construction; soil sampled 3 feet from tire layers and 4 feet below the surface	Fifteen metals measured; 5 were elevated (about 2-fold) relative to background levels, however, the differences were not significant
Newman et al., 1997	Ground tire rubber mixed with peat and/or vermiculite for use as a medium for growing hot-house geraniums (2 months duration)	Medium containing rubber had zinc and copper levels that were 40- and 11-fold greater than controls.
Smolders and Degryse, 2002	Fine rubber tire debris mixed with soil and allowed to weather outside for eleven months	Leachates from soil/rubber mixtures analyzed for Zn: the Zn content of leachate from truck tire rubber/soil was not different from controls, while the Zn content of leachate from car tire rubber/soil was three-fold higher than control

A Case Study of Possible Soil Contamination: Evaluation of the Construction Completion Report for the Yulupa Elementary School Tire Chip Fire, Sonoma County, June 2004 (CIWMB, 2004)

Summary

- A playground surface made of recycled tire chips burned at the Yulupa School. A clean-up followed.
- Environmental measurements were made by the US EPA and by DTSC of CAL EPA.
- The US EPA report showed:
 5. The soil/rubber material removed from the site was not hazardous waste and could be disposed of in a Class III landfill.
 6. The air above the burn site posed no health risks to clean-up workers.
 7. The soil below the burned layer posed no significant risks to human health.
- The DTSC report showed:
 1. The soil remaining after the clean-up contained only background levels of chemicals, suggesting the tire chips had not released chemicals into the soil.
 2. A human health risk assessment confirmed that the background levels of chemicals in the soil remaining after the clean-up were not expected to produce health effects in persons using the school site.

Introduction

The Yulupa School fire occurred in August, 2003, in a playground surface composed of metal-free rubber chips derived from recycled tire side-walls. The chips had been in place for over five years. The chip layer varied from 3-24 inches deep. Under the chip layer was a bed of fill material of undetermined depth. Approximately 50 percent of the chip surface burned in the fire, which lasted about 15 minutes. The subsequent activities were aimed at removing all rubber material and a layer of soil under the rubber, followed by testing whether the remaining soil contained tire chip-derived toxicants that posed a health hazard to persons attending the school.

US EPA Assessment Sampling Report

A contractor was hired by US EPA to assess the following:

1. Whether the soil below the burned chip layer had become contaminated with rubber-derived chemicals.
2. Whether the soil removed from the site should be classified as hazardous waste.
3. Whether the air sampled during one day of clean-up activities was contaminated with any rubber-derived chemicals or dust.

OEHHA Evaluation: While some soil samples from beneath the combusted tire chip layer contained levels of metals and/or chemicals that were above reporting limits, since

only a single background sample was analyzed, it was not possible to determine whether any substance detected below the tire chip layer was significantly higher than background. Accurate determination of background was particularly important in this instance, given that the entire playground was built on top of fill material brought in from another location. None of the reported levels approached the US EPA Region 9 Preliminary Remediation Goals for Soil or the OEHHA (2005b) Human-Exposure-Based Screening Numbers to Aid Estimation of Cleanup Costs for Contaminated Soil. Thus, human health effects were not expected.

A variety of procedures were used to demonstrate that the soil removed from the burn area was not hazardous waste. Thus, the soil could be disposed of in a class III landfill.

Two of four air samples taken from around the perimeter of the playground during the clean-up were slightly above the detection limit for zinc. It was concluded that no significant personal health risks were posed to clean-up workers by any of the monitored chemicals (zinc, dust, benzene, polycyclic aromatic hydrocarbons, total hydrocarbons, carbon monoxide or explosive atmospheres).

DTSC Confirmation Sampling Plan and Report

After the tire chips had been removed along with a layer of fill extending 1.5 feet below the chip layer, the remaining soil was sampled for analysis of metals, VOCs, PAHs, dioxins and furans. Four background samples from nonimpacted areas at the school were analyzed for metals only. In addition, three soil samples were taken from points adjacent to the playground downwind of the fire. These “adjacent” samples were from under a six inch layer of wood chips.

OEHHA Evaluation: No VOCs were detected in any samples. A variety of PAHs were detected in samples from under the playground and adjacent/downwind of the playground fire. Although background PAH levels at nonimpacted locations were not determined, historical background levels measured in urban US soil (ATSDR, 1995) were actually higher than the levels measured in the Yulupa school samples. Similarly, levels of dioxins and furans in soil samples from under the burned chip layer were five-fold lower than the mean background levels in US rural soil and in California agricultural soil (Australian Government, 2004). These results suggest that neither the burned nor unburned tire chips released measurable amounts of these chemicals into the soil that remained after the clean-up (i.e., in soil at 1.5 feet below the chip layer).

Levels of five metals detected at one of three adjacent sites downwind of the playground were considered above background; however, the following suggest that these levels were not tire-derived:

1. The two other samples at adjacent/downwind sites were not above background for these metals.
2. No samples from under the chip layer were above background for these metals.

The soil measurements made by DTSC suggest that neither burned nor unburned tire chips in the Yulupa playground released chemicals into the soil that remained following the clean-up. Nonetheless, a human health risk assessment was performed based on the measured levels of both carcinogens and noncarcinogens. For carcinogens, the risk was determined to be less than 10^{-6} , and for noncarcinogens the hazard index was less than 1. Thus, health effects were not expected for persons using the school site following the clean-up.

Groundwater contamination

Although groundwater is a part of most local ecologies, its contamination usually represents only a human health risk in so far as it serves as a source of drinking water. However, groundwater can also be used for crop irrigation and as a drinking water source for livestock. Groundwater can also enter surface water systems such as lakes and streams. Thus, groundwater contamination has the potential to affect surface flora and fauna.

Five studies were located which analyzed groundwater for tire-derived metals and compounds (Table 30). For the studies by the Minnesota Pollution Control Agency (1990), Humphrey and Katz (2001) and Exponent (2003), the tire shreds were located below the water table; thus, the shreds were in constant hydraulic communication with the local groundwater. In the cases of storm runoff from crumb rubber-covered areas of a parking lot (FCCJNC, 1999) or storm seepage through a road embankment made of sand and tire shreds (Yoon et al., 2005), the rainwater entered the local groundwater followed by sampling of the groundwater.

Iron was noteworthy as the only substance identified in four of the studies as exceeding the US EPA National Drinking Water Standard (2005a); for iron the standard was a Secondary National Drinking Water Standard. Exceeding a Secondary Drinking Water Standard is associated with cosmetic or aesthetic effects. In the study by the Minnesota Pollution Control Agency (1990) the iron standard was exceeded by 1000-fold. As discussed earlier in this report, the source of iron in these studies was most likely the steel belts and beads used in tire construction. Since current methods for processing tires into crumb rubber for use in playgrounds includes a step that removes 99% of the steel material, the iron levels leaching from rubberized playgrounds should be at least 100-fold lower than those cited above.

Manganese exceeded its Secondary National Drinking Water Standard in two of the studies (maximum 26-fold higher). Like iron, it probably also originated from the steel belts and beads in the tires. Cadmium, chromium, aluminum and lead exceeded their National Primary Drinking Water Standards in the single study by the Minnesota Pollution Control Agency (1990). All other levels of compounds or metals either fell below their National Drinking Water Standard or had no standard established for them.

It should be noted that in the study by Humphrey and Katz (2001), almost all high values from within the tire trench fell to background at three meters downgradient from the trench. Similarly, Exponent (2003) reported that the iron concentration was only elevated in the area close to the tire shreds, and that leached iron was quickly diluted or precipitated within 2-10 feet of the tire trench. Iron was specifically discussed since it was believed to be responsible for the toxicity of the groundwater from the tire trench towards *Ceriodaphnia dubia*. Thus, these limited data suggest that the tire-derived contaminants in groundwater do not migrate very far from their source.

Table 30. Groundwater analysis in the vicinity of recycled tires used in road and parking lot construction, and in underground test trenches.

Citation	Methods	Findings
Exponent, 2003	Groundwater collected from shredded tire trench located in saturated soil below the water table; water samples taken from inside trench and at a well 2 feet downgradient from the trench	Concentrations above background, all in ppb: chloroethane 2; 1,1-dichloroethane 2; cis-1,2-dichloroethene 16; benzene 1.6; trichloroethene 0.8; toluene 2.6; N-Nitrosodimethylamine 7; N-Nitrosodiphenylamine 7; aniline 100; bis(2-ethylhexyl)phthalate 5; acetone 11; iron 80,000; manganese 570; zinc 90; barium 30
FCCJNC, 1999	Ground rubber used to cover dirt parking areas and internal roadways of a community college; groundwater sampled from wells within a few meters of rubber-covered areas; wells were "in hydraulic communication with the aquifer"	Concentrations above background, all in ppb: total xylenes 1.4; iron 1,500; chromium 4
Humphrey and Katz, 2001	Groundwater collected from shredded tire trench located in saturated soil below the water table; water samples taken from inside trench and at a well 3 meters downgradient from the trench	Concentrations inside trench and above background, all in ppb: 1,1-dichloroethane 6; 4-methyl-2-pentanone 58; acetone 28; benzene 4; chloroethane 4; cis-1,2-dichloroethene 24; aniline 71; phenol 33; m+p cresol 39; iron 33,000; manganese 1,300; zinc 26; almost all values were at background in the groundwater sampled 3 meters downgradient from the tire trench
Minnesota Pollution Control Agency, 1990	Road bed construction with tire shreds over a wetland area; groundwater sampled from wells within a few feet of road bed	Concentrations above background, all in ppb: aluminum 180,000; barium 2000; cadmium 32; chromium (total) 350; iron 300,000; lead 230; zinc 870
Yoon et al., 2005	Tires shreds used in constructing a road embankment; groundwater sampled from a well adjacent to and downgradient of the embankment	Metal concentrations above background, all in ppb: arsenic 19; barium 113; cadmium 1.1; chromium (total) 55; selenium 23

Toxicity tests in sentinel organisms

Table 31 shows results of toxicity tests with sentinel organisms used as a means of identifying potential ecological toxicants. In almost all cases, whole tires, tire shreds or crumb rubber was used to produce concentrated leachates in the laboratory. The organisms used to test these concentrated leachates included single-celled bacteria (*Vibrio fisheri*) and algae (*S. capricornutum*, *R. subcapitata*), the aquatic invertebrates *Daphnia* and shrimp, three species of fish (rainbow trout, fathead minnows and sheepshead minnows), the frog species *X. laevis* and lettuce. In addition, four studies measured the effects of recycled crumb rubber on the growth of turf grass, while one study followed the growth of hot-house geraniums, all prompted by its use as a soil amendment.

The study by Birkholz et al. (2003) utilized crumb rubber manufactured specifically for use in playground surfaces. All other studies utilized either whole tires or tires processed into chips, shreds, plugs or powder.

Toxicity, often measured as lethality, was observed for all aquatic organisms (bacteria, algae, *Daphnia*, shrimp, minnows, trout, frog) exposed to recycled tires, although some individual studies were negative. Fathead minnows appeared to be less sensitive than rainbow trout, since 2/6 studies with the former detected toxicity compared to 3/3 studies with the latter. Three studies out of eight involving terrestrial plants documented adverse effects: decreased germination in turfgrass (Boniak et al., 2001), decreased growth rates for bermudagrass (Owings and Bush, 2001) and decreased growth rates and flower count in geraniums (Newman et al., 1997).

With regard to identifying the responsible toxicant(s), in *Daphnia* metals were thought to be responsible: zinc in the studies by Nelson et al. (1994) and Gaultieri et al. (2005) and iron precipitates forming on the feeding apparatus in the study by Exponent (2003). The lethality in rainbow trout was consistent with a nonvolatile (Day et al., 1993) and nonmetallic (Ontario Ministry of Environment and Energy, 1994) toxicant.

While these studies (mostly laboratory) show that recycled tire rubber has the potential to cause adverse effects in non-human organisms, whether this would occur in the environment surrounding rubberized playground surfaces would depend on the dilution, dispersion and precipitation of the relatively low levels of chemicals released by these surfaces. The chemicals released by tires could also be transformed through interactions with reactive chemicals already in the environment.

All but one of the studies with aquatic sentinel organisms discussed here utilized tire leachates produced in the laboratory. Chemicals in such leachates may be at lower or higher concentrations than would be achieved in the area surrounding rubberized playground surfaces. For the single study of tire leachate produced in the field (Exponent, 2003), only tire shreds below the water table released sufficient iron to cause toxicity, and then only within 2-10 feet of the tire trench. The tire trench above the water table did not release toxic levels of iron. This latter situation more closely represents what would be expected in the environment surrounding rubberized playground surfaces, where the surfaces are not in constant hydraulic communication with groundwater.

Table 31. Toxicologic responses of sentinel organisms to recycled tire rubber and its leachate.

Citation	Methods	Findings
Bacteria		
Birkholz et al., 2003	Playground crumb rubber used to produce leachate in lab; toxicity measured in luminescent bacteria <i>Vibrio fischeri</i>	Toxicity observed-less for crumb rubber aged by use in playground for 3 months
Algae		
Basel Convention, 1999	Powdered tire rubber shaken in water for 24 h; growth of <i>S. capricornutum</i> measured	No effects at highest dose tested
Gualtieri et al., 2005	Finely ground tire rubber shaken in water at pH 3 for 24 h; growth of <i>R. subcapitata</i> measured	Growth inhibited over the 72 h of incubation
Minnesota DOT, 1995	Chipped tires and chipped wood used to produce leachate in lab; survival and reproduction measured in green algae (<i>S. capricornutum</i>)	Tire and wood leachates were equitoxic at lowest dose level tested
Daphnia (aquatic invertebrate)		
Basel Convention, 1999	Powdered tire rubber shaken in water for 24 h; testing for changes in mobility of <i>Daphnia magna</i>	No effects at highest dose level tested
Birkholz et al., 2003	Playground crumb rubber used to produce leachate in lab; lethality measured in <i>Daphnia magna</i> (exposure time not specified)	Lethality observed-less for crumb rubber aged by use in playground for 3 months
Day et al., 1993	Whole tires immersed in water in tanks for increasing times	No lethality observed
Exponent, 2003	Leachate from tire trench below and above water table; survival and reproduction measured in <i>Ceriodaphnia dubia</i>	Lower survival and less reproduction compared to controls for below water table application only-believed due to iron precipitates forming on feeding apparatus
Gualtieri et al., 2005	Finely ground tire rubber shaken in water at pH 3 for 24 h; toxicity to <i>D. magna</i> measured	Immobility/mortality was observed after 24 and 48 h of incubation

Citation	Methods	Findings
Minnesota DOT, 1995	Chipped tires and chipped wood used to produce leachate in lab; survival and reproduction measured in <i>Ceriodaphnia dubia</i>	Tire chip leachate was 5- to 8-fold more toxic than wood chip leachate
Nelson et al., 1994	Tire plugs immersed in lake water in lab for 31 days; 24 h LC ₅₀ determined in <i>Ceriodaphnia dubia</i>	Lethality observed; believed due to Zn
Ontario Ministry of Environment and Energy, 1994	Whole tire immersed in water in tank for up to 2 weeks; water tested with <i>Daphnia magna</i> and <i>Ceriodaphnia dubia</i> in 48 hour incubations	No lethality observed
Wik and Dave, 2005	Finely ground tire rubber incubated in water for 72 h prior to addition of <i>Daphnia magna</i> for another 24 h	Variable toxicity in tire samples possibly due to nonpolar organic compounds
Daggerblade Grass Shrimp (aquatic invertebrate)		
Hartwell et al., 1998	Shredded tires used to produce leachate in lab at salinities of 5-25 percent; survival and growth measured over 96 hrs in grass shrimp <i>Palaemonetes pugio</i>	Lethality and growth inhibition both observed in response to tire leachate
Minnows		
Basel Convention, 1999	Powdered tire rubber shaken in water for 24 h; mortality of <i>Brachydanio rerio</i> measured	No mortality observed at highest dose level tested
Birkholz et al., 2003	Playground crumb rubber used to produce leachate in lab; lethality measured in the fathead minnow <i>P. promelas</i> (exposure time not specified)	Lethality observed-less for crumb rubber aged by use in playground for 3 months
Day et al., 1993	Whole tires immersed in water in tanks for increasing times; lethality measured in the fathead minnow	No lethality observed
Exponent, 2003	Leachate from tire trench below and above water table; seven day survival and reproduction measured in fathead minnow <i>P. promelas</i>	No effects observed

Citation	Methods	Findings
Hartwell et al., 1998	Shredded tires used to produce leachate in lab at salinities of 5-25 percent; survival and growth measured over 96 hrs in larval sheepshead minnows <i>Cyprinodon variegatus</i>	Lethality and growth inhibition both observed in response to tire leachate
Minnesota DOT, 1995	Chipped tires and chipped wood used to produce leachate in lab; survival and reproduction measured in fathead minnow (<i>P. promelas</i>)	For survival and growth the leachate from tires was 2 to 3-fold more toxic than the leachate from wood
Ontario Ministry of Environment and Energy, 1994	Whole tire immersed in water in tank for up to 2 weeks; water tested with fathead minnow <i>P. promelas</i> in 4 day exposures	No lethality observed
Trout		
Day et al., 1993	Whole tires immersed in water in tanks for increasing times; lethality measured in rainbow trout	Lethality observed-lethality was stable for 2-3 days if tires removed, then slowly decreased over 32 days (believed due to break down of nonvolatile toxicants)
Ontario Ministry of Environment and Energy, 1994	Whole tire immersed in water in tank for up to 2 weeks; lethality measured in rainbow trout fry for exposures of up to 4 days	Lethality observed after 24 hours of exposure; toxicity completely removed by pretreating water with activated carbon
Stephensen et al., 2003	Whole tires immersed in water in tanks with rainbow trout; liver and bile examined from the fish	Tire-exposed fish exhibited the following: increased liver weight, increased hepatic CYP1A1, glutathione, glutathione reductase, glutathione S-transferase and glucose-6-phosphate dehydrogenase; bile contained hydroxylated PAHs and aromatic nitrogen compounds

Citation	Methods	Findings
<i>X. laevis</i> (frog) embryos		
Gaultieri et al., 2005	Finely ground tire rubber shaken in water at pH 3 for 24 h; toxicity measured with <i>X. laevis</i> (frog) embryos incubated in Petri dishes	Lethality and malformations produced in the frog embryos during the 120 h incubation
Plants		
Boniak et al., 2001	Crumb rubber mixed with soil for use as a rootzone mix in the cultivation of turf grass (tall fescue and Kentucky bluegrass)	Smallest size of crumb rubber caused a dose-dependent decrease in germination rate and decrease in turf quality
Groenevelt and Grunthal, 1998	Crumb rubber mixed with soil used to grow turf grass	The Zn content of the turf grass approximately doubled, to over 80 mg/kg; no accompanying toxicity
Lisi et al., 2004	Crumb rubber installed as a drainage layer 30 cm beneath the root zone of a golf course putting green	No detrimental effects observed on turf grass quality, color or density
Minnesota DOT, 1995	Chipped tires and chipped wood used to produce leachate in lab; survival and growth of lettuce (<i>Lactuca sativa</i>) from seed measured	No effects observed on survival or growth
Minnesota Pollution Control Agency, 1990	Shredded tires used in roadbed construction	No differences observed in the diversity of plant species growing in the tire and control areas
Newman et al., 1997	Ground tire rubber mixed with peat and/or vermiculite for use as a medium for growing hot-house geraniums (2 months duration)	Plant growth and flower count were lower for plants grown in medium containing ground rubber, possibly due to released zinc and copper, both of which were elevated in the plant tissue

<i>Citation</i>	<i>Methods</i>	<i>Findings</i>
Owings and Bush, 2001	Growth of bermudagrass in containers of sand, peat moss and various concentrations of crumb rubber	Growth rates decreased, possibly due to released zinc and manganese
Tompkins et al., 1997	Crumb rubber as a soil amendment for the growth of turf grass	No effects observed on emergence rates; slightly better color was observed in the presence of the crumb rubber

Conclusions

- Only a limited number of soil samples from locations adjacent to recycled tire shreds have been analyzed; while a number of metals were above background in some studies, most increases were small.
- In the single case where soil samples from under a playground surface made of recycled tires were analyzed, the metals, VOCs, PAHs, dioxins and furans were at or below background levels, suggesting no risk to the local ecology.
- Measurements of chemicals released from recycled tires into groundwater are also scarce.
- Groundwater in contact with tire shreds contained elevated levels of many chemicals; however, those levels rapidly approached background a few feet outside of the tire trench.
- Recycled tires released chemicals that were toxic to a variety of sentinel organisms including bacteria, algae, aquatic invertebrates, fish, frogs and plants; importantly, almost all of these studies in animals, bacteria and algae utilized concentrated leachate produced in the laboratory.
- Considering all the data, it seems doubtful that recycled tire rubber in outdoor applications such as playground surfaces releases high enough levels of chemicals to cause toxicity to animals and plants living in the vicinity.

Chapter 11: Evaluating the Risk of Serious Head Injury Due to Falls on California Playground Surfaces Made of Recycled Tires

Abstract

Recycled tires continue to be used in the construction of rubberized playground surfaces in California. To function as an effective means of reducing the incidence of serious head injury when children fall in the playground, these surfaces should meet standards for impact attenuation, as cited in the California Code of Regulations (sections 65700-65750). This study was conducted to determine whether rubberized surfaces are meeting the standards for impact attenuation, and whether those properties change as the surfaces age. Data have been gathered from 32 rubberized playground surfaces and 5 surfaces made of wood chips/engineered wood fiber.

An accelerometer was used to measure maximal deceleration rates (G_{\max}) and Head Impact Criterion (HIC) values for the surface below each play structure (131 tested) within the playgrounds, which were then compared to the American Society for Testing and Materials (ASTM) F1292 standard for impact attenuation by playground surfaces. Approximately 33 percent of the play structures on rubberized surfaces failed to meet the HIC standard, compared to no failures on wood chips. Approximately 69 percent of the rubberized playground surfaces contained at least one failing structure. Failing structures over rubberized surfaces included swings, climbers, slides, upper body rings and elevated platforms.

As the heights of the play structures in rubberized playgrounds increased, so did the likelihood that the surface below would fail to meet the HIC standard, although some of the highest structures had underlying surfaces that met the standard. There appeared to be little or no difference in impact attenuation by surfaces less than one year old compared to surfaces that were between one and two years old. In addition, HIC values in two pour-in-place surfaces were stable for at least the first two to three months following installation. Lastly, HIC values of pour-in-place surfaces increased with increasing surface temperature. These results demonstrate the importance of testing rubberized playground surfaces following installation, to verify that the surfaces meet the standards for impact attenuation.

Introduction

Nationwide, up to 80 percent of serious playground injuries are the results of falls to the surface (Tinsworth and McDonald, 2001). Most were injuries to the upper limbs (Altman et al., 1996; Chalmers et al., 1996), although this varied with age; for children younger than five years old the head or face was injured most frequently, while for children 5-14 years old injuries to the hand or arm predominated (Tinsworth and McDonald, 2001).

Epidemiologic studies performed with data from hospitals and daycare centers demonstrated that as the height of playground equipment increased, the injury rate from falls also increased (Briss et al., 1995; Chalmers et al., 1996; Mott et al., 1997; Macarthur et al., 2000). Less clear, however, is the influence of playground surface type on

frequency and kind of injury. In some instances impact-absorbing surfaces such as wood chips, sand, rubber tile/mats and rubber shreds were effective at reducing injuries from falls compared to hard surfaces such as asphalt, cement, turf and dirt (Chalmers et al., 1996; Mott et al., 1997; Mowat et al., 1998; Norton et al., 2004b), while other studies found little or no benefit (Sosin et al., 1993; Briss et al., 1995; Waltzman et al., 1999).

There are too few data to draw reliable conclusions on impact attenuation and injury reduction by rubber playground surfaces compared to other surfaces. An epidemiologic study by Mott et al. (1997) found that playgrounds with “rubber surfaces” (rubber surface type not specified) performed better than those consisting of bark or concrete. However, as discussed above, other epidemiologic studies have failed to detect any significant differences among surfaces.

Turning to laboratory studies where impact attenuation was measured with mechanical devices under controlled conditions, in two studies rubber chips outperformed sand, wood chips and gravel (Mack et al., 2000; CPSC, undated), while in a third study wood chips outperformed rubber mats (Lewis et al., 1993). Clearly, data collected from playgrounds being used by children are needed in order to determine whether the different types of rubber surfacing (crumb, shreds, pour-in-place, molded tiles) lower the injury rate compared to other impact-absorbing surfaces.

Therefore, discussions were held with members of the Injury Surveillance and Epidemiology Section of the California Department of Health Services and the Department of Epidemiology in the UCLA School of Public Health, in an effort to locate injury data collected from playgrounds both before and after installation of rubberized surfaces. No such data were located, including no information on insurance savings directly attributable to decreased playground injuries. Thus, OEHHA decided to collect impact attenuation data from California playground surfaces made of recycled tires, from which to estimate the risk of serious head injury from falls.

That lowering the number of playground injuries would produce a large reduction in health care-related costs is demonstrated by the estimate that playground-related injuries in the United States cost 1.2 billion dollars to treat in 1995 (U.S. Centers for Disease Control, 2005). If ten percent of these occurred in California, then approximately 120 million dollars were spent in this state. Since approximately 80 percent of these injuries resulted from falls (Tinsworth and McDonald, 2001), then reducing the injury rate from falls by only ten percent has the potential to save almost 10 million dollars in California (higher savings in 2006 dollars). An accompanying reduction in injury severity would save even more.

It may also be particularly important to compare injury rates for specific types of injuries, such as head concussions and long-bone fractures of the arm. Some studies suggest that impact attenuation properties vary between surfaces, such that head injury might be optimally prevented by one surface, while long-bone injury might be optimally prevented by another (Briss et al., 1995; Rabinovitch and Chiu, 1998; Petridou et al., 2002; Norton et al., 2004a; Norton et al., 2004b). This was in fact demonstrated in a laboratory study that used a test dummy to simulate the short-distance falls that children experience when falling out of bed (Bertocci et al., 2003). While similar “g” forces for head impact were measured on playground foam compared to padded carpet, the foam produced significantly less axial tension to the femur. Similar data are needed for the different types of rubberized playground surfaces.

More than 40 million waste tires are generated each year in California (CIWMB, 2006). Increasingly, these used tires are being recycled into rubberized playground surfaces. Such surfaces can be made thick enough to provide significant impact attenuation when children fall from play structures in the playground, thereby reducing the chance of serious head injury (U.S. CPSC, 1997). This is accomplished by deformation and/or displacement of the surface in the local area of the impact, thereby absorbing some of the energy of impact. While the standards for impact attenuation by playground surfaces are cited in the California Code of Regulations (sections 65700-65750), these standards have never been enforced.

Thus, it is currently unknown whether the standards are being met, either by the relatively new playground safety surfaces made of recycled tires, or by more traditional surfaces also in use in California including sand, wood chips and pea gravel. The primary objective of this study was to determine whether California playground surfaces made of recycled tires are in compliance with the California standards for impact attenuation. In addition, since these surfaces are exposed to the environment, we studied whether their impact attenuating properties are influenced by temperature and whether they change over time.

Materials and Methods

We tested playgrounds of municipalities and school districts awarded grants by the CIWMB for the installation of playground surfaces made of recycled tires. These were located in San Francisco and surrounding regions. In a number of instances, grantees had additional playgrounds with rubberized surfaces made of recycled tires that were not funded by the CIWMB. Permission was obtained to test both the CIWMB-funded and non-funded surfaces. There were no obvious differences in the types or sizes of playground structures contained in these two groups. One private childcare facility with a rubberized playground surface made of recycled tires was included in the study.

A total of 32 rubberized playground surfaces were tested for impact attenuation. Twenty-six were pour-in-place surfaces consisting of a bottom layer of shredded tires and a top layer of the synthetic rubber called ethylene propylene diene monomer (EPDM). Pour-in-place surfaces are made by mixing shredded tire rubber with polyurethane binder on site, and pouring the mixture into the playground to harden into a unitary surface. The top layer of EPDM is then added using a similar process. Four playground surfaces were constructed out of tiles made of shredded tires. Such tiles are pre-molded by the manufacturer and transported to the playground site, where they are attached to each other by glue or other method to form a unitary surface. Two surfaces were tested that consisted of loose-fill shredded tires. This material is raked into place, and requires periodic maintenance that includes removal of foreign objects and evening of the surface. Five playgrounds were tested that had surfaces made of wood chips/engineered wood fiber. These surfaces are also raked into place, and require regular maintenance similar to that required by the loose-fill rubber surfaces. Table 32 lists some of the advantages and disadvantages of these safety surfaces, including sand.

Table 32. Advantages and disadvantages of different playground safety surfaces (adapted with modification from Huber, 2001)

Pour-in-place or tiles made of shredded tires
<i>Advantages:</i> low maintenance and easy to clean; consistent shock absorbency; does not harbor foreign objects; does not readily support microbial growth; not subject to displacement during children's play; accessible to the disabled; good footing; unattractive to dogs and cats as a place

to defecate; cannot be swallowed by children
<i>Disadvantages:</i> high installation cost; shock absorbency may decrease somewhat over a time frame of years; can become uncomfortably hot on warm days; flammable
Loose-fill shredded tires
<i>Advantages:</i> low installation cost; drains well; depth easily increased to increase shock absorbency; does not readily support microbial growth; less attractive to dogs and cats as a place to defecate; less subject to compaction over time
<i>Disadvantages:</i> requires regular maintenance; gets dirty over time; harbors/hides foreign objects; subject to displacement during children's play; can be thrown by children; flammable; less accessible to the disabled; can be swallowed by children; difficult footing; smaller particles prone to being tracked indoors by children
Wood chips/engineered wood fiber
<i>Advantages:</i> low installation cost; drains well; depth easily increased to increase shock absorbency; stays relatively cool on hot days
<i>Disadvantages:</i> requires regular maintenance; combines with dirt over time; harbors/hides foreign objects; subject to displacement during children's play; can be thrown by children; supports microbial growth; used by cats and dogs as a place to defecate; flammable; can become compacted over time; less accessible to the disabled; can be swallowed by children
Sand
<i>Advantages:</i> low installation cost; drains well; depth easily increased to increase shock absorbency; nonflammable; does not readily support microbial growth
<i>Disadvantages:</i> requires regular maintenance; combines with dirt over time; harbors/hides foreign objects; subject to displacement during children's play; can be thrown by children; used by cats and dogs as a place to defecate; can become compacted over time; not accessible to the disabled; can be swallowed by children; difficult footing; loses shock absorbency when water saturated
Pea Gravel
<i>Advantages:</i> low installation cost; drains well; depth easily increased to increase shock absorbency; nonflammable; does not readily support microbial growth
<i>Disadvantages:</i> requires regular maintenance; combines with dirt over time; harbors/hides foreign objects; subject to displacement during children's play; can be thrown by children; used by cats and dogs as a place to defecate; can become compacted over time; not accessible to the disabled; can be swallowed by children; difficult footing; can be inserted by the child into its body openings such as ears and nose

Measurement of surface impact attenuation (HIC, G_{max}) was performed with a Triax2000 triaxial accelerometer (Playground Clearing House, Trenton, New Jersey) according to the American Society for Testing and Materials (ASTM, 2004) standard number F1292: Standard Specification for Impact Attenuation of Surfacing Materials Within the Use Zone of Playground Equipment. HIC and G_{max} data can be used to predict whether serious head injury would result from a fall onto a surface. According to this standard, the surface below each play structure is tested at its fall height at three locations within its use zone. Fall heights and use zones were according to ASTM standard F1487 and United States Consumer Products Safety Commission publication No. 325: Handbook for Public Playground Safety.

The Triax2000 utilizes a ten pound headform (Figure 2). For reference comparison and quality control purposes, the accelerometer in the headform was routinely tested by performing drops onto a rubber reference pad supplied by the manufacturer. Those HIC and G_{\max} values were always within 2% of the reference pad values specified for our accelerometer, as required by the ASTM F1292 standard (ASTM, 2004).

All testing was conducted on days when it had not rained, and on dry surfaces (other than surface dampness that might be due to fog or morning dew). Prior to testing, loose-fill surfaces were compacted with a hand tamper as described in ASTM F1292. Temperatures of both the surface and ambient air were recorded.

Results

Figure 3 shows the results of drops at 368 locations around 121 playground structures standing on rubberized surfaces. For a drop location to meet the ASTM F1292 standard, the G_{\max} value must be less than or equal to 200, and the HIC value must be less than or equal to 1000. A number of drops failed the HIC standard, while a smaller number failed the G_{\max} standard. Every drop that passed the HIC standard also passed the G_{\max} standard. In contrast, many drops that passed the G_{\max} standard failed to pass the HIC standard. Thus, the HIC=1000 standard is a more sensitive test of impact attenuation by these rubber surfaces, and in subsequent graphs only the HIC value was plotted for each drop location.

Figure 4 contains the HIC data from Figure 3 plotted as a function of playground structure fall height. Data from five playgrounds with surfaces made of wood chips/engineered wood fiber are included. Both sets of data show increasing HIC with increasing fall height, although the increase appears to be greater for the drops on rubber. As stated in the Methods section, each structure was tested at three drop locations within the use zone. Many of the drops on rubber surfaces exceeded the HIC=1000 standard, leading to a playground structure compliance rate of 67 percent (Table 33), and an overall playground surface California regulatory compliance rate of 31 percent. There were no failures out of ten structures tested on surfaces made of wood chips.

While the data in Figure 4 show a generally greater likelihood of rubberized surfaces to fail the HIC=1000 standard at higher fall heights, a number of drops at heights up to almost twelve feet yielded values that met the standard. This demonstrates that rubber surfaces in the use zones of quite tall playground structures can be constructed to meet the standard.

The data from Figure 4 have been plotted in Figure 5 so as to show how the playground structure compliance rate decreased as the fall height increased. Only a single structure failed the HIC standard at < six feet. However, above six feet the compliance rate fell continuously up to nine feet. At structure drop heights greater than nine feet, the small number of structures makes it difficult to know the true compliance rate.

The structures failing the HIC standard are shown in Table 34, where they have been categorized according to structure type. No specific type of play structure stood out as being responsible for the failure rate observed here.

To determine whether rubberized playground surfaces failed the HIC standard at only a single location or at multiple locations, the number of failing structures per playground were plotted in Figure 6. While the largest group (ten playgrounds) contained only a single failing structure, three surfaces each contained three failing structures and two

surfaces each contained four failing structures. Clearly, some rubberized playgrounds did not comply with the HIC standard over much of their surface.

Some municipalities were able to supply the installation dates for their particular playground surfaces. Figure 7 uses these data to calculate surface age, and compare those ages to the corresponding HIC compliance rate. The small numbers of surfaces greater than two years old make those data unreliable. Comparing surfaces in their first year following installation to those in their second year, the compliance rates were not significantly different according to a 2-tailed Fisher's Exact Test, suggesting that the surfaces experienced little or no change in impact attenuation over their first two years of life. However, since other explanations are possible, we followed impact attenuation over time at the same locations in the same playgrounds.

Figures 8 and 9 show surface HIC values as a function of time, over the first two to three months of surface life. The playground represented in Figure 8 was first measured two days after installation of the top EPDM layer, while the playground in Figure 9 was first measured at four days after installation. Both surfaces were pour-in-place with bottom layers of recycled tire rubber and tops layers of EPDM. Normally, these two layers are poured on consecutive days. Thus, these data give an indication of how quickly the surfaces hardened, and to what extent the hardness changed over the first few months of surface life. Because surface hardness is affected by temperature, the air temperatures measured in the shade are presented, showing that the HIC data were collected over a relatively narrow temperature range. The data show little or no change in hardness over the first two to three months, indicating that these surfaces provide stable impact attenuation soon after they are poured, and for months thereafter. Taken together, the data in Figures 7-9 are consistent with stable impact attenuation by these surfaces for at least the first two years of surface life.

Two surfaces composed of loose-fill shredded tire rubber were also tested. One had play structures that were less than two feet high, yielding HIC values of 129 or less (data not shown). The second playground had structures up to eight feet tall. The HIC testing data for this playground are shown in Figure 10. The values fluctuated over a wide range. For example, the three testing locations for the swing set ranged from a low of 558 to a high of 2821. Also, comparing the platform values to the rings values, both tested at a fall height of 6.5 feet, the platform values were approximately three fold higher than those of the rings. Since this surface consisted of loose-fill shredded tire rubber, each drop location was inspected to determine thickness of the rubber layer. It was immediately obvious that the locations with high HIC values were spots where most of the rubber shreds had been kicked away, leaving only a relatively thin layer behind. Thus, variability in surface thickness was responsible for the variability in HIC values. We believe it likely that for pour-in-place surfaces, variability in surface thickness is also the primary cause of the variability in HIC values, as exemplified by the data in Figure 4.

As mentioned briefly above, the temperature of the pour-in-place surface had a small but reproducible effect on its HIC value. The data in Figures 11 and 12 show HIC values for three drop locations as a function of surface temperature. These data were collected in a single playground, beginning early in the morning when the temperature was cool until the last measurements were made during the heat of the day (Figure 11), or starting in the hottest part of the afternoon with measurements lasting until just after sundown (Figure 12). At all three locations, the HIC values increased with increasing temperature. The largest increases were at location #1 in Figure 11, where the HIC values increased approximately 20 percent as the surface temperature rose from 52 to 114 degrees

Fahrenheit. Counterintuitively, the surface became harder as it warmed and softer as it cooled.

To substantiate the findings regarding surface temperature, two series of drops were performed at location #1 over a range of fall heights, one at a surface temperature of 49 degrees Fahrenheit and one at 108 degrees. Figure 13 shows that the higher temperature was associated with higher HIC values at every drop height, and that the temperature effect increased with increasing fall height. Thus, the surface was consistently harder at the higher temperature. This temperature experiment was repeated at a second playground (playground II, Figure 14), over a lower range of HIC values (approximately 200 to 500) compared to playground I in Figure 13 (approximately 400 to 2000). As for playground I, every fall height in playground II gave higher HIC values when measured at the higher temperature. The smaller temperature effect in playground II may have been due to the smaller temperature difference: 36 degrees F for playground II compared to 59 degrees F for playground I. These results demonstrate the importance of controlling the temperature of these surfaces for obtaining consistent HIC values. In addition, these data indicate that testing pour-in-place surfaces for compliance with the ASTM standards is best done on warmer days rather than cooler days, to help ensure that the surface is compliant throughout the entire year.

Discussion

Extent and nature of injuries

A total of 1,299 Californians (presumably children) were admitted to California hospitals in 2003 due to fall-related playground injuries (California Department of Health Services, 2006). The USCPSC estimates that for each playground injury requiring hospitalization, there are at least 22 emergency room “treat and release” playground injuries (USCPSC, 2006). Therefore, there were an estimated $1,299 \times 22 = 28,578$ fall-related playground injuries in California in 2003 serious enough to require an emergency room visit. Thus, injury due to falls in the playground represents a significant public health problem. Furthermore, since fall-related injuries comprise about 80 percent of all playground injuries (Tinsworth and McDonald, 2001), impact-attenuating surfaces represent an effective means for reducing the playground injury rate. (Chalmers et al., 1996; Mott et al., 1997; Mowat et al., 1998).

However, care must be taken to ensure that such safety surfacing is thick enough and installed correctly to provide sufficient impact attenuation (U.S. CPSC, 1997). Various standards have been promulgated to help achieve this goal. California is one of the few states with regulatory playground surface safety standards. The Code of Regulations, sections 65700 through 65750 specify compliance with the U.S. CPSC Handbook for Public Playground Safety (Publication Number 325, 1997) and ASTM standard F1487-98 (ASTM, 1998), both of which cite ASTM standard F1292. It is F1292 (ASTM, 2004) that specifies the actual physical measures of impact attenuation ($G_{\max} \leq 200$ and $HIC \leq 1000$) and the methodology for their measurement. Prior to our work, none of the playground surfaces comprising this study had been tested after installation to determine compliance with these regulatory standards.

Development of the regulatory standard

G_{\max} is the maximum deceleration produced by contact between the falling Triax2000 headform and the surface. HIC is derived by transforming the deceleration versus time data and integrating under the curve (ASTM, 2004). Both values have a history of use by

those concerned with predicting head injury, including the automotive and airline crash test communities (Bandak et al., 1996; Nahum and Melvin, 2002) and the sports helmet industry (Camacho et al., 2001; Duma et al., 2005). However, significant uncertainty is associated with the use of these measures to predict serious head injury. This uncertainty is due to many factors, including the limited dataset used to define the relationship of G_{max} and HIC to serious head injury, and a general paucity of child head injury data. Evidence indicating that as children develop, their skulls become harder (Goldsmith and Plunkett, 2004) and their brains become more viscous (Thibault and Margulies, 1998) illustrates the difficulties raised by this gap in child head injury data. Nonetheless, ASTM standard F1292 states that a playground surface must have a G_{max} value ≤ 200 and an HIC value ≤ 1000 .

An HIC value of 1000 is associated with a risk of critical head injury from a head-first fall of from 5 percent (ASTM, 2004) to 16 percent (Prasad and Mertz, 1985). The threshold for fatal head injury has been estimated as low as HIC = 840 to as high as HIC = 1475 (Cory et al., 2001). To give an idea of how high the HIC = 1000 value is, the mean HIC value for an impact to the football helmet of an NFL player that resulted in a concussion was 400, while the blows of an Olympic boxer produced HIC values below 100 (Viano et al., 2005). ASTM F1292 states that playgrounds with surfaces not meeting the standard should be closed until the surface is brought into compliance.

G_{max} vs. HIC

Since values for G_{max} and HIC were collected for every test drop performed with the accelerometer, it was a simple matter to plot these data to study the relationship between these two parameters. Figure 3 shows that for the rubber surfaces made of recycled tires, the HIC values tended to increase faster than the G_{max} values. As a result, the HIC = 1000 standard was often exceeded while the corresponding G_{max} value remained in compliance at ≤ 200 . In fact, in no instance either on rubber or any other material did the surface pass the HIC standard pass but fail the G_{max} standard. Thus, it may well be a general finding that the HIC = 1000 standard is a more sensitive test of playground surface impact attenuation than the $G_{max} = 200$ standard.

Compliance as a function of fall height

Plotting the HIC data from Figure 2 as a function of fall height (Figure 4), there is a clear trend towards a greater HIC failure rate as the fall height increases. These data also illustrate a generally large degree of variability in the HIC values associated with any given fall height. For example, at a fall height of slightly less than eight feet, the HIC values range from less than 500 up to almost 2000. While a number of explanations are possible for these HIC failures and variability, we believe the simplest one is that of a failure to install a surface of sufficient thickness. This was shown to be the case for the loose-fill surface in Figure 10, where a rubber layer of varying thickness yielded a number of high HIC values.

This hypothesis is also supported by the finding that surfaces under some quite high play structures easily passed the HIC standard. For example, one structure just over nine feet tall yielded two drops with HIC values around 500 (Figure 4). Two structures over eleven feet tall also had surfaces that were in compliance at some or all drop locations. From these observations, we conclude that rubberized surfaces under high playground structures can be constructed to meet the HIC standard. The determining factor in surface thickness may only be cost, not technological infeasibility or absence of a performance standard.

In comparison to rubberized surfaces, surfaces of wood chips yielded HIC values that were always in compliance with the standard, and the HIC values at any given fall height appeared to vary less than those for the rubber surfaces (Figure 4). These results could be explained if wood chips were routinely installed at relatively great depth providing a high degree of impact attenuation. The approximately 10-fold lower cost of installing wood chips compared to pour-in-place rubber provides a possible reason for why municipalities might have the resources to install a surface of great depth out of wood chips but not of pour-in-place rubber.

Number and location of failures

Approximately 33 percent of all playground structures over rubber surfaces failed the HIC standard (Table 33). ASTM standard F1292 states that if a single drop location within the use zone of a single structure fails the standard, then the playground fails and should be closed until the problem is corrected. Since most playgrounds contained multiple structures, the overall failure rate of rubberized surfaces was considerably higher, at 69 percent (Table 33).

To get a better sense of whether failing surfaces were failing at only one or many locations within the playground, the numbers of failing structures per playground were plotted (Figure 6). The data show that many surfaces failed due to a single structure. Thus, correcting these inadequacies might be a cost-effective approach towards bringing these surfaces into compliance. However, other surfaces failed at multiple structures, suggesting that most if not all of the rubberized surfaces in those playgrounds were noncompliant. If, as discussed earlier, this is due to the surfaces being of insufficient thickness, a completely new and thicker surface may be required to bring these playgrounds into compliance. Alternatively, the playground structures could be lowered.

Compliance as a function of surface age

Pour-in-place surfaces made of recycled tires require considerably less day-to-day maintenance than traditional surfaces such as wood chips or sand. In addition, the unitary rubber surfaces are expected to be long lasting, with advertised useful lifetimes of 5-10 years or more. These desirable characteristics are important considerations when deciding whether to pay the relatively high cost of installing a pour-in-place surface. If the useful lifetime of these surfaces is on the order of 10 years or greater, it is important to determine if their impact attenuating properties change as a function of surface age.

For example, a surface that hardens over time in response to environmental factors could be in compliance with F1292 during the first few years following installation, but not in subsequent years. We have addressed this question by comparing the playground structure failure rate to surface age (Figure 7). Because the use of recycled tires in playground surfaces is a relatively recent development, most of the surfaces we tested were less than two years old.

Nonetheless, the failure rates were not significantly different between the first and second years post-installation, suggesting that surface hardness had not changed over this period. However, other explanations are possible. Therefore, to better address the effects of surface age, we also measured surface hardness at the same locations within the same playgrounds over the first two to three months of surface life. There was little or no change in HIC values at three locations in each of two playgrounds (Figures 8 and 9), suggesting that once these pour-in-place surfaces harden, they provide stable impact attenuation.

Discussion of the head injury standard

As mentioned above, there is much uncertainty associated with the estimate that an HIC = 1000 yields a less than 5 percent risk of critical head injury (ASTM, 2004). Much of this uncertainty stems from the small data set that was used to construct the head injury risk curve (King, 2000; Melvin and Lighthall, 2002). Since only a small subset of these data were from children, application of the HIC standard to predict child head injury is even more problematic (Goldsmith, 1981; Goldsmith and Plunkett, 2004). Thus, a surface with an HIC value that is significantly lower than 1000 may be highly desirable to provide a greater level of protection against critical head injury. In addition, a lower HIC might help protect against minor head/brain injury, which actually comprises 60-80 percent of all head injury, with unknown health consequences over the long term (Fearnside and Simpson, 1997).

An HIC value below 250 has been recommended to reduce the chance of such relatively minor brain injury (Pellman et al., 2003). Looking at the data in Figure 4, it is hard to escape the conclusion that the surfaces of wood chips currently in use in California playgrounds provide a greater margin of safety than those of pour-in-place rubber. This need not be the case, since those same data show that pour-in-place surfaces can be constructed to provide as great a margin of safety as the surfaces of wood chips.

While the HIC was developed to predict serious head injury, a recently published study by Sherker et al. (2005) indicates that reducing the HIC value of a given surface also helps reduce the risk of arm fracture. This is welcome news since arm fracture is a more common playground-related fall injury than head injury (Tinsworth and McDonald, 2001). However, the high coefficient of friction associated with pour-in-place rubber surfaces may increase the likelihood of long bone fractures relative to smoother surfaces or surfaces of loose-fill material. Further studies are needed to address these issues.

In summary, our study indicates that California surfaces made of recycled tires commonly fail to meet the HIC standard for impact attenuation specified in state regulations. It is likely that these failures resulted from installation of surfaces that were not sufficiently thick, given the heights of the play structures in the playgrounds. It seems that a relatively simple way to prevent this would be for future purchasers to require that the installer test the surface after installation, to verify that all structures in the playground had surfaces below that met the HIC standard. Given the temperature dependence of the HIC measurements, it would probably be public health protective to make the measurements on a day when the ambient temperature was near the maximum expected for that location. That testing after installation is rarely done is suggested by our finding that none of the surfaces comprising this study had been tested prior to our work.

Conclusions

- The head impact criterion (HIC) standard = 1000 was a more sensitive measure of impact attenuation by rubberized playground surfaces than the G_{\max} standard = 200.
- As the fall height of playground structures increased, the underlying rubberized playground surface was more likely to fail the HIC standard; however, even at fall heights of 9-12 feet, some rubberized surfaces passed the standard.

- Only 31 percent of rubberized playground surfaces (32 tested) passed the HIC standard below every play structure, compared to 100 percent for surfaces made of wood chips (5 tested).
- The large proportion (69 percent) of new rubberized playground surfaces in California not meeting impact attenuation standards represents a missed opportunity for prevention of playground fall injuries, which are estimated to be in the thousands and which include serious trauma such as brain injury.
- Some rubberized surfaces failed the HIC standard at multiple locations, indicating a widespread deficiency in impact attenuation for those surfaces.
- HIC values were not influenced by surface age, either during the first 2-3 months following installation or during the first 2 years.
- HIC values of rubberized surfaces increased with increasing surface temperature; in one playground the HIC value measured at dawn increased almost 20 percent when measured again in the afternoon during the heat of the day.
- These data point out the importance of testing the impact attenuation of rubberized playground surfaces following installation, to ensure that they meet the standards.
- Given the uncertainty associated with the $HIC \leq 1000$ standard, as well as the seriousness of the endpoint (critical head injury), customers should consider installing rubberized surfaces that provide as low an HIC value as possible.

Table 33. HIC standard compliance rates (HIC ≤ 1000) for playground surfaces: rubber vs wood.¹

	<u>No. tested</u>	<u>percent passing HIC standard</u>
Structures over rubber surfaces	121	67
Structures over wood surfaces	10	100
Entire rubber playground surface	32	31
Entire wood playground surface	5	100

¹Rubber surfaces were made of recycled tires and wood surfaces were made of wood chips/engineered wood fiber.

Table 34. Types of playground structures failing the HIC standard¹

	<u>No. of failing structures/No. tested</u>
Standard swings	12/22
Tot swings	8/18
Slides	4/13
Climbers	8/16
Upper body rings	6/11
Platforms	5/29

¹ A total of 121 structures were tested (these six types and other types not shown), with these 43 having at least one HIC value greater than 1000.



Figure 2: Triax2000 triaxial accelerometer.

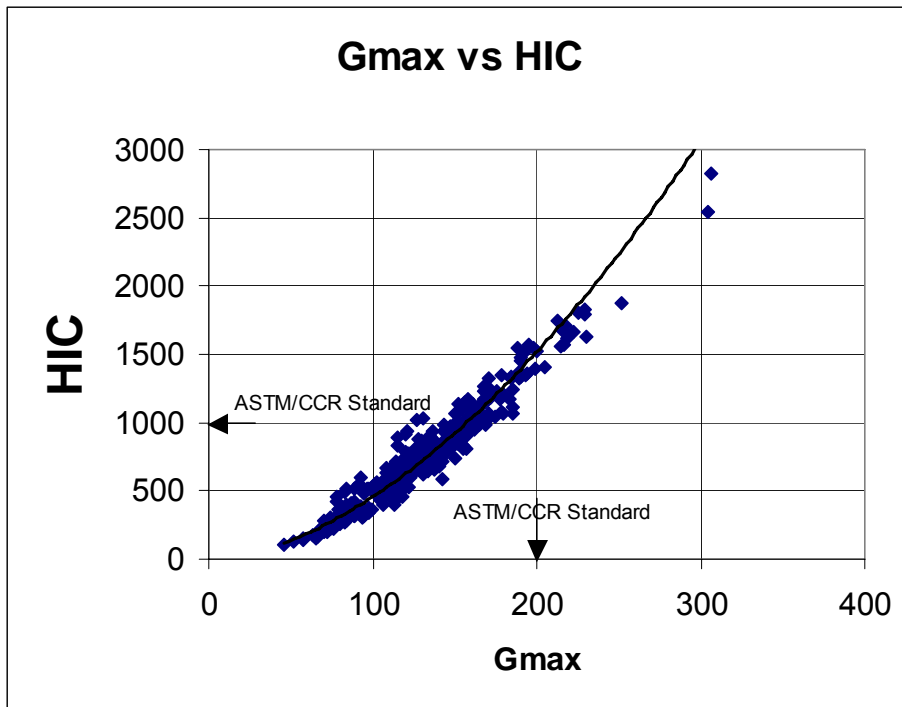


Figure 3: HIC as a function of G_{max} .

Data points represent 368 individual drop locations in 32 rubberized playground surfaces (26 pour-in-place, 4 tiles, 2 shredded rubber). The trend line was fitted by regression analysis according to a power function. ASTM/CCR standards: $G_{max} \leq 200$ and $HIC \leq 1000$.

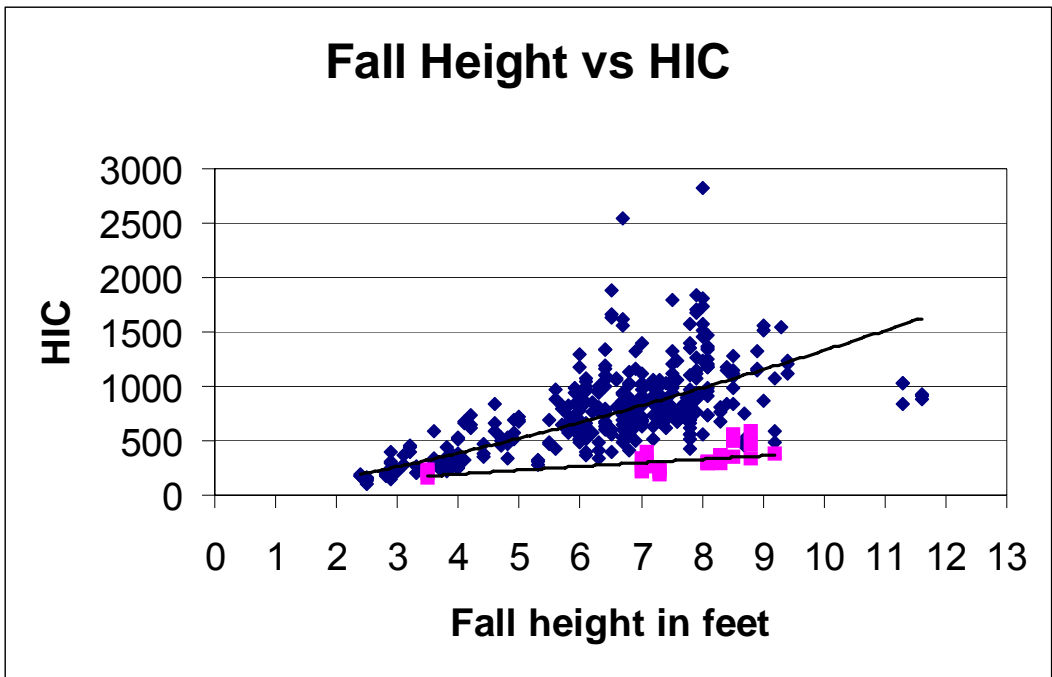


Figure 4: HIC as a function of playground structure fall height.
Data points represent individual drop locations in 32 rubberized playgrounds (diamonds) and 5 playgrounds with surfaces of wood chips/engineered wood fiber (squares). Trend lines were fitted by regression analysis according to power functions.

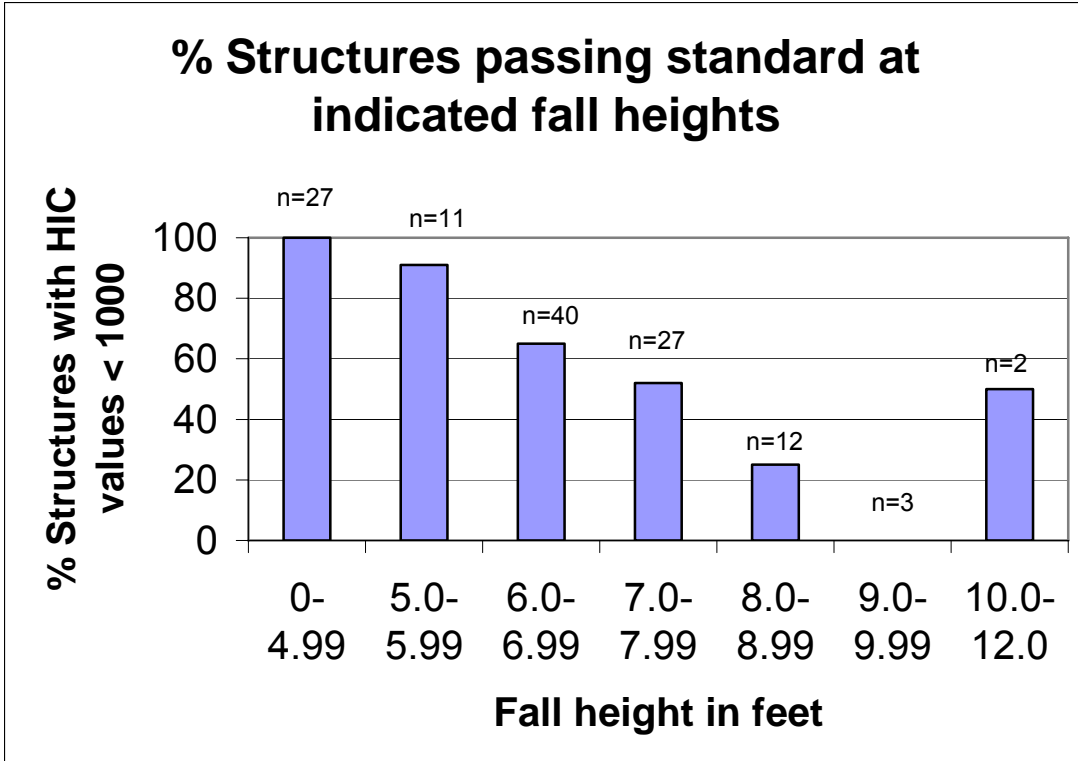


Figure 5: Percentages of playground structures on rubberized surfaces passing the HIC standard at increasing fall height.

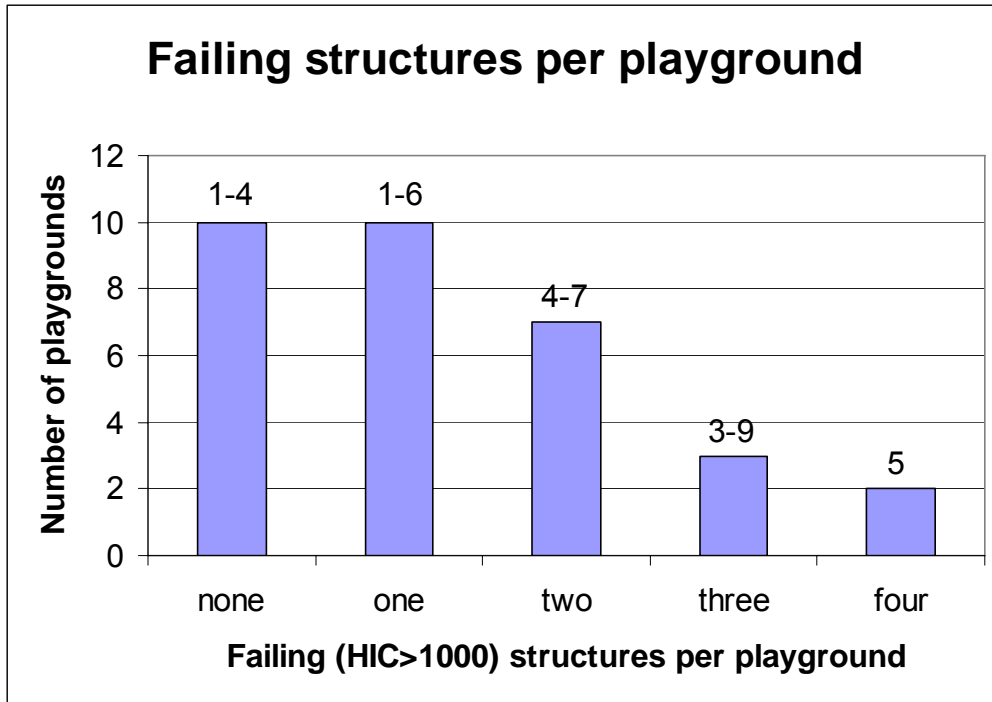


Figure 6: Numbers of failing structures (HIC > 1000) per rubberized playground surface.

A total of 131 structures in 32 playgrounds were tested. Ranges at the top of each bar indicate the numbers of structures per playground.

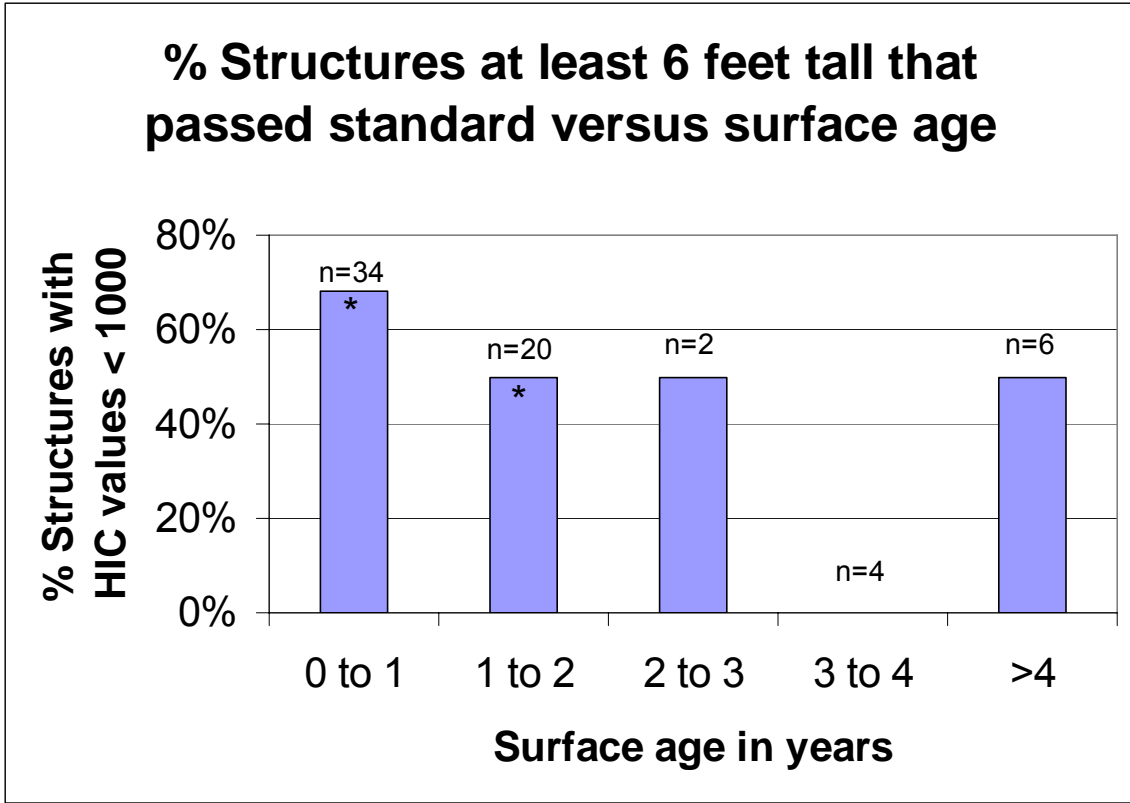


Figure 7: Percentages of playground structures with fall heights ≥ 6 feet yielding HIC values ≤ 1000 as a function of rubberized surface age.

Data from pour-in-place and tiled surfaces were included. Each n represents the total number of structures tested at the indicated surface age. Asterisks (*) indicate no significant difference between the two bars in a 2-tailed Fisher's Exact Test.

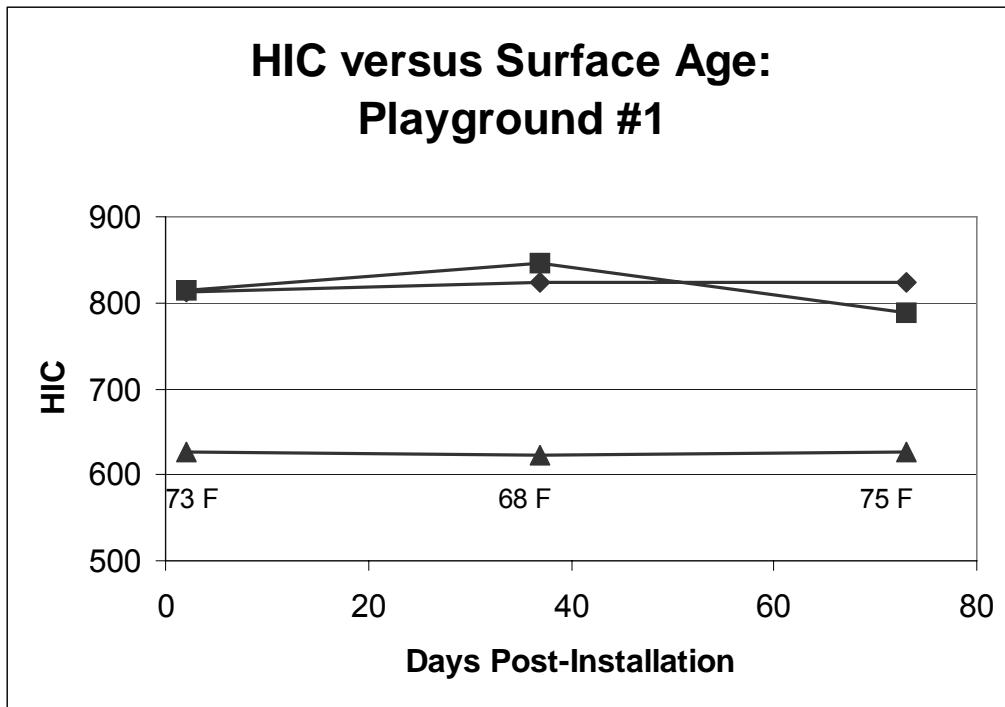


Figure 8. HIC as a function of surface age during the first two to three months following installation.

This pour-in-place playground surface consisted of a bottom layer of recycled tire rubber and a top layer of EPDM. At two days after the top layer was poured, HIC measurements were made at three locations (squares, triangles or diamonds) on the surface from a drop height of seven feet. Measurements were repeated on the indicated days at the same locations. The temperature of the air in the shade was recorded on each day as indicated on the graph.

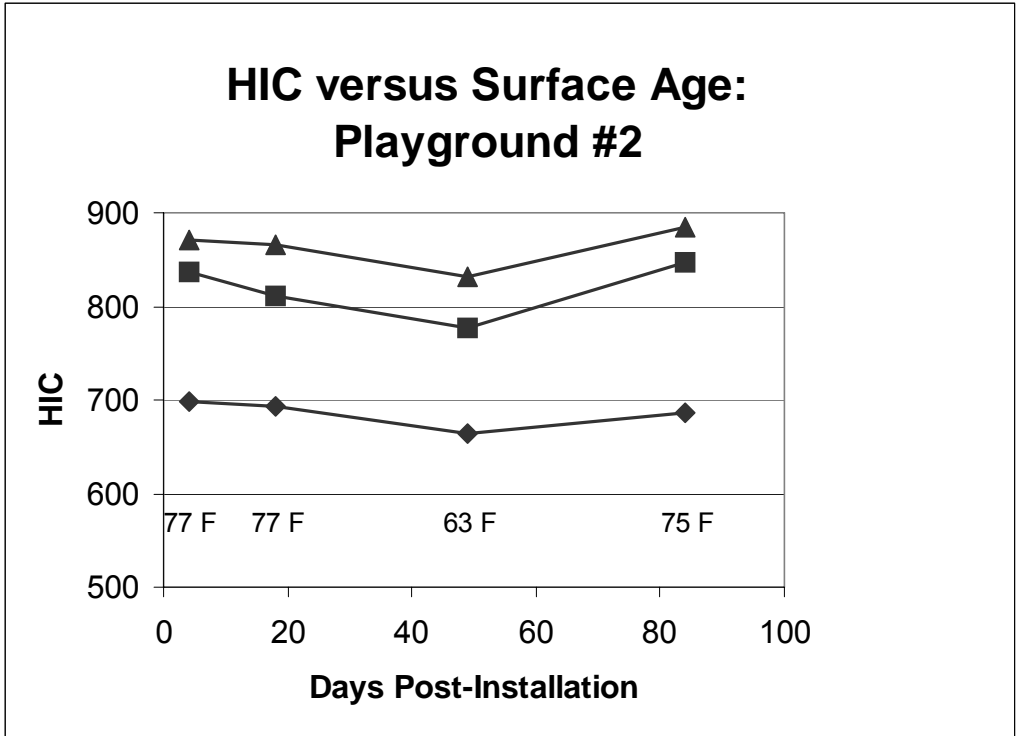


Figure 9: Same as for Figure 8, except that for this playground the first measurement day was at four days after installation of the top layer.

Three different locations on the playground were followed, represented by the squares, triangles or diamonds.

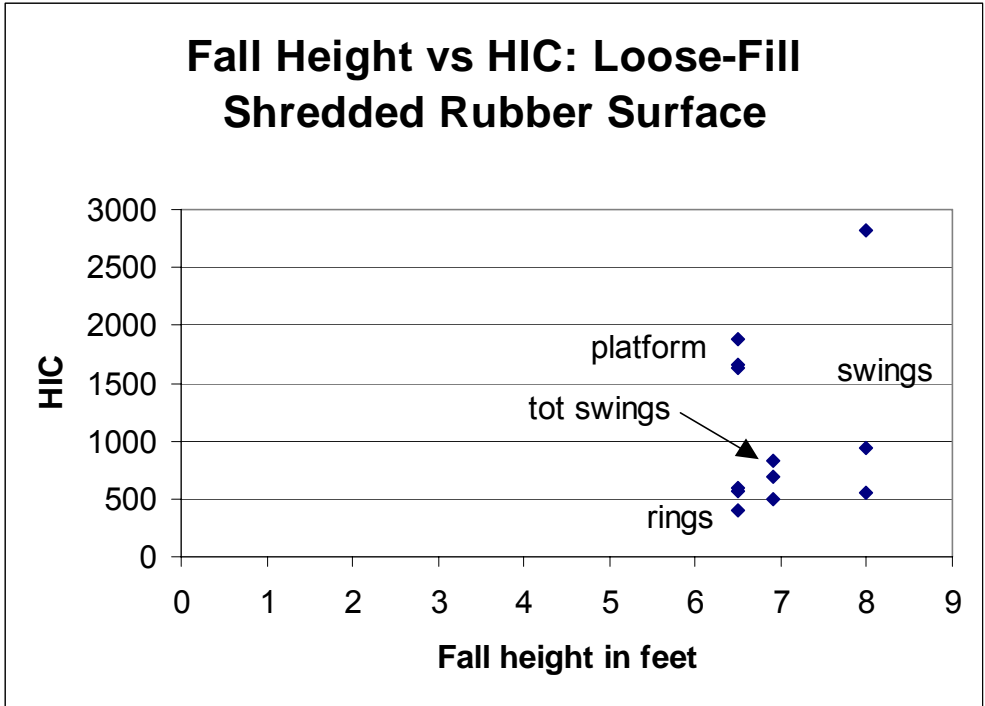


Figure 10: HIC values for four playground structures on a loose-fill surface of shredded tire rubber.

Each datum point represents the HIC value for one of three drop locations around each playground structure.

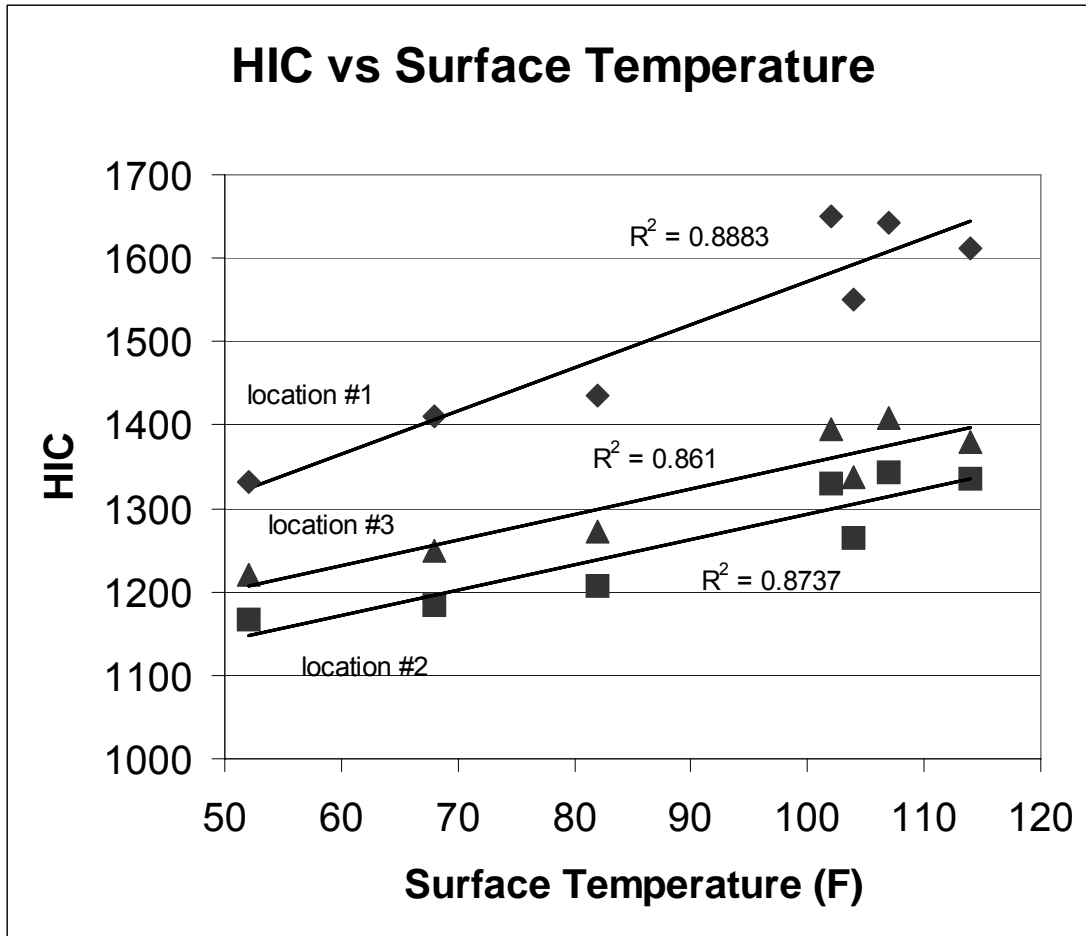


Figure 11: Temperature dependence of HIC measurements on a pour-in-place surface: cold to hot.

HIC measurements were made at three locations in a single playground. The drop height was seven feet. Measurements began at 8:00 am in the coolest part of the day, and finished at 2:00 pm during the heat of the day. Curves were fit by linear regression and correlation coefficients are also shown.

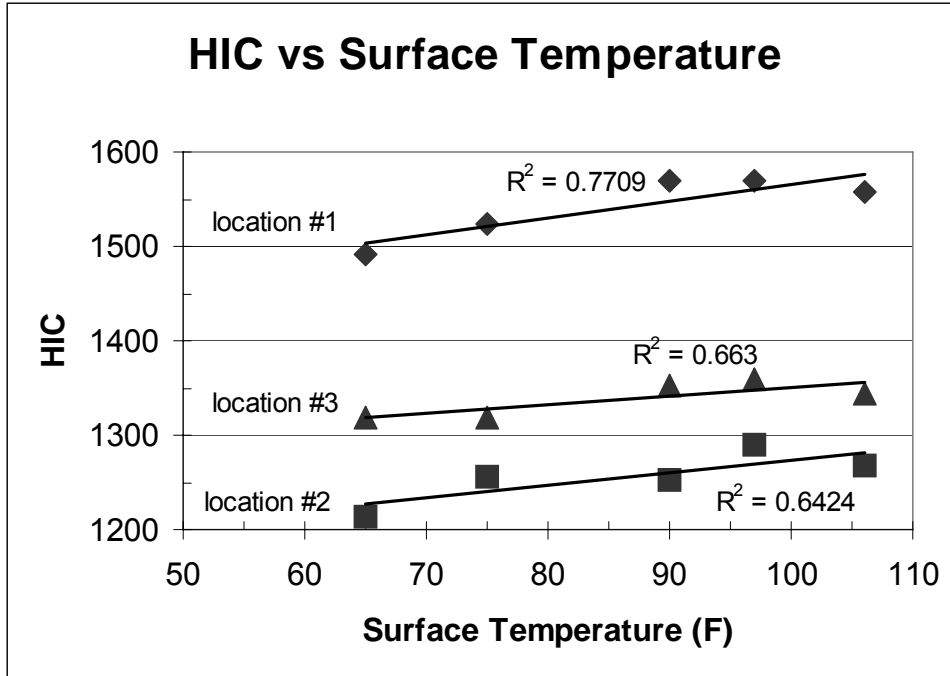


Figure 12: Temperature dependence of HIC measurements on a pour-in-place surface: hot to cold.

Same playground and protocol as for Figure 11 except that measurements began at 3:00 pm during the heat of the day and ended at sundown at 7:20 pm. Curves were fit by linear regression and correlation coefficients are also shown.

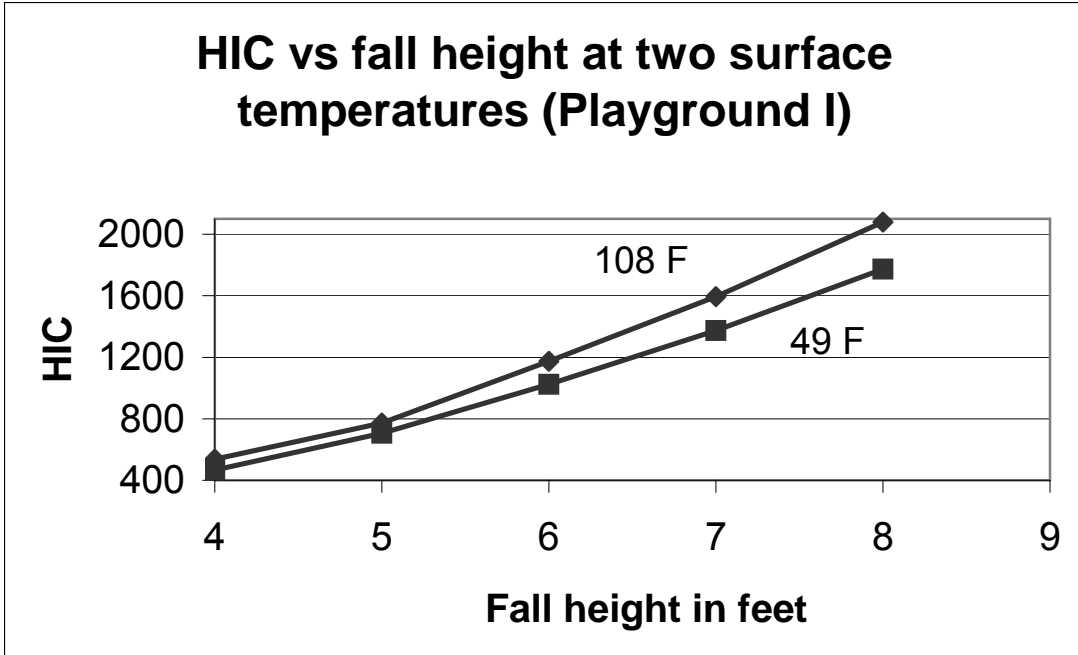


Figure 13: HIC as a function of fall height measured at two different surface temperatures: Playground I.

Drops were performed at the same location #1 shown in Figures 11 and 12. The drops at 108 degrees Fahrenheit were performed during the heat of the day at 2:00 pm, while the drops at 49 degrees Fahrenheit were performed shortly after sunrise at 7:45 am.

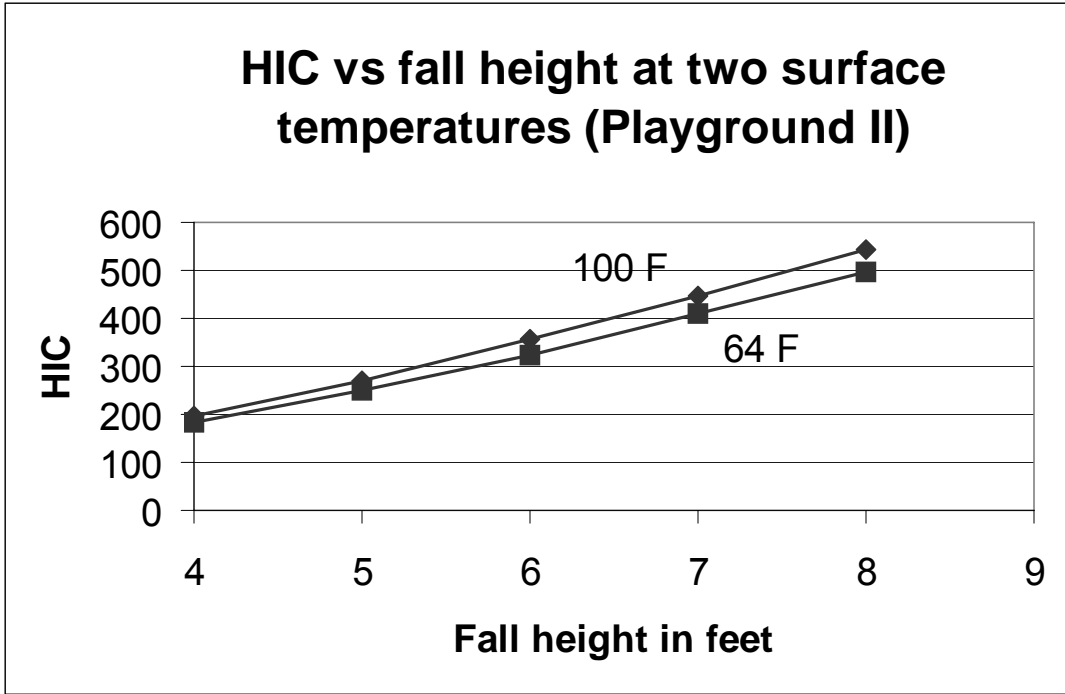


Figure 14: HIC as a function of fall height measured at two different surface temperatures: Playground II.

Drops were performed at the same location on two different days, with the surface temperature varying by 36 degrees F between.

Abbreviations

ASTM	American Society for Testing and Materials International
ATSDR	Agency for Toxic Substances and Disease Registry
C	Centigrade
CCA	Chromated Copper Arsenate
CDC	Centers for Disease Control
cm ²	square centimeters
CIWMB	California Integrated Waste Management Board
DOT	Department of Transportation
DTSC	Department of Toxic Substances Control
EPDM	ethylene propylene diene monomer
F	Fahrenheit
FCCJNC	Florida Community College at Jacksonville Nassau Center
FDA	Food and Drug Administration
g	grams
GCMS-SIM	Gas chromatography mass spec selective ion monitoring
G _{max}	maximum acceleration during impact
GRAS	Generally recognized as safe
HCA	alpha-Hexylcinnamaldehyde
HD	high density
HIC	Head impact criterion
hr	hour
IARC	International Agency for Research on Cancer
IRIS	Integrated Risk Information System
kg	kilogram (approximately 2.2 pounds)
kg-d	kilograms per day
l	liter
LD ₅₀	Lethal dose 50 percent
LOAEL	Lowest observed adverse effect level
m ²	square meters
m ³	cubic meters
MADL	Maximum Allowable Dose Level
mg	milligram

ml	milliliter
mM	millimolar
MRL	Minimal Risk Level
n	number
NAS	National Academy of Sciences
ND	not detected
ng	nanogram (10^{-9} grams)
NOAEL	No observed adverse effect level
NRC	National Research Council
NSRL	No Significant Risk Level
NTP	National Toxicology Program
OEHHA	Office of Environmental Health Hazard Assessment
OSHA	Occupational Safety and Health Administration
PAH	polycyclic aromatic hydrocarbon
PEL	Permissible Exposure Limit
pg	picogram (10^{-12} grams)
PHG	Public Health Goal
ppb	parts per billion
ppm	parts per million
PRG	Preliminary Remediation Goal
RDA	Recommended Daily Allowance
REL	Reference Exposure Level
RfC	Reference concentration
RfD	Reference dose
SBR	styrene butadiene rubber
SF	safety factor
SOD	superoxide dismutase
sVOC	semi-volatile organic compound
UF	uncertainty factor
µg	microgram (10^{-6} grams)
ul	microliter (10^{-6} liters)
U.S. CPSC	United States Consumer Products Safety Commission
U.S. EPA	United States Environmental Protection Agency
VOC	volatile organic compound

Bibliography

1. Adolph, K., Vereijken, B. and Denny, M. (1998) Learning to crawl. *Child Devel* 69: 1299-1312.
2. Agren, M.S. (1990) Percutaneous absorption of zinc from zinc oxide applied topically to intact skin in man. *Dermatologica* 180: 36-39.
3. Agren, M.S., Krusell, M. and Franzen, L. (1991) Release and absorption of zinc from zinc oxide and zinc sulfate in open wounds. *Acta Derm Venereol (Stockh)* 71: 330-333.
4. Air Resources Board, CA EPA (1991) Study of children's activity patterns. Contract No. A733-149, Final Report, September, 1991.
5. Al-Tabbaa, A. and Aravinthan, T. (1998) Natural clay-shredded tire mixtures as landfill barrier materials. *Waste Management* 18: 9-16.
6. Altmann, A., Ashby, K. and Stathakis, V. (1996) Childhood injuries from playground equipment. *Hazard* 29: 1-12.
7. Amoozegar, A. and Robarge, W.P. (undated) Evaluation of tire chips as a substitute for gravel in the trenches of septic systems. Final Report submitted to: Division of Pollution Prevention and Environmental Assistance, Department of Environment and Natural Resources and the Chatham County Board of Commissioners.
8. Anthony, D.H.J. and Latawiec (1993) A preliminary chemical examination of hydrophobic tire leachate components. National Water Research Institute, Burlington, Ontario, Canada, Report No. 93-78.
9. Anthony, D.H.J., Latawiec, A., Hartwell, S.I. and Jordahl, D.M. (1995) a spectrometric and chromatographic chemical comparison of solvent extracts of whole tire leachate and of shredded tire leachates obtained at varying salinity. National Water Research Institute, Burlington, Ontario, Canada, Report No. 95-112.
10. Aoyama, H., Izawa, Y., Nishizaki, A., Sunada, H. and Okuda, J. (1986) Studies on systemic absorption of tobramycin in polyethylene glycol ointment applied to wounds of burn patients. *Burns Incl Therm Inj.* 12: 153-160.
11. ASTM (1998) Standard consumer safety performance specification for playground equipment for public use, Designation F 1487-98, American Society of Testing and Materials, West Conshohocken, PA.
12. ASTM (2004) Standard specification for impact attenuation of surfacing materials within the use zone of playground equipment, Designation F 1292-04, American Society for Testing and Materials International, West Conshohocken, PA.
13. ATSDR (1990) Toxicological profile for 1,1-dichloroethane. <http://www.atsdr.cdc.gov/toxprofiles/tp133.html> accessed 1/04.
14. ATSDR (1992a) Toxicological profile for 2-butanone. <http://www.atsdr.cdc.gov/toxprofiles/tp29.html> accessed 1/04.
15. ATSDR (1992b) Toxicological profile for styrene. <http://www.atsdr.cdc.gov/toxprofiles/tp53.html> accessed 1/04.
16. ATSDR (1992c) Toxicological profile for vanadium. <http://www.atsdr.cdc.gov/toxprofiles/tp58.html> accessed 4/05.
17. ATSDR (1994) Toxicological profile for acetone. <http://www.atsdr.cdc.gov/toxprofiles/tp21.html> accessed 1/04.
18. ATSDR (1995) Toxicological profile for polycyclic aromatic hydrocarbons. www.atsdr.cdc.gov/toxprofiles/tp69.html accessed 10/04.
19. ATSDR (1996) Toxicological profile for 1,2-dichloroethene. <http://www.atsdr.cdc.gov/toxprofiles/tp87.html> accessed 1/04.
20. ATSDR (1997a) Toxicological profile for benzene. <http://www.atsdr.cdc.gov/toxprofiles/tp3.html> accessed 1/04.
21. ATSDR (1997b) Toxicological profile for trichloroethylene. <http://www.atsdr.cdc.gov/toxprofiles/tp19.html> accessed 1/04.
22. ATSDR (1998) Toxicological profile for phenol. <http://www.atsdr.cdc.gov/toxprofiles/tp115.html> accessed 2/04.
23. ATSDR (1999a) Toxicological profile for aluminum. <http://www.atsdr.cdc.gov/toxprofiles/tp22.html> accessed 1/04.
24. ATSDR (1999b) Toxicological profile for cadmium. <http://www.atsdr.cdc.gov/toxprofiles/tp5.html> accessed 2/04.

25. ATSDR (1999c) Toxicological profile for lead. <http://www.atsdr.cdc.gov/toxprofiles/tp13.html> accessed 1/04.
26. ATSDR (1999d) Toxicological profile for mercury. <http://www.atsdr.cdc.gov/toxprofiles/tp46.html> accessed 2/04.
27. ATSDR (2000a) Toxicological profile for arsenic. <http://www.atsdr.cdc.gov/toxprofiles/tp2.html> accessed 2/04.
28. ATSDR (2000b) Toxicological profile for manganese. <http://www.atsdr.cdc.gov/toxprofiles/tp151.html> accessed 11/03.
29. ATSDR (2000c) Toxicological profile for toluene. <http://www.atsdr.cdc.gov/toxprofiles/tp56.html> accessed 1/04.
30. ATSDR (2000d) Toxicological profile for chromium. <http://www.atsdr.cdc.gov/toxprofiles/tp7.html> accessed 4/06.
31. ATSDR (2002) Toxicological profile for copper. <http://www.atsdr.cdc.gov/toxprofiles/tp132.html>, accessed 12/03.
32. ATSDR (2003a) Toxicological profile for selenium. <http://www.atsdr.cdc.gov/toxprofiles/tp92.html> accessed 8/04.
33. ATSDR (2003b) Toxicological profile for zinc. <http://www.atsdr.cdc.gov/toxprofiles/tp60.html>, accessed 11/03.
34. ATSDR (2004) Medical management guidelines for benzene. <http://www.atsdr.cdc.gov/MHMI/mmg3.html> accessed 8/04.
35. ATSDR (2004b) Toxicological profile for cobalt. <http://www.atsdr.cdc.gov/toxprofiles/tp33.html> accessed 4/05.
36. ATSDR (2005) Toxicological profile for naphthalene, 1-methylnaphthalene, and 2-methylnaphthalene. <http://www.atsdr.cdc.gov/toxprofiles/tp67.html> accessed 11/05.
37. ATSDR (2005b) Toxicological profile for barium. <http://www.atsdr.cdc.gov/toxprofiles/tp24.html> accessed 4/06.
38. ATSDR (2005c) Toxicological profile for lead. <http://www.atsdr.cdc.gov/toxprofiles/tp13.html> accessed 4/06.
39. ATSDR (2005d) Toxicological profile for zinc. <http://www.atsdr.cdc.gov/toxprofiles/tp60.html> accessed 4/06.
40. Australian Government (2004) National Dioxins Program, Technical Report No. 5, Dioxins in Soil in Australia.
41. Au Yeung, W., Canales, R., Beamer, P., Ferguson, A. and Leckie, J. (2004a) Young children's hand contact activities, poster, annual meeting of the International Society for Environmental Epidemiology, Johannesburg, South Africa.
42. Au Yeung, W., Canales, R., Beamer, P., Ferguson, A. and Leckie, J. (2004b) Young children's mouthing behavior: an observational study via videotaping in a primarily outdoor residential setting. *J Children's Health* 2: 1-25.
43. Bandak, F., Eppinger, R. and Ommaya, A. Eds. (1996) *Traumatic Brain Injury*, Bioscience and Mechanics. Mary ann Liebert Inc., Larchmont, New York.
44. BAS Recycling Inc. (1993) Material Safety Data Sheet for crumb rubber, 1400 North H Street, San Bernardino, CA, 92405-4316.
45. Basel Convention on the Control of Transboundary Movements of Hazardous Wastes and Their Disposal (1999) Technical guidelines on hazardous wastes: Identification and management of used tyres. Basel Convention Series/SBC No: 99/008, Geneva, October 1999.
46. Bayley, N. (1936) *The California Infant Scale of Motor Development, Birth to Three Years*; University of California Press, Berkeley, CA.
47. Beamer, P., Ferguson, A.C., Canales, R.A., Yeung, W.A., M.E. Key and J.O. Leckie (2004) Analysis of a child's mobility on their micro-level activity pattern. Abstract, International Society of Exposure Analysis 14th Annual Conference, October 17-21, 2004, Philadelphia, PA.
48. Bertholf, R.L. (1988) Zinc. In: *Handbook on Toxicity of Inorganic Compounds* (Seiler, H.G. and Sigel, H., Eds.) Marcel Dekker Inc., New York, pp. 787-800.
49. Bertocci, G., Pierce, M., Deemer, E., Aguel, F., Janosky, J. and Vogeley, E. (2003) Using test dummy experiments to investigate pediatric injury risk in simulated short-distance falls. *Arch Pediatr Adolesc Med* 157: 480-486.
50. Birkholz, D., Belton, K. and Guidotti, T. (2003) Toxicological evaluation for the hazard assessment of tire crumb for use in public playgrounds. *J. Air & Waste Manage. Assoc.* 53: 903-907.

51. Bjorklid-Chu, P. (1977) A survey of children's outdoor activities in two modern housing areas in Sweden. In: *Biology of Play*, Tizard, B. and Harvey, D., Eds., Spastics International Medical Publications, London.
52. Black, K., Shalat, S.L., Freeman, N.C., Jimenez, M., Donnelly, K.C. and Calvin, J.A. (2004) Children's mouthing and food-handling behavior in an agricultural community on the US/Mexico border. *J Expo Anal Environ Epidemiol* 15: 244-251.
53. Boniak, R., Chong, S., Ok, C.H. and Diesburg, K.L. (2001) Rootzone mixes amended with crumb rubber-field study. *Inter. Turfgrass Soc. Res. J.* 9: 487-492.
54. Bottos, M., Dalla Barba, B., Stefani, D., Pettena, G., Tonin, C. and D'Este, A. (1989) Locomotor strategies preceding independent walking: prospective study of neurological and language development in 424 cases. *Devel Med Child Neurol* 31: 25-34.
55. Briss, P., Sacks, J., Addiss, D., Kresnow, M. and O'Neil, J. (1995) Injuries from falls on playgrounds. *Arch Pediatr Adolesc Med* 149: 906-911.
56. Brunmark, P., Bruze, M., Skerfving, S. and Skarping, G. (1995) Biomonitoring of 4,4'-methylene dianiline by measurement in hydrolysed urine and plasma after epicutaneous exposure in humans. *Int. Arch. Occup. Environ. Health* 67: 95-100.
57. Buehler, E.V. (1994) Occlusive patch method for skin sensitization in guinea pigs: The Buehler method. *Fd. Chem. Toxic.* 32: 97-101.
58. California Department of Health Services (2006) www.dhs.ca.gov/EPICenter accessed 2/06.
59. California Regional Water Quality Control Board (2003) *Screening for Environmental Concerns at Sites with Contaminated Soil and Groundwater. Volume 1: Summary Tier 1 Lookup Tables*, updated 2/4/04.
60. Centers for Disease Control (2005) *Playground Injuries Fact Sheet*; accessed 12/19/05 at www.cdc.gov/ncipc/factsheets/playgr.htm
61. Chalmers, D., Marshall, S., Langley, J., Evans, M., Brunton, C., Kelly, A. and Pickering, A. (1996) Height and surfacing as risk factors for injury in falls from playground equipment: a case-control study. *Injury Prevention* 2: 98-104.
62. Chang, F., Lin, T., Huang, C., Chao, H., Chang, T. and Lu, C. (1999) Emission characteristics of VOCs from athletic tracks. *J. Hazard. Mater.* A70: 1-20.
63. Chien, Y., Ton, S., Lee, M., Chia, T., Shu, H. and Wu, Y. (2003) Assessment of occupational health hazards in scrap-tire shredding facilities. *Science Total Environ.* 309: 35-46.
64. CIWMB (1996) *Effects of waste tires, waste tire facilities, and waste tire projects on the environment. Publication # 432-96-029.*
65. CIWMB (2004) *Construction completion report for the Yulupa Elementary School tire chip fire, prepared by Todd Thalhamer.*
66. CIWMB (2006) *California Waste Tire Generation, Markets, and Disposal: 2004 Staff Report, California Integrated Waste Management Board.*
67. Cohen Hubal, E., Sheldon, L., Burke, J., McCurdy, T., Berry, M., Rigas, M., Zartarian, V. and Freeman, N. (2000) Children's exposure assessment: a review of factors influencing children's exposure, and the data available to characterize and assess that exposure. *Environ Health Perspect* 108: 475-486.
68. Cohen Hubal, E., Suggs, J., Nishioka, M. and Ivancic, W. (2005) Characterizing residue transfer efficiencies using a fluorescent imaging technique. *J Exp Anal Environ Epidemiol* 15: 261-270.
69. Comacho, D., Nightingale, R. and Myers, B. (2001) The influence of surface padding properties on head and neck injury risk. *J Biomech Engineer* 123: 432-439.
70. Cory, C.Z., Jones, M.D., James, D.S., Leadbeatter, S. and Nokes, L.D.M. (2001) The potential and limitations of utilizing head impact injury models to assess the likelihood of significant head injury in infants after a fall. *Forensic Sci Int* 123: 89-106.
71. Cratty, B. (1979) *Perceptual and Motor Development in Infants and Children*, Prentice-Hall Inc., Englewood Cliffs, New Jersey.
72. Cuddihy, T.G., Hall, R.P. and Griffith, W.C. (1974) Inhalation exposures to barium aerosols: physical, chemical, and mathematical analysis. *Health Phys.* 26: 405-416.
73. Day, K., Holtze, K., Metcalfe-Smith, J., Bishop, C. and Dutka, B. (1993) Toxicity of leachate from automobile tires to aquatic biota. *Chemosphere* 27: 665-675.
74. Department of Trade and Industry (UK) (2002) *Research into the mouthing behaviour of children up to 5 years old. Consumer and Competition Policy Directorate*, accessed in 2/05 at www.dti.gov.uk/homesafetynetwork/ck_rmout.htm

75. Duma, S., Manoogian, S., Bussone, W., Brolinson, P., Goforth, M., Donnenwerth, J., Greenwald, R., Chu, J. and Crisco, J. (2005) Analysis of real-time head accelerations in collegiate football players. *Clinical J Sports Medicine* 15: 3-8.
76. Edil, T.B., Park, J.K. and Kim, J.Y. (2003) Effectiveness of scrap tire chips as sorptive drainage material. *J. Environ. Engineer.*, in press.
77. Efrogmson, R., Suter, G., Sample, B. and Jones, D. (1997) Preliminary remediation goals for ecological endpoints. Report ES/ER/TM-162/R2, Oak Ridge National Laboratory, Oak Ridge, Tennessee.
78. Exponent (2003) Tire shred leachate study: Chemical composition and aquatic toxicity for above- and below-water-table applications. Exponent, Oakland, CA.
79. Fearnside, M.R. and Simpson, D.A. (1997) Epidemiology. In: *Head Injury* (Reilly, P. and Bullock, R., Eds.) Chapman & Hall, London, pp. 3-23.
80. Fischer, P.W., Giroux, A. and L'Abbe, M.R. (1984) Effect of zinc supplementation on copper status in adult man. *Am. J Clin. Nutr.* 40: 743-746.
81. Flarend, R., Bin, T., Elmore, D. and Hem, S.L. (2001) A preliminary study of the dermal absorption of aluminium from antiperspirants using aluminium-26. *Food Chem. Toxicol.* 39: 163-168.
82. Florida Community College at Jacksonville Nassau Center (1999) Study of the suitability of ground rubber tire as a parking lot surface, prepared for: State of Florida Department of Environmental Protection.
83. Florida Department of Environmental Protection (1999) Representative Summary of Scrap Tire Leaching Data. Prepared by T.A.G. Resource Recovery.
84. Freeman, N.C.G., Jimenez, M., Reed, K.J., Gurunathan, S., Edwards, R.D., Roy, A., Adgate, J.L., Pellizari, E.D., Quackenboss, J., Sexton, K. and Liroy, P.J. (2001) Quantitative analysis of children's microactivity patterns: The Minnesota Children's Pesticide Exposure Study. *J Exposure Anal Environ Epidemiol* 11: 501-509.
85. Freeman, N., Black, K., Rodriguez, M., Donnelly, K. and Shalat, S. (2005) Characterizing indoor/outdoor activity patterns of young children, poster, annual meeting of the International Society of Exposure Analysis, Tucson, Arizona.
86. Fukuzaki, N., Yanaka, T. and Urushiyama, Y. (1986) Effects of studded tires on roadside airborne dust pollution in Niigata, Japan. *Atmosph. Environ.* 20: 377-386.
87. Gallup Organization (2003) Quality of community playgrounds. Submitted to KaBoom!, 333 South Wabash Ave., Suite 165, Chicago, IL, April, 2003.
88. Gualtieri, M., Andrioletti, M., Vismara, C., Milani, M. and Camatini, M. (2005) Toxicity of tire debris leachates. *Environ Inter* 31: 723-730.
89. Goldsmith, W. (1981) Current controversies in the stipulation of head injury criteria. *J Biomech* 14: 883-884.
90. Goldsmith, W. and Plunkett, J. (2004) A biomechanical analysis of the causes of traumatic brain injury in infants and children. *Am. J Foren. Med. Pathol.* 25: 89-100.
91. Goyer, R.A. (1988) Lead. In: *Handbook on Toxicity of Inorganic Compounds* (Seiler, H.G. and Sigel, H., Eds.) Marcel Dekker Inc., New York, pp. 359-382.
92. Goyer, R.A. (1996) Toxic effects of metals. In: *Casarett and Doull's Toxicology, The Basic Science of Poisons, Fifth Edition* (Klaassen, C.D. Ed.) McGraw-Hill, New York, pp. 691-736.
93. Groenevelt, P. and Grunthal, P. (1998) Utilisation of crumb rubber as a soil amendment for sports turf. *Soil & Tillage Res* 47: 169-172.
94. Gunter, M., Edil, T.B., Benson, C.H. and Park, J.K. (undated) The environmental suitability of scrap tire chips in environmental and civil engineering applications: A laboratory investigation. Report from the Department of Civil and Environmental Engineering, University of Wisconsin, Madison.
95. Guyton, A.C. and Hall, J.E. (2000) *Textbook of Medical Physiology*, Tenth Edition, W.B. Saunders Company, Philadelphia.
96. Halasa, A., Hsu, W., Austin, L. and Jasiunas, C. (2003) Process for synthesizing trans polydiene rubber. U.S. Patent and Trademark Office, Patent # 6,608,154.
97. Hale, W.E., May, F.E., Thomas, R.G., Moore, M.T. and Stewart, R.B. (1988) Effect of zinc supplementation on the development of cardiovascular disease in the elderly. *J Nutr. Elder.* 8: 49-57.
98. Hamula, C., Wang, Z., Kwon, E., Li, X., Gabos, S. and Le, X. (2006) Chromium on the hands of children after playing in playgrounds built from chromated copper arsenate (CCA)-treated wood. *Environ Health Perspect* 114: 460-465.

99. Hartwell, S., Jordahl, D., Dawson, C. and Ives, A. (1998) Toxicity of scrap tire leachates in estuarine salinities: Are tires acceptable for artificial reefs? *Transactions American Fisheries Society* 127: 796-806.
100. Hazardous Substances Data Bank (2004) Aniline. <http://toxnet.nlm.nih.gov/cgi-bin/sis/search/f?/.temp/~l8sQsn:1> accessed 8/04.
101. Hazardous Substances Data Bank (2006a) Iron compounds. <http://toxnet.nlm.nih.gov/cgi-bin/sis/search/f?/.temp/~Qqlonc:1> accessed 4/06.
102. Hazardous Substances Data Bank (2006b) Manganese, elemental. <http://toxnet.nlm.nih.gov/cgi-bin/sis/search/f?/.temp/~kji519:1> accessed 4/06.
103. Hazardous Substances Data Bank (2006c) Captan. <http://toxnet.nlm.nih.gov/cgi-bin/sis/search/f?/.temp/~JbkaxD:1> accessed 4/06.
104. Hazardous Substances Data Bank (2006d) Chrysene. <http://toxnet.nlm.nih.gov/cgi-bin/sis/search/f?/.temp/~rc0eDA:1> accessed 4/06.
105. Hazardous Substances Data Bank (2006e) Fluoranthene. <http://toxnet.nlm.nih.gov/cgi-bin/sis/search/f?/.temp/~14UPSj:1> accessed 4/06.
106. Hazardous Substances Data Bank (2006f) Naphthalene. <http://toxnet.nlm.nih.gov/cgi-bin/sis/search/f?/.temp/~dWKke0:1> accessed 4/06.
107. Hazardous Substances Data Bank (2006g) Phenanthrene. <http://toxnet.nlm.nih.gov/cgi-bin/sis/search/f?/.temp/~9WZPyN:1> accessed 4/06. <http://toxnet.nlm.nih.gov/cgi-bin/sis/search/f?/.temp/~9WZPyN:1>
108. Hazardous Substances Data Bank (2006h) Pyrene. <http://toxnet.nlm.nih.gov/cgi-bin/sis/search/f?/.temp/~VGN1Cz:1> accessed 4/06.
109. Hazardous Substances Data Bank (2006i) Toluene. <http://toxnet.nlm.nih.gov/cgi-bin/sis/search/f?/.temp/~LYVc9W:1> accessed 4/06.
110. Hildemann, L.M., Markowski, G.R. and Cass, G.R. (1991) Chemical composition of emissions from urban sources of fine organic aerosol. *Environ. Sci. Technol.* 25: 744-759.
111. Horner, J.M. (1996) Environmental health implications of heavy metal pollution from car tires. *Reviews Environ. Health* 11: 175-178.
112. Hubal, E.A., Sheldon, L.S., Burke, J.M., McCurdy, T.R., Berry, M.R., Rigas, M.L., Zartarian, V.G. and Freeman, N.C. (2000) Children's exposure assessment: A review of factors influencing children's exposure, and the data available to characterize and assess that exposure. *Env. Health Persp.* 108: 475-486.
113. Huber, R. (2001) *Playground Surfacing U.S. Standards & Practices*, Canadian Playground Advisory, Inc., 2344 Manor House Court, Mississauga, Ontario, Canada L5M 5Y3.
114. Humphrey, D.N. (1999) Water quality results for Whitter Farm Road tire shred field trial. Report from the Department of Civil and Environmental Engineering, University of Maine, Orono, ME.
115. Humphrey, D.N. and Katz, L.E. (2000) Five-year study of the water quality effects of tire shreds placed above the water table. Transportation Research Board, 79th Annual Meeting, January 9-13, 2000, Washington, D.C., Paper No. 00-0892.
116. Humphrey, D.N. and Katz, L.E. (2001) Field study of water quality effects of tire shreds placed below the water table. Proceedings of the Conference on Beneficial Use of Recycled Materials in Transportation Applications, Air and Waste Management Association, Pittsburgh, PA.
117. IARC (1982) IARC Monographs on the evaluation of the carcinogenic risk of chemicals to humans. Vol. 27: p. 51.
118. IARC (1994) Styrene; <http://www-cie.iarc.fr/htdocs/monographs/vol60/m60-06.htm> accessed 1/04.
119. Institute of Medicine (2002) Dietary Reference Intakes (DRIs) for vitamin A, vitamin K, arsenic, boron, chromium, copper, iodine, iron, manganese, molybdenum, nickel, silicon, vanadium and zinc. National Academy Press, Washington, DC, pp. 357-378.
120. IRIS (1987) Cyclohexanone. <http://www.epa.gov/iris/subst/0219.htm> accessed 4/05.
121. IRIS (1989) Captan (1H-isoindole-1,3(2H)-dione). <http://epa.gov/iris/subst/0018.htm> accessed 4/05.
122. IRIS (1990a) Styrene. <http://www.epa.gov/iris/subst/0104.htm> accessed 1/04.
123. IRIS (1990b) Fluoranthene. <http://www.epa.gov/iris/subst/0444.htm> accessed 10/05.
124. IRIS (1990c) Phenanthrene. <http://www.epa.gov/iris/subst/0459.htm> accessed 10/05.
125. IRIS (1991a) Copper. <http://www.epa.gov/iris/subst/0368.htm> accessed 12/03.
126. IRIS (1991b) Pyrene. <http://www.epa.gov/iris/subst/0445.htm> accessed 10/05.

127. IRIS (1992) Zinc and compounds. <http://www.epa.gov/iris/subst/0426.htm> accessed 11/03.
128. IRIS (1993a) Lead and compounds (inorganic). <http://www.epa.gov/iris/subst/0277.htm> accessed 1/04.
129. IRIS (1993b) Selenium and compounds. <http://www.epa.gov/iris/subst/0472.htm> accessed 8/04.
130. IRIS (1993c) Molybdenum. <http://www.epa.gov/iris/subst/0425.htm> accessed 4/05.
131. IRIS (1994a) Cadmium. <http://www.epa.gov/iris/subst/0141.htm> accessed 1/04.
132. IRIS (1994b) Toluene. <http://www.epa.gov/iris/subst/0118.htm> accessed 1/04.
133. IRIS (1994c) Aniline. <http://www.epa.gov/iris/subst/0350.htm> accessed 4/04.
134. IRIS (1994d) Benzo[b]fluoranthene. <http://www.epa.gov/iris/subst/0453.htm> accessed 10/05.
135. IRIS (1994e) Chrysene. <http://www.epa.gov/iris/subst/0455.htm> accessed 10/05.
136. IRIS (1995a) Cis-1,2-dichloroethylene. <http://www.epa.gov/iris/subst/0418.htm> accessed 1/04.
137. IRIS (1995b) Mercuric chloride. <http://www.epa.gov/iris/subst/0692.htm> accessed 2/04.
138. IRIS (1996a) Manganese. <http://www.epa.gov/iris/subst/0373.htm> accessed 11/03.
139. IRIS (1996b) Nickel, soluble salts. <http://www.epa.gov/iris/subst/0271.htm> accessed 2/04.
140. IRIS (1996c) Vanadium. <http://www.epa.gov/iris/subst/0125.htm> accessed 4/05.
141. IRIS (1998a) Arsenic, inorganic. <http://www.epa.gov/iris/subst/0278.htm> accessed 2/04.
142. IRIS (1998b) Chromium (VI) <http://www.epa.gov/iris/subst/0144.htm> accessed 1/04.
143. IRIS (1999) Barium and compounds. <http://www.epa.gov/iris/subst/0010.htm> accessed 12/03.
144. IRIS (2000) Benzene. <http://www.epa.gov/iris/subst/0276.htm> accessed 1/04.
145. IRIS (2002) Phenol. <http://www.epa.gov/iris/subst/0088.htm> accessed 4/04.
146. IRIS (2003a) Methyl ethyl ketone. <http://www.epa.gov/iris/subst/0071.htm> accessed on 1/04.
147. IRIS (2003b) Toxicological review of methyl isobutyl ketone. www.epa.gov/iris/toxreviews/0173-tr.pdf accessed on 1/04.
148. IRIS (2003c) Acetone. <http://www.epa.gov/iris/subst/0128.htm> accessed 1/04.
149. Jenkins, F., Robinson, J., Gellatly, J. and Salmond, G. (1972) The no-effect dose of aniline in human subjects and a comparison of aniline toxicity in man and the rat. *Food and Cosmetics Toxicology* 10: 671-679.
150. Johnson, B.L., Belluck, D.A. and Melby, A.M. (2002) Hazard analysis and risk management of road subbase materials using the comparative risk bioassay methodology. Minnesota Department of Transportation.
151. Kim, M.G., Yagawa, K., Inoue, H., Lee, Y.K. and Shirai, T. (1990) Measurement of tire tread in urban air by pyrolysis-gas chromatography with flame photometric detection. *Atmospheric Environ.* 24A: 1417-1422.
152. King, A. (2000) Fundamentals of impact biomechanics: Biomechanics of the head, neck and thorax. *Ann Rev Biomed Engineer* 02: 55-81.
153. Koizumi, A. (1991) Experimental evidence for the possible exposure of workers to hexachlorobenzene by skin contamination. *Br. J Ind. Med.* 48: 622-628.
154. Kumata, H., Yamada, J., Masuda, K., Takada, H., Sato, Y., Sakurai, T. and Fujiwara, K. (2002) Benzothiazolamines as tire-derived molecular markers: Sorptive behavior in street runoff and application to source apportioning. *Environ. Sci. Technol.* 36: 702-708.
155. Kumata, H., Takada, H. and Ogura, N. (1996) Determination of 2-(4-morpholinyl)benzothiazole in environmental samples by a gas chromatograph equipped with a flame photometric detector. *Analyt. Chem.* 68: 1976-1981.
156. Lewis, L., Naunheim, R., Standeven, J. and Naunheim, K. (1993) Quantitation of impact attenuation of different playground surfaces under various environmental conditions using a tri-axial accelerometer. *J Trauma* 35: 932-935.
157. Lisi, R., Park, J. and Stier, J. (2004) Mitigating nutrient leaching with a sub-surface drainage layer of granulated tires. *Waste Management* 24: 831-839.
158. Liu, H.S., Mead, J.L. and Stacer, R.G. (1998) Environmental impacts of recycled rubber in light fill applications. Chelsea Center for Recycling and Economic Development, University of Massachusetts, Lowell.
159. Macarthur, C., Hu, X., Wesson, D. and Parkin, P. (2000) Risk factors for severe injuries associated with falls from playground equipment. *Accident Analysis and Prevention* 32: 377-382.
160. Mack, M., Sacks, J. and Thompson, D. (2000) Testing the impact attenuation of loose-fill playground surfaces. *Injury Prevention* 6: 141-144.
161. Melvin, J. and Lighthall, J. (2002) Brain-injury biomechanics. In: *Accidental Injury Biomechanics and Prevention*. Nahum, A. and Melvin, J. Eds. pp. 277-302, Springer, New York.

162. Meuling, W.J., Ravensberg, L.C., Roza, L. and van Hemmen, J.J. (2004) Dermal absorption of chlorpyrifos in human volunteers. *Int. Arch. Occup. Environ. Health* 78: 44-50.
163. Miguel, A., Cass, G., Weiss, J. and Glovsky, M. (1996) Latex allergens in tire dust and airborne particles. *Environ. Health Perspect.* 104: 1180-1186.
164. Miller, W.L. and Chadik, P.A. (1993) A study of waste tire leachability in potential disposal and usage environments. Report from the College of Engineering, University of Florida, Department of Environmental Engineering Sciences.
165. Minnesota Department of Transportation (1995) A comparative study of the toxicity of chipped tires and wood chips leachate. Report # 95-10-6161.
166. Minnesota Pollution Control Agency (1990) Environmental study of the use of shredded waste tires for roadway sub-grade support.
167. Moody, R.P., Nadeau, B. and Chu, I. (1995) In vivo and in vitro dermal absorption of benzo[a]pyrene in rat, guinea pig, human and tissue-cultured skin. *J Dermatol. Sci.* 9: 48-58.
168. Mott, A., Rolfe, K., James, R., Evans, R., Kemp, A., Dunstan, F., Kemp, K. and Sibert, J. (1997) Safety of surfaces and equipment for children in playgrounds. *Lancet* 349: 1874-1876.
169. Mowat, D., Wang, F., Pickett, W. and Brison, R. (1998) A case-control study of risk factors for playground injuries among children in Kingston and area. *Injury Prevention* 4: 39-43.
170. MSDS for crumb rubber (1993) BAS Recycling, Inc.
171. Nahum, A. and Melvin, J. Eds. (2002) *Accidental Injury Biomechanics and Prevention*. Springer, New York.
172. The National Academies (2001) *Dietary Reference Intakes for Vitamin A, Vitamin K, Arsenic, Boron, Chromium, Copper, Iodine, Iron, Manganese, Molybdenum, Nickel, Vanadium and Zinc*. National Academies Press, Washington, DC.
173. Nelson, S.M., Mueller, G. and Hemphill, D.C. (1994) Identification of tire leachate toxicants and a risk assessment of water quality effects using tire reefs in canals. *Bull. Environ. Contam. Toxicol.* 52: 574-581.
174. Newman, S.E., Panter, K.L., Roll, M.J. and Miller, R.O. (1997) Growth and nutrition of geraniums grown in media developed from waste tire components. *HortScience* 32: 674-676.
175. Norton, C., Rolfe, K., Morris, S., Evans, R., James, R., Jones, M., Cory, C., Dunstan, F. and Sibert, J. (2004a) Head injury and limb fracture in modern playgrounds. *Arch Dis Child* 89: 152-153.
176. Norton, C., Nixon, J. and Sibert, J. (2004b) Playground injuries to children. *Arch Dis Child* 89: 103-8.
177. NTP (2004) Benzothiazole. <http://ntp-server.niehs.nih.gov/> accessed 4/04.
178. OEHHA (1997a) Public health goal for copper in drinking water.
179. OEHHA (1997b) Public health goal for lead in drinking water.
180. OEHHA (1997c) Public health goal for antimony in drinking water.
181. OEHHA (1999a) Public health goal for cadmium in drinking water.
182. OEHHA (1999b) Public health goal for inorganic mercury in drinking water.
183. OEHHA (1999c) Public health goal for toluene in drinking water.
184. OEHHA (1999d) Public health goal for trichloroethylene in drinking water.
185. OEHHA (2000a) Chronic toxicity summary for cadmium and cadmium compounds. http://www.oehha.ca.gov/air/chronic_rels/AllChrels.html accessed 2/04.
186. OEHHA (2000b) Chronic toxicity summary for hexavalent chromium. http://www.oehha.ca.gov/air/chronic_rels/AllChrels.html accessed 2/04.
187. OEHHA (2000c) Technical support document for exposure assessment and stochastic analysis, September, 2000.
188. OEHHA (2001a) Public health goal for aluminum in drinking water.
189. OEHHA (2001b) Public health goal for nickel in drinking water.
190. OEHHA (2001c) Public health goal for benzene in drinking water.
191. OEHHA (2003a) All Chronic Reference Exposure Levels Adopted by OEHHA as of August 2003. http://www.oehha.ca.gov/air/chronic_rels/AllChrels.html accessed 8/04.
192. OEHHA (2003b) Public health goal for barium in drinking water.
193. OEHHA (2003c) Public health goal for 1,1-dichloroethane in drinking water.
194. OEHHA (2004a) Public health goal for arsenic in drinking water.
195. OEHHA (2004b) Proposition 65 status report safe harbor levels, accessed 1/04 at <http://www.oehha.ca.gov/prop65/getNSRLs.html>

196. OEHHA (2004c) No significant risk levels (NSRLS) for the Proposition 65 carcinogens benzo[B]fluoranthene, benzo[J]fluoranthene, chrysene, dibenzo[A,H]pyrene, dibenzo[A,I]pyrene, and 5-methylchrysene by the oral route. Accessed at www.oehha.ca.gov in 11/05.
197. OEHHA (2005) Chemicals Known to the State to Cause Cancer or Reproductive Toxicity, December 2, 2005, accessed 12/05 at www.oehha.ca.gov/prop65/prop65_listfiles/P65single120205.pdf
198. OEHHA (2005b) Human-Exposure-Based Screening Numbers Developed to Aid Estimation of Cleanup Costs for Contaminated Soil, January 2005 revision.
199. OEHHA (2006) A Guide to Health Risk Assessment, available at www.oehha.ca.gov/pdf/HRSguide2001.pdf
200. Ontario Ministry of Environment and Energy (1994) The acute lethality to rainbow trout of water contaminated by an automobile tire. Report prepared by Scott Abernethy, Aquatic Toxicology Section, Standards Development Branch.
201. OSHA (2004) Cadmium. http://www.osha.gov/dts/chemicalsampling/data/CH_223897.html accessed on 8/04.
202. O'Shaughnessy, V. and Garga, V. (2000) Tire-reinforced earthfill. Part 3: Environmental assessment. *Can. Geotech. J* 37: 117-131.
203. Owings, A. and Bush, E. (2001) Assessment of macro and micro-nutrient accumulation in Bermudagrass grown in crumb rubber amended media. *HortScience* 36: 541.
204. Park, J.K., Edil, T.B., Kim, J.Y. Huh, M., Lee, S.H. and Lee, J.J. (2003) Suitability of shredded tyres as a substitute for a landfill leachate collection medium. *Waste Manage. Res.* 21: 278-289.
205. Pellman, E.J., Viano, D.C., Tucker, A.M., Casson, I.R. and Waeckerle, J.F. (2003) Concussion in professional football: Reconstruction of game impacts and injuries. *Neurosurgery* 53: 799-812.
206. Petridou, E., Sibert, J., Dedoukou, X., Skalkidis, I. and Trichopoulos, D. (2002) Injuries in public and private playgrounds: the relative contribution of structural, equipment and human factors. *Acta Paediatr* 91: 691-697.
207. Pierce, C. and Blackwell, M. (2003) Potential of scrap tire rubber as lightweight aggregate in flowable fill. *Waste Management* 23: 197-208.
208. Prasad, P. and Mertz, H.J. (1985) The position of the United States Delegation to the ISO working group 6 on the use of HIC in the automotive environment, SAE Paper No. 851246.
209. Qiao, G.L. and Riviere, J.E. (2002) Systemic uptake and cutaneous disposition of pentachlorophenol in a sequential exposure scenario: effects of skin preexposure to bezo[a]pyrene. *J Toxicol. Environ. Health A* 65: 1307-1331.
210. Radian Corporation (1989) A report on the RMA TCLP assessment project. Prepared for the Rubber Manufacturers Association.
211. Reddy, C. and Quinn, J. (1997) Environmental chemistry of benzothiazoles derived from rubber. *Environ. Sci. Technol.* 31: 2847-2853.
212. Robinovitch, S. and Chiu, J. (1998) Surface stiffness affects impact force during a fall on the outstretched hand. *J Orthopaedic Res. Soc.* 16: 309-313.
213. Robinson, M.K., Stottis, J., Danneman, P.J., Nusair, T.L. and Bay, P.H.S. (1989) A risk assessment process for allergic contact sensitization. *Fd. Chem. Toxic.* 27: 479-489.
214. Rogge, W.F., Hildemann, L.M., Mazurek, M.A. and Cass, G.R. (1993) Sources of fine organic aerosol. 3. Road dust, tire debris, and organometallic brake lining dust: Roads as sources and sinks. *Environ. Sci. Technol.* 27: 1892-1904.
215. Ross, J. (2005) Characterizing hand to mouth activity improves regulatory exposure estimates, poster, annual meeting of the International Society of Exposure Analysis, Tucson, Arizona.
216. Schauer, J.J., Fraser, M.P., Cass, G.R. and Simoneit, B.R. (2002) Source reconciliation of atmospheric gas-phase and particle-phase pollutants during a severe photochemical smog episode. *Environ. Sci. Technol.* 36: 3806-3814.
217. Scrap Tire Management Council (1991) The RMA TCLP Assessment Project: Radian Report. Educational seminar on scrap tire management, Washington D.C., September 6-7, 1991.
218. Semple, J.I., Newton, J.L., Westley, B.R. and May, F.E.B. (2001) Dramatic diurnal variation in the concentration of the human trefoil peptide TFF2 in gastric juice. *Gut* 48: 648-655.
219. Sengupta, S. and Miller, H.J. (1999) Preliminary investigation of tire shreds for use in residential subsurface leaching field systems. Chelsea Center for Recycling and Economic Development, University of Massachusetts, Lowell.

220. Shah, P.V., Fisher, H.L., Month, N.J., Sumler, M.R. and Hall, L.L. (1987) Dermal penetration of carbofuran in young and adult Fischer 344 rats. *J Toxicol. Environ. Health* 22: 207-223.
221. Sherker, S., Ozanne-Smith, J., Rechnitzer, G. and Grzebieta, R. (2003) Development of a multidisciplinary method to determine risk factors for arm fracture in falls from playground equipment. *Injury Prevention* 9: 279-283.
222. Sherker, S., Ozanne-Smith, J., Rechnitzer, G. and Grzebieta, R. (2005) Out on a limb: risk factors for arm fracture in playground equipment falls. *Injury Prevention* 11: 120-124.
223. Shieh, C. (2001) Criteria of selecting toxicity characteristics leaching procedure (TCLP) and synthetic precipitation leaching procedure (SPLP) tests to characterize special wastes. Florida Center for Solid and Hazardous Waste Management, University of Florida, Report # 01-2.
224. Smolders, E. and Degryse, F. (2002) Fate and effect of zinc from tire debris in soil. *Environ Sci Technol* 36: 3706-3710.
225. Sosin, D., Keller, P., Sacks, J., Kresnow, M. and van Dyck, P. (1993) Surface-specific fall injury rates on Utah school playgrounds. *Am J Public Health* 83: 733-735.
226. Spies, R.B., Andresen, B.D. and Rice, D.W. (1987) Benzthiazoles in estuarine sediments as indicators of street runoff. *Nature* 327: 697-699.
227. Spivey, M.R. and Rader, J.I. (1988) Iron. In: *Handbook on Toxicity of Inorganic Compounds* (Seiler, H.G. and Sigel, H., Eds.) Marcel Dekker Inc., New York, pp. 345-354.
228. Stephensen, E., Adolfsson-Erici, M., Celander, M., Hulander, M., Parkkonen, J., Hegelund, T., Sturve, J., Hasselberg, L., Bengtsson, M. and Forlin, L. (2003) Biomarker responses and chemical analyses in fish indicate leakage of polycyclic aromatic hydrocarbons and other compounds from car tire rubber. *Environ Toxicol Chem* 22: 2926-2931.
229. Sugiura, M., Hayakawa, R., Sugiura, K., Shamoto, M. and Yagami, T. (2002) Latex protein induced delayed-type contact allergy. *Environ. Dermatol.* 9: 47-52.
230. Sullivan, J., Van Ert, M. and Lewis, R. (1992) Chemical hazards in the tire and rubber manufacturing industry. In: *Hazardous Materials Toxicology, Clinical Principles of Environmental Health* (Sullivan, J. and Krieger, G., Eds.) Williams and Wilkins, Baltimore, pp. 516-532.
231. Tatlisoz, N., Edil, T., Benson, C., Park, J. and Kim, J. (1996) Review of environmental suitability of scrap tires. *Environmental Geotechnics Report No: 96-7*, Department of Civil and Environmental Engineering, University of Wisconsin, Madison.
232. Taylor, D., Pligh, P. and Duggan, M. (1962) The absorption of calcium, strontium, barium, and radium from the gastrointestinal tract of the rat. *Biochem. J.* 83: 25-29.
233. Thibault, K. and Margulies, S. (1998) Age-dependent material properties of the porcine cerebrum: effect on pediatric inertial head injury criteria. *J Biomech* 31: 1119-1126.
234. Timchalk, C., Selium, S., Sangha, G. and Bartels, M.J. (1998) The pharmacokinetics and metabolism of ¹⁴C/¹³C-labeled ortho-phenylphenol formation following dermal application to human volunteers. *Hum. Exp. Toxicol.* 17: 411-417.
235. Tinsworth, D. and McDonald, J. (2001) Special study: injuries and deaths associated with children's playground equipment. U.S. Consumer Products Safety Commission, Washington, D.C.
236. Tompkins, D., moroz, D., Abiola, A., Chaw, D., Clark, T. and Ross, J. (1997) The effect of crumb rubber and compost soil amendments on *Agrostis palustris* Huds. cv. *Penncross*. *Prairie Turfgrass Research Center, Research Report 9714*; accessed 12/05 at http://ptrc.oldscollege.ab.ca/1997_ar/9714.html
237. Tulve, N.S., Suggs, J.C., McCurdy, T., Hubal, E.A. and Moya, J. (2002) Frequency of mouthing behavior in young children. *J Expos Anal Environ Epidemiol* 12: 259-264.
238. U.S. CPSC (undated) Handbook for public playground safety, U.S. Consumer Product Safety Commission, Washington, DC, Pub. No. 325.
239. U.S. CPSC (1997) United States Consumer Products Safety Commission, Publication Number 325: Handbook for Public Playground Safety.
240. U.S. CPSC (2006) United States Consumer Products Safety Commission, www.cpsc.gov/cpscpub/pubs/cpsr_nws30.pdf accessed 2/06.
241. USDA (2006) Recommended Intakes for Individuals, accessed 4/06 at www.nal.usda.gov/fnic/etext/000105.html
242. U.S. EPA (1992) Dermal exposure assessment: Principles and applications. Exposure Assessment Group, Office of Health and Environmental Assessment, Washington, D.C.
243. U.S. EPA (1998) Health Effects Test Guidelines OPPTS 870.2600, Skin Sensitization 1998.

244. U.S. EPA (2001) Memorandum: Acephate-sensitivity analysis for turf risk assessment [Case #819371, PC Code 103301, DP Barcode D276433] Office of Prevention, Pesticides, and Toxic Substances, Washington, D.C.
245. U.S. EPA (2002) Child-Specific Exposure Factors Handbook, EPA-600-00-002B, Interim Report September 2002, Washington, D.C.
246. U.S. EPA (2003a) Evaluation of the Effectiveness of Coatings in Reducing Dislodgeable Arsenic, Chromium, and Copper from CCA Treated Wood (Project No. RN992014.0041), United States Environmental Protection Agency, Air Pollution Prevention and Control Division, Research Triangle Park, NC.
247. U.S. EPA (2003b) Toxicological Review of Methyl Isobutyl Ketone (CAS No. 108-10-1), United States Environmental Protection Agency, Washington DC.
248. U.S. EPA (2003c) Supplemental guidance for assessing cancer susceptibility from early-life exposures to carcinogens, External Review Draft, EPA/630/R-03/003, February, 2003.
249. U.S. EPA (2003d) Preliminary Remediation Goals (PRGs) published by U.S. EPA Region 9, <http://www.epa.gov/region09/waste/sfund/prg/index.htm>
250. U.S. EPA (2004) Revised Assessment of Detection and Quantitation Approaches, EPA-821-B-04-005, United States Environmental Protection Agency.
251. U.S. EPA (2005) A probabilistic exposure assessment for children who contact CCA-treated playsets and decks. United States Environmental Protection Agency.
252. U.S. EPA (2005a) National Secondary Drinking Water Regulations, www.epa.gov/safewater/md.html accessed 12/05.
253. VanRooij, J.G., De Roos, J.H., Bodelier-Bade, M.M. and Jongeneelen, F.J. (1993) Absorption of polycyclic aromatic hydrocarbons through human skin: differences between anatomical sites and individuals. *J Toxicol. Environ. Health* 38: 355-368.
254. Viano, D.C., Casson, I.R., Pellman, E.J., Bir, C.A., Zhang, L., Sherman, D.C. and Boitano, M.A. (2005) Concussion in professional football: Comparison with boxing head impacts-Part 10. *Neurosurgery* 57: 1154-1172.
255. Waltzman, M., Shannon, M., Bowen, A. and Bailey, M. (1999) Monkey bar injuries: complications of play. *Pediatrics* 103: e58-61.
256. Wik, A and Dave, Goran (2005) Environmental labeling of car tires-toxicity to *Daphnia magna* can be used as a screening method. *Chemosphere* 58: 645-651.
257. Williams, P.B., Buhr, M.P., Weber, R.W., Volz, M.A., Koepke, J.W. and Selner, J.C. (1995) Latex allergens in respirable particulate air pollution. *J. Allergy Clin. Immunol.* 95: 88-95.
258. Yadrick, M., Kenney, M. and Winterfeldt (1989) Iron, copper, and zinc status: responses to supplementation with zinc or zinc and iron in adult females. *Am J Clin Nutr* 49: 145-150.
259. Yip, E., Palosuo, T., Alenius, H. and Turjanmaa, K. (1997) Correlation between total extractable proteins and allergen levels of natural rubber latex gloves. *J. Nat. Rubb. Res.* 12: 120-130.
260. Yoon, S., Prezzi, M., Siddiki, N. and Kim, B. (2005) Construction of a test embankment using a sand-tire shred mixture as fill material. *Waste Manag.*, December 9, Epub ahead of print.
261. Zartarian, V.G., Ozkaynak, H., Burke, J.M., Zufall, M.J., Rigas, M.L. and Furtaw, E.J. (2000) A modeling framework for estimating children's residential exposure and dose to chlorpyrifos via dermal residue contact and nondietary ingestion. *Env. Health Persp.* 108: 505-514.
262. Zheng, E., Tran, K. and Young, D. (2004) Evaluation of potential molecular markers for urban stormwater runoff. *Environ. Monit. Assess.* 90: 23-43.

Contractor's Report to the Board

Evaluation of Health Effects of Recycled Waste Tires in Playground and Track Products

(Publication #622-06-013)

Produced under contract by:



January 2007

Appendix A: Raw Data From Gastric Digestion Experiment





24 March, 2005

Vidair
Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley, CA 94710

RE: OEHHA Playground Study
Work Order: MOC0103

Enclosed are the results of analyses for samples received by the laboratory on 03/02/05 18:40. If you have any questions concerning this report, please feel free to contact me.

Sincerely,

James Hartley
Dept Manager - Project Manager

CA ELAP Certificate #1210

Dept. of Toxic Substances Control-Berkeley 700 Heinz Avenue, Suite 100 Berkeley CA, 94710	Project:OEHHA Playground Study Project Number:SAU5634 Project Manager:Vidair	MOC0103 Reported: 03/24/05 15:53
---	--	---

ANALYTICAL REPORT FOR SAMPLES

Sample ID	Laboratory ID	Matrix	Date Sampled	Date Received
G	MOC0103-01	Water	03/01/05 00:00	03/02/05 18:40
S	MOC0103-02	Water	03/01/05 00:00	03/02/05 18:40
O	MOC0103-03	Water	03/01/05 00:00	03/02/05 18:40
CON	MOC0103-04	Water	03/01/05 00:00	03/02/05 18:40

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
Reported:
 03/24/05 15:53

**Total Metals by EPA 6000/7000 Series Methods
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
G (MOC0103-01) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40									
Antimony	110	0.50	ug/l	1	5C14015	03/14/05	03/16/05	EPA 6020	
Arsenic	6.1	1.0	"	"	"	"	"	"	
Barium	130	1.0	"	"	"	"	"	"	
Beryllium	ND	0.50	"	"	"	"	"	"	
Cadmium	2.2	0.25	"	"	"	"	"	"	
Chromium	41	2.0	"	"	"	"	"	"	
Cobalt	45	0.50	"	"	"	"	"	"	
Copper	1500	50	"	100	"	"	03/16/05	"	
Lead	140	0.50	"	1	"	"	03/16/05	"	
Molybdenum	11	1.0	"	"	"	"	"	"	
Nickel	27	1.0	"	"	"	"	"	"	
Selenium	18	1.0	"	"	"	"	"	"	
Silver	ND	0.25	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	9.0	1.0	"	"	"	"	"	"	
Zinc	17000	500	"	100	"	"	03/16/05	"	
S (MOC0103-02) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40									
Antimony	42	0.50	ug/l	1	5C14015	03/14/05	03/16/05	EPA 6020	
Arsenic	5.4	1.0	"	"	"	"	"	"	
Barium	110	1.0	"	"	"	"	"	"	
Beryllium	ND	0.50	"	"	"	"	"	"	
Cadmium	2.8	0.25	"	"	"	"	"	"	
Chromium	57	2.0	"	"	"	"	"	"	
Cobalt	50	0.50	"	"	"	"	"	"	
Copper	960	50	"	100	"	"	03/16/05	"	
Lead	120	0.50	"	1	"	"	03/16/05	"	
Molybdenum	18	1.0	"	"	"	"	"	"	
Nickel	27	1.0	"	"	"	"	"	"	
Selenium	10	1.0	"	"	"	"	"	"	
Silver	ND	0.25	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	9.5	1.0	"	"	"	"	"	"	
Zinc	26000	500	"	100	"	"	03/16/05	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
Reported:
 03/24/05 15:53

**Total Metals by EPA 6000/7000 Series Methods
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
O (MOC0103-03) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40									
Antimony	1.7	0.50	ug/l	1	5C14015	03/14/05	03/16/05	EPA 6020	
Arsenic	4.7	1.0	"	"	"	"	"	"	
Barium	870	100	"	100	"	"	03/16/05	"	
Beryllium	ND	0.50	"	1	"	"	03/16/05	"	
Cadmium	1.1	0.25	"	"	"	"	"	"	
Chromium	35	2.0	"	"	"	"	"	"	
Cobalt	33	0.50	"	"	"	"	"	"	
Copper	1600	50	"	100	"	"	03/16/05	"	
Lead	48	0.50	"	1	"	"	03/16/05	"	
Molybdenum	8.5	1.0	"	"	"	"	"	"	
Nickel	22	1.0	"	"	"	"	"	"	
Selenium	7.1	1.0	"	"	"	"	"	"	
Silver	ND	0.25	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	5.8	1.0	"	"	"	"	"	"	
Zinc	13000	500	"	100	"	"	03/16/05	"	
CON (MOC0103-04) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40									
Antimony	ND	0.50	ug/l	1	5C14015	03/14/05	03/16/05	EPA 6020	
Arsenic	ND	1.0	"	"	"	"	"	"	
Barium	4.2	1.0	"	"	"	"	"	"	
Beryllium	ND	0.50	"	"	"	"	"	"	
Cadmium	0.44	0.25	"	"	"	"	"	"	
Chromium	16	2.0	"	"	"	"	"	"	
Cobalt	ND	0.50	"	"	"	"	"	"	
Copper	8.3	0.50	"	"	"	"	"	"	
Lead	4.6	0.50	"	"	"	"	"	"	
Molybdenum	ND	1.0	"	"	"	"	"	"	
Nickel	1.1	1.0	"	"	"	"	"	"	
Selenium	3.0	1.0	"	"	"	"	"	"	
Silver	ND	0.25	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	3.3	1.0	"	"	"	"	"	"	
Zinc	16	5.0	"	"	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
Reported:
 03/24/05 15:53

Tentatively Identified Compounds by GC/MS

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
G (MOC0103-01) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40									
o-cyanobenzoic acid	990	190	ug/l	10	5C19005	03/19/05	03/23/05	EPA 8270C	
cyclohexanamine, N-cyclohexyl-Benzothiazole	190	190	"	"	"	"	"	"	
2(3H)-Benzothiazolone	320	190	"	"	"	"	"	"	
2(3H)-Benzothiazolone	640	190	"	"	"	"	"	"	
S (MOC0103-02) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40									
Benzothiazole	450	190	ug/l	10	5C19005	03/19/05	03/23/05	EPA 8270C	
1H-isoindole-1,3(2H)-dione	490	190	"	"	"	"	"	"	
cyclohexanamine, N-cyclohexyl-2(3H)-Benzothiazolone	410	190	"	"	"	"	"	"	
2(3H)-Benzothiazolone	450	190	"	"	"	"	"	"	
O (MOC0103-03) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40									
o-cyanobenzoic acid	910	36	ug/l	2	5C19005	03/19/05	03/23/05	EPA 8270C	HT-03
2(3H)-Benzothiazolone	480	36	"	"	"	"	"	"	HT-03
Benzothiazole	390	36	"	"	"	"	"	"	HT-03
cyclohexanone	48	36	"	"	"	"	"	"	HT-03
Formamide, N-cyclohexyl-	110	36	"	"	"	"	"	"	HT-03
CON (MOC0103-04) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40									
benzaldehyde, 3-hydroxy-4-methoxy-	25	19	ug/l	1	5C19005	03/19/05	03/23/05	EPA 8270C	HT-03
Hexanedioic acid, bis(2-ethylhexyl)	28	19	"	"	"	"	"	"	HT-03

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
Reported:
 03/24/05 15:53

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
G (MOC0103-01) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40									HT-03
Aniline	2800	190	ug/l	10	5C19005	03/19/05	03/23/05	EPA 8270C	
Acenaphthene	ND	190	"	"	"	"	"	"	
Acenaphthylene	ND	190	"	"	"	"	"	"	
Anthracene	ND	190	"	"	"	"	"	"	
Benzo (a) anthracene	ND	190	"	"	"	"	"	"	
Benzo (a) pyrene	ND	190	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	190	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	370	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	190	"	"	"	"	"	"	
Benzoic acid	ND	740	"	"	"	"	"	"	
Benzyl alcohol	ND	370	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	190	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	370	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	190	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	370	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	190	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	190	"	"	"	"	"	"	
4-Chloroaniline	ND	1900	"	"	"	"	"	"	
2-Chloronaphthalene	ND	190	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	190	"	"	"	"	"	"	
2-Chlorophenol	ND	190	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	370	"	"	"	"	"	"	
Chrysene	ND	190	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	190	"	"	"	"	"	"	
Dibenzofuran	ND	190	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	190	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	370	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	370	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	370	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	1900	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	190	"	"	"	"	"	"	
Diethyl phthalate	ND	190	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	370	"	"	"	"	"	"	
Dimethyl phthalate	ND	190	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	190	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	370	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	190	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	190	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	370	"	"	"	"	"	"	
Fluoranthene	ND	190	"	"	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
Reported:
 03/24/05 15:53

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
G (MOC0103-01) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40									
Fluorene	ND	190	ug/l	10	5C19005	03/19/05	03/23/05	EPA 8270C	
Hexachlorobenzene	ND	190	"	"	"	"	"	"	
Hexachlorobutadiene	ND	370	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	370	"	"	"	"	"	"	
Hexachloroethane	ND	370	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	370	"	"	"	"	"	"	
Isophorone	ND	190	"	"	"	"	"	"	
2-Methylnaphthalene	ND	190	"	"	"	"	"	"	
2-Methylphenol	ND	190	"	"	"	"	"	"	
4-Methylphenol	ND	190	"	"	"	"	"	"	
Naphthalene	ND	190	"	"	"	"	"	"	
2-Nitroaniline	ND	370	"	"	"	"	"	"	
3-Nitroaniline	ND	3700	"	"	"	"	"	"	
4-Nitroaniline	ND	1900	"	"	"	"	"	"	
Nitrobenzene	ND	190	"	"	"	"	"	"	
2-Nitrophenol	ND	190	"	"	"	"	"	"	
4-Nitrophenol	ND	370	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	190	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	370	"	"	"	"	"	"	
Pentachlorophenol	ND	370	"	"	"	"	"	"	
Phenanthrene	ND	190	"	"	"	"	"	"	
Phenol	190	190	"	"	"	"	"	"	
Pyrene	ND	190	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	370	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	190	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	190	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		90 %		40-115	"	"	"	"	
<i>Surrogate: Phenol-d6</i>		93 %		20-115	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		81 %		50-115	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		90 %		70-115	"	"	"	"	
<i>Surrogate: 2,4,6-Tribromophenol</i>		77 %		35-115	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		99 %		70-130	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
Reported:
 03/24/05 15:53

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
S (MOC0103-02) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40									
Aniline	3000	190	ug/l	10	5C19005	03/19/05	03/23/05	EPA 8270C	
Acenaphthene	ND	190	"	"	"	"	"	"	
Acenaphthylene	ND	190	"	"	"	"	"	"	
Anthracene	ND	190	"	"	"	"	"	"	
Benzo (a) anthracene	ND	190	"	"	"	"	"	"	
Benzo (a) pyrene	ND	190	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	190	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	380	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	190	"	"	"	"	"	"	
Benzoic acid	ND	770	"	"	"	"	"	"	
Benzyl alcohol	ND	380	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	190	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	380	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	190	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	380	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	190	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	190	"	"	"	"	"	"	
4-Chloroaniline	ND	1900	"	"	"	"	"	"	
2-Chloronaphthalene	ND	190	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	190	"	"	"	"	"	"	
2-Chlorophenol	ND	190	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	380	"	"	"	"	"	"	
Chrysene	ND	190	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	190	"	"	"	"	"	"	
Dibenzofuran	ND	190	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	190	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	380	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	380	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	380	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	1900	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	190	"	"	"	"	"	"	
Diethyl phthalate	ND	190	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	380	"	"	"	"	"	"	
Dimethyl phthalate	ND	190	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	190	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	380	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	190	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	190	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	380	"	"	"	"	"	"	
Fluoranthene	ND	190	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
Reported:
 03/24/05 15:53

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
S (MOC0103-02) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40									
Fluorene	ND	190	ug/l	10	5C19005	03/19/05	03/23/05	EPA 8270C	
Hexachlorobenzene	ND	190	"	"	"	"	"	"	
Hexachlorobutadiene	ND	380	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	380	"	"	"	"	"	"	
Hexachloroethane	ND	380	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	380	"	"	"	"	"	"	
Isophorone	ND	190	"	"	"	"	"	"	
2-Methylnaphthalene	ND	190	"	"	"	"	"	"	
2-Methylphenol	ND	190	"	"	"	"	"	"	
4-Methylphenol	ND	190	"	"	"	"	"	"	
Naphthalene	ND	190	"	"	"	"	"	"	
2-Nitroaniline	ND	380	"	"	"	"	"	"	
3-Nitroaniline	ND	3800	"	"	"	"	"	"	
4-Nitroaniline	ND	1900	"	"	"	"	"	"	
Nitrobenzene	ND	190	"	"	"	"	"	"	
2-Nitrophenol	ND	190	"	"	"	"	"	"	
4-Nitrophenol	ND	380	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	190	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	380	"	"	"	"	"	"	
Pentachlorophenol	ND	380	"	"	"	"	"	"	
Phenanthrene	ND	190	"	"	"	"	"	"	
Phenol	ND	190	"	"	"	"	"	"	
Pyrene	ND	190	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	380	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	190	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	190	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		93 %		40-115	"	"	"	"	
<i>Surrogate: Phenol-d6</i>		98 %		20-115	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		84 %		50-115	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		89 %		70-115	"	"	"	"	
<i>Surrogate: 2,4,6-Tribromophenol</i>		76 %		35-115	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		104 %		70-130	"	"	"	"	

Dept. of Toxic Substances Contol-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
Reported:
 03/24/05 15:53

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
O (MOC0103-03) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40 HT-03, R-05									
Aniline	6700	360	ug/l	20	5C19005	03/19/05	03/22/05	EPA 8270C	
Acenaphthene	ND	360	"	"	"	"	"	"	
Acenaphthylene	ND	360	"	"	"	"	"	"	
Anthracene	ND	360	"	"	"	"	"	"	
Benzo (a) anthracene	ND	360	"	"	"	"	"	"	
Benzo (a) pyrene	ND	360	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	360	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	710	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	360	"	"	"	"	"	"	
Benzoic acid	ND	1400	"	"	"	"	"	"	
Benzyl alcohol	ND	710	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	360	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	710	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	360	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	710	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	360	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	360	"	"	"	"	"	"	
4-Chloroaniline	ND	3600	"	"	"	"	"	"	
2-Chloronaphthalene	ND	360	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	360	"	"	"	"	"	"	
2-Chlorophenol	ND	360	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	710	"	"	"	"	"	"	
Chrysene	ND	360	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	360	"	"	"	"	"	"	
Dibenzofuran	ND	360	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	360	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	710	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	710	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	710	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	3600	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	360	"	"	"	"	"	"	
Diethyl phthalate	ND	360	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	710	"	"	"	"	"	"	
Dimethyl phthalate	ND	360	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	360	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	710	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	360	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	360	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	710	"	"	"	"	"	"	
Fluoranthene	ND	360	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
Reported:
 03/24/05 15:53

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
O (MOC0103-03) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40 HT-03, R-05									
Fluorene	ND	360	ug/l	20	5C19005	03/19/05	03/22/05	EPA 8270C	
Hexachlorobenzene	ND	360	"	"	"	"	"	"	
Hexachlorobutadiene	ND	710	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	710	"	"	"	"	"	"	
Hexachloroethane	ND	710	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	710	"	"	"	"	"	"	
Isophorone	ND	360	"	"	"	"	"	"	
2-Methylnaphthalene	ND	360	"	"	"	"	"	"	
2-Methylphenol	ND	360	"	"	"	"	"	"	
4-Methylphenol	ND	360	"	"	"	"	"	"	
Naphthalene	ND	360	"	"	"	"	"	"	
2-Nitroaniline	ND	710	"	"	"	"	"	"	
3-Nitroaniline	ND	7100	"	"	"	"	"	"	
4-Nitroaniline	ND	3600	"	"	"	"	"	"	
Nitrobenzene	ND	360	"	"	"	"	"	"	
2-Nitrophenol	ND	360	"	"	"	"	"	"	
4-Nitrophenol	ND	710	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	360	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	710	"	"	"	"	"	"	
Pentachlorophenol	ND	710	"	"	"	"	"	"	
Phenanthrene	ND	360	"	"	"	"	"	"	
Phenol	ND	360	"	"	"	"	"	"	
Pyrene	ND	360	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	710	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	360	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	360	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		98 %		40-115	"	"	"	"	
<i>Surrogate: Phenol-d6</i>		101 %		20-115	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		78 %		50-115	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		86 %		70-115	"	"	"	"	
<i>Surrogate: 2,4,6-Tribromophenol</i>		69 %		35-115	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		90 %		70-130	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
Reported:
 03/24/05 15:53

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
CON (MOC0103-04) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40 HT-03									
Acenaphthene	ND	19	ug/l	1	5C19005	03/19/05	03/23/05	EPA 8270C	
Acenaphthylene	ND	19	"	"	"	"	"	"	
Anthracene	ND	19	"	"	"	"	"	"	
Benzo (a) anthracene	ND	19	"	"	"	"	"	"	
Benzo (a) pyrene	ND	19	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	19	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	37	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	19	"	"	"	"	"	"	
Benzoic acid	ND	74	"	"	"	"	"	"	
Benzyl alcohol	ND	37	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	19	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	37	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	19	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	37	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	19	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	19	"	"	"	"	"	"	
4-Chloroaniline	ND	190	"	"	"	"	"	"	
2-Chloronaphthalene	ND	19	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	19	"	"	"	"	"	"	
2-Chlorophenol	ND	19	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	37	"	"	"	"	"	"	
Chrysene	ND	19	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	19	"	"	"	"	"	"	
Dibenzofuran	ND	19	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	19	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	37	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	37	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	37	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	190	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	19	"	"	"	"	"	"	
Diethyl phthalate	ND	19	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	37	"	"	"	"	"	"	
Dimethyl phthalate	ND	19	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	19	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	37	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	19	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	19	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	37	"	"	"	"	"	"	
Fluoranthene	ND	19	"	"	"	"	"	"	
Fluorene	ND	19	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
Reported:
 03/24/05 15:53

Semivolatile Organic Compounds by EPA Method 8270C

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
CON (MOC0103-04) Water Sampled: 03/01/05 00:00 Received: 03/02/05 18:40									
Hexachlorobenzene	ND	19	ug/l	1	5C19005	03/19/05	03/23/05	EPA 8270C	
Hexachlorobutadiene	ND	37	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	37	"	"	"	"	"	"	
Hexachloroethane	ND	37	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	37	"	"	"	"	"	"	
Isophorone	ND	19	"	"	"	"	"	"	
2-Methylnaphthalene	ND	19	"	"	"	"	"	"	
2-Methylphenol	ND	19	"	"	"	"	"	"	
4-Methylphenol	ND	19	"	"	"	"	"	"	
Naphthalene	ND	19	"	"	"	"	"	"	
2-Nitroaniline	ND	37	"	"	"	"	"	"	
3-Nitroaniline	ND	370	"	"	"	"	"	"	
4-Nitroaniline	ND	190	"	"	"	"	"	"	
Nitrobenzene	ND	19	"	"	"	"	"	"	
2-Nitrophenol	ND	19	"	"	"	"	"	"	
4-Nitrophenol	ND	37	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	19	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	37	"	"	"	"	"	"	
Pentachlorophenol	ND	37	"	"	"	"	"	"	
Phenanthrene	ND	19	"	"	"	"	"	"	
Phenol	ND	19	"	"	"	"	"	"	
Pyrene	ND	19	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	37	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	19	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	19	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		78 %	40-115		"	"	"	"	
<i>Surrogate: Phenol-d6</i>		81 %	20-115		"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		76 %	50-115		"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		69 %	70-115		"	"	"	"	S02
<i>Surrogate: 2,4,6-Tribromophenol</i>		64 %	35-115		"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		76 %	70-130		"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
Reported:
 03/24/05 15:53

Total Metals by EPA 6000/7000 Series Methods - Quality Control
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5C14015 - EPA 3005A / EPA 6020
Blank (5C14015-BLK1)

Prepared & Analyzed: 03/14/05

Antimony	ND	0.50	ug/l							
Arsenic	ND	1.0	"							
Cadmium	ND	0.25	"							
Chromium	ND	2.0	"							
Cobalt	ND	0.50	"							
Copper	ND	0.50	"							
Lead	ND	0.50	"							
Nickel	ND	1.0	"							
Selenium	ND	1.0	"							
Silver	ND	0.25	"							
Thallium	ND	1.0	"							
Vanadium	ND	1.0	"							
Zinc	ND	5.0	"							

Blank (5C14015-BLK1)

Prepared: 03/14/05 Analyzed: 03/16/05

Barium	ND	1.0	"							
Beryllium	ND	0.50	"							
Molybdenum	ND	1.0	"							

Laboratory Control Sample (5C14015-BS1)

Prepared & Analyzed: 03/14/05

Antimony	48.8	0.50	ug/l	50.0		98	85-115			
Arsenic	48.1	1.0	"	50.0		96	85-115			
Cadmium	48.7	0.25	"	50.0		97	90-115			
Chromium	46.1	2.0	"	50.0		92	85-115			
Cobalt	47.5	0.50	"	50.0		95	85-110			
Copper	48.1	0.50	"	50.0		96	90-115			
Lead	49.4	0.50	"	50.0		99	90-115			
Nickel	48.1	1.0	"	50.0		96	90-115			
Selenium	49.1	1.0	"	50.0		98	85-120			
Silver	47.0	0.25	"	50.0		94	90-115			
Thallium	48.0	1.0	"	50.0		96	75-115			
Vanadium	44.1	1.0	"	50.0		88	75-115			
Zinc	49.8	5.0	"	50.0		100	90-120			

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
 Reported:
 03/24/05 15:53

Total Metals by EPA 6000/7000 Series Methods - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5C14015 - EPA 3005A / EPA 6020
Laboratory Control Sample (5C14015-BS1)

Prepared: 03/14/05 Analyzed: 03/16/05

Barium	48.8	1.0	ug/l	50.0	98	85-115
Beryllium	48.1	0.50	"	50.0	96	75-125
Molybdenum	47.7	1.0	"	50.0	95	85-110

Matrix Spike (5C14015-MS1)

Source: MOB0728-05

Prepared & Analyzed: 03/14/05

Antimony	44.1	0.50	ug/l	50.0	0.54	87	85-115
Arsenic	50.6	1.0	"	50.0	1.7	98	85-115
Cadmium	48.4	0.25	"	50.0	0.37	96	90-115
Chromium	55.8	2.0	"	50.0	9.2	93	85-120
Cobalt	48.4	0.50	"	50.0	1.1	95	85-110
Copper	55.8	0.50	"	50.0	8.4	95	90-115
Lead	54.2	0.50	"	50.0	4.0	100	90-115
Nickel	56.1	1.0	"	50.0	8.5	95	90-115
Selenium	50.3	1.0	"	50.0	1.5	98	85-120
Silver	46.1	0.25	"	50.0	0.033	92	90-115
Thallium	49.2	1.0	"	50.0	0.0050	98	85-120
Vanadium	52.9	1.0	"	50.0	7.6	91	75-115
Zinc	81.6	5.0	"	50.0	37	89	90-120

QM02

Matrix Spike (5C14015-MS1)

Source: MOB0728-05

Prepared: 03/14/05 Analyzed: 03/16/05

Barium	131	10	"	50.0	76	110	85-115
Beryllium	46.7	5.0	"	50.0	0.090	93	75-125
Molybdenum	46.6	10	"	50.0	1.1	91	85-110

Matrix Spike Dup (5C14015-MSD1)

Source: MOB0728-05

Prepared & Analyzed: 03/14/05

Antimony	44.4	0.50	ug/l	50.0	0.54	88	85-115	0.7	10
Arsenic	50.6	1.0	"	50.0	1.7	98	85-115	0	10
Cadmium	48.5	0.25	"	50.0	0.37	96	90-115	0.2	10
Chromium	56.2	2.0	"	50.0	9.2	94	85-120	0.7	10
Cobalt	49.0	0.50	"	50.0	1.1	96	85-110	1	10
Copper	56.1	0.50	"	50.0	8.4	95	90-115	0.5	10
Lead	55.1	0.50	"	50.0	4.0	102	90-115	2	10
Nickel	56.8	1.0	"	50.0	8.5	97	90-115	1	15
Selenium	49.1	1.0	"	50.0	1.5	95	85-120	2	10
Silver	46.3	0.25	"	50.0	0.033	93	90-115	0.4	10
Thallium	49.8	1.0	"	50.0	0.0050	100	85-120	1	10
Vanadium	53.8	1.0	"	50.0	7.6	92	75-115	2	10
Zinc	83.0	5.0	"	50.0	37	92	90-120	2	10

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5634
Project Manager:Vidair

MOC0103
Reported:
03/24/05 15:53

**Total Metals by EPA 6000/7000 Series Methods - Quality Control
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5C14015 - EPA 3005A / EPA 6020

Matrix Spike Dup (5C14015-MSD1) **Source: MOB0728-05** Prepared: 03/14/05 Analyzed: 03/16/05

Barium	128	10	ug/l	50.0	76	104	85-115	2	10	
Beryllium	46.3	5.0	"	50.0	0.090	92	75-125	0.9	15	
Molybdenum	46.4	10	"	50.0	1.1	91	85-110	0.4	10	

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5634
Project Manager:Vidair

MOC0103
Reported:
03/24/05 15:53

**Tentatively Identified Compounds by GC/MS - Quality Control
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5C19005 - EPA 3510C SepFunnel / EPA 8270C

Blank (5C19005-BLK1)

Prepared: 03/19/05 Analyzed: 03/21/05

Hexanedioic acid, bis(2-ethylhexyl)	ND	5.0	ug/l							
benzaldehyde, 3-hydroxy-4-methoxy-	ND	5.0	"							
2(3H)-Benzothiazolone	ND	5.0	"							
1H-isoindole-1,3(2H)-dione	ND	5.0	"							
o-cyanobenzoic acid	ND	5.0	"							
cyclohexanamine, N-cyclohexyl-	ND	5.0	"							
Formamide, N-cyclohexyl-	ND	5.0	"							
cyclohexanone	ND	5.0	"							
Benzothiazole	ND	5.0	"							

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5634
Project Manager:Vidair

MOC0103
Reported:
03/24/05 15:53

**Semivolatile Organic Compounds by EPA Method 8270C - Quality Control
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5C19005 - EPA 3510C SepFunnel / EPA 8270C

Blank (5C19005-BLK1)

Prepared: 03/19/05 Analyzed: 03/21/05

N-Nitrosodimethylamine	ND	5.0	ug/l							
Carbazole	ND	5.0	"							
Pyridine	ND	20	"							
Benzidine	ND	100	"							
Aniline	ND	5.0	"							
Acenaphthene	ND	5.0	"							
Acenaphthylene	ND	5.0	"							
Anthracene	ND	5.0	"							
Benzo (a) anthracene	ND	5.0	"							
Benzo (a) pyrene	ND	5.0	"							
Benzo (b) fluoranthene	ND	5.0	"							
Benzo (g,h,i) perylene	ND	10	"							
Benzo (k) fluoranthene	ND	5.0	"							
Benzoic acid	ND	20	"							
Benzyl alcohol	ND	10	"							
Bis(2-chloroethoxy)methane	ND	5.0	"							
Bis(2-chloroethyl)ether	ND	10	"							
Bis(2-chloroisopropyl)ether	ND	5.0	"							
Bis(2-ethylhexyl)phthalate	ND	10	"							
4-Bromophenyl phenyl ether	ND	5.0	"							
Butyl benzyl phthalate	ND	5.0	"							
4-Chloroaniline	ND	50	"							
2-Chloronaphthalene	ND	5.0	"							
4-Chloro-3-methylphenol	ND	5.0	"							
2-Chlorophenol	ND	5.0	"							
4-Chlorophenyl phenyl ether	ND	10	"							
Chrysene	ND	5.0	"							
Dibenz (a,h) anthracene	ND	5.0	"							
Dibenzofuran	ND	5.0	"							
Di-n-butyl phthalate	ND	5.0	"							
1,2-Dichlorobenzene	ND	10	"							
1,3-Dichlorobenzene	ND	10	"							
1,4-Dichlorobenzene	ND	10	"							
3,3'-Dichlorobenzidine	ND	50	"							
2,4-Dichlorophenol	ND	5.0	"							
Diethyl phthalate	ND	5.0	"							

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5634
Project Manager:Vidair

MOC0103
Reported:
03/24/05 15:53

**Semivolatile Organic Compounds by EPA Method 8270C - Quality Control
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5C19005 - EPA 3510C SepFunnel / EPA 8270C

Blank (5C19005-BLK1)

Prepared: 03/19/05 Analyzed: 03/21/05

2,4-Dimethylphenol	ND	10	ug/l							
Dimethyl phthalate	ND	5.0	"							
4,6-Dinitro-2-methylphenol	ND	5.0	"							
2,4-Dinitrophenol	ND	10	"							
2,4-Dinitrotoluene	ND	5.0	"							
2,6-Dinitrotoluene	ND	5.0	"							
Di-n-octyl phthalate	ND	10	"							
Fluoranthene	ND	5.0	"							
Fluorene	ND	5.0	"							
Hexachlorobenzene	ND	5.0	"							
Hexachlorobutadiene	ND	10	"							
Hexachlorocyclopentadiene	ND	10	"							
Hexachloroethane	ND	10	"							
Indeno (1,2,3-cd) pyrene	ND	10	"							
Isophorone	ND	5.0	"							
2-Methylnaphthalene	ND	5.0	"							
2-Methylphenol	ND	5.0	"							
4-Methylphenol	ND	5.0	"							
Naphthalene	ND	5.0	"							
2-Nitroaniline	ND	10	"							
3-Nitroaniline	ND	100	"							
4-Nitroaniline	ND	50	"							
Nitrobenzene	ND	5.0	"							
2-Nitrophenol	ND	5.0	"							
4-Nitrophenol	ND	10	"							
N-Nitrosodi-n-propylamine	ND	5.0	"							
N-Nitrosodiphenylamine	ND	10	"							
Pentachlorophenol	ND	10	"							
Phenanthrene	ND	5.0	"							
Phenol	ND	5.0	"							
Pyrene	ND	5.0	"							
1,2,4-Trichlorobenzene	ND	10	"							
2,4,5-Trichlorophenol	ND	5.0	"							
2,4,6-Trichlorophenol	ND	5.0	"							
Surrogate: 2-Fluorophenol	54.1		"	100		54	40-115			

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
 Reported:
 03/24/05 15:53

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5C19005 - EPA 3510C SepFunnel / EPA 8270C
Blank (5C19005-BLK1)

Prepared: 03/19/05 Analyzed: 03/21/05

Surrogate: Phenol-d6	36.2		ug/l	100		36	20-115			
Surrogate: Nitrobenzene-d5	40.0		"	50.0		80	50-115			
Surrogate: 2-Fluorobiphenyl	39.4		"	50.0		79	70-115			
Surrogate: 2,4,6-Tribromophenol	75.8		"	100		76	35-115			
Surrogate: p-Terphenyl-d14	45.5		"	50.0		91	70-130			

Laboratory Control Sample (5C19005-BS1)

Prepared: 03/19/05 Analyzed: 03/21/05

Acenaphthene	49.8	5.0	ug/l	50.0		100	75-115			
4-Chloro-3-methylphenol	51.0	5.0	"	50.0		102	75-130			
2-Chlorophenol	44.1	5.0	"	50.0		88	45-120			
1,4-Dichlorobenzene	38.7	10	"	50.0		77	35-115			
2,4-Dinitrotoluene	52.7	5.0	"	50.0		105	75-120			
4-Nitrophenol	23.7	10	"	50.0		47	15-115			
N-Nitrosodi-n-propylamine	48.7	5.0	"	50.0		97	55-120			
Pentachlorophenol	48.5	10	"	50.0		97	30-120			
Phenol	23.7	5.0	"	50.0		47	25-115			
Pyrene	49.2	5.0	"	50.0		98	75-140			
1,2,4-Trichlorobenzene	41.6	10	"	50.0		83	35-115			
Surrogate: 2-Fluorophenol	55.9		"	100		56	40-115			
Surrogate: Phenol-d6	38.4		"	100		38	20-115			
Surrogate: Nitrobenzene-d5	39.0		"	50.0		78	50-115			
Surrogate: 2-Fluorobiphenyl	37.7		"	50.0		75	70-115			
Surrogate: 2,4,6-Tribromophenol	77.1		"	100		77	35-115			
Surrogate: p-Terphenyl-d14	40.9		"	50.0		82	70-130			

Laboratory Control Sample Dup (5C19005-BSD1)

Prepared: 03/19/05 Analyzed: 03/21/05

Acenaphthene	45.2	5.0	ug/l	50.0		90	75-115	10	15	
4-Chloro-3-methylphenol	45.8	5.0	"	50.0		92	75-130	11	15	
2-Chlorophenol	41.8	5.0	"	50.0		84	45-120	5	35	
1,4-Dichlorobenzene	37.1	10	"	50.0		74	35-115	4	20	
2,4-Dinitrotoluene	45.5	5.0	"	50.0		91	75-120	15	20	
4-Nitrophenol	19.2	10	"	50.0		38	15-115	21	35	
N-Nitrosodi-n-propylamine	45.0	5.0	"	50.0		90	55-120	8	20	
Pentachlorophenol	43.2	10	"	50.0		86	30-120	12	35	
Phenol	22.0	5.0	"	50.0		44	25-115	7	30	
Pyrene	44.5	5.0	"	50.0		89	75-140	10	15	
1,2,4-Trichlorobenzene	39.6	10	"	50.0		79	35-115	5	15	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Vidair

 MOC0103
Reported:
 03/24/05 15:53

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5C19005 - EPA 3510C SepFunnel / EPA 8270C
Laboratory Control Sample Dup (5C19005-BSD1)

Prepared: 03/19/05 Analyzed: 03/21/05

Surrogate: 2-Fluorophenol	55.5		ug/l	100		56	40-115			
Surrogate: Phenol-d6	37.3		"	100		37	20-115			
Surrogate: Nitrobenzene-d5	40.2		"	50.0		80	50-115			
Surrogate: 2-Fluorobiphenyl	38.0		"	50.0		76	70-115			
Surrogate: 2,4,6-Tribromophenol	77.8		"	100		78	35-115			
Surrogate: p-Terphenyl-d14	40.9		"	50.0		82	70-130			

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHHA Playground Study
Project Number:SAU5634
Project Manager:Vidair

MOC0103
Reported:
03/24/05 15:53

Notes and Definitions

S02 The surrogate recovery was below control limits.

R-05 The sample was diluted due to the presence of high levels of non-target analytes resulting in elevated reporting limits.

QM02 The spike recovery was below control limits for the MS and/or MSD. The batch was accepted based on acceptable LCS recovery.

HT-03 This sample was extracted beyond the EPA recommended holding time.

DET Analyte DETECTED

ND Analyte NOT DETECTED at or above the reporting limit or MDL, if MDL is specified

NR Not Reported

dry Sample results reported on a dry weight basis

RPD Relative Percent Difference

MDC 0103

HAZARDOUS MATERIALS ANALYSIS REQUEST	1. Authorization Number	HML No.	2. Page
	S A U S 6 3 4	To	of

REQUESTOR: VIDAIR/PETREAS
 ADDRESS (To Receive Results): 700 HEINZ AVE, SUITE 100, BERKELEY, CA 94710
 Phone: (510) 540-3003
 FAX: () - 2305

7. TAT Level: (check one)

1 2 3 4

* Unit Chief's Signature

8. DATE SAMPLED: 3/1/05
 10. ACTIVITY: SCD SRPD CIB SMB FPB SPPT Others

9. Codes (fill in all applicable codes)

a. Office	
b. INDEX	
c. PCA	
d. MPC	
e. SITE	
f. County	

11. SAMPLING LOCATION

a. EPA ID No.

b. Site: DEHHA PLAYGROUND STUDY

c. Address

Number	Street	City	ZIP
--------	--------	------	-----

12. SAMPLES:

a. ID	b. Collector's No.	c. HML No.	d. Type	e. Type	f. Size	g. Field Information
A	G		ANALYTICAL	GLASS	200 ml	1/16 OZ CONTAINER
B	S		"	"	"	"
C	O		"	"	"	"
D	CON		"	"	"	"
E						
F						

13. ANALYSIS REQUESTED: (X desired analysis and enter I.D.s from 12.u.)

INORGANIC ANALYSIS	Sample(s) ID	ORGANIC ANALYSIS	Sample(s) ID
<input checked="" type="checkbox"/> Metals Scan (6010)	6020 A-D	<input type="checkbox"/> CL-Pesticides (8081)	
<input type="checkbox"/> Metal(s) Specific		<input type="checkbox"/> OP-Pesticides (3141)	
<input type="checkbox"/> WET		<input type="checkbox"/> PCBs (8092)	
<input type="checkbox"/> Cyanides		<input type="checkbox"/> G R O (8015B)	
<input checked="" type="checkbox"/> Hg 7471 (others write in)	A-D	<input type="checkbox"/> D R O / Motor Oil / Both (circle one)	
<input type="checkbox"/> TCLP Analysis		<input type="checkbox"/> n-Hexane Extractables (1664)	
		<input type="checkbox"/> Flash Point (1020)	
		<input type="checkbox"/> VOCs including BTEX (8260)	
		<input type="checkbox"/> VOCs - LO Level (5035)	
		<input type="checkbox"/> VOCs - HI Level (5035)	
		<input checked="" type="checkbox"/> SVOCs (8270)	A-D
		<input checked="" type="checkbox"/> PAHs (8270) / SIM	A-D

14. ANALYSIS OBJECTIVE:

(check a box)

Waste Characterization
 Drinking H₂O Standards (applies to DW only)
 Treatment Standards
 Others (contact Lab supervisors first)

15. DETECTION LIMIT REQUIREMENTS: AS low as possible

16. SUPPLEMENTAL REQUESTS

Initials: _____
 Date: _____

17. LAB REMARKS: BUFFER CONTAINS CITRIC ACID SODIUM CITRATE, KCL, NaCl, PEPSIN (1mg/ml)

18. CHAIN OF CUSTODY:

a. M. Petreas, HAIL	3/1/05	to	
b. MAURICE SEALS, SEDONA	3/2/05	to	
c. J. Diamond	3/2/05	to	1840
d.		to	

Signature(s) Name(s) / Title(s) Inclusive Dates of Custody

California Department of Toxic Substances Control
Hazardous Materials Laboratory
 700 Heinz Avenue, Suite#150, Berkeley, CA 94710

SAMPLE / SAMPLE EXTRACT TRANSPORT CUSTODY

Receiving Lab / Section: Sequoia Lab

MDC0103

Sample Collection Site: BEHA PLAYGROUND

STUDY

HML # or Collector's #	Sample Type *	Analysis Requested	Location of Sample (s)	Remarks
G	AQUEOUS	Refer to SAR		
S	"	↓		
O	"			
CON	"			

- OSC = original sample container; SS = split sample; A = Aliquot; C = Citrate WET; E = Extract; D = acid digest; T = TCLP extract.

Release for transport by: Dr. Michael Chand

Time / Date 2:20 3/2/05

Transported to: Sequoia Lab/ GC/MS/ Org sec / Inorg sec/ Fed Ex / Others

By: ~~Sarah Satten~~ [Signature]

Time / Date 3/2/05 2:20pm

Received by: [Signature]

Time / Date 3/2/05

Returned to HML by: _____

Time / Date _____

SEQUOIA ANALYTICAL SAMPLE RECEIPT LOG

CLIENT NAME: DTSC
 REC. BY (PRINT): JH
 WORKORDER: MOB 6/03

DATE REC'D AT LAB: 3/2/05
 TIME REC'D AT LAB: 1840
 DATE LOGGED IN: 3-9-05

For Regulatory Purposes?
 DRINKING WATER YES/NO
 WASTE WATER YES/NO

(For clients requiring preservation checks at receipt, document here ↓)

CIRCLE THE APPROPRIATE RESPONSE	LAB SAMPLE #	DASH #	CLIENT ID	CONTAINER DESCRIPTION	PRESERVATIVE	pH	SAMPLE MATRIX	DATE SAMPLED	REMARKS: CONDITION (ETC.)
1. Custody Seal(s) Present / <u>Absent</u> Intact / Broken*	01	A	G	16oz Jar	-	-	W	3/1/05	[Large diagonal line with handwritten '3/2/05' and scribbles]
2. Chain-of-Custody <u>Present</u> / Absent*	02	L	S	L	L	L	L	L	
3. Traffic Reports or Packing List: Present / <u>Absent</u>	03	L	CON	L	L	L	L	L	
4. Airbill: Airbill / Sticker Present / <u>Absent</u>									
5. Airbill #:									
6. Sample Labels: <u>Present</u> / Absent									
7. Sample IDs: <u>Listed</u> / Not Listed on Chain-of-Custody									
8. Sample Condition: <u>Intact</u> / Broken* / Leaking*									
9. Does information on chain-of-custody, traffic reports and sample labels agree? <u>Yes</u> / No*									
10. Sample received within hold time? <u>Yes</u> / No*									
11. Adequate sample volume received? <u>Yes</u> / No*									
12. Proper Preservatives used? <u>Yes</u> / No*									
13. Trip Blank / Temp Blank Received? (circle which, if yes) <u>Yes</u> / No*									
14. Temp Rec. at Lab: <u>4.3</u> Is temp 4 +/- 2°C? <u>Yes</u> / No** <small>(Acceptance range for samples requiring thermal pres.)</small>									

**Exception (if any): METALS / DFF ON ICE or Problem COC

*IF CIRCLED, CONTACT PROJECT MANAGER AND ATTACH RECORD OF RESOLUTION.

Contractor's Report to the Board

Evaluation of Health Effects of Recycled Waste Tires in Playground and Track Products

(Publication #622-06-013)

Produced under contract by:



January 2007

Appendix B: Wipe Sampling Raw Data




30 June, 2005

Myrto Petreas
Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley, CA 94710

RE: OEHHA Playground Study
Work Order: MOF0403

Enclosed are the results of analyses for samples received by the laboratory on 06/08/05 18:45. If you have any questions concerning this report, please feel free to contact me.

Sincerely,



Theresa Allen
Project Manager

CA ELAP Certificate #1210

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5634
Project Manager:Myrto Petreas

MOF0403
Reported:
06/30/05 13:37

ANALYTICAL REPORT FOR SAMPLES

Sample ID	Laboratory ID	Matrix	Date Sampled	Date Received
A	MOF0403-01	Wipe	06/07/05 00:00	06/08/05 18:45
B	MOF0403-02	Wipe	06/07/05 00:00	06/08/05 18:45
C	MOF0403-03	Wipe	06/07/05 00:00	06/08/05 18:45
D	MOF0403-04	Wipe	06/07/05 00:00	06/08/05 18:45
E	MOF0403-05	Wipe	06/07/05 00:00	06/08/05 18:45
F	MOF0403-06	Wipe	06/07/05 00:00	06/08/05 18:45
G	MOF0403-07	Wipe	06/07/05 00:00	06/08/05 18:45
H	MOF0403-08	Wipe	06/07/05 00:00	06/08/05 18:45
I	MOF0403-09	Wipe	06/07/05 00:00	06/08/05 18:45
J	MOF0403-10	Wipe	06/07/05 00:00	06/08/05 18:45
K	MOF0403-11	Wipe	06/07/05 00:00	06/08/05 18:45
L	MOF0403-12	Wipe	06/07/05 00:00	06/08/05 18:45

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5634
Project Manager:Myrto Petreas

MOF0403
Reported:
06/30/05 13:37

**Total Metals by EPA 6020 ICPMS
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
A (MOF0403-01) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
Aluminum	71	2.0	ug/Wipe	20	5F22029	06/22/05	06/22/05	EPA 6020	
B (MOF0403-02) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
Aluminum	110	2.0	ug/Wipe	20	5F22029	06/22/05	06/22/05	EPA 6020	
C (MOF0403-03) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
Aluminum	75	2.0	ug/Wipe	20	5F22029	06/22/05	06/22/05	EPA 6020	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
 Reported:
 06/30/05 13:37

Total Metals by EPA 6000/7000 Series Methods Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
A (MOF0403-01) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
Calcium	400	12	ug/Wipe	1	5F22022	06/22/05	06/22/05	EPA 6010B	
Iron	140	5.0	"	"	"	"	"	"	
Potassium	ND	100	"	"	"	"	06/22/05	"	
Antimony	2.8	1.0	"	20	5F22029	"	06/22/05	EPA 6020	
Arsenic	ND	1.0	"	"	"	"	"	"	
Barium	ND	5.0	"	"	"	"	"	"	
Beryllium	ND	0.20	"	"	"	"	"	"	
Cadmium	ND	0.60	"	"	"	"	"	"	
Chromium	ND	10	"	"	"	"	"	"	
Cobalt	ND	2.0	"	"	"	"	"	"	
Copper	ND	5.0	"	"	"	"	"	"	
Lead	ND	5.0	"	"	"	"	"	"	
Molybdenum	ND	2.0	"	"	"	"	"	"	
Nickel	ND	8.0	"	"	"	"	"	"	
Selenium	ND	1.0	"	"	"	"	"	"	
Silver	ND	1.0	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	ND	2.0	"	"	"	"	"	"	
Zinc	ND	10	"	"	"	"	"	"	
Magnesium	67	2.5	"	1	5F22022	"	06/22/05	EPA 6010B	
B (MOF0403-02) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
Calcium	450	12	ug/Wipe	1	5F22022	06/22/05	06/22/05	EPA 6010B	
Iron	220	5.0	"	"	"	"	"	"	
Potassium	120	100	"	"	"	"	"	"	
Antimony	2.8	1.0	"	20	5F22029	"	06/22/05	EPA 6020	
Arsenic	ND	1.0	"	"	"	"	"	"	
Barium	ND	5.0	"	"	"	"	"	"	
Beryllium	ND	0.20	"	"	"	"	"	"	
Cadmium	ND	0.60	"	"	"	"	"	"	
Chromium	ND	10	"	"	"	"	"	"	
Cobalt	ND	2.0	"	"	"	"	"	"	
Copper	ND	5.0	"	"	"	"	"	"	
Lead	ND	5.0	"	"	"	"	"	"	
Molybdenum	ND	2.0	"	"	"	"	"	"	
Nickel	ND	8.0	"	"	"	"	"	"	
Selenium	ND	1.0	"	"	"	"	"	"	
Silver	ND	1.0	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	ND	2.0	"	"	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
Reported:
 06/30/05 13:37

**Total Metals by EPA 6000/7000 Series Methods
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
B (MOF0403-02) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
Zinc	ND	10	ug/Wipe	20	5F22029	06/22/05	06/22/05	EPA 6020	
Magnesium	88	2.5	"	1	5F22022	"	06/22/05	EPA 6010B	
C (MOF0403-03) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
Calcium	240	12	ug/Wipe	1	5F22022	06/22/05	06/22/05	EPA 6010B	
Iron	170	5.0	"	"	"	"	"	"	
Potassium	ND	100	"	"	"	"	"	"	
Antimony	4.2	1.0	"	20	5F22029	"	06/22/05	EPA 6020	
Arsenic	ND	1.0	"	"	"	"	"	"	
Barium	ND	5.0	"	"	"	"	"	"	
Beryllium	ND	0.20	"	"	"	"	"	"	
Cadmium	ND	0.60	"	"	"	"	"	"	
Chromium	ND	10	"	"	"	"	"	"	
Cobalt	ND	2.0	"	"	"	"	"	"	
Copper	ND	5.0	"	"	"	"	"	"	
Lead	ND	5.0	"	"	"	"	"	"	
Molybdenum	ND	2.0	"	"	"	"	"	"	
Nickel	ND	8.0	"	"	"	"	"	"	
Selenium	ND	1.0	"	"	"	"	"	"	
Silver	ND	1.0	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	ND	2.0	"	"	"	"	"	"	
Zinc	ND	10	"	"	"	"	"	"	
Magnesium	58	2.5	"	1	5F22022	"	06/22/05	EPA 6010B	

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5634
Project Manager:Myrto Petreas

MOF0403
Reported:
06/30/05 13:37

**Total Metals by EPA 6000/7000 Series Methods
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
D (MOF0403-04) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
Mercury	ND	0.0050	ug/Wipe	1	5F24016	06/24/05	06/24/05	EPA 7471A	
E (MOF0403-05) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
Mercury	ND	0.0050	ug/Wipe	1	5F24016	06/24/05	06/24/05	EPA 7471A	
F (MOF0403-06) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
Mercury	ND	0.0050	ug/Wipe	1	5F24016	06/24/05	06/24/05	EPA 7471A	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
 Reported:
 06/30/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
---------	--------	-----------------	-------	----------	-------	----------	----------	--------	-------

G (MOF0403-07) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45

Acenaphthene	ND	5.0	ug/Wipe	1	5F15018	06/15/05	06/16/05	EPA 8270C	
Acenaphthylene	ND	5.0	"	"	"	"	"	"	
Anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) pyrene	ND	5.0	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzoic acid	ND	10	"	"	"	"	"	"	
Benzyl alcohol	ND	10	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	5.0	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	10	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	5.0	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	10	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	5.0	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	5.0	"	"	"	"	"	"	
4-Chloroaniline	ND	50	"	"	"	"	"	"	
2-Chloronaphthalene	ND	5.0	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	5.0	"	"	"	"	"	"	
2-Chlorophenol	ND	5.0	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	10	"	"	"	"	"	"	
Chrysene	ND	5.0	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	5.0	"	"	"	"	"	"	
Dibenzofuran	ND	5.0	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	5.0	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	10	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	50	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	5.0	"	"	"	"	"	"	
Diethyl phthalate	ND	5.0	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	10	"	"	"	"	"	"	
Dimethyl phthalate	ND	5.0	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	5.0	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	10	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	10	"	"	"	"	"	"	
Fluoranthene	ND	5.0	"	"	"	"	"	"	
Fluorene	ND	5.0	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
Reported:
 06/30/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
---------	--------	-----------------	-------	----------	-------	----------	----------	--------	-------

G (MOF0403-07) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45

Hexachlorobenzene	ND	5.0	ug/Wipe	1	5F15018	06/15/05	06/16/05	EPA 8270C	
Hexachlorobutadiene	ND	10	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	10	"	"	"	"	"	"	
Hexachloroethane	ND	10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	10	"	"	"	"	"	"	
Isophorone	ND	5.0	"	"	"	"	"	"	
2-Methylnaphthalene	ND	5.0	"	"	"	"	"	"	
2-Methylphenol	ND	5.0	"	"	"	"	"	"	
4-Methylphenol	ND	5.0	"	"	"	"	"	"	
Naphthalene	ND	5.0	"	"	"	"	"	"	
2-Nitroaniline	ND	10	"	"	"	"	"	"	
3-Nitroaniline	ND	100	"	"	"	"	"	"	
4-Nitroaniline	ND	50	"	"	"	"	"	"	
Nitrobenzene	ND	5.0	"	"	"	"	"	"	
2-Nitrophenol	ND	5.0	"	"	"	"	"	"	
4-Nitrophenol	ND	10	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	5.0	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	10	"	"	"	"	"	"	
Pentachlorophenol	ND	10	"	"	"	"	"	"	
Phenanthrene	ND	5.0	"	"	"	"	"	"	
Phenol	ND	5.0	"	"	"	"	"	"	
Pyrene	ND	5.0	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	10	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		77 %		25-121	"	"	"	"	
<i>Surrogate: Phenol-d6</i>		82 %		24-113	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		68 %		23-120	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		77 %		30-115	"	"	"	"	
<i>Surrogate: 2,4,6-Tribromophenol</i>		78 %		19-122	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		69 %		18-137	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5634
Project Manager:Myrto Petreas

MOF0403
Reported:
06/30/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
H (MOF0403-08) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
Acenaphthene	ND	5.0	ug/Wipe	1	5F15018	06/15/05	06/16/05	EPA 8270C	
Acenaphthylene	ND	5.0	"	"	"	"	"	"	
Anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) pyrene	ND	5.0	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzoic acid	ND	10	"	"	"	"	"	"	
Benzyl alcohol	ND	10	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	5.0	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	10	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	5.0	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	10	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	5.0	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	5.0	"	"	"	"	"	"	
4-Chloroaniline	ND	50	"	"	"	"	"	"	
2-Chloronaphthalene	ND	5.0	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	5.0	"	"	"	"	"	"	
2-Chlorophenol	ND	5.0	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	10	"	"	"	"	"	"	
Chrysene	ND	5.0	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	5.0	"	"	"	"	"	"	
Dibenzofuran	ND	5.0	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	5.0	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	10	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	50	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	5.0	"	"	"	"	"	"	
Diethyl phthalate	ND	5.0	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	10	"	"	"	"	"	"	
Dimethyl phthalate	ND	5.0	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	5.0	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	10	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	10	"	"	"	"	"	"	
Fluoranthene	ND	5.0	"	"	"	"	"	"	
Fluorene	ND	5.0	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
Reported:
 06/30/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
---------	--------	-----------------	-------	----------	-------	----------	----------	--------	-------

H (MOF0403-08) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45

Hexachlorobenzene	ND	5.0	ug/Wipe	1	5F15018	06/15/05	06/16/05	EPA 8270C	
Hexachlorobutadiene	ND	10	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	10	"	"	"	"	"	"	
Hexachloroethane	ND	10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	10	"	"	"	"	"	"	
Isophorone	ND	5.0	"	"	"	"	"	"	
2-Methylnaphthalene	ND	5.0	"	"	"	"	"	"	
2-Methylphenol	ND	5.0	"	"	"	"	"	"	
4-Methylphenol	ND	5.0	"	"	"	"	"	"	
Naphthalene	ND	5.0	"	"	"	"	"	"	
2-Nitroaniline	ND	10	"	"	"	"	"	"	
3-Nitroaniline	ND	100	"	"	"	"	"	"	
4-Nitroaniline	ND	50	"	"	"	"	"	"	
Nitrobenzene	ND	5.0	"	"	"	"	"	"	
2-Nitrophenol	ND	5.0	"	"	"	"	"	"	
4-Nitrophenol	ND	10	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	5.0	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	10	"	"	"	"	"	"	
Pentachlorophenol	ND	10	"	"	"	"	"	"	
Phenanthrene	ND	5.0	"	"	"	"	"	"	
Phenol	ND	5.0	"	"	"	"	"	"	
Pyrene	ND	5.0	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	10	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		86 %		25-121	"	"	"	"	
<i>Surrogate: Phenol-d6</i>		94 %		24-113	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		79 %		23-120	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		89 %		30-115	"	"	"	"	
<i>Surrogate: 2,4,6-Tribromophenol</i>		97 %		19-122	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		84 %		18-137	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
Reported:
 06/30/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
I (MOF0403-09) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
Acenaphthene	ND	5.0	ug/Wipe	1	5F15018	06/15/05	06/16/05	EPA 8270C	
Acenaphthylene	ND	5.0	"	"	"	"	"	"	
Anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) pyrene	ND	5.0	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzoic acid	ND	10	"	"	"	"	"	"	
Benzyl alcohol	ND	10	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	5.0	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	10	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	5.0	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	10	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	5.0	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	5.0	"	"	"	"	"	"	
4-Chloroaniline	ND	50	"	"	"	"	"	"	
2-Chloronaphthalene	ND	5.0	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	5.0	"	"	"	"	"	"	
2-Chlorophenol	ND	5.0	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	10	"	"	"	"	"	"	
Chrysene	ND	5.0	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	5.0	"	"	"	"	"	"	
Dibenzofuran	ND	5.0	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	5.0	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	10	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	50	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	5.0	"	"	"	"	"	"	
Diethyl phthalate	ND	5.0	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	10	"	"	"	"	"	"	
Dimethyl phthalate	ND	5.0	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	5.0	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	10	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	10	"	"	"	"	"	"	
Fluoranthene	ND	5.0	"	"	"	"	"	"	
Fluorene	ND	5.0	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
Reported:
 06/30/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
I (MOF0403-09) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
Hexachlorobenzene	ND	5.0	ug/Wipe	1	5F15018	06/15/05	06/16/05	EPA 8270C	
Hexachlorobutadiene	ND	10	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	10	"	"	"	"	"	"	
Hexachloroethane	ND	10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	10	"	"	"	"	"	"	
Isophorone	ND	5.0	"	"	"	"	"	"	
2-Methylnaphthalene	ND	5.0	"	"	"	"	"	"	
2-Methylphenol	ND	5.0	"	"	"	"	"	"	
4-Methylphenol	ND	5.0	"	"	"	"	"	"	
Naphthalene	ND	5.0	"	"	"	"	"	"	
2-Nitroaniline	ND	10	"	"	"	"	"	"	
3-Nitroaniline	ND	100	"	"	"	"	"	"	
4-Nitroaniline	ND	50	"	"	"	"	"	"	
Nitrobenzene	ND	5.0	"	"	"	"	"	"	
2-Nitrophenol	ND	5.0	"	"	"	"	"	"	
4-Nitrophenol	ND	10	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	5.0	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	10	"	"	"	"	"	"	
Pentachlorophenol	ND	10	"	"	"	"	"	"	
Phenanthrene	ND	5.0	"	"	"	"	"	"	
Phenol	ND	5.0	"	"	"	"	"	"	
Pyrene	ND	5.0	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	10	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		81 %		25-121	"	"	"	"	
<i>Surrogate: Phenol-d6</i>		92 %		24-113	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		78 %		23-120	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		93 %		30-115	"	"	"	"	
<i>Surrogate: 2,4,6-Tribromophenol</i>		76 %		19-122	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		82 %		18-137	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
 Reported:
 06/30/05 13:37

Polynuclear Aromatic Compounds by GC/MS with Selected Ion Monitoring

Sequoia Analytical - Petaluma

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
---------	--------	-----------------	-------	----------	-------	----------	----------	--------	-------

J (MOF0403-10) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45

Naphthalene	ND	810	ug/Wipe	1	5060028	06/16/05	06/16/05	GCMS-SIM	
Acenaphthylene	ND	810	"	"	"	"	"	"	
Acenaphthene	ND	810	"	"	"	"	"	"	
Fluorene	ND	810	"	"	"	"	"	"	
Phenanthrene	ND	810	"	"	"	"	"	"	
Anthracene	ND	810	"	"	"	"	"	"	
Fluoranthene	ND	810	"	"	"	"	"	"	
Pyrene	ND	810	"	"	"	"	"	"	
Benzo (a) anthracene	ND	810	"	"	"	"	"	"	
Chrysene	ND	810	"	"	"	"	"	"	
Benzo (b+k) fluoranthene (total)	ND	1600	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	810	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	810	"	"	"	"	"	"	
Benzo (a) pyrene	ND	810	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	810	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	810	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	810	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		99 %	50-150		"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		104 %	50-150		"	"	"	"	
<i>Surrogate: Terphenyl-d14</i>		108 %	50-150		"	"	"	"	

K (MOF0403-11) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45

Naphthalene	ND	810	ug/Wipe	1	5060028	06/16/05	06/16/05	GCMS-SIM	
Acenaphthylene	ND	810	"	"	"	"	"	"	
Acenaphthene	ND	810	"	"	"	"	"	"	
Fluorene	ND	810	"	"	"	"	"	"	
Phenanthrene	ND	810	"	"	"	"	"	"	
Anthracene	ND	810	"	"	"	"	"	"	
Fluoranthene	ND	810	"	"	"	"	"	"	
Pyrene	ND	810	"	"	"	"	"	"	
Benzo (a) anthracene	ND	810	"	"	"	"	"	"	
Chrysene	ND	810	"	"	"	"	"	"	
Benzo (b+k) fluoranthene (total)	ND	1600	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	810	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	810	"	"	"	"	"	"	
Benzo (a) pyrene	ND	810	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	810	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	810	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	810	"	"	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
 Reported:
 06/30/05 13:37

Polynuclear Aromatic Compounds by GC/MS with Selected Ion Monitoring
Sequoia Analytical - Petaluma

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
K (MOF0403-11) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
<i>Surrogate: Nitrobenzene-d5</i>		88 %	50-150		5060028	06/16/05	06/16/05	GCMS-SIM	
<i>Surrogate: 2-Fluorobiphenyl</i>		90 %	50-150		"	"	"	"	
<i>Surrogate: Terphenyl-d14</i>		98 %	50-150		"	"	"	"	
L (MOF0403-12) Wipe Sampled: 06/07/05 00:00 Received: 06/08/05 18:45									
Naphthalene	ND	810	ug/Wipe	1	5060028	06/16/05	06/16/05	GCMS-SIM	
Acenaphthylene	ND	810	"	"	"	"	"	"	
Acenaphthene	ND	810	"	"	"	"	"	"	
Fluorene	ND	810	"	"	"	"	"	"	
Phenanthrene	ND	810	"	"	"	"	"	"	
Anthracene	ND	810	"	"	"	"	"	"	
Fluoranthene	ND	810	"	"	"	"	"	"	
Pyrene	ND	810	"	"	"	"	"	"	
Benzo (a) anthracene	ND	810	"	"	"	"	"	"	
Chrysene	ND	810	"	"	"	"	"	"	
Benzo (b+k) fluoranthene (total)	ND	1600	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	810	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	810	"	"	"	"	"	"	
Benzo (a) pyrene	ND	810	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	810	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	810	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	810	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		94 %	50-150		"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		94 %	50-150		"	"	"	"	
<i>Surrogate: Terphenyl-d14</i>		98 %	50-150		"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5634
Project Manager:Myrto Petreas

MOF0403
Reported:
06/30/05 13:37

**Total Metals by EPA 6020 ICPMS - Quality Control
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5F22029 - EPA 3050B / EPA 6020

Blank (5F22029-BLK1)

Prepared & Analyzed: 06/22/05

Aluminum ND 2.0 ug/Wipe

Laboratory Control Sample (5F22029-BS1)

Prepared & Analyzed: 06/22/05

Aluminum 51.0 2.0 ug/Wipe 50.0 102 80-120

Laboratory Control Sample Dup (5F22029-BSD1)

Prepared & Analyzed: 06/22/05

Aluminum 51.3 2.0 ug/Wipe 50.0 103 80-120 0.6 200

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
Reported:
 06/30/05 13:37

Total Metals by EPA 6000/7000 Series Methods - Quality Control
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F22022 - EPA 3050B / EPA 6010B
Blank (5F22022-BLK1)

Prepared & Analyzed: 06/22/05

Magnesium	ND	2.5	ug/Wipe							
Calcium	ND	12	"							
Iron	ND	5.0	"							
Potassium	ND	100	"							

Laboratory Control Sample (5F22022-BS1)

Prepared & Analyzed: 06/22/05

Magnesium	514	2.5	ug/Wipe	500		103	85-115			
Calcium	551	12	"	500		110	85-115			
Iron	52.6	5.0	"	50.0		105	85-115			
Potassium	506	100	"	500		101	70-125			

Laboratory Control Sample (5F22022-BS2)

Prepared & Analyzed: 06/22/05

Magnesium	509	2.5	ug/Wipe	500		102	85-115			
Calcium	532	12	"	500		106	85-115			
Iron	52.4	5.0	"	50.0		105	85-115			
Potassium	470	100	"	500		94	70-125			

Batch 5F22029 - EPA 3050B / EPA 6020
Blank (5F22029-BLK1)

Prepared & Analyzed: 06/22/05

Antimony	ND	1.0	ug/Wipe							
Arsenic	ND	1.0	"							
Barium	ND	5.0	"							
Beryllium	ND	0.20	"							
Cadmium	ND	0.60	"							
Chromium	ND	10	"							
Cobalt	ND	2.0	"							
Copper	ND	5.0	"							
Lead	ND	5.0	"							
Molybdenum	ND	2.0	"							
Nickel	ND	8.0	"							
Selenium	ND	1.0	"							
Silver	ND	1.0	"							
Thallium	ND	1.0	"							
Vanadium	ND	2.0	"							
Zinc	ND	10	"							

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5634
Project Manager:Myrto Petreas

MOF0403
Reported:
06/30/05 13:37

**Total Metals by EPA 6000/7000 Series Methods - Quality Control
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5F22029 - EPA 3050B / EPA 6020

Laboratory Control Sample (5F22029-BS1)

Prepared & Analyzed: 06/22/05

Antimony	48.3	1.0	ug/Wipe	50.0		97	80-120			
Arsenic	49.8	1.0	"	50.0		100	80-120			
Barium	47.7	5.0	"	50.0		95	80-120			
Beryllium	52.0	0.20	"	50.0		104	80-120			
Cadmium	49.3	0.60	"	50.0		99	80-120			
Chromium	54.2	10	"	50.0		108	80-120			
Cobalt	53.4	2.0	"	50.0		107	80-120			
Copper	52.5	5.0	"	50.0		105	80-120			
Lead	53.4	5.0	"	50.0		107	80-120			
Molybdenum	49.6	2.0	"	50.0		99	80-120			
Nickel	52.4	8.0	"	50.0		105	80-120			
Selenium	49.7	1.0	"	50.0		99	80-120			
Silver	50.6	1.0	"	50.0		101	80-120			
Thallium	53.8	1.0	"	50.0		108	80-120			
Vanadium	48.1	2.0	"	50.0		96	80-120			
Zinc	53.2	10	"	50.0		106	80-120			

Laboratory Control Sample Dup (5F22029-BS1)

Prepared & Analyzed: 06/22/05

Antimony	49.1	1.0	ug/Wipe	50.0		98	80-120	2	20	
Arsenic	50.5	1.0	"	50.0		101	80-120	1	20	
Barium	47.7	5.0	"	50.0		95	80-120	0	20	
Beryllium	51.8	0.20	"	50.0		104	80-120	0.4	20	
Cadmium	49.5	0.60	"	50.0		99	80-120	0.4	20	
Chromium	55.0	10	"	50.0		110	80-120	1	20	
Cobalt	53.5	2.0	"	50.0		107	80-120	0.2	20	
Copper	53.0	5.0	"	50.0		106	80-120	0.9	20	
Lead	53.4	5.0	"	50.0		107	80-120	0	20	
Molybdenum	50.5	2.0	"	50.0		101	80-120	2	20	
Nickel	53.0	8.0	"	50.0		106	80-120	1	20	
Selenium	49.9	1.0	"	50.0		100	80-120	0.4	20	
Silver	51.8	1.0	"	50.0		104	80-120	2	20	
Thallium	53.5	1.0	"	50.0		107	80-120	0.6	20	
Vanadium	48.4	2.0	"	50.0		97	80-120	0.6	20	
Zinc	54.0	10	"	50.0		108	80-120	1	20	

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5634
Project Manager:Myrto Petreas

MOF0403
Reported:
06/30/05 13:37

**Total Metals by EPA 6000/7000 Series Methods - Quality Control
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5F24016 - EPA 7471A / EPA 7471A

Blank (5F24016-BLK1)

Prepared & Analyzed: 06/24/05

Mercury ND 0.0050 ug/Wipe

Laboratory Control Sample (5F24016-BS1)

Prepared & Analyzed: 06/24/05

Mercury 0.361 0.0050 ug/Wipe 0.400 90 75-125

Laboratory Control Sample (5F24016-BS2)

Prepared & Analyzed: 06/24/05

Mercury 0.382 0.0050 ug/Wipe 0.400 96 75-125

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
Reported:
 06/30/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F15018 - EPA 3550 Wipe / EPA 8270C
Blank (5F15018-BLK1)

Prepared: 06/15/05 Analyzed: 06/16/05

Acenaphthene	ND	0.17	ug/Wipe							
Acenaphthylene	ND	0.17	"							
Anthracene	ND	0.17	"							
Benzo (a) anthracene	ND	0.17	"							
Benzo (a) pyrene	ND	0.17	"							
Benzo (b) fluoranthene	ND	0.17	"							
Benzo (g,h,i) perylene	ND	0.33	"							
Benzo (k) fluoranthene	ND	0.17	"							
Benzoic acid	ND	0.33	"							
Benzyl alcohol	ND	0.33	"							
Bis(2-chloroethoxy)methane	ND	0.17	"							
Bis(2-chloroethyl)ether	ND	0.33	"							
Bis(2-chloroisopropyl)ether	ND	0.17	"							
Bis(2-ethylhexyl)phthalate	ND	0.33	"							
4-Bromophenyl phenyl ether	ND	0.17	"							
Butyl benzyl phthalate	ND	0.17	"							
4-Chloroaniline	ND	1.7	"							
2-Chloronaphthalene	ND	0.17	"							
4-Chloro-3-methylphenol	ND	0.17	"							
2-Chlorophenol	ND	0.17	"							
4-Chlorophenyl phenyl ether	ND	0.33	"							
Chrysene	ND	0.17	"							
Dibenz (a,h) anthracene	ND	0.17	"							
Dibenzofuran	ND	0.17	"							
Di-n-butyl phthalate	ND	0.17	"							
1,2-Dichlorobenzene	ND	0.33	"							
1,3-Dichlorobenzene	ND	0.33	"							
1,4-Dichlorobenzene	ND	0.33	"							
3,3'-Dichlorobenzidine	ND	1.7	"							
2,4-Dichlorophenol	ND	0.17	"							
Diethyl phthalate	ND	0.17	"							
2,4-Dimethylphenol	ND	0.33	"							
Dimethyl phthalate	ND	0.17	"							
4,6-Dinitro-2-methylphenol	ND	0.17	"							
2,4-Dinitrophenol	ND	0.33	"							
2,4-Dinitrotoluene	ND	0.17	"							

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
Reported:
 06/30/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5F15018 - EPA 3550 Wipe / EPA 8270C
Blank (5F15018-BLK1)

Prepared: 06/15/05 Analyzed: 06/16/05

2,6-Dinitrotoluene	ND	0.17	ug/Wipe							
Di-n-octyl phthalate	ND	0.33	"							
Fluoranthene	ND	0.17	"							
Fluorene	ND	0.17	"							
Hexachlorobenzene	ND	0.17	"							
Hexachlorobutadiene	ND	0.33	"							
Hexachlorocyclopentadiene	ND	0.33	"							
Hexachloroethane	ND	0.33	"							
Indeno (1,2,3-cd) pyrene	ND	0.33	"							
Isophorone	ND	0.17	"							
2-Methylnaphthalene	ND	0.17	"							
2-Methylphenol	ND	0.17	"							
4-Methylphenol	ND	0.17	"							
Naphthalene	ND	0.17	"							
2-Nitroaniline	ND	0.33	"							
3-Nitroaniline	ND	3.3	"							
4-Nitroaniline	ND	1.7	"							
Nitrobenzene	ND	0.17	"							
2-Nitrophenol	ND	0.17	"							
4-Nitrophenol	ND	0.33	"							
N-Nitrosodi-n-propylamine	ND	0.17	"							
N-Nitrosodiphenylamine	ND	0.33	"							
Pentachlorophenol	ND	0.33	"							
Phenanthrene	ND	0.17	"							
Phenol	ND	0.17	"							
Pyrene	ND	0.17	"							
1,2,4-Trichlorobenzene	ND	0.33	"							
2,4,5-Trichlorophenol	ND	0.17	"							
2,4,6-Trichlorophenol	ND	0.17	"							
<i>Surrogate: 2-Fluorophenol</i>	3.18		"	3.33		95	25-121			
<i>Surrogate: Phenol-d6</i>	3.40		"	3.33		102	24-113			
<i>Surrogate: Nitrobenzene-d5</i>	1.43		"	1.67		86	23-120			
<i>Surrogate: 2-Fluorobiphenyl</i>	1.64		"	1.67		98	30-115			
<i>Surrogate: 2,4,6-Tribromophenol</i>	2.85		"	3.33		86	19-122			
<i>Surrogate: p-Terphenyl-d14</i>	1.55		"	1.67		93	18-137			

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
Reported:
 06/30/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F15018 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample (5F15018-BS1)

Prepared: 06/15/05 Analyzed: 06/16/05

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
Acenaphthene	1.67	0.17	ug/Wipe	1.67		100	31-137			
Acenaphthylene	1.70	0.17	"	1.67		102	0-200			
Anthracene	1.69	0.17	"	1.67		101	0-200			
Benzo (a) anthracene	1.67	0.17	"	1.67		100	0-200			
Benzo (a) pyrene	1.64	0.17	"	1.67		98	0-200			
Benzo (b) fluoranthene	1.52	0.17	"	1.67		91	0-200			
Benzo (g,h,i) perylene	1.82	0.33	"	1.67		109	0-200			
Benzo (k) fluoranthene	1.57	0.17	"	1.67		94	0-200			
Benzyl alcohol	1.59	0.33	"	1.67		95	0-200			
Bis(2-chloroethoxy)methane	1.70	0.17	"	1.67		102	0-200			
Bis(2-chloroethyl)ether	1.55	0.33	"	1.67		93	0-200			
Bis(2-chloroisopropyl)ether	1.55	0.17	"	1.67		93	0-200			
Bis(2-ethylhexyl)phthalate	1.73	0.33	"	1.67		104	0-200			
4-Bromophenyl phenyl ether	1.70	0.17	"	1.67		102	0-200			
Butyl benzyl phthalate	1.78	0.17	"	1.67		107	0-200			
4-Chloroaniline	1.23	1.7	"	1.67		74	0-200			
2-Chloronaphthalene	1.58	0.17	"	1.67		95	0-200			
4-Chloro-3-methylphenol	1.72	0.17	"	1.67		103	26-103			
2-Chlorophenol	1.55	0.17	"	1.67		93	25-102			
4-Chlorophenyl phenyl ether	1.61	0.33	"	1.67		96	0-200			
Chrysene	1.73	0.17	"	1.67		104	0-200			
Dibenz (a,h) anthracene	1.91	0.17	"	1.67		114	0-200			
Dibenzofuran	1.64	0.17	"	1.67		98	0-200			
Di-n-butyl phthalate	1.83	0.17	"	1.67		110	0-200			
1,2-Dichlorobenzene	1.30	0.33	"	1.67		78	0-200			
1,3-Dichlorobenzene	1.26	0.33	"	1.67		75	0-200			
1,4-Dichlorobenzene	1.30	0.33	"	1.67		78	28-104			
2,4-Dichlorophenol	1.61	0.17	"	1.67		96	0-200			
Diethyl phthalate	1.64	0.17	"	1.67		98	0-200			
2,4-Dimethylphenol	1.32	0.33	"	1.67		79	0-200			
Dimethyl phthalate	1.63	0.17	"	1.67		98	0-200			
4,6-Dinitro-2-methylphenol	1.62	0.17	"	1.67		97	0-200			
2,4-Dinitrophenol	1.41	0.33	"	1.67		84	0-200			
2,4-Dinitrotoluene	1.61	0.17	"	1.67		96	28-89			QL06
2,6-Dinitrotoluene	1.82	0.17	"	1.67		109	0-200			
Di-n-octyl phthalate	1.53	0.33	"	1.67		92	0-200			

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
Reported:
 06/30/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F15018 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample (5F15018-BS1)

Prepared: 06/15/05 Analyzed: 06/16/05

Fluoranthene	1.68	0.17	ug/Wipe	1.67		101	0-200			
Fluorene	1.69	0.17	"	1.67		101	0-200			
Hexachlorobenzene	1.66	0.17	"	1.67		99	0-200			
Hexachlorobutadiene	1.43	0.33	"	1.67		86	0-200			
Hexachlorocyclopentadiene	1.69	0.33	"	1.67		101	0-200			
Hexachloroethane	1.28	0.33	"	1.67		77	0-200			
Indeno (1,2,3-cd) pyrene	1.92	0.33	"	1.67		115	0-200			
Isophorone	1.46	0.17	"	1.67		87	0-200			
2-Methylnaphthalene	1.49	0.17	"	1.67		89	0-200			
2-Methylphenol	1.45	0.17	"	1.67		87	0-200			
4-Methylphenol	1.47	0.17	"	0.833		176	0-200			
Naphthalene	1.52	0.17	"	1.67		91	0-200			
2-Nitroaniline	1.65	0.33	"	1.67		99	0-200			
3-Nitroaniline	1.43	3.3	"	1.67		86	0-200			
4-Nitroaniline	1.49	1.7	"	1.67		89	0-200			
Nitrobenzene	1.50	0.17	"	1.67		90	0-200			
2-Nitrophenol	1.58	0.17	"	1.67		95	0-200			
4-Nitrophenol	1.57	0.33	"	1.67		94	11-114			
N-Nitrosodi-n-propylamine	1.44	0.17	"	1.67		86	41-126			
N-Nitrosodiphenylamine	2.07	0.33	"	1.67		124	0-200			
Pentachlorophenol	1.56	0.33	"	1.67		93	17-109			
Phenanthrene	1.73	0.17	"	1.67		104	0-200			
Phenol	1.68	0.17	"	1.67		101	26-90			QL06
Pyrene	1.84	0.17	"	1.67		110	35-142			
1,2,4-Trichlorobenzene	1.40	0.33	"	1.67		84	38-107			
2,4,5-Trichlorophenol	1.70	0.17	"	1.67		102	0-200			
2,4,6-Trichlorophenol	1.67	0.17	"	1.67		100	0-200			
<i>Surrogate: 2-Fluorophenol</i>	<i>3.03</i>		<i>"</i>	<i>3.33</i>		<i>91</i>	<i>25-121</i>			
<i>Surrogate: Phenol-d6</i>	<i>3.21</i>		<i>"</i>	<i>3.33</i>		<i>96</i>	<i>24-113</i>			
<i>Surrogate: Nitrobenzene-d5</i>	<i>1.50</i>		<i>"</i>	<i>1.67</i>		<i>90</i>	<i>23-120</i>			
<i>Surrogate: 2-Fluorobiphenyl</i>	<i>1.52</i>		<i>"</i>	<i>1.67</i>		<i>91</i>	<i>30-115</i>			
<i>Surrogate: 2,4,6-Tribromophenol</i>	<i>3.29</i>		<i>"</i>	<i>3.33</i>		<i>99</i>	<i>19-122</i>			
<i>Surrogate: p-Terphenyl-d14</i>	<i>1.60</i>		<i>"</i>	<i>1.67</i>		<i>96</i>	<i>18-137</i>			

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
 Reported:
 06/30/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F15018 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample Dup (5F15018-BSD1)

Prepared: 06/15/05 Analyzed: 06/16/05

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
Acenaphthene	1.73	0.17	ug/Wipe	1.67	104	31-137	4	40		
Acenaphthylene	1.69	0.17	"	1.67	101	0-200	0.6	200		
Anthracene	1.70	0.17	"	1.67	102	0-200	0.6	200		
Benzo (a) anthracene	1.71	0.17	"	1.67	102	0-200	2	200		
Benzo (a) pyrene	1.67	0.17	"	1.67	100	0-200	2	200		
Benzo (b) fluoranthene	1.60	0.17	"	1.67	96	0-200	5	200		
Benzo (g,h,i) perylene	1.97	0.33	"	1.67	118	0-200	8	200		
Benzo (k) fluoranthene	1.64	0.17	"	1.67	98	0-200	4	200		
Benzyl alcohol	1.66	0.33	"	1.67	99	0-200	4	200		
Bis(2-chloroethoxy)methane	1.74	0.17	"	1.67	104	0-200	2	200		
Bis(2-chloroethyl)ether	1.62	0.33	"	1.67	97	0-200	4	200		
Bis(2-chloroisopropyl)ether	1.64	0.17	"	1.67	98	0-200	6	200		
Bis(2-ethylhexyl)phthalate	1.75	0.33	"	1.67	105	0-200	1	200		
4-Bromophenyl phenyl ether	1.75	0.17	"	1.67	105	0-200	3	200		
Butyl benzyl phthalate	1.82	0.17	"	1.67	109	0-200	2	200		
4-Chloroaniline	1.15	1.7	"	1.67	69	0-200	7	200		
2-Chloronaphthalene	1.63	0.17	"	1.67	98	0-200	3	200		
4-Chloro-3-methylphenol	1.75	0.17	"	1.67	105	26-103	2	40		QL06
2-Chlorophenol	1.63	0.17	"	1.67	98	25-102	5	40		
4-Chlorophenyl phenyl ether	1.62	0.33	"	1.67	97	0-200	0.6	200		
Chrysene	1.70	0.17	"	1.67	102	0-200	2	200		
Dibenz (a,h) anthracene	2.06	0.17	"	1.67	123	0-200	8	200		
Dibenzofuran	1.60	0.17	"	1.67	96	0-200	2	200		
Di-n-butyl phthalate	1.83	0.17	"	1.67	110	0-200	0	200		
1,2-Dichlorobenzene	1.38	0.33	"	1.67	83	0-200	6	200		
1,3-Dichlorobenzene	1.39	0.33	"	1.67	83	0-200	10	200		
1,4-Dichlorobenzene	1.39	0.33	"	1.67	83	28-104	7	40		
2,4-Dichlorophenol	1.65	0.17	"	1.67	99	0-200	2	200		
Diethyl phthalate	1.64	0.17	"	1.67	98	0-200	0	200		
2,4-Dimethylphenol	1.11	0.33	"	1.67	66	0-200	17	200		
Dimethyl phthalate	1.63	0.17	"	1.67	98	0-200	0	200		
4,6-Dinitro-2-methylphenol	1.65	0.17	"	1.67	99	0-200	2	200		
2,4-Dinitrophenol	1.44	0.33	"	1.67	86	0-200	2	200		
2,4-Dinitrotoluene	1.60	0.17	"	1.67	96	28-89	0.6	40		QL06
2,6-Dinitrotoluene	1.82	0.17	"	1.67	109	0-200	0	200		
Di-n-octyl phthalate	1.65	0.33	"	1.67	99	0-200	8	200		

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
 Reported:
 06/30/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F15018 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample Dup (5F15018-BSD1)

Prepared: 06/15/05 Analyzed: 06/16/05

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
Fluoranthene	1.74	0.17	ug/Wipe	1.67		104	0-200	4	200	
Fluorene	1.67	0.17	"	1.67		100	0-200	1	200	
Hexachlorobenzene	1.69	0.17	"	1.67		101	0-200	2	200	
Hexachlorobutadiene	1.48	0.33	"	1.67		89	0-200	3	200	
Hexachlorocyclopentadiene	1.71	0.33	"	1.67		102	0-200	1	200	
Hexachloroethane	1.41	0.33	"	1.67		84	0-200	10	200	
Indeno (1,2,3-cd) pyrene	2.04	0.33	"	1.67		122	0-200	6	200	
Isophorone	1.53	0.17	"	1.67		92	0-200	5	200	
2-Methylnaphthalene	1.54	0.17	"	1.67		92	0-200	3	200	
2-Methylphenol	1.45	0.17	"	1.67		87	0-200	0	200	
4-Methylphenol	1.48	0.17	"	0.833		178	0-200	0.7	200	
Naphthalene	1.57	0.17	"	1.67		94	0-200	3	200	
2-Nitroaniline	1.70	0.33	"	1.67		102	0-200	3	200	
3-Nitroaniline	1.26	3.3	"	1.67		75	0-200	13	200	
4-Nitroaniline	1.35	1.7	"	1.67		81	0-200	10	200	
Nitrobenzene	1.57	0.17	"	1.67		94	0-200	5	200	
2-Nitrophenol	1.65	0.17	"	1.67		99	0-200	4	200	
4-Nitrophenol	1.59	0.33	"	1.67		95	11-114	1	40	
N-Nitrosodi-n-propylamine	1.52	0.17	"	1.67		91	41-126	5	40	
N-Nitrosodiphenylamine	2.07	0.33	"	1.67		124	0-200	0	200	
Pentachlorophenol	1.51	0.33	"	1.67		90	17-109	3	40	
Phenanthrene	1.76	0.17	"	1.67		105	0-200	2	200	
Phenol	1.74	0.17	"	1.67		104	26-90	4	40	QL06
Pyrene	1.81	0.17	"	1.67		108	35-142	2	40	
1,2,4-Trichlorobenzene	1.47	0.33	"	1.67		88	38-107	5	40	
2,4,5-Trichlorophenol	1.73	0.17	"	1.67		104	0-200	2	200	
2,4,6-Trichlorophenol	1.72	0.17	"	1.67		103	0-200	3	200	
<i>Surrogate: 2-Fluorophenol</i>	<i>3.13</i>		<i>"</i>	<i>3.33</i>		<i>94</i>	<i>25-121</i>			
<i>Surrogate: Phenol-d6</i>	<i>3.33</i>		<i>"</i>	<i>3.33</i>		<i>100</i>	<i>24-113</i>			
<i>Surrogate: Nitrobenzene-d5</i>	<i>1.57</i>		<i>"</i>	<i>1.67</i>		<i>94</i>	<i>23-120</i>			
<i>Surrogate: 2-Fluorobiphenyl</i>	<i>1.58</i>		<i>"</i>	<i>1.67</i>		<i>95</i>	<i>30-115</i>			
<i>Surrogate: 2,4,6-Tribromophenol</i>	<i>3.29</i>		<i>"</i>	<i>3.33</i>		<i>99</i>	<i>19-122</i>			
<i>Surrogate: p-Terphenyl-d14</i>	<i>1.62</i>		<i>"</i>	<i>1.67</i>		<i>97</i>	<i>18-137</i>			

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5634
 Project Manager:Myrto Petreas

 MOF0403
Reported:
 06/30/05 13:37

Polynuclear Aromatic Compounds by GC/MS with Selected Ion Monitoring - Quality Control
Sequoia Analytical - Petaluma

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5060028 - EPA 3580A Waste Dil / GCMS-SIM
Blank (5060028-BLK1)

Prepared & Analyzed: 06/16/05

Naphthalene	ND	810	ug/Wipe							
Acenaphthylene	ND	810	"							
Acenaphthene	ND	810	"							
Fluorene	ND	810	"							
Phenanthrene	ND	810	"							
Anthracene	ND	810	"							
Fluoranthene	ND	810	"							
Pyrene	ND	810	"							
Benzo (a) anthracene	ND	810	"							
Chrysene	ND	810	"							
Benzo (b+k) fluoranthene (total)	ND	1600	"							
Benzo (b) fluoranthene	ND	810	"							
Benzo (k) fluoranthene	ND	810	"							
Benzo (a) pyrene	ND	810	"							
Indeno (1,2,3-cd) pyrene	ND	810	"							
Benzo (g,h,i) perylene	ND	810	"							
Dibenz (a,h) anthracene	ND	810	"							
<i>Surrogate: Nitrobenzene-d5</i>	318		"	200		159	50-150			S01
<i>Surrogate: 2-Fluorobiphenyl</i>	314		"	200		157	50-150			S01
<i>Surrogate: Terphenyl-d14</i>	327		"	200		164	50-150			S01

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5634
Project Manager:Myrto Petreas

MOF0403
Reported:
06/30/05 13:37

Notes and Definitions

S01	The surrogate recovery was above control limits.
QL06	Laboratory Control Sample and/or Laboratory Control Sample Duplicate recovery was above the acceptance limits. Analyte not detected, data not impacted.
DET	Analyte DETECTED
ND	Analyte NOT DETECTED at or above the reporting limit or MDL, if MDL is specified
NR	Not Reported
dry	Sample results reported on a dry weight basis
RPD	Relative Percent Difference

California Department of Toxic Substances Control
Hazardous Materials Laboratory
700 Heinz Avenue, Suite#150, Berkeley, CA 94710

MOF0403

SAMPLE / SAMPLE EXTRACT TRANSPORT CUSTODY

Receiving Lab / Section: Sequoia Analytical Lab

Sample Collection Site: OEHHA Playground Study

HML # or Collector's #	Sample Type *	Analysis Requested	Location of Sample (s)	Remarks
A to L	Polyester wipe-wetted	SAR		

- OSC = original sample container; SS = split sample; A = Aliquot; C = Citrate WET; E = Extract; D = acid digest; T = TCLP extract.

Release for transport by: Amel Chand Time / Date 06-08-05 3pm

Transported to: Sequoia Lab/ GC/MS/ Org sec / Inorg sec/ Fed Ex / Others
By: M... Time / Date 6/7/05 1500

Received by: _____ Time / Date _____

Returned to HML by: _____ Time / Date _____

SEQUOIA ANALYTICAL SAMPLE RECEIPT LOG

CLIENT NAME: DFCL
 REC. BY (PRINT) JAY
 WORKORDER: MOF0403

DATE REC'D AT LAB: 6/8/05
 TIME REC'D AT LAB: 1845
 DATE LOGGED IN: 6-12-05

For Regulatory Purposes?
 DRINKING WATER YES/NO YES / NO
 WASTE WATER YES/NO YES / NO

(For clients requiring preservation checks at receipt, document here ↓)

CIRCLE THE APPROPRIATE RESPONSE		LAB SAMPLE #	DASH #	CLIENT ID	CONTAINER DESCRIPTION	PRESERVATIVE	pH	SAMPLE MATRIX	DATE SAMPLED	REMARKS: CONDITION (ETC.)
1. Custody Seal(s)	Present / <input checked="" type="checkbox"/> Absent Intact / Broken*	01	A	A	16oz jar	—	—	Wipe	6/2/05	
2. Chain-of-Custody	<input checked="" type="checkbox"/> Present / Absent*	02	↓	B	↓	↓	↓	↓	↓	
3. Traffic Reports or Packing List:	Present / <input checked="" type="checkbox"/> Absent	03	↓	C	↓	↓	↓	↓	↓	
4. Airbill:	Airbill / Sticker Present / <input checked="" type="checkbox"/> Absent	04	↓	D	↓	↓	↓	↓	↓	
5. Airbill #:				E						
6. Sample Labels:	<input checked="" type="checkbox"/> Present / Absent			F						
7. Sample IDs:	Listed / Not Listed on Chain-of-Custody									
8. Sample Condition:	<input checked="" type="checkbox"/> Intact / Broken* / Leaking*									
9. Does information on chain-of-custody, traffic reports and sample labels agree?	Yes / <input checked="" type="checkbox"/> No*									
10. Sample received within hold time?	Yes / <input checked="" type="checkbox"/> No*									
11. Adequate sample volume received?	Yes / <input checked="" type="checkbox"/> No*									
12. Proper Preservatives used?	Yes / <input checked="" type="checkbox"/> No*									
13. Trip Blank / Temp Blank Received? (circle which, if yes)	Yes / <input checked="" type="checkbox"/> No*									
14. Temp Rec. at Lab: Is temp 4 +/-2°C? <small>(acceptance range for samples requiring thermal pres.)</small>	<u>20°C</u> Yes / <input checked="" type="checkbox"/> No**									
Reception (if any): METALS / DFF ON ICE										
Problem COC										

*IF CIRCLED, CONTACT PROJECT MANAGER AND ATTACH RECORD OF RESOLUTION.


2 August, 2005

Myrto Petreas
Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley, CA 94710

RE: OEHHA Playground Study
Work Order: MOF0623

Enclosed are the results of analyses for samples received by the laboratory on 06/16/05 19:20. If you have any questions concerning this report, please feel free to contact me.

Sincerely,



Theresa Allen
Project Manager

CA ELAP Certificate #1210

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:-
Project Manager:Myrto Petreas

MOF0623
Reported:
08/02/05 13:37

ANALYTICAL REPORT FOR SAMPLES

Sample ID	Laboratory ID	Matrix	Date Sampled	Date Received
A	MOF0623-01	Wipe	06/15/05 00:00	06/16/05 19:20
B	MOF0623-02	Wipe	06/15/05 00:00	06/16/05 19:20
C	MOF0623-03	Wipe	06/15/05 00:00	06/16/05 19:20
D	MOF0623-04	Wipe	06/15/05 00:00	06/16/05 19:20
E	MOF0623-05	Wipe	06/15/05 00:00	06/16/05 19:20
F	MOF0623-06	Wipe	06/15/05 00:00	06/16/05 19:20
G	MOF0623-07	Wipe	06/15/05 00:00	06/16/05 19:20
H	MOF0623-08	Wipe	06/15/05 00:00	06/16/05 19:20
I	MOF0623-09	Wipe	06/15/05 00:00	06/16/05 19:20
J	MOF0623-10	Wipe	06/15/05 00:00	06/16/05 19:20
K	MOF0623-11	Wipe	06/15/05 00:00	06/16/05 19:20
L	MOF0623-12	Wipe	06/15/05 00:00	06/16/05 19:20

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHHA Playground Study
Project Number:-
Project Manager:Myrto Petreas

MOF0623
Reported:
08/02/05 13:37

**Metals Scan by ICP
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
A (MOF0623-01) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20									
Silver	ND	25	ug/Wipe	1	5F27021	06/27/05	06/28/05	ICP Scan	
Antimony	ND	250	"	"	"	"	"	"	
Sodium	ND	600	"	"	"	"	"	"	
Arsenic	ND	250	"	"	"	"	"	"	
Barium	ND	250	"	"	"	"	"	"	
Beryllium	ND	10	"	"	"	"	"	"	
Calcium	1600	600	"	"	"	"	"	"	
Cadmium	ND	10	"	"	"	"	"	"	
Cobalt	ND	25	"	"	"	"	"	"	
Copper	ND	200	"	"	"	"	"	"	
Chromium	ND	250	"	"	"	"	"	"	
Iron	ND	500	"	"	"	"	"	"	
Lead	ND	250	"	"	"	"	"	"	
Manganese	ND	500	"	"	"	"	"	"	
Molybdenum	ND	50	"	"	"	"	"	"	
Nickel	ND	250	"	"	"	"	"	"	
Potassium	ND	1200	"	"	"	"	"	"	
Selenium	ND	500	"	"	"	"	"	"	
Thallium	ND	250	"	"	"	"	"	"	
Vanadium	ND	250	"	"	"	"	"	"	
Zinc	ND	250	"	"	"	"	"	"	
B (MOF0623-02) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20									
Silver	ND	25	ug/Wipe	1	5F27021	06/27/05	06/28/05	ICP Scan	
Antimony	ND	250	"	"	"	"	"	"	
Sodium	ND	600	"	"	"	"	"	"	
Arsenic	ND	250	"	"	"	"	"	"	
Barium	ND	250	"	"	"	"	"	"	
Beryllium	ND	10	"	"	"	"	"	"	
Calcium	2700	600	"	"	"	"	"	"	
Cadmium	ND	10	"	"	"	"	"	"	
Cobalt	ND	25	"	"	"	"	"	"	
Copper	ND	200	"	"	"	"	"	"	
Chromium	ND	250	"	"	"	"	"	"	
Iron	ND	500	"	"	"	"	"	"	
Lead	ND	250	"	"	"	"	"	"	
Manganese	ND	500	"	"	"	"	"	"	
Molybdenum	ND	50	"	"	"	"	"	"	
Nickel	ND	250	"	"	"	"	"	"	
Potassium	ND	1200	"	"	"	"	06/28/05	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:-
Project Manager:Myrto Petreas

MOF0623
Reported:
08/02/05 13:37

**Metals Scan by ICP
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
B (MOF0623-02) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20									
Selenium	ND	500	ug/Wipe	1	5F27021	06/27/05	06/28/05	ICP Scan	
Thallium	ND	250	"	"	"	"	"	"	
Vanadium	ND	250	"	"	"	"	"	"	
Zinc	ND	250	"	"	"	"	"	"	
C (MOF0623-03) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20									
Silver	ND	25	ug/Wipe	1	5F27021	06/27/05	06/28/05	ICP Scan	
Antimony	ND	250	"	"	"	"	"	"	
Sodium	600	600	"	"	"	"	"	"	
Arsenic	ND	250	"	"	"	"	"	"	
Barium	ND	250	"	"	"	"	"	"	
Beryllium	ND	10	"	"	"	"	"	"	
Calcium	2700	600	"	"	"	"	"	"	
Cadmium	ND	10	"	"	"	"	"	"	
Cobalt	ND	25	"	"	"	"	"	"	
Copper	ND	200	"	"	"	"	"	"	
Chromium	ND	250	"	"	"	"	"	"	
Iron	1000	500	"	"	"	"	"	"	
Lead	ND	250	"	"	"	"	"	"	
Manganese	ND	500	"	"	"	"	"	"	
Molybdenum	ND	50	"	"	"	"	"	"	
Nickel	ND	250	"	"	"	"	"	"	
Potassium	ND	1200	"	"	"	"	"	"	
Selenium	ND	500	"	"	"	"	"	"	
Thallium	ND	250	"	"	"	"	"	"	
Vanadium	ND	250	"	"	"	"	"	"	
Zinc	ND	250	"	"	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHHA Playground Study
Project Number:-
Project Manager:Myrto Petreas

MOF0623
Reported:
08/02/05 13:37

**Total Metals by EPA 6000/7000 Series Methods
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
---------	--------	-----------------	-------	----------	-------	----------	----------	--------	-------

A (MOF0623-01) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20

Antimony	120	1.0	ug/Wipe	20	5G05011	06/27/05	07/20/05	EPA 6020	
Arsenic	ND	1.0	"	"	"	"	"	"	
Barium	5.9	5.0	"	"	"	"	"	"	
Beryllium	ND	0.20	"	"	"	"	"	"	
Cadmium	ND	0.60	"	"	"	"	"	"	
Chromium	ND	10	"	"	"	"	"	"	
Cobalt	ND	2.0	"	"	"	"	"	"	
Copper	ND	5.0	"	"	"	"	"	"	
Lead	ND	5.0	"	"	"	"	"	"	
Molybdenum	ND	2.0	"	"	"	"	"	"	
Nickel	ND	8.0	"	"	"	"	"	"	
Selenium	ND	1.0	"	"	"	"	"	"	
Silver	ND	1.0	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	ND	2.0	"	"	"	"	"	"	
Zinc	70	10	"	"	"	"	"	"	

B (MOF0623-02) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20

Antimony	190	1.0	ug/Wipe	20	5G05011	06/27/05	07/20/05	EPA 6020	
Arsenic	ND	1.0	"	"	"	"	"	"	
Barium	7.0	5.0	"	"	"	"	"	"	
Beryllium	ND	0.20	"	"	"	"	"	"	
Cadmium	ND	0.60	"	"	"	"	"	"	
Chromium	ND	10	"	"	"	"	"	"	
Cobalt	ND	2.0	"	"	"	"	"	"	
Copper	ND	5.0	"	"	"	"	"	"	
Lead	ND	5.0	"	"	"	"	"	"	
Molybdenum	ND	2.0	"	"	"	"	"	"	
Nickel	ND	8.0	"	"	"	"	"	"	
Selenium	ND	1.0	"	"	"	"	"	"	
Silver	ND	1.0	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	ND	2.0	"	"	"	"	"	"	
Zinc	75	10	"	"	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
Reported:
 08/02/05 13:37

**Total Metals by EPA 6000/7000 Series Methods
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
C (MOF0623-03) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20									
Antimony	220	1.0	ug/Wipe	20	5G05011	06/27/05	07/20/05	EPA 6020	
Arsenic	ND	1.0	"	"	"	"	"	"	
Barium	19	5.0	"	"	"	"	"	"	
Beryllium	ND	0.20	"	"	"	"	"	"	
Cadmium	ND	0.60	"	"	"	"	"	"	
Chromium	ND	10	"	"	"	"	"	"	
Cobalt	ND	2.0	"	"	"	"	"	"	
Copper	6.3	5.0	"	"	"	"	"	"	
Lead	ND	5.0	"	"	"	"	"	"	
Molybdenum	ND	2.0	"	"	"	"	"	"	
Nickel	ND	8.0	"	"	"	"	"	"	
Selenium	ND	1.0	"	"	"	"	"	"	
Silver	ND	1.0	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	ND	2.0	"	"	"	"	"	"	
Zinc	66	10	"	"	"	"	"	"	
D (MOF0623-04) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20									
Mercury	ND	0.0050	ug/Wipe	1	5F24016	06/24/05	06/24/05	EPA 7471A	
E (MOF0623-05) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20									
Mercury	ND	0.0050	ug/Wipe	1	5F24016	06/24/05	06/24/05	EPA 7471A	
F (MOF0623-06) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20									
Mercury	0.012	0.0050	ug/Wipe	1	5F24016	06/24/05	06/24/05	EPA 7471A	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
 Reported:
 08/02/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
G (MOF0623-07) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20									
Acenaphthene	ND	5.0	ug/Wipe	1	5F21026	06/21/05	06/22/05	EPA 8270C	
Acenaphthylene	ND	5.0	"	"	"	"	"	"	
Anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) pyrene	ND	5.0	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzoic acid	ND	10	"	"	"	"	"	"	
Benzyl alcohol	ND	10	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	5.0	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	10	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	5.0	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	10	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	5.0	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	5.0	"	"	"	"	"	"	
4-Chloroaniline	ND	50	"	"	"	"	"	"	
2-Chloronaphthalene	ND	5.0	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	5.0	"	"	"	"	"	"	
2-Chlorophenol	ND	5.0	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	10	"	"	"	"	"	"	
Chrysene	ND	5.0	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	5.0	"	"	"	"	"	"	
Dibenzofuran	ND	5.0	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	5.0	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	10	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	50	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	5.0	"	"	"	"	"	"	
Diethyl phthalate	ND	5.0	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	10	"	"	"	"	"	"	
Dimethyl phthalate	ND	5.0	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	5.0	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	10	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	10	"	"	"	"	"	"	
Fluoranthene	ND	5.0	"	"	"	"	"	"	
Fluorene	ND	5.0	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
 Reported:
 08/02/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
G (MOF0623-07) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20									
Hexachlorobenzene	ND	5.0	ug/Wipe	1	5F21026	06/21/05	06/22/05	EPA 8270C	
Hexachlorobutadiene	ND	10	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	10	"	"	"	"	"	"	
Hexachloroethane	ND	10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	10	"	"	"	"	"	"	
Isophorone	ND	5.0	"	"	"	"	"	"	
2-Methylnaphthalene	ND	5.0	"	"	"	"	"	"	
2-Methylphenol	ND	5.0	"	"	"	"	"	"	
4-Methylphenol	ND	5.0	"	"	"	"	"	"	
Naphthalene	ND	5.0	"	"	"	"	"	"	
2-Nitroaniline	ND	10	"	"	"	"	"	"	
3-Nitroaniline	ND	100	"	"	"	"	"	"	
4-Nitroaniline	ND	50	"	"	"	"	"	"	
Nitrobenzene	ND	5.0	"	"	"	"	"	"	
2-Nitrophenol	ND	5.0	"	"	"	"	"	"	
4-Nitrophenol	ND	10	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	5.0	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	10	"	"	"	"	"	"	
Pentachlorophenol	ND	10	"	"	"	"	"	"	
Phenanthrene	ND	5.0	"	"	"	"	"	"	
Phenol	ND	5.0	"	"	"	"	"	"	
Pyrene	ND	5.0	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	10	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		74 %		25-121	"	"	"	"	
<i>Surrogate: Phenol-d6</i>		87 %		24-113	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		75 %		23-120	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		74 %		30-115	"	"	"	"	
<i>Surrogate: 2,4,6-Tribromophenol</i>		81 %		19-122	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		67 %		18-137	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
 Reported:
 08/02/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
H (MOF0623-08) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20									
Acenaphthene	ND	5.0	ug/Wipe	1	5F21026	06/21/05	06/22/05	EPA 8270C	
Acenaphthylene	ND	5.0	"	"	"	"	"	"	
Anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) pyrene	ND	5.0	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzoic acid	ND	10	"	"	"	"	"	"	
Benzyl alcohol	ND	10	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	5.0	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	10	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	5.0	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	10	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	5.0	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	5.0	"	"	"	"	"	"	
4-Chloroaniline	ND	50	"	"	"	"	"	"	
2-Chloronaphthalene	ND	5.0	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	5.0	"	"	"	"	"	"	
2-Chlorophenol	ND	5.0	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	10	"	"	"	"	"	"	
Chrysene	ND	5.0	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	5.0	"	"	"	"	"	"	
Dibenzofuran	ND	5.0	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	5.0	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	10	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	50	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	5.0	"	"	"	"	"	"	
Diethyl phthalate	ND	5.0	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	10	"	"	"	"	"	"	
Dimethyl phthalate	ND	5.0	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	5.0	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	10	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	10	"	"	"	"	"	"	
Fluoranthene	ND	5.0	"	"	"	"	"	"	
Fluorene	ND	5.0	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
 Reported:
 08/02/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
---------	--------	-----------------	-------	----------	-------	----------	----------	--------	-------

H (MOF0623-08) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20

Hexachlorobenzene	ND	5.0	ug/Wipe	1	5F21026	06/21/05	06/22/05	EPA 8270C	
Hexachlorobutadiene	ND	10	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	10	"	"	"	"	"	"	
Hexachloroethane	ND	10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	10	"	"	"	"	"	"	
Isophorone	ND	5.0	"	"	"	"	"	"	
2-Methylnaphthalene	ND	5.0	"	"	"	"	"	"	
2-Methylphenol	ND	5.0	"	"	"	"	"	"	
4-Methylphenol	ND	5.0	"	"	"	"	"	"	
Naphthalene	ND	5.0	"	"	"	"	"	"	
2-Nitroaniline	ND	10	"	"	"	"	"	"	
3-Nitroaniline	ND	100	"	"	"	"	"	"	
4-Nitroaniline	ND	50	"	"	"	"	"	"	
Nitrobenzene	ND	5.0	"	"	"	"	"	"	
2-Nitrophenol	ND	5.0	"	"	"	"	"	"	
4-Nitrophenol	ND	10	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	5.0	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	10	"	"	"	"	"	"	
Pentachlorophenol	ND	10	"	"	"	"	"	"	
Phenanthrene	ND	5.0	"	"	"	"	"	"	
Phenol	ND	5.0	"	"	"	"	"	"	
Pyrene	ND	5.0	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	10	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		78 %		25-121	"	"	"	"	
<i>Surrogate: Phenol-d6</i>		95 %		24-113	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		75 %		23-120	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		70 %		30-115	"	"	"	"	
<i>Surrogate: 2,4,6-Tribromophenol</i>		88 %		19-122	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		76 %		18-137	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHHA Playground Study
Project Number:-
Project Manager:Myrto Petreas

MOF0623
Reported:
08/02/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
I (MOF0623-09) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20									
Acenaphthene	ND	5.0	ug/Wipe	1	5F21026	06/21/05	06/22/05	EPA 8270C	
Acenaphthylene	ND	5.0	"	"	"	"	"	"	
Anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) pyrene	ND	5.0	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzoic acid	ND	10	"	"	"	"	"	"	
Benzyl alcohol	ND	10	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	5.0	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	10	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	5.0	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	10	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	5.0	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	5.0	"	"	"	"	"	"	
4-Chloroaniline	ND	50	"	"	"	"	"	"	
2-Chloronaphthalene	ND	5.0	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	5.0	"	"	"	"	"	"	
2-Chlorophenol	ND	5.0	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	10	"	"	"	"	"	"	
Chrysene	ND	5.0	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	5.0	"	"	"	"	"	"	
Dibenzofuran	ND	5.0	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	5.0	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	10	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	50	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	5.0	"	"	"	"	"	"	
Diethyl phthalate	ND	5.0	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	10	"	"	"	"	"	"	
Dimethyl phthalate	ND	5.0	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	5.0	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	10	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	10	"	"	"	"	"	"	
Fluoranthene	ND	5.0	"	"	"	"	"	"	
Fluorene	ND	5.0	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:-
Project Manager:Myrto Petreas

MOF0623
Reported:
08/02/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
I (MOF0623-09) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20									
Hexachlorobenzene	ND	5.0	ug/Wipe	1	5F21026	06/21/05	06/22/05	EPA 8270C	
Hexachlorobutadiene	ND	10	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	10	"	"	"	"	"	"	
Hexachloroethane	ND	10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	10	"	"	"	"	"	"	
Isophorone	ND	5.0	"	"	"	"	"	"	
2-Methylnaphthalene	ND	5.0	"	"	"	"	"	"	
2-Methylphenol	ND	5.0	"	"	"	"	"	"	
4-Methylphenol	ND	5.0	"	"	"	"	"	"	
Naphthalene	ND	5.0	"	"	"	"	"	"	
2-Nitroaniline	ND	10	"	"	"	"	"	"	
3-Nitroaniline	ND	100	"	"	"	"	"	"	
4-Nitroaniline	ND	50	"	"	"	"	"	"	
Nitrobenzene	ND	5.0	"	"	"	"	"	"	
2-Nitrophenol	ND	5.0	"	"	"	"	"	"	
4-Nitrophenol	ND	10	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	5.0	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	10	"	"	"	"	"	"	
Pentachlorophenol	ND	10	"	"	"	"	"	"	
Phenanthrene	ND	5.0	"	"	"	"	"	"	
Phenol	ND	5.0	"	"	"	"	"	"	
Pyrene	ND	5.0	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	10	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		73 %		25-121	"	"	"	"	
<i>Surrogate: Phenol-d6</i>		86 %		24-113	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		71 %		23-120	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		74 %		30-115	"	"	"	"	
<i>Surrogate: 2,4,6-Tribromophenol</i>		82 %		19-122	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		72 %		18-137	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
 Reported:
 08/02/05 13:37

Polynuclear Aromatic Compounds by GC/MS with Selected Ion Monitoring
Sequoia Analytical - Petaluma

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
---------	--------	-----------------	-------	----------	-------	----------	----------	--------	-------

J (MOF0623-10) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20

Naphthalene	ND	530	ug/Wipe	1	5060031	06/21/05	06/22/05	GCMS-SIM	
Acenaphthylene	ND	530	"	"	"	"	"	"	
Acenaphthene	ND	530	"	"	"	"	"	"	
Fluorene	ND	530	"	"	"	"	"	"	
Phenanthrene	ND	530	"	"	"	"	"	"	
Anthracene	ND	530	"	"	"	"	"	"	
Fluoranthene	ND	530	"	"	"	"	"	"	
Pyrene	ND	530	"	"	"	"	"	"	
Benzo (a) anthracene	ND	530	"	"	"	"	"	"	
Chrysene	ND	530	"	"	"	"	"	"	
Benzo (b+k) fluoranthene (total)	ND	1100	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	530	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	530	"	"	"	"	"	"	
Benzo (a) pyrene	ND	530	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	530	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	530	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	530	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		75 %	30-101		"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		83 %	21-111		"	"	"	"	
<i>Surrogate: Terphenyl-d14</i>		80 %	38-123		"	"	"	"	

K (MOF0623-11) Wipe Sampled: 06/15/05 00:00 Received: 06/16/05 19:20

Naphthalene	ND	530	ug/Wipe	1	5060031	06/21/05	06/22/05	GCMS-SIM	
Acenaphthylene	ND	530	"	"	"	"	"	"	
Acenaphthene	ND	530	"	"	"	"	"	"	
Fluorene	ND	530	"	"	"	"	"	"	
Phenanthrene	ND	530	"	"	"	"	"	"	
Anthracene	ND	530	"	"	"	"	"	"	
Fluoranthene	ND	530	"	"	"	"	"	"	
Pyrene	ND	530	"	"	"	"	"	"	
Benzo (a) anthracene	ND	530	"	"	"	"	"	"	
Chrysene	ND	530	"	"	"	"	"	"	
Benzo (b+k) fluoranthene (total)	ND	1100	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	530	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	530	"	"	"	"	"	"	
Benzo (a) pyrene	ND	530	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	530	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	530	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	530	"	"	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley 700 Heinz Avenue, Suite 100 Berkeley CA, 94710	Project:OEHHA Playground Study Project Number:- Project Manager:Myrto Petreas	MOF0623 Reported: 08/02/05 13:37
---	---	---

Polynuclear Aromatic Compounds by GC/MS with Selected Ion Monitoring
Sequoia Analytical - Petaluma

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
---------	--------	-----------------	-------	----------	-------	----------	----------	--------	-------

K (MOF0623-11) Wipe **Sampled: 06/15/05 00:00** **Received: 06/16/05 19:20**

Surrogate: Nitrobenzene-d5		81 %	30-101		5060031	06/21/05	06/22/05	GCMS-SIM	
Surrogate: 2-Fluorobiphenyl		86 %	21-111		"	"	"	"	
Surrogate: Terphenyl-d14		85 %	38-123		"	"	"	"	

L (MOF0623-12) Wipe **Sampled: 06/15/05 00:00** **Received: 06/16/05 19:20**

Naphthalene	ND	530	ug/Wipe	1	5060031	06/21/05	06/22/05	GCMS-SIM	
Acenaphthylene	ND	530	"	"	"	"	"	"	
Acenaphthene	ND	530	"	"	"	"	"	"	
Fluorene	ND	530	"	"	"	"	"	"	
Phenanthrene	ND	530	"	"	"	"	"	"	
Anthracene	ND	530	"	"	"	"	"	"	
Fluoranthene	ND	530	"	"	"	"	"	"	
Pyrene	ND	530	"	"	"	"	"	"	
Benzo (a) anthracene	ND	530	"	"	"	"	"	"	
Chrysene	ND	530	"	"	"	"	"	"	
Benzo (b+k) fluoranthene (total)	ND	1100	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	530	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	530	"	"	"	"	"	"	
Benzo (a) pyrene	ND	530	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	530	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	530	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	530	"	"	"	"	"	"	
Surrogate: Nitrobenzene-d5		86 %	30-101		"	"	"	"	
Surrogate: 2-Fluorobiphenyl		86 %	21-111		"	"	"	"	
Surrogate: Terphenyl-d14		84 %	38-123		"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
Reported:
 08/02/05 13:37

Metals Scan by ICP - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F27021 - EPA 3050B / ICP Scan
Blank (5F27021-BLK1)

Prepared: 06/27/05 Analyzed: 06/28/05

Silver	ND	25	ug/Wipe							
Antimony	ND	250	"							
Sodium	ND	600	"							
Arsenic	ND	250	"							
Barium	ND	250	"							
Beryllium	ND	10	"							
Calcium	ND	600	"							
Cadmium	ND	10	"							
Cobalt	ND	25	"							
Copper	ND	200	"							
Chromium	ND	250	"							
Iron	ND	500	"							
Lead	ND	250	"							
Manganese	ND	500	"							
Molybdenum	ND	50	"							
Nickel	ND	250	"							
Potassium	ND	1200	"							
Selenium	ND	500	"							
Thallium	ND	250	"							
Vanadium	ND	250	"							
Zinc	ND	250	"							

Laboratory Control Sample (5F27021-BS1)

Prepared: 06/27/05 Analyzed: 06/28/05

Silver	50.2	25	ug/Wipe	50.0	100	80-110
Antimony	50.7	250	"	50.0	101	80-115
Sodium	486	600	"	500	97	70-115
Arsenic	50.6	250	"	50.0	101	80-110
Barium	48.8	250	"	50.0	98	80-110
Beryllium	47.6	10	"	50.0	95	80-110
Calcium	517	600	"	500	103	75-120
Cadmium	50.5	10	"	50.0	101	80-110
Cobalt	51.5	25	"	50.0	103	85-115
Copper	49.1	200	"	50.0	98	85-110
Chromium	51.1	250	"	50.0	102	85-110
Iron	51.8	500	"	50.0	104	80-120
Lead	51.3	250	"	50.0	103	75-120

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
Reported:
 08/02/05 13:37

Metals Scan by ICP - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F27021 - EPA 3050B / ICP Scan
Laboratory Control Sample (5F27021-BS1)

Prepared: 06/27/05 Analyzed: 06/28/05

Manganese	50.8	500	ug/Wipe	50.0		102	80-115			
Molybdenum	50.6	50	"	50.0		101	80-110			
Nickel	51.0	250	"	50.0		102	80-115			
Potassium	519	1200	"	500		104	70-125			
Selenium	50.9	500	"	50.0		102	80-110			
Thallium	52.6	250	"	50.0		105	75-115			
Vanadium	50.5	250	"	50.0		101	75-115			
Zinc	50.2	250	"	50.0		100	80-115			

Laboratory Control Sample (5F27021-BS2)

Prepared: 06/27/05 Analyzed: 06/28/05

Silver	49.6	25	ug/Wipe	50.0		99	80-110			
Antimony	50.0	250	"	50.0		100	80-115			
Sodium	473	600	"	500		95	70-115			
Arsenic	48.9	250	"	50.0		98	80-110			
Barium	47.8	250	"	50.0		96	80-110			
Beryllium	47.0	10	"	50.0		94	80-110			
Calcium	510	600	"	500		102	75-120			
Cadmium	50.0	10	"	50.0		100	80-110			
Cobalt	51.0	25	"	50.0		102	85-115			
Copper	48.3	200	"	50.0		97	85-110			
Chromium	50.4	250	"	50.0		101	85-110			
Iron	51.1	500	"	50.0		102	80-120			
Lead	51.2	250	"	50.0		102	75-120			
Manganese	50.2	500	"	50.0		100	80-115			
Molybdenum	50.2	50	"	50.0		100	80-110			
Nickel	50.2	250	"	50.0		100	80-115			
Potassium	512	1200	"	500		102	70-125			
Selenium	50.2	500	"	50.0		100	80-110			
Thallium	51.4	250	"	50.0		103	75-115			
Vanadium	49.8	250	"	50.0		100	75-115			
Zinc	49.7	250	"	50.0		99	80-115			

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
Reported:
 08/02/05 13:37

Total Metals by EPA 6000/7000 Series Methods - Quality Control
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5G05011 - EPA 3050B / EPA 6020
Blank (5G05011-BLK1)

Prepared: 06/27/05 Analyzed: 07/05/05

Antimony	ND	1.0	ug/Wipe							
Arsenic	ND	1.0	"							
Barium	ND	5.0	"							
Beryllium	ND	0.20	"							
Cadmium	ND	0.60	"							
Chromium	ND	10	"							
Cobalt	ND	2.0	"							
Copper	ND	5.0	"							
Lead	ND	5.0	"							
Molybdenum	ND	2.0	"							
Nickel	ND	8.0	"							
Selenium	1.40	1.0	"							QB02
Silver	ND	1.0	"							
Thallium	ND	1.0	"							
Vanadium	ND	2.0	"							
Zinc	ND	10	"							

Laboratory Control Sample (5G05011-BS1)

Prepared: 06/27/05 Analyzed: 07/05/05

Antimony	48.9	1.0	ug/Wipe	50.0		98	80-120			
Arsenic	48.0	1.0	"	50.0		96	80-120			
Barium	47.8	5.0	"	50.0		96	80-120			
Beryllium	50.1	0.20	"	50.0		100	80-120			
Cadmium	47.2	0.60	"	50.0		94	80-120			
Chromium	50.9	10	"	50.0		102	80-120			
Cobalt	49.8	2.0	"	50.0		100	80-120			
Copper	50.5	5.0	"	50.0		101	80-120			
Lead	50.2	5.0	"	50.0		100	80-120			
Molybdenum	48.7	2.0	"	50.0		97	80-120			
Nickel	49.4	8.0	"	50.0		99	80-120			
Selenium	45.9	1.0	"	50.0		92	80-120			
Silver	49.5	1.0	"	50.0		99	80-120			
Thallium	49.9	1.0	"	50.0		100	80-120			
Vanadium	47.5	2.0	"	50.0		95	80-120			
Zinc	51.3	10	"	50.0		103	80-120			

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
Reported:
 08/02/05 13:37

**Total Metals by EPA 6000/7000 Series Methods - Quality Control
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5G05011 - EPA 3050B / EPA 6020
Laboratory Control Sample (5G05011-BS2)

Prepared: 06/27/05 Analyzed: 07/05/05

Antimony	48.8	1.0	ug/Wipe	50.0		98	80-120			
Arsenic	47.7	1.0	"	50.0		95	80-120			
Barium	47.5	5.0	"	50.0		95	80-120			
Beryllium	48.7	0.20	"	50.0		97	80-120			
Cadmium	47.0	0.60	"	50.0		94	80-120			
Chromium	50.2	10	"	50.0		100	80-120			
Cobalt	50.2	2.0	"	50.0		100	80-120			
Copper	50.6	5.0	"	50.0		101	80-120			
Lead	50.1	5.0	"	50.0		100	80-120			
Molybdenum	48.1	2.0	"	50.0		96	80-120			
Nickel	49.4	8.0	"	50.0		99	80-120			
Selenium	45.3	1.0	"	50.0		91	80-120			
Silver	49.3	1.0	"	50.0		99	80-120			
Thallium	50.1	1.0	"	50.0		100	80-120			
Vanadium	46.9	2.0	"	50.0		94	80-120			
Zinc	51.3	10	"	50.0		103	80-120			

Batch 5F24016 - EPA 7471A / EPA 7471A
Blank (5F24016-BLK1)

Prepared & Analyzed: 06/24/05

Mercury	ND	0.0050	ug/Wipe							
---------	----	--------	---------	--	--	--	--	--	--	--

Laboratory Control Sample (5F24016-BS1)

Prepared & Analyzed: 06/24/05

Mercury	0.361	0.0050	ug/Wipe	0.400		90	75-125			
---------	-------	--------	---------	-------	--	----	--------	--	--	--

Laboratory Control Sample (5F24016-BS2)

Prepared & Analyzed: 06/24/05

Mercury	0.382	0.0050	ug/Wipe	0.400		96	75-125			
---------	-------	--------	---------	-------	--	----	--------	--	--	--

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
Reported:
 08/02/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F21026 - EPA 3550 Wipe / EPA 8270C
Blank (5F21026-BLK1)

Prepared: 06/21/05 Analyzed: 06/22/05

Analyte	Result	Reporting Limit	Units
Acenaphthene	ND	5.0	ug/Wipe
Acenaphthylene	ND	5.0	"
Anthracene	ND	5.0	"
Benzo (a) anthracene	ND	5.0	"
Benzo (a) pyrene	ND	5.0	"
Benzo (b) fluoranthene	ND	5.0	"
Benzo (g,h,i) perylene	ND	10	"
Benzo (k) fluoranthene	ND	5.0	"
Benzoic acid	ND	10	"
Benzyl alcohol	ND	10	"
Bis(2-chloroethoxy)methane	ND	5.0	"
Bis(2-chloroethyl)ether	ND	10	"
Bis(2-chloroisopropyl)ether	ND	5.0	"
Bis(2-ethylhexyl)phthalate	ND	10	"
4-Bromophenyl phenyl ether	ND	5.0	"
Butyl benzyl phthalate	ND	5.0	"
4-Chloroaniline	ND	50	"
2-Chloronaphthalene	ND	5.0	"
4-Chloro-3-methylphenol	ND	5.0	"
2-Chlorophenol	ND	5.0	"
4-Chlorophenyl phenyl ether	ND	10	"
Chrysene	ND	5.0	"
Dibenz (a,h) anthracene	ND	5.0	"
Dibenzofuran	ND	5.0	"
Di-n-butyl phthalate	ND	5.0	"
1,2-Dichlorobenzene	ND	10	"
1,3-Dichlorobenzene	ND	10	"
1,4-Dichlorobenzene	ND	10	"
3,3'-Dichlorobenzidine	ND	50	"
2,4-Dichlorophenol	ND	5.0	"
Diethyl phthalate	ND	5.0	"
2,4-Dimethylphenol	ND	10	"
Dimethyl phthalate	ND	5.0	"
4,6-Dinitro-2-methylphenol	ND	5.0	"
2,4-Dinitrophenol	ND	10	"
2,4-Dinitrotoluene	ND	5.0	"

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
Reported:
 08/02/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5F21026 - EPA 3550 Wipe / EPA 8270C
Blank (5F21026-BLK1)

Prepared: 06/21/05 Analyzed: 06/22/05

2,6-Dinitrotoluene	ND	5.0	ug/Wipe							
Di-n-octyl phthalate	ND	10	"							
Fluoranthene	ND	5.0	"							
Fluorene	ND	5.0	"							
Hexachlorobenzene	ND	5.0	"							
Hexachlorobutadiene	ND	10	"							
Hexachlorocyclopentadiene	ND	10	"							
Hexachloroethane	ND	10	"							
Indeno (1,2,3-cd) pyrene	ND	10	"							
Isophorone	ND	5.0	"							
2-Methylnaphthalene	ND	5.0	"							
2-Methylphenol	ND	5.0	"							
4-Methylphenol	ND	5.0	"							
Naphthalene	ND	5.0	"							
2-Nitroaniline	ND	10	"							
3-Nitroaniline	ND	100	"							
4-Nitroaniline	ND	50	"							
Nitrobenzene	ND	5.0	"							
2-Nitrophenol	ND	5.0	"							
4-Nitrophenol	ND	10	"							
N-Nitrosodi-n-propylamine	ND	5.0	"							
N-Nitrosodiphenylamine	ND	10	"							
Pentachlorophenol	ND	10	"							
Phenanthrene	ND	5.0	"							
Phenol	ND	5.0	"							
Pyrene	ND	5.0	"							
1,2,4-Trichlorobenzene	ND	10	"							
2,4,5-Trichlorophenol	ND	5.0	"							
2,4,6-Trichlorophenol	ND	5.0	"							
<i>Surrogate: 2-Fluorophenol</i>	76.7		"	100		77	25-121			
<i>Surrogate: Phenol-d6</i>	88.5		"	100		88	24-113			
<i>Surrogate: Nitrobenzene-d5</i>	39.6		"	50.0		79	23-120			
<i>Surrogate: 2-Fluorobiphenyl</i>	39.8		"	50.0		80	30-115			
<i>Surrogate: 2,4,6-Tribromophenol</i>	84.8		"	100		85	19-122			
<i>Surrogate: p-Terphenyl-d14</i>	42.5		"	50.0		85	18-137			

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
 Reported:
 08/02/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F21026 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample (5F21026-BS1)

Prepared: 06/21/05 Analyzed: 06/22/05

Acenaphthene	44.9	5.0	ug/Wipe	50.0		90	31-137			
Acenaphthylene	44.3	5.0	"	50.0		89	0-200			
Anthracene	46.2	5.0	"	50.0		92	0-200			
Benzo (a) anthracene	44.8	5.0	"	50.0		90	0-200			
Benzo (a) pyrene	45.3	5.0	"	50.0		91	0-200			
Benzo (b) fluoranthene	43.6	5.0	"	50.0		87	0-200			
Benzo (g,h,i) perylene	36.2	10	"	50.0		72	0-200			
Benzo (k) fluoranthene	43.6	5.0	"	50.0		87	0-200			
Benzyl alcohol	44.8	10	"	50.0		90	0-200			
Bis(2-chloroethoxy)methane	41.8	5.0	"	50.0		84	0-200			
Bis(2-chloroethyl)ether	27.4	10	"	50.0		55	0-200			
Bis(2-chloroisopropyl)ether	37.7	5.0	"	50.0		75	0-200			
Bis(2-ethylhexyl)phthalate	43.4	10	"	50.0		87	0-200			
4-Bromophenyl phenyl ether	40.9	5.0	"	50.0		82	0-200			
Butyl benzyl phthalate	43.6	5.0	"	50.0		87	0-200			
4-Chloroaniline	35.7	50	"	50.0		71	0-200			
2-Chloronaphthalene	41.1	5.0	"	50.0		82	0-200			
4-Chloro-3-methylphenol	45.5	5.0	"	50.0		91	26-103			
2-Chlorophenol	41.1	5.0	"	50.0		82	25-102			
4-Chlorophenyl phenyl ether	44.2	10	"	50.0		88	0-200			
Chrysene	42.5	5.0	"	50.0		85	0-200			
Dibenz (a,h) anthracene	37.3	5.0	"	50.0		75	0-200			
Dibenzofuran	44.1	5.0	"	50.0		88	0-200			
Di-n-butyl phthalate	48.5	5.0	"	50.0		97	0-200			
1,2-Dichlorobenzene	38.8	10	"	50.0		78	0-200			
1,3-Dichlorobenzene	39.0	10	"	50.0		78	0-200			
1,4-Dichlorobenzene	39.9	10	"	50.0		80	28-104			
2,4-Dichlorophenol	44.4	5.0	"	50.0		89	0-200			
Diethyl phthalate	46.6	5.0	"	50.0		93	0-200			
2,4-Dimethylphenol	38.5	10	"	50.0		77	0-200			
Dimethyl phthalate	43.7	5.0	"	50.0		87	0-200			
4,6-Dinitro-2-methylphenol	42.7	5.0	"	50.0		85	0-200			
2,4-Dinitrophenol	52.8	10	"	50.0		106	0-200			
2,4-Dinitrotoluene	47.2	5.0	"	50.0		94	28-89			QL06
2,6-Dinitrotoluene	45.9	5.0	"	50.0		92	0-200			
Di-n-octyl phthalate	43.2	10	"	50.0		86	0-200			

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
 Reported:
 08/02/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F21026 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample (5F21026-BS1)

Prepared: 06/21/05 Analyzed: 06/22/05

Fluoranthene	52.5	5.0	ug/Wipe	50.0		105	0-200			
Fluorene	48.2	5.0	"	50.0		96	0-200			
Hexachlorobenzene	42.5	5.0	"	50.0		85	0-200			
Hexachlorobutadiene	41.0	10	"	50.0		82	0-200			
Hexachlorocyclopentadiene	41.7	10	"	50.0		83	0-200			
Hexachloroethane	37.6	10	"	50.0		75	0-200			
Indeno (1,2,3-cd) pyrene	47.6	10	"	50.0		95	0-200			
Isophorone	37.3	5.0	"	50.0		75	0-200			
2-Methylnaphthalene	45.3	5.0	"	50.0		91	0-200			
2-Methylphenol	43.3	5.0	"	50.0		87	0-200			
4-Methylphenol	48.2	5.0	"	25.0		193	0-200			
Naphthalene	44.6	5.0	"	50.0		89	0-200			
2-Nitroaniline	41.2	10	"	50.0		82	0-200			
3-Nitroaniline	36.0	100	"	50.0		72	0-200			
4-Nitroaniline	43.5	50	"	50.0		87	0-200			
Nitrobenzene	41.3	5.0	"	50.0		83	0-200			
2-Nitrophenol	42.8	5.0	"	50.0		86	0-200			
4-Nitrophenol	48.1	10	"	50.0		96	11-114			
N-Nitrosodi-n-propylamine	43.5	5.0	"	50.0		87	41-126			
N-Nitrosodiphenylamine	48.4	10	"	50.0		97	0-200			
Pentachlorophenol	47.0	10	"	50.0		94	17-109			
Phenanthrene	46.6	5.0	"	50.0		93	0-200			
Phenol	43.4	5.0	"	50.0		87	26-90			
Pyrene	40.8	5.0	"	50.0		82	35-142			
1,2,4-Trichlorobenzene	42.0	10	"	50.0		84	38-107			
2,4,5-Trichlorophenol	42.0	5.0	"	50.0		84	0-200			
2,4,6-Trichlorophenol	41.9	5.0	"	50.0		84	0-200			
<i>Surrogate: 2-Fluorophenol</i>	<i>80.6</i>		<i>"</i>	<i>100</i>		<i>81</i>	<i>25-121</i>			
<i>Surrogate: Phenol-d6</i>	<i>86.1</i>		<i>"</i>	<i>100</i>		<i>86</i>	<i>24-113</i>			
<i>Surrogate: Nitrobenzene-d5</i>	<i>40.4</i>		<i>"</i>	<i>50.0</i>		<i>81</i>	<i>23-120</i>			
<i>Surrogate: 2-Fluorobiphenyl</i>	<i>41.8</i>		<i>"</i>	<i>50.0</i>		<i>84</i>	<i>30-115</i>			
<i>Surrogate: 2,4,6-Tribromophenol</i>	<i>85.9</i>		<i>"</i>	<i>100</i>		<i>86</i>	<i>19-122</i>			
<i>Surrogate: p-Terphenyl-d14</i>	<i>39.6</i>		<i>"</i>	<i>50.0</i>		<i>79</i>	<i>18-137</i>			

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
 Reported:
 08/02/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F21026 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample Dup (5F21026-BSD1)

Prepared: 06/21/05 Analyzed: 06/22/05

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
Acenaphthene	45.8	5.0	ug/Wipe	50.0		92	31-137	2	40	
Acenaphthylene	45.6	5.0	"	50.0		91	0-200	3	200	
Anthracene	47.7	5.0	"	50.0		95	0-200	3	200	
Benzo (a) anthracene	47.7	5.0	"	50.0		95	0-200	6	200	
Benzo (a) pyrene	47.9	5.0	"	50.0		96	0-200	6	200	
Benzo (b) fluoranthene	47.0	5.0	"	50.0		94	0-200	8	200	
Benzo (g,h,i) perylene	38.3	10	"	50.0		77	0-200	6	200	
Benzo (k) fluoranthene	44.5	5.0	"	50.0		89	0-200	2	200	
Benzyl alcohol	47.6	10	"	50.0		95	0-200	6	200	
Bis(2-chloroethoxy)methane	42.8	5.0	"	50.0		86	0-200	2	200	
Bis(2-chloroethyl)ether	27.6	10	"	50.0		55	0-200	0.7	200	
Bis(2-chloroisopropyl)ether	38.6	5.0	"	50.0		77	0-200	2	200	
Bis(2-ethylhexyl)phthalate	46.4	10	"	50.0		93	0-200	7	200	
4-Bromophenyl phenyl ether	42.7	5.0	"	50.0		85	0-200	4	200	
Butyl benzyl phthalate	46.2	5.0	"	50.0		92	0-200	6	200	
4-Chloroaniline	37.9	50	"	50.0		76	0-200	6	200	
2-Chloronaphthalene	40.6	5.0	"	50.0		81	0-200	1	200	
4-Chloro-3-methylphenol	50.3	5.0	"	50.0		101	26-103	10	40	
2-Chlorophenol	42.4	5.0	"	50.0		85	25-102	3	40	
4-Chlorophenyl phenyl ether	47.1	10	"	50.0		94	0-200	6	200	
Chrysene	44.1	5.0	"	50.0		88	0-200	4	200	
Dibenz (a,h) anthracene	39.9	5.0	"	50.0		80	0-200	7	200	
Dibenzofuran	46.2	5.0	"	50.0		92	0-200	5	200	
Di-n-butyl phthalate	49.7	5.0	"	50.0		99	0-200	2	200	
1,2-Dichlorobenzene	39.7	10	"	50.0		79	0-200	2	200	
1,3-Dichlorobenzene	39.1	10	"	50.0		78	0-200	0.3	200	
1,4-Dichlorobenzene	40.1	10	"	50.0		80	28-104	0.5	40	
2,4-Dichlorophenol	45.8	5.0	"	50.0		92	0-200	3	200	
Diethyl phthalate	52.0	5.0	"	50.0		104	0-200	11	200	
2,4-Dimethylphenol	37.7	10	"	50.0		75	0-200	2	200	
Dimethyl phthalate	47.3	5.0	"	50.0		95	0-200	8	200	
4,6-Dinitro-2-methylphenol	45.6	5.0	"	50.0		91	0-200	7	200	
2,4-Dinitrophenol	58.4	10	"	50.0		117	0-200	10	200	
2,4-Dinitrotoluene	53.9	5.0	"	50.0		108	28-89	13	40	QL06
2,6-Dinitrotoluene	50.2	5.0	"	50.0		100	0-200	9	200	
Di-n-octyl phthalate	46.2	10	"	50.0		92	0-200	7	200	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0623
 Reported:
 08/02/05 13:37

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F21026 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample Dup (5F21026-BSD1)

Prepared: 06/21/05 Analyzed: 06/22/05

Fluoranthene	53.0	5.0	ug/Wipe	50.0		106	0-200	0.9	200	
Fluorene	51.6	5.0	"	50.0		103	0-200	7	200	
Hexachlorobenzene	43.6	5.0	"	50.0		87	0-200	3	200	
Hexachlorobutadiene	40.4	10	"	50.0		81	0-200	1	200	
Hexachlorocyclopentadiene	40.0	10	"	50.0		80	0-200	4	200	
Hexachloroethane	39.0	10	"	50.0		78	0-200	4	200	
Indeno (1,2,3-cd) pyrene	50.3	10	"	50.0		101	0-200	6	200	
Isophorone	39.1	5.0	"	50.0		78	0-200	5	200	
2-Methylnaphthalene	46.7	5.0	"	50.0		93	0-200	3	200	
2-Methylphenol	44.2	5.0	"	50.0		88	0-200	2	200	
4-Methylphenol	50.8	5.0	"	25.0		203	0-200	5	200	QL06
Naphthalene	45.0	5.0	"	50.0		90	0-200	0.9	200	
2-Nitroaniline	45.0	10	"	50.0		90	0-200	9	200	
3-Nitroaniline	38.5	100	"	50.0		77	0-200	7	200	
4-Nitroaniline	46.6	50	"	50.0		93	0-200	7	200	
Nitrobenzene	41.8	5.0	"	50.0		84	0-200	1	200	
2-Nitrophenol	43.1	5.0	"	50.0		86	0-200	0.7	200	
4-Nitrophenol	52.7	10	"	50.0		105	11-114	9	40	
N-Nitrosodi-n-propylamine	45.7	5.0	"	50.0		91	41-126	5	40	
N-Nitrosodiphenylamine	50.1	10	"	50.0		100	0-200	3	200	
Pentachlorophenol	46.8	10	"	50.0		94	17-109	0.4	40	
Phenanthrene	49.1	5.0	"	50.0		98	0-200	5	200	
Phenol	44.6	5.0	"	50.0		89	26-90	3	40	
Pyrene	43.9	5.0	"	50.0		88	35-142	7	40	
1,2,4-Trichlorobenzene	41.5	10	"	50.0		83	38-107	1	40	
2,4,5-Trichlorophenol	43.1	5.0	"	50.0		86	0-200	3	200	
2,4,6-Trichlorophenol	43.2	5.0	"	50.0		86	0-200	3	200	
<i>Surrogate: 2-Fluorophenol</i>	82.2		"	100		82	25-121			
<i>Surrogate: Phenol-d6</i>	90.5		"	100		90	24-113			
<i>Surrogate: Nitrobenzene-d5</i>	40.9		"	50.0		82	23-120			
<i>Surrogate: 2-Fluorobiphenyl</i>	40.8		"	50.0		82	30-115			
<i>Surrogate: 2,4,6-Tribromophenol</i>	89.7		"	100		90	19-122			
<i>Surrogate: p-Terphenyl-d14</i>	43.2		"	50.0		86	18-137			

Dept. of Toxic Substances Control-Berkeley 700 Heinz Avenue, Suite 100 Berkeley CA, 94710	Project:OEHHA Playground Study Project Number:- Project Manager:Myrto Petreas	MOF0623 Reported: 08/02/05 13:37
---	---	---

Polynuclear Aromatic Compounds by GC/MS with Selected Ion Monitoring - Quality Control
Sequoia Analytical - Petaluma

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5060031 - EPA 3580A Waste Dil / GCMS-SIM

Blank (5060031-BLK1)

Prepared: 06/21/05 Analyzed: 06/22/05

Naphthalene	ND	530	ug/Wipe							
Acenaphthylene	ND	530	"							
Acenaphthene	ND	530	"							
Fluorene	ND	530	"							
Phenanthrene	ND	530	"							
Anthracene	ND	530	"							
Fluoranthene	ND	530	"							
Pyrene	ND	530	"							
Benzo (a) anthracene	ND	530	"							
Chrysene	ND	530	"							
Benzo (b+k) fluoranthene (total)	ND	1100	"							
Benzo (b) fluoranthene	ND	530	"							
Benzo (k) fluoranthene	ND	530	"							
Benzo (a) pyrene	ND	530	"							
Indeno (1,2,3-cd) pyrene	ND	530	"							
Benzo (g,h,i) perylene	ND	530	"							
Dibenz (a,h) anthracene	ND	530	"							
<i>Surrogate: Nitrobenzene-d5</i>	99.4		"	100		99	30-101			
<i>Surrogate: 2-Fluorobiphenyl</i>	101		"	100		101	21-111			
<i>Surrogate: Terphenyl-d14</i>	98.2		"	100		98	38-123			

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:-
Project Manager:Myrto Petreas

MOF0623
Reported:
08/02/05 13:37

Notes and Definitions

QL06 Laboratory Control Sample and/or Laboratory Control Sample Duplicate recovery was above the acceptance limits. Analyte not detected, data not impacted.

QB02 The method blank contains this analyte at a concentration above the method reporting limit.

DET Analyte DETECTED

ND Analyte NOT DETECTED at or above the reporting limit or MDL, if MDL is specified

NR Not Reported

dry Sample results reported on a dry weight basis

RPD Relative Percent Difference

MOF 6423

HAZARDOUS MATERIALS SAMPLE ANALYSIS REQUEST	1. Authorization Number	HML No. To	2. Page 1 of 2
--	-------------------------	---------------	------------------------------

3. REQUESTOR: <u>VTDAIR/PETREAS</u>	4. Phone <u>(510) 540-3003</u>	7. TAT Level: (check one) <input type="checkbox"/> 1 <input type="checkbox"/> 2 <input type="checkbox"/> 3 <input type="checkbox"/> 4	
5. ADDRESS (To Receive Results) <u>700 HEINZ AVE SUITE 100 BERKELEY CA 94710</u>	6. FAX () <u>-3305</u>		

8. DATE SAMPLED: <u>6/15/05</u>	9. Codes (fill in all applicable codes)		
10. ACTIVITY: <input type="checkbox"/> SCD <input type="checkbox"/> SRPD <input type="checkbox"/> CIB <input type="checkbox"/> SMB <input type="checkbox"/> FPB <input type="checkbox"/> SPPT <input type="checkbox"/> Others			
11. SAMPLING LOCATION			
a. EPA ID No.			
b. Site <u>OEHA PLAYGROUND STUDY</u>			
c. Address			
Number	Street	City	ZIP

12. SAMPLES:		Sample		Container		Field Information	
a. ID	b. Collector's No.	c. HML No.	d. Type	e. Type	f. Size	g. Field Information	
A	A		POLYESTER WIFE WETTED WATER			GLASS JAR 8 OZ	
B	B		"			"	
C	C		"			"	
D	D		"			"	
E	E		"			"	
F	F		"			"	

13. ANALYSIS REQUESTED: (X desired analysis and enter I.D.s from 12.a.)																																																																																																																					
<table border="1" style="width:100%; border-collapse: collapse;"> <tr><th colspan="2">INORGANIC ANALYSIS</th><th colspan="2">Sample(s) ID</th></tr> <tr><td><input checked="" type="checkbox"/> pH</td><td></td><td></td><td></td></tr> <tr><td><input checked="" type="checkbox"/> Metals Scan (6010) 6020</td><td></td><td>A, B, C</td><td></td></tr> <tr><td><input type="checkbox"/> Metal(s) Specific</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> WET</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> Cyanides</td><td></td><td></td><td></td></tr> <tr><td><input checked="" type="checkbox"/> Hg 7471 (others, write in)</td><td></td><td>DEF</td><td></td></tr> <tr><td>(others, write in)</td><td></td><td></td><td></td></tr> <tr><td colspan="2">TCLP Analysis</td><td><input type="checkbox"/></td><td><input type="checkbox"/></td></tr> <tr><td colspan="4" style="text-align:center;">(only if necessary) (do TCLP regardless)</td></tr> <tr><td><input type="checkbox"/> Metals</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> Mercury</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> Volatiles</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> Semivolatiles</td><td></td><td></td><td></td></tr> <tr><td colspan="2">(others, write in)</td><td></td><td></td></tr> </table>	INORGANIC ANALYSIS		Sample(s) ID		<input checked="" type="checkbox"/> pH				<input checked="" type="checkbox"/> Metals Scan (6010) 6020		A, B, C		<input type="checkbox"/> Metal(s) Specific				<input type="checkbox"/> WET				<input type="checkbox"/> Cyanides				<input checked="" type="checkbox"/> Hg 7471 (others, write in)		DEF		(others, write in)				TCLP Analysis		<input type="checkbox"/>	<input type="checkbox"/>	(only if necessary) (do TCLP regardless)				<input type="checkbox"/> Metals				<input type="checkbox"/> Mercury				<input type="checkbox"/> Volatiles				<input type="checkbox"/> Semivolatiles				(others, write in)				<table border="1" style="width:100%; border-collapse: collapse;"> <tr><th colspan="2">ORGANIC ANALYSIS</th><th colspan="2">Sample(s) ID</th></tr> <tr><td><input type="checkbox"/> CL-Pesticides (8081)</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> OP-Pesticides (8141)</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> PCBs (8082)</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> G R O (8015B)</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> D R O / Motor Oil / Both (circle one)</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> n-Hexane Extractables (1664)</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> Flash Point (1020)</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> VOCs including BTEX (8260)</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> VOCs - LO Level (5035)</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> VOCs - HI Level (5035)</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> SVOCs (8270)</td><td></td><td></td><td></td></tr> <tr><td><input type="checkbox"/> PAHs (8270)</td><td></td><td></td><td></td></tr> <tr><td colspan="2">(others, write in)</td><td></td><td></td></tr> </table>	ORGANIC ANALYSIS		Sample(s) ID		<input type="checkbox"/> CL-Pesticides (8081)				<input type="checkbox"/> OP-Pesticides (8141)				<input type="checkbox"/> PCBs (8082)				<input type="checkbox"/> G R O (8015B)				<input type="checkbox"/> D R O / Motor Oil / Both (circle one)				<input type="checkbox"/> n-Hexane Extractables (1664)				<input type="checkbox"/> Flash Point (1020)				<input type="checkbox"/> VOCs including BTEX (8260)				<input type="checkbox"/> VOCs - LO Level (5035)				<input type="checkbox"/> VOCs - HI Level (5035)				<input type="checkbox"/> SVOCs (8270)				<input type="checkbox"/> PAHs (8270)				(others, write in)			
INORGANIC ANALYSIS		Sample(s) ID																																																																																																																			
<input checked="" type="checkbox"/> pH																																																																																																																					
<input checked="" type="checkbox"/> Metals Scan (6010) 6020		A, B, C																																																																																																																			
<input type="checkbox"/> Metal(s) Specific																																																																																																																					
<input type="checkbox"/> WET																																																																																																																					
<input type="checkbox"/> Cyanides																																																																																																																					
<input checked="" type="checkbox"/> Hg 7471 (others, write in)		DEF																																																																																																																			
(others, write in)																																																																																																																					
TCLP Analysis		<input type="checkbox"/>	<input type="checkbox"/>																																																																																																																		
(only if necessary) (do TCLP regardless)																																																																																																																					
<input type="checkbox"/> Metals																																																																																																																					
<input type="checkbox"/> Mercury																																																																																																																					
<input type="checkbox"/> Volatiles																																																																																																																					
<input type="checkbox"/> Semivolatiles																																																																																																																					
(others, write in)																																																																																																																					
ORGANIC ANALYSIS		Sample(s) ID																																																																																																																			
<input type="checkbox"/> CL-Pesticides (8081)																																																																																																																					
<input type="checkbox"/> OP-Pesticides (8141)																																																																																																																					
<input type="checkbox"/> PCBs (8082)																																																																																																																					
<input type="checkbox"/> G R O (8015B)																																																																																																																					
<input type="checkbox"/> D R O / Motor Oil / Both (circle one)																																																																																																																					
<input type="checkbox"/> n-Hexane Extractables (1664)																																																																																																																					
<input type="checkbox"/> Flash Point (1020)																																																																																																																					
<input type="checkbox"/> VOCs including BTEX (8260)																																																																																																																					
<input type="checkbox"/> VOCs - LO Level (5035)																																																																																																																					
<input type="checkbox"/> VOCs - HI Level (5035)																																																																																																																					
<input type="checkbox"/> SVOCs (8270)																																																																																																																					
<input type="checkbox"/> PAHs (8270)																																																																																																																					
(others, write in)																																																																																																																					

14. ANALYSIS OBJECTIVE:	<input type="checkbox"/> Waste Characterization <input type="checkbox"/> Drinking H ₂ O Standards (applies to DW only)	<input type="checkbox"/> Treatment Standards <input checked="" type="checkbox"/> Others (contact Lab supervisors first)
-------------------------	--	--

15. DETECTION LIMIT REQUIREMENTS: (specify if known and contact lab) AS LOW AS POSSIBLE

16. SUPPLEMENTAL REQUESTS	Initials _____ Date _____
---------------------------	------------------------------

17. LAB REMARKS: POLYESTER WIPES WETTED WITH WATER IN 8 OZ JARS

18. CHAIN OF CUSTODY:			
a. <u>[Signature]</u>	Dinesh Chand	06/15/05	to 06/16/05
b. <u>[Signature]</u>	MAURICE	06/16/05	to
c. <u>[Signature]</u>	PEDRO HUFANO / DM	6/16/05	to
d. _____			to

MDF0623

HAZARDOUS MATERIALS SAMPLE ANALYSIS REQUEST

1. Authorization Number: _____ HML No. _____ To _____ 2. Page 2 of 2

3. REQUESTOR: VIDAIR/PETREAS 4. Phone () - _____
5. ADDRESS (To Receive Results) 6. FAX () - _____
700 HEINZ AVE, SUIT 100
BERKELEY, CA 94710

7. TAT Level: (check one)

1 2 3 4

* Unit Chief's Signature _____

8. DATE SAMPLED: 6/15/05

9. Codes (fill in all applicable codes)

10. ACTIVITY: SCD SRPD CIB SMB FPB SPPT Others _____

11. SAMPLING LOCATION

a. EPA ID No. _____

b. Site OEWA PLAYGROUND STUDY

c. Address _____

Number Street City ZIP

a. Office _____

b. INDEX _____

c. PCA _____

d. MPC _____

e. SITE _____

f. County _____

12. SAMPLES:

a. ID	b. Collector's No.	c. HML No.	d. Type	e. Type	f. Size	g. Field Information
A	G		POLYESTER WIFE	WETTED WITH WATER	IN 8 OZ JAR	
B	H				11	
C	I				11	
D	J		POLYESTER WIFE	WETTED ISOPROPYL ALCOHOL	IN 8 OZ JAR	
E	K				11	
F	L				11	

13. ANALYSIS REQUESTED: (X desired analysis and enter I.D.s from 12.a.)

INORGANIC ANALYSIS

Sample(s) ID
pH
Metals Scan (6010)
Metal(s) Specific
WET
Cyanides
(others, write in)
(others, write in)
TCLP Analysis <input type="checkbox"/> (only if necessary) <input type="checkbox"/> (do TCLP regardless)
Metals
Mercury
Volatiles
Semivolatiles
(others, write in)

ORGANIC ANALYSIS

Sample(s) ID
CL-Pesticides (8081)
OP-Pesticides (8141)
PCBs (8082)
GRO (8015B)
DRO / Motor Oil / Bath (circle one)
n-Hexane Extractables (1664)
Flash Point (1020)
VOCs Including BTEX (8260)
VOCs - LO Level (5035)
VOCs - HI Level (5035)
X SVOCs (8270) G, H, I
X PAHs (8270) / SIM J, K, L
(others, write in)

14. ANALYSIS OBJECTIVE: (check a box)

Waste Characterization Treatment Standards

Drinking H₂O Standards (applies to DW only) Others (contact Lab supervisors first)

15. DETECTION LIMIT REQUIREMENTS: (specify if known and contact lab) AS LOW AS POSSIBLE

16. SUPPLEMENTAL REQUESTS _____ Initials _____ Date _____

17. LAB REMARKS: POLYESTER WIPES WETTED WITH WATER OF ISOPROPYL ALCOHOL IN 8 OZ JARS

18. CHAIN OF CUSTODY:

a.	Signature(s)	Name(s) / Title(s)	Inclusive Dates of Custody
	<u>[Signature]</u>	<u>Patricia Chan</u>	<u>06/15/05</u> to <u>06/16/05</u>
	<u>[Signature]</u>	<u>MAURIE</u>	<u>06/16/05</u> to _____
	<u>[Signature]</u>	<u>PEDRO HUFANO / DM</u>	<u>6/14/05</u> to _____
			to _____

California Department of Toxic Substances Control
Hazardous Materials Laboratory
 700 Heinz Avenue, Suite#150, Berkeley, CA 94710

70F623

SAMPLE / SAMPLE EXTRACT TRANSPORT CUSTODY

Receiving Lab / Section: Sequoia Analytical Lab

Sample Collection Site: OE HAA PLAYGROUND STUDY

HML # or Collector's #	Sample Type *	Analysis Requested	Location of Sample (s)	Remarks
A TO L	Polyester wipe	SAR		

- OSC = original sample container; SS = split sample; A = Aliquot; C = Citrate WET; E = Extract; D = acid digest; T = TCLP extract

Release for transport by: Dinesh Chand Time / Date 6/16/05 1:40pm

Transported to: Sequoia Lab/ GC/MS/ Org sec / Inorg sec/ Fed Ex / Others
 By: [Signature] Time / Date 6/16/05 1:40pm

Received by: [Signature] SEQ.MH Time / Date 6/16/05 1:40pm

Returned to HML by: _____ Time / Date _____

SEQUOIA ANALYTICAL SAMPLE RECEIPT LOG

CLIENT NAME: DTSC
 REC. BY (PRINT) PI
 WORKORDER: MOF0423

DATE REC'D AT LAB: 6/16/05
 TIME REC'D AT LAB: 1920
 DATE LOGGED IN: 4-18-05

For Regulatory Purposes?
 DRINKING WATER YES/NO NO
 WASTE WATER YES/NO NO

(For clients requiring preservation checks at receipt, document here ↓)

CIRCLE THE APPROPRIATE RESPONSE	LAB SAMPLE #	DASH #	CLIENT ID	CONTAINER DESCRIPTION	PRESERVATIVE	pH	SAMPLE MATRIX	DATE SAMPLED	REMARKS: CONDITION (ETC.)
1. Custody Seal(s) Present / <u>Absent</u> Intact / Broken*	01		A	800 JAR	—	—	WIDE	6/15/05	
2. Chain-of-Custody <u>Present</u> / Absent*	02		B						
3. Traffic Reports or Packing List: Present / <u>Absent</u>	03		C						
4. Airbill: Airbill / Sticker Present / <u>Absent</u>	04		D						
5. Airbill #:	05		E						
6. Sample Labels: <u>Present</u> / Absent	06		F						
7. Sample IDs: <u>Listed</u> / Not Listed on Chain-of-Custody	07		G						
8. Sample Condition: <u>Intact</u> / Broken* / Leaking*	08		H						
9. Does information on chain-of-custody, traffic reports and sample labels agree? <u>Yes</u> / No*	09		I						
10. Sample received within hold time? <u>Yes</u> / No*	10		J						
11. Adequate sample volume received? <u>Yes</u> / No*	11		K						
12. Proper Preservatives used? <u>Yes</u> / No*	12		L						
13. Trip Blank / Temp Blank Received? (circle which, if yes) <u>Yes</u> / <u>No</u> *									
14. Temp Rec. at Lab: Is temp 4 +/- 2°C? <u>4-6 °C</u> <u>Yes</u> / No**									

(Acceptance range for samples requiring thermal pres.)

**Exception (if any): METALS / DFF ON ICE
or Problem COC

*IF CIRCLED, CONTACT PROJECT MANAGER AND ATTACH RECORD OF RESOLUTION.



4 August, 2005

Myrto Petreas
Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley, CA 94710

RE: OEHHA Playground Study
Work Order: MOF0858

Enclosed are the results of analyses for samples received by the laboratory on 06/23/05 16:30. If you have any questions concerning this report, please feel free to contact me.

Sincerely,

Theresa Allen
Project Manager

CA ELAP Certificate #1210

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:-
Project Manager:Myrto Petreas

MOF0858
Reported:
08/04/05 16:42

ANALYTICAL REPORT FOR SAMPLES

Sample ID	Laboratory ID	Matrix	Date Sampled	Date Received
A	MOF0858-01	Wipe	06/21/05 00:00	06/23/05 16:30
B	MOF0858-02	Wipe	06/21/05 00:00	06/23/05 16:30
C	MOF0858-03	Wipe	06/21/05 00:00	06/23/05 16:30
D	MOF0858-04	Wipe	06/21/05 00:00	06/23/05 16:30
E	MOF0858-05	Wipe	06/21/05 00:00	06/23/05 16:30
F	MOF0858-06	Wipe	06/21/05 00:00	06/23/05 16:30
G	MOF0858-07	Wipe	06/21/05 00:00	06/23/05 16:30
H	MOF0858-08	Wipe	06/21/05 00:00	06/23/05 16:30
I	MOF0858-09	Wipe	06/21/05 00:00	06/23/05 16:30
J	MOF0858-10	Wipe	06/21/05 00:00	06/23/05 16:30
K	MOF0858-11	Wipe	06/21/05 00:00	06/23/05 16:30
L	MOF0858-12	Wipe	06/21/05 00:00	06/23/05 16:30

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:-
Project Manager:Myrto Petreas

MOF0858
Reported:
08/04/05 16:42

**Total Metals by EPA 6020 ICPMS
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
A (MOF0858-01) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Aluminum	370	2.0	ug/Wipe	20	5G05011	06/27/05	07/05/05	EPA 6020	
B (MOF0858-02) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Aluminum	370	2.0	ug/Wipe	20	5G05011	06/27/05	07/05/05	EPA 6020	
C (MOF0858-03) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Aluminum	330	2.0	ug/Wipe	20	5G05011	06/27/05	07/05/05	EPA 6020	

Dept. of Toxic Substances Control-Berkeley 700 Heinz Avenue, Suite 100 Berkeley CA, 94710	Project:OEHHA Playground Study Project Number:- Project Manager:Myrto Petreas	MOF0858 Reported: 08/04/05 16:42
---	---	---

**Total Metals by EPA 6000/7000 Series Methods
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
---------	--------	-----------------	-------	----------	-------	----------	----------	--------	-------

A (MOF0858-01) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30

Calcium	410	12	ug/Wipe	1	5F27021	06/27/05	06/28/05	EPA 6010B	
Iron	720	5.0	"	"	"	"	"	"	
Potassium	150	100	"	"	"	"	"	"	
Antimony	130	1.0	"	20	5G05011	"	07/05/05	EPA 6020	
Arsenic	ND	1.0	"	"	"	"	"	"	
Barium	ND	5.0	"	"	"	"	"	"	
Beryllium	ND	0.20	"	"	"	"	"	"	
Cadmium	ND	0.60	"	"	"	"	"	"	
Chromium	ND	10	"	"	"	"	"	"	
Cobalt	ND	2.0	"	"	"	"	"	"	
Copper	ND	5.0	"	"	"	"	"	"	
Lead	ND	5.0	"	"	"	"	"	"	
Molybdenum	ND	2.0	"	"	"	"	"	"	
Nickel	ND	8.0	"	"	"	"	"	"	
Selenium	ND	1.0	"	"	"	"	"	"	
Silver	ND	1.0	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	ND	2.0	"	"	"	"	"	"	
Zinc	100	10	"	"	"	"	"	"	
Magnesium	210	2.5	"	1	5F27021	"	06/28/05	EPA 6010B	

B (MOF0858-02) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30

Calcium	400	12	ug/Wipe	1	5F27021	06/27/05	06/28/05	EPA 6010B	
Iron	650	5.0	"	"	"	"	"	"	
Potassium	140	100	"	"	"	"	"	"	
Antimony	210	1.0	"	20	5G05011	"	07/05/05	EPA 6020	
Arsenic	ND	1.0	"	"	"	"	"	"	
Barium	ND	5.0	"	"	"	"	"	"	
Beryllium	ND	0.20	"	"	"	"	"	"	
Cadmium	ND	0.60	"	"	"	"	"	"	
Chromium	ND	10	"	"	"	"	"	"	
Cobalt	ND	2.0	"	"	"	"	"	"	
Copper	ND	5.0	"	"	"	"	"	"	
Lead	ND	5.0	"	"	"	"	"	"	
Molybdenum	ND	2.0	"	"	"	"	"	"	
Nickel	ND	8.0	"	"	"	"	"	"	
Selenium	ND	1.0	"	"	"	"	"	"	
Silver	ND	1.0	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	ND	2.0	"	"	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
Reported:
 08/04/05 16:42

**Total Metals by EPA 6000/7000 Series Methods
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
B (MOF0858-02) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Zinc	110	10	ug/Wipe	20	5G05011	06/27/05	07/05/05	EPA 6020	
Magnesium	210	2.5	"	1	5F27021	"	06/28/05	EPA 6010B	
C (MOF0858-03) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Calcium	1300	12	ug/Wipe	1	5F27021	06/27/05	06/28/05	EPA 6010B	
Iron	670	5.0	"	"	"	"	"	"	
Potassium	120	100	"	"	"	"	"	"	
Antimony	170	1.0	"	20	5G05011	"	07/05/05	EPA 6020	
Arsenic	ND	1.0	"	"	"	"	"	"	
Barium	ND	5.0	"	"	"	"	"	"	
Beryllium	ND	0.20	"	"	"	"	"	"	
Cadmium	ND	0.60	"	"	"	"	"	"	
Chromium	ND	10	"	"	"	"	"	"	
Cobalt	ND	2.0	"	"	"	"	"	"	
Copper	ND	5.0	"	"	"	"	"	"	
Lead	ND	5.0	"	"	"	"	"	"	
Molybdenum	ND	2.0	"	"	"	"	"	"	
Nickel	ND	8.0	"	"	"	"	"	"	
Selenium	ND	1.0	"	"	"	"	"	"	
Silver	ND	1.0	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	ND	2.0	"	"	"	"	"	"	
Zinc	26	10	"	"	"	"	"	"	
Magnesium	220	2.5	"	1	5F27021	"	06/28/05	EPA 6010B	

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:-
Project Manager:Myrto Petreas

MOF0858
Reported:
08/04/05 16:42

**Total Metals by EPA 6000/7000 Series Methods
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
D (MOF0858-04) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Mercury	ND	0.0050	ug/Wipe	1	5F27009	06/27/05	06/27/05	EPA 7471A	
E (MOF0858-05) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Mercury	ND	0.0050	ug/Wipe	1	5F27009	06/27/05	06/27/05	EPA 7471A	
F (MOF0858-06) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Mercury	ND	0.0050	ug/Wipe	1	5F27009	06/27/05	06/27/05	EPA 7471A	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
Reported:
 08/04/05 16:42

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
G (MOF0858-07) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Acenaphthene	ND	5.0	ug/Wipe	1	5F27024	06/27/05	06/28/05	EPA 8270C	
Acenaphthylene	ND	5.0	"	"	"	"	"	"	
Anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) pyrene	ND	5.0	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzoic acid	ND	10	"	"	"	"	"	"	
Benzyl alcohol	ND	10	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	5.0	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	10	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	5.0	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	10	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	5.0	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	5.0	"	"	"	"	"	"	
4-Chloroaniline	ND	50	"	"	"	"	"	"	
2-Chloronaphthalene	ND	5.0	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	5.0	"	"	"	"	"	"	
2-Chlorophenol	ND	5.0	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	10	"	"	"	"	"	"	
Chrysene	ND	5.0	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	5.0	"	"	"	"	"	"	
Dibenzofuran	ND	5.0	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	5.0	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	10	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	50	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	5.0	"	"	"	"	"	"	
Diethyl phthalate	ND	5.0	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	10	"	"	"	"	"	"	
Dimethyl phthalate	ND	5.0	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	5.0	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	10	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	10	"	"	"	"	"	"	
Fluoranthene	ND	5.0	"	"	"	"	"	"	
Fluorene	ND	5.0	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
 Reported:
 08/04/05 16:42

Semivolatile Organic Compounds by EPA Method 8270C

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
---------	--------	-----------------	-------	----------	-------	----------	----------	--------	-------

G (MOF0858-07) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30

Hexachlorobenzene	ND	5.0	ug/Wipe	1	5F27024	06/27/05	06/28/05	EPA 8270C	
Hexachlorobutadiene	ND	10	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	10	"	"	"	"	"	"	
Hexachloroethane	ND	10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	10	"	"	"	"	"	"	
Isophorone	ND	5.0	"	"	"	"	"	"	
2-Methylnaphthalene	ND	5.0	"	"	"	"	"	"	
2-Methylphenol	ND	5.0	"	"	"	"	"	"	
4-Methylphenol	ND	5.0	"	"	"	"	"	"	
Naphthalene	ND	5.0	"	"	"	"	"	"	
2-Nitroaniline	ND	10	"	"	"	"	"	"	
3-Nitroaniline	ND	100	"	"	"	"	"	"	
4-Nitroaniline	ND	50	"	"	"	"	"	"	
Nitrobenzene	ND	5.0	"	"	"	"	"	"	
2-Nitrophenol	ND	5.0	"	"	"	"	"	"	
4-Nitrophenol	ND	10	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	5.0	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	10	"	"	"	"	"	"	
Pentachlorophenol	ND	10	"	"	"	"	"	"	
Phenanthrene	ND	5.0	"	"	"	"	"	"	
Phenol	ND	5.0	"	"	"	"	"	"	
Pyrene	ND	5.0	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	10	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		76 %		25-121		"	"	"	"
<i>Surrogate: Phenol-d6</i>		87 %		24-113		"	"	"	"
<i>Surrogate: Nitrobenzene-d5</i>		77 %		23-120		"	"	"	"
<i>Surrogate: 2-Fluorobiphenyl</i>		79 %		30-115		"	"	"	"
<i>Surrogate: 2,4,6-Tribromophenol</i>		86 %		19-122		"	"	"	"
<i>Surrogate: p-Terphenyl-d14</i>		72 %		18-137		"	"	"	"

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
 Reported:
 08/04/05 16:42

Semivolatile Organic Compounds by EPA Method 8270C

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
H (MOF0858-08) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Acenaphthene	ND	5.0	ug/Wipe	1	5F27024	06/27/05	06/28/05	EPA 8270C	
Acenaphthylene	ND	5.0	"	"	"	"	"	"	
Anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) pyrene	ND	5.0	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzoic acid	ND	10	"	"	"	"	"	"	
Benzyl alcohol	ND	10	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	5.0	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	10	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	5.0	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	10	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	5.0	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	5.0	"	"	"	"	"	"	
4-Chloroaniline	ND	50	"	"	"	"	"	"	
2-Chloronaphthalene	ND	5.0	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	5.0	"	"	"	"	"	"	
2-Chlorophenol	ND	5.0	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	10	"	"	"	"	"	"	
Chrysene	ND	5.0	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	5.0	"	"	"	"	"	"	
Dibenzofuran	ND	5.0	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	5.0	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	10	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	50	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	5.0	"	"	"	"	"	"	
Diethyl phthalate	ND	5.0	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	10	"	"	"	"	"	"	
Dimethyl phthalate	ND	5.0	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	5.0	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	10	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	10	"	"	"	"	"	"	
Fluoranthene	ND	5.0	"	"	"	"	"	"	
Fluorene	ND	5.0	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
Reported:
 08/04/05 16:42

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
H (MOF0858-08) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Hexachlorobenzene	ND	5.0	ug/Wipe	1	5F27024	06/27/05	06/28/05	EPA 8270C	
Hexachlorobutadiene	ND	10	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	10	"	"	"	"	"	"	
Hexachloroethane	ND	10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	10	"	"	"	"	"	"	
Isophorone	ND	5.0	"	"	"	"	"	"	
2-Methylnaphthalene	ND	5.0	"	"	"	"	"	"	
2-Methylphenol	ND	5.0	"	"	"	"	"	"	
4-Methylphenol	ND	5.0	"	"	"	"	"	"	
Naphthalene	ND	5.0	"	"	"	"	"	"	
2-Nitroaniline	ND	10	"	"	"	"	"	"	
3-Nitroaniline	ND	100	"	"	"	"	"	"	
4-Nitroaniline	ND	50	"	"	"	"	"	"	
Nitrobenzene	ND	5.0	"	"	"	"	"	"	
2-Nitrophenol	ND	5.0	"	"	"	"	"	"	
4-Nitrophenol	ND	10	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	5.0	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	10	"	"	"	"	"	"	
Pentachlorophenol	ND	10	"	"	"	"	"	"	
Phenanthrene	ND	5.0	"	"	"	"	"	"	
Phenol	ND	5.0	"	"	"	"	"	"	
Pyrene	ND	5.0	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	10	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		78 %		25-121	"	"	"	"	
<i>Surrogate: Phenol-d6</i>		91 %		24-113	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		78 %		23-120	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		79 %		30-115	"	"	"	"	
<i>Surrogate: 2,4,6-Tribromophenol</i>		89 %		19-122	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		68 %		18-137	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
 Reported:
 08/04/05 16:42

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
---------	--------	-----------------	-------	----------	-------	----------	----------	--------	-------

I (MOF0858-09) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30

Acenaphthene	ND	5.0	ug/Wipe	1	5F27024	06/27/05	06/28/05	EPA 8270C	
Acenaphthylene	ND	5.0	"	"	"	"	"	"	
Anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) pyrene	ND	5.0	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzoic acid	ND	10	"	"	"	"	"	"	
Benzyl alcohol	ND	10	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	5.0	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	10	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	5.0	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	10	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	5.0	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	5.0	"	"	"	"	"	"	
4-Chloroaniline	ND	50	"	"	"	"	"	"	
2-Chloronaphthalene	ND	5.0	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	5.0	"	"	"	"	"	"	
2-Chlorophenol	ND	5.0	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	10	"	"	"	"	"	"	
Chrysene	ND	5.0	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	5.0	"	"	"	"	"	"	
Dibenzofuran	ND	5.0	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	5.0	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	10	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	50	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	5.0	"	"	"	"	"	"	
Diethyl phthalate	ND	5.0	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	10	"	"	"	"	"	"	
Dimethyl phthalate	ND	5.0	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	5.0	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	10	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	10	"	"	"	"	"	"	
Fluoranthene	ND	5.0	"	"	"	"	"	"	
Fluorene	ND	5.0	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
Reported:
 08/04/05 16:42

Semivolatile Organic Compounds by EPA Method 8270C

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
I (MOF0858-09) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Hexachlorobenzene	ND	5.0	ug/Wipe	1	5F27024	06/27/05	06/28/05	EPA 8270C	
Hexachlorobutadiene	ND	10	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	10	"	"	"	"	"	"	
Hexachloroethane	ND	10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	10	"	"	"	"	"	"	
Isophorone	ND	5.0	"	"	"	"	"	"	
2-Methylnaphthalene	ND	5.0	"	"	"	"	"	"	
2-Methylphenol	ND	5.0	"	"	"	"	"	"	
4-Methylphenol	ND	5.0	"	"	"	"	"	"	
Naphthalene	ND	5.0	"	"	"	"	"	"	
2-Nitroaniline	ND	10	"	"	"	"	"	"	
3-Nitroaniline	ND	100	"	"	"	"	"	"	
4-Nitroaniline	ND	50	"	"	"	"	"	"	
Nitrobenzene	ND	5.0	"	"	"	"	"	"	
2-Nitrophenol	ND	5.0	"	"	"	"	"	"	
4-Nitrophenol	ND	10	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	5.0	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	10	"	"	"	"	"	"	
Pentachlorophenol	ND	10	"	"	"	"	"	"	
Phenanthrene	ND	5.0	"	"	"	"	"	"	
Phenol	ND	5.0	"	"	"	"	"	"	
Pyrene	ND	5.0	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	10	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		79 %		25-121	"	"	"	"	
<i>Surrogate: Phenol-d6</i>		93 %		24-113	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		82 %		23-120	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		82 %		30-115	"	"	"	"	
<i>Surrogate: 2,4,6-Tribromophenol</i>		91 %		19-122	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		77 %		18-137	"	"	"	"	

Dept. of Toxic Substances Contol-Berkeley 700 Heinz Avenue, Suite 100 Berkeley CA, 94710	Project:OEHHA Playground Study Project Number:- Project Manager:Myrto Petreas	MOF0858 Reported: 08/04/05 16:42
--	---	--

Polynuclear Aromatic Compounds by GC/MS with Selected Ion Monitoring
Sequoia Analytical - Petaluma

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
J (MOF0858-10) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Naphthalene	ND	66	ug/Wipe	1	5060042	06/30/05	08/03/05	GCMS-SIM	
Acenaphthylene	ND	66	"	"	"	"	"	"	
Acenaphthene	ND	66	"	"	"	"	"	"	
Fluorene	ND	66	"	"	"	"	"	"	
Phenanthrene	ND	66	"	"	"	"	"	"	
Anthracene	ND	66	"	"	"	"	"	"	
Fluoranthene	ND	66	"	"	"	"	"	"	
Pyrene	ND	66	"	"	"	"	"	"	
Benzo (a) anthracene	ND	66	"	"	"	"	"	"	
Chrysene	ND	66	"	"	"	"	"	"	
Benzo (b+k) fluoranthene (total)	ND	130	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	66	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	66	"	"	"	"	"	"	
Benzo (a) pyrene	ND	66	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	66	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	66	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	66	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		35 %	50-150		"	"	"	"	S02
<i>Surrogate: 2-Fluorobiphenyl</i>		44 %	50-150		"	"	"	"	S02
<i>Surrogate: Terphenyl-d14</i>		77 %	50-150		"	"	"	"	
K (MOF0858-11) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Naphthalene	ND	66	ug/Wipe	1	5060042	06/30/05	08/03/05	GCMS-SIM	
Acenaphthylene	ND	66	"	"	"	"	"	"	
Acenaphthene	ND	66	"	"	"	"	"	"	
Fluorene	ND	66	"	"	"	"	"	"	
Phenanthrene	ND	66	"	"	"	"	"	"	
Anthracene	ND	66	"	"	"	"	"	"	
Fluoranthene	ND	66	"	"	"	"	"	"	
Pyrene	ND	66	"	"	"	"	"	"	
Benzo (a) anthracene	ND	66	"	"	"	"	"	"	
Chrysene	ND	66	"	"	"	"	"	"	
Benzo (b+k) fluoranthene (total)	ND	130	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	66	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	66	"	"	"	"	"	"	
Benzo (a) pyrene	ND	66	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	66	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	66	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	66	"	"	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
 Reported:
 08/04/05 16:42

Polynuclear Aromatic Compounds by GC/MS with Selected Ion Monitoring
Sequoia Analytical - Petaluma

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
K (MOF0858-11) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
<i>Surrogate: Nitrobenzene-d5</i>		52 %	50-150		5060042	06/30/05	08/03/05	GCMS-SIM	
<i>Surrogate: 2-Fluorobiphenyl</i>		58 %	50-150		"	"	"	"	
<i>Surrogate: Terphenyl-d14</i>		86 %	50-150		"	"	"	"	
L (MOF0858-12) Wipe Sampled: 06/21/05 00:00 Received: 06/23/05 16:30									
Naphthalene	ND	66	ug/Wipe	1	5060042	06/30/05	08/03/05	GCMS-SIM	
Acenaphthylene	ND	66	"	"	"	"	"	"	
Acenaphthene	ND	66	"	"	"	"	"	"	
Fluorene	ND	66	"	"	"	"	"	"	
Phenanthrene	ND	66	"	"	"	"	"	"	
Anthracene	ND	66	"	"	"	"	"	"	
Fluoranthene	ND	66	"	"	"	"	"	"	
Pyrene	ND	66	"	"	"	"	"	"	
Benzo (a) anthracene	ND	66	"	"	"	"	"	"	
Chrysene	ND	66	"	"	"	"	"	"	
Benzo (b+k) fluoranthene (total)	ND	130	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	66	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	66	"	"	"	"	"	"	
Benzo (a) pyrene	ND	66	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	66	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	66	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	66	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		37 %	50-150		"	"	"	"	S02
<i>Surrogate: 2-Fluorobiphenyl</i>		50 %	50-150		"	"	"	"	
<i>Surrogate: Terphenyl-d14</i>		63 %	50-150		"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
Reported:
 08/04/05 16:42

**Total Metals by EPA 6020 ICPMS - Quality Control
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5G05011 - EPA 3050B / EPA 6020

Blank (5G05011-BLK1)				Prepared: 06/27/05 Analyzed: 07/05/05						
Aluminum	ND	2.0	ug/Wipe							
Laboratory Control Sample (5G05011-BS1)				Prepared: 06/27/05 Analyzed: 07/05/05						
Aluminum	51.9	2.0	ug/Wipe	50.0		104	80-120			
Laboratory Control Sample (5G05011-BS2)				Prepared: 06/27/05 Analyzed: 07/05/05						
Aluminum	50.9	2.0	ug/Wipe	50.0		102	80-120			

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
Reported:
 08/04/05 16:42

Total Metals by EPA 6000/7000 Series Methods - Quality Control
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F27021 - EPA 3050B / EPA 6010B
Blank (5F27021-BLK1)

Prepared: 06/27/05 Analyzed: 06/28/05

Magnesium	ND	2.5	ug/Wipe							
Calcium	ND	12	"							
Iron	ND	5.0	"							
Potassium	ND	100	"							

Laboratory Control Sample (5F27021-BS1)

Prepared: 06/27/05 Analyzed: 06/28/05

Magnesium	500	2.5	ug/Wipe	500		100	85-115			
Calcium	517	12	"	500		103	85-115			
Iron	51.8	5.0	"	50.0		104	85-115			
Potassium	519	100	"	500		104	70-125			

Laboratory Control Sample (5F27021-BS2)

Prepared: 06/27/05 Analyzed: 06/28/05

Magnesium	487	2.5	ug/Wipe	500		97	85-115			
Calcium	510	12	"	500		102	85-115			
Iron	51.1	5.0	"	50.0		102	85-115			
Potassium	512	100	"	500		102	70-125			

Batch 5G05011 - EPA 3050B / EPA 6020
Blank (5G05011-BLK1)

Prepared: 06/27/05 Analyzed: 07/05/05

Antimony	ND	1.0	ug/Wipe							
Arsenic	ND	1.0	"							
Barium	ND	5.0	"							
Beryllium	ND	0.20	"							
Cadmium	ND	0.60	"							
Chromium	ND	10	"							
Cobalt	ND	2.0	"							
Copper	ND	5.0	"							
Lead	ND	5.0	"							
Molybdenum	ND	2.0	"							
Nickel	ND	8.0	"							
Selenium	1.40	1.0	"							
Silver	ND	1.0	"							
Thallium	ND	1.0	"							
Vanadium	ND	2.0	"							
Zinc	ND	10	"							

QB02

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
Reported:
 08/04/05 16:42

Total Metals by EPA 6000/7000 Series Methods - Quality Control
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5G05011 - EPA 3050B / EPA 6020
Laboratory Control Sample (5G05011-BS1)

Prepared: 06/27/05 Analyzed: 07/05/05

Antimony	48.9	1.0	ug/Wipe	50.0		98	80-120			
Arsenic	48.0	1.0	"	50.0		96	80-120			
Barium	47.8	5.0	"	50.0		96	80-120			
Beryllium	50.1	0.20	"	50.0		100	80-120			
Cadmium	47.2	0.60	"	50.0		94	80-120			
Chromium	50.9	10	"	50.0		102	80-120			
Cobalt	49.8	2.0	"	50.0		100	80-120			
Copper	50.5	5.0	"	50.0		101	80-120			
Lead	50.2	5.0	"	50.0		100	80-120			
Molybdenum	48.7	2.0	"	50.0		97	80-120			
Nickel	49.4	8.0	"	50.0		99	80-120			
Selenium	45.9	1.0	"	50.0		92	80-120			
Silver	49.5	1.0	"	50.0		99	80-120			
Thallium	49.9	1.0	"	50.0		100	80-120			
Vanadium	47.5	2.0	"	50.0		95	80-120			
Zinc	51.3	10	"	50.0		103	80-120			

Laboratory Control Sample (5G05011-BS2)

Prepared: 06/27/05 Analyzed: 07/05/05

Antimony	48.8	1.0	ug/Wipe	50.0		98	80-120			
Arsenic	47.7	1.0	"	50.0		95	80-120			
Barium	47.5	5.0	"	50.0		95	80-120			
Beryllium	48.7	0.20	"	50.0		97	80-120			
Cadmium	47.0	0.60	"	50.0		94	80-120			
Chromium	50.2	10	"	50.0		100	80-120			
Cobalt	50.2	2.0	"	50.0		100	80-120			
Copper	50.6	5.0	"	50.0		101	80-120			
Lead	50.1	5.0	"	50.0		100	80-120			
Molybdenum	48.1	2.0	"	50.0		96	80-120			
Nickel	49.4	8.0	"	50.0		99	80-120			
Selenium	45.3	1.0	"	50.0		91	80-120			
Silver	49.3	1.0	"	50.0		99	80-120			
Thallium	50.1	1.0	"	50.0		100	80-120			
Vanadium	46.9	2.0	"	50.0		94	80-120			
Zinc	51.3	10	"	50.0		103	80-120			

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:-
Project Manager:Myrto Petreas

MOF0858
Reported:
08/04/05 16:42

**Total Metals by EPA 6000/7000 Series Methods - Quality Control
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5F27009 - EPA 7471A / EPA 7471A

Blank (5F27009-BLK1)

Prepared & Analyzed: 06/27/05

Mercury ND 0.0050 ug/Wipe

Laboratory Control Sample (5F27009-BS1)

Prepared & Analyzed: 06/27/05

Mercury 0.391 0.0050 ug/Wipe 0.400 98 75-125

Laboratory Control Sample (5F27009-BS2)

Prepared & Analyzed: 06/27/05

Mercury 0.407 0.0050 ug/Wipe 0.400 102 75-125

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
Reported:
 08/04/05 16:42

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F27024 - EPA 3550 Wipe / EPA 8270C
Blank (5F27024-BLK1)

Prepared: 06/27/05 Analyzed: 06/28/05

Acenaphthene	ND	5.0	ug/Wipe							
Acenaphthylene	ND	5.0	"							
Anthracene	ND	5.0	"							
Benzo (a) anthracene	ND	5.0	"							
Benzo (a) pyrene	ND	5.0	"							
Benzo (b) fluoranthene	ND	5.0	"							
Benzo (g,h,i) perylene	ND	10	"							
Benzo (k) fluoranthene	ND	5.0	"							
Benzoic acid	ND	10	"							
Benzyl alcohol	ND	10	"							
Bis(2-chloroethoxy)methane	ND	5.0	"							
Bis(2-chloroethyl)ether	ND	10	"							
Bis(2-chloroisopropyl)ether	ND	5.0	"							
Bis(2-ethylhexyl)phthalate	ND	10	"							
4-Bromophenyl phenyl ether	ND	5.0	"							
Butyl benzyl phthalate	ND	5.0	"							
4-Chloroaniline	ND	50	"							
2-Chloronaphthalene	ND	5.0	"							
4-Chloro-3-methylphenol	ND	5.0	"							
2-Chlorophenol	ND	5.0	"							
4-Chlorophenyl phenyl ether	ND	10	"							
Chrysene	ND	5.0	"							
Dibenz (a,h) anthracene	ND	5.0	"							
Dibenzofuran	ND	5.0	"							
Di-n-butyl phthalate	ND	5.0	"							
1,2-Dichlorobenzene	ND	10	"							
1,3-Dichlorobenzene	ND	10	"							
1,4-Dichlorobenzene	ND	10	"							
3,3'-Dichlorobenzidine	ND	50	"							
2,4-Dichlorophenol	ND	5.0	"							
Diethyl phthalate	ND	5.0	"							
2,4-Dimethylphenol	ND	10	"							
Dimethyl phthalate	ND	5.0	"							
4,6-Dinitro-2-methylphenol	ND	5.0	"							
2,4-Dinitrophenol	ND	10	"							
2,4-Dinitrotoluene	ND	5.0	"							

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
Reported:
 08/04/05 16:42

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F27024 - EPA 3550 Wipe / EPA 8270C
Blank (5F27024-BLK1)

Prepared: 06/27/05 Analyzed: 06/28/05

2,6-Dinitrotoluene	ND	5.0	ug/Wipe							
Di-n-octyl phthalate	ND	10	"							
Fluoranthene	ND	5.0	"							
Fluorene	ND	5.0	"							
Hexachlorobenzene	ND	5.0	"							
Hexachlorobutadiene	ND	10	"							
Hexachlorocyclopentadiene	ND	10	"							
Hexachloroethane	ND	10	"							
Indeno (1,2,3-cd) pyrene	ND	10	"							
Isophorone	ND	5.0	"							
2-Methylnaphthalene	ND	5.0	"							
2-Methylphenol	ND	5.0	"							
4-Methylphenol	ND	5.0	"							
Naphthalene	ND	5.0	"							
2-Nitroaniline	ND	10	"							
3-Nitroaniline	ND	100	"							
4-Nitroaniline	ND	50	"							
Nitrobenzene	ND	5.0	"							
2-Nitrophenol	ND	5.0	"							
4-Nitrophenol	ND	10	"							
N-Nitrosodi-n-propylamine	ND	5.0	"							
N-Nitrosodiphenylamine	ND	10	"							
Pentachlorophenol	ND	10	"							
Phenanthrene	ND	5.0	"							
Phenol	ND	5.0	"							
Pyrene	ND	5.0	"							
1,2,4-Trichlorobenzene	ND	10	"							
2,4,5-Trichlorophenol	ND	5.0	"							
2,4,6-Trichlorophenol	ND	5.0	"							
<i>Surrogate: 2-Fluorophenol</i>	78.8		"	100		79	25-121			
<i>Surrogate: Phenol-d6</i>	90.4		"	100		90	24-113			
<i>Surrogate: Nitrobenzene-d5</i>	42.0		"	50.0		84	23-120			
<i>Surrogate: 2-Fluorobiphenyl</i>	43.0		"	50.0		86	30-115			
<i>Surrogate: 2,4,6-Tribromophenol</i>	83.6		"	100		84	19-122			
<i>Surrogate: p-Terphenyl-d14</i>	41.7		"	50.0		83	18-137			

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
 Reported:
 08/04/05 16:42

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5F27024 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample (5F27024-BS1)

Prepared: 06/27/05 Analyzed: 06/28/05

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
Acenaphthene	45.4	5.0	ug/Wipe	50.0		91	31-137			
Acenaphthylene	45.5	5.0	"	50.0		91	0-200			
Anthracene	48.0	5.0	"	50.0		96	0-200			
Benzo (a) anthracene	47.6	5.0	"	50.0		95	0-200			
Benzo (a) pyrene	47.5	5.0	"	50.0		95	0-200			
Benzo (b) fluoranthene	45.8	5.0	"	50.0		92	0-200			
Benzo (g,h,i) perylene	37.7	10	"	50.0		75	0-200			
Benzo (k) fluoranthene	44.7	5.0	"	50.0		89	0-200			
Benzyl alcohol	47.0	10	"	50.0		94	0-200			
Bis(2-chloroethoxy)methane	42.8	5.0	"	50.0		86	0-200			
Bis(2-chloroethyl)ether	31.2	10	"	50.0		62	0-200			
Bis(2-chloroisopropyl)ether	38.8	5.0	"	50.0		78	0-200			
Bis(2-ethylhexyl)phthalate	47.3	10	"	50.0		95	0-200			
4-Bromophenyl phenyl ether	45.0	5.0	"	50.0		90	0-200			
Butyl benzyl phthalate	46.2	5.0	"	50.0		92	0-200			
4-Chloroaniline	35.9	50	"	50.0		72	0-200			
2-Chloronaphthalene	42.3	5.0	"	50.0		85	0-200			
4-Chloro-3-methylphenol	47.2	5.0	"	50.0		94	26-103			
2-Chlorophenol	43.6	5.0	"	50.0		87	25-102			
4-Chlorophenyl phenyl ether	45.1	10	"	50.0		90	0-200			
Chrysene	44.6	5.0	"	50.0		89	0-200			
Dibenz (a,h) anthracene	50.5	5.0	"	50.0		101	0-200			
Dibenzofuran	43.7	5.0	"	50.0		87	0-200			
Di-n-butyl phthalate	50.9	5.0	"	50.0		102	0-200			
1,2-Dichlorobenzene	40.2	10	"	50.0		80	0-200			
1,3-Dichlorobenzene	40.6	10	"	50.0		81	0-200			
1,4-Dichlorobenzene	40.7	10	"	50.0		81	28-104			
2,4-Dichlorophenol	44.9	5.0	"	50.0		90	0-200			
Diethyl phthalate	47.4	5.0	"	50.0		95	0-200			
2,4-Dimethylphenol	39.5	10	"	50.0		79	0-200			
Dimethyl phthalate	45.0	5.0	"	50.0		90	0-200			
4,6-Dinitro-2-methylphenol	45.6	5.0	"	50.0		91	0-200			
2,4-Dinitrophenol	51.9	10	"	50.0		104	0-200			
2,4-Dinitrotoluene	48.7	5.0	"	50.0		97	28-89			QL06
2,6-Dinitrotoluene	48.2	5.0	"	50.0		96	0-200			
Di-n-octyl phthalate	47.0	10	"	50.0		94	0-200			

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
Reported:
 08/04/05 16:42

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F27024 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample (5F27024-BS1)

Prepared: 06/27/05 Analyzed: 06/28/05

Fluoranthene	54.6	5.0	ug/Wipe	50.0		109	0-200			
Fluorene	47.9	5.0	"	50.0		96	0-200			
Hexachlorobenzene	45.8	5.0	"	50.0		92	0-200			
Hexachlorobutadiene	41.4	10	"	50.0		83	0-200			
Hexachlorocyclopentadiene	45.4	10	"	50.0		91	0-200			
Hexachloroethane	39.7	10	"	50.0		79	0-200			
Indeno (1,2,3-cd) pyrene	48.8	10	"	50.0		98	0-200			
Isophorone	37.8	5.0	"	50.0		76	0-200			
2-Methylnaphthalene	45.3	5.0	"	50.0		91	0-200			
2-Methylphenol	44.4	5.0	"	50.0		89	0-200			
4-Methylphenol	51.1	5.0	"	25.0		204	0-200			QL06
Naphthalene	44.7	5.0	"	50.0		89	0-200			
2-Nitroaniline	45.3	10	"	50.0		91	0-200			
3-Nitroaniline	39.4	100	"	50.0		79	0-200			
4-Nitroaniline	46.4	50	"	50.0		93	0-200			
Nitrobenzene	42.0	5.0	"	50.0		84	0-200			
2-Nitrophenol	43.3	5.0	"	50.0		87	0-200			
4-Nitrophenol	50.0	10	"	50.0		100	11-114			
N-Nitrosodi-n-propylamine	46.4	5.0	"	50.0		93	41-126			
N-Nitrosodiphenylamine	54.2	10	"	50.0		108	0-200			
Pentachlorophenol	50.9	10	"	50.0		102	17-109			
Phenanthrene	48.3	5.0	"	50.0		97	0-200			
Phenol	45.0	5.0	"	50.0		90	26-90			
Pyrene	41.7	5.0	"	50.0		83	35-142			
1,2,4-Trichlorobenzene	42.4	10	"	50.0		85	38-107			
2,4,5-Trichlorophenol	44.8	5.0	"	50.0		90	0-200			
2,4,6-Trichlorophenol	44.8	5.0	"	50.0		90	0-200			
<i>Surrogate: 2-Fluorophenol</i>	83.3		"	100		83	25-121			
<i>Surrogate: Phenol-d6</i>	88.2		"	100		88	24-113			
<i>Surrogate: Nitrobenzene-d5</i>	40.1		"	50.0		80	23-120			
<i>Surrogate: 2-Fluorobiphenyl</i>	42.2		"	50.0		84	30-115			
<i>Surrogate: 2,4,6-Tribromophenol</i>	92.9		"	100		93	19-122			
<i>Surrogate: p-Terphenyl-d14</i>	39.8		"	50.0		80	18-137			

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
 Reported:
 08/04/05 16:42

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F27024 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample Dup (5F27024-BSD1)

Prepared: 06/27/05 Analyzed: 06/28/05

Acenaphthene	45.5	5.0	ug/Wipe	50.0		91	31-137	0.2	40	
Acenaphthylene	45.3	5.0	"	50.0		91	0-200	0.4	200	
Anthracene	48.4	5.0	"	50.0		97	0-200	0.8	200	
Benzo (a) anthracene	47.5	5.0	"	50.0		95	0-200	0.2	200	
Benzo (a) pyrene	48.0	5.0	"	50.0		96	0-200	1	200	
Benzo (b) fluoranthene	46.9	5.0	"	50.0		94	0-200	2	200	
Benzo (g,h,i) perylene	37.1	10	"	50.0		74	0-200	2	200	
Benzo (k) fluoranthene	43.7	5.0	"	50.0		87	0-200	2	200	
Benzyl alcohol	46.9	10	"	50.0		94	0-200	0.2	200	
Bis(2-chloroethoxy)methane	42.7	5.0	"	50.0		85	0-200	0.2	200	
Bis(2-chloroethyl)ether	41.3	10	"	50.0		83	0-200	28	200	
Bis(2-chloroisopropyl)ether	39.5	5.0	"	50.0		79	0-200	2	200	
Bis(2-ethylhexyl)phthalate	46.2	10	"	50.0		92	0-200	2	200	
4-Bromophenyl phenyl ether	45.2	5.0	"	50.0		90	0-200	0.4	200	
Butyl benzyl phthalate	45.3	5.0	"	50.0		91	0-200	2	200	
4-Chloroaniline	33.1	50	"	50.0		66	0-200	8	200	
2-Chloronaphthalene	43.0	5.0	"	50.0		86	0-200	2	200	
4-Chloro-3-methylphenol	45.5	5.0	"	50.0		91	26-103	4	40	
2-Chlorophenol	43.0	5.0	"	50.0		86	25-102	1	40	
4-Chlorophenyl phenyl ether	45.4	10	"	50.0		91	0-200	0.7	200	
Chrysene	44.3	5.0	"	50.0		89	0-200	0.7	200	
Dibenz (a,h) anthracene	50.3	5.0	"	50.0		101	0-200	0.4	200	
Dibenzofuran	44.1	5.0	"	50.0		88	0-200	0.9	200	
Di-n-butyl phthalate	50.5	5.0	"	50.0		101	0-200	0.8	200	
1,2-Dichlorobenzene	40.7	10	"	50.0		81	0-200	1	200	
1,3-Dichlorobenzene	40.5	10	"	50.0		81	0-200	0.2	200	
1,4-Dichlorobenzene	41.4	10	"	50.0		83	28-104	2	40	
2,4-Dichlorophenol	44.5	5.0	"	50.0		89	0-200	0.9	200	
Diethyl phthalate	46.9	5.0	"	50.0		94	0-200	1	200	
2,4-Dimethylphenol	38.2	10	"	50.0		76	0-200	3	200	
Dimethyl phthalate	44.6	5.0	"	50.0		89	0-200	0.9	200	
4,6-Dinitro-2-methylphenol	43.5	5.0	"	50.0		87	0-200	5	200	
2,4-Dinitrophenol	48.3	10	"	50.0		97	0-200	7	200	
2,4-Dinitrotoluene	47.3	5.0	"	50.0		95	28-89	3	40	QL06
2,6-Dinitrotoluene	47.9	5.0	"	50.0		96	0-200	0.6	200	
Di-n-octyl phthalate	46.0	10	"	50.0		92	0-200	2	200	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:-
 Project Manager:Myrto Petreas

 MOF0858
 Reported:
 08/04/05 16:42

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F27024 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample Dup (5F27024-BSD1)

Prepared: 06/27/05 Analyzed: 06/28/05

Fluoranthene	53.2	5.0	ug/Wipe	50.0		106	0-200	3	200	
Fluorene	47.2	5.0	"	50.0		94	0-200	1	200	
Hexachlorobenzene	45.4	5.0	"	50.0		91	0-200	0.9	200	
Hexachlorobutadiene	42.0	10	"	50.0		84	0-200	1	200	
Hexachlorocyclopentadiene	44.1	10	"	50.0		88	0-200	3	200	
Hexachloroethane	39.3	10	"	50.0		79	0-200	1	200	
Indeno (1,2,3-cd) pyrene	48.4	10	"	50.0		97	0-200	0.8	200	
Isophorone	38.1	5.0	"	50.0		76	0-200	0.8	200	
2-Methylnaphthalene	45.2	5.0	"	50.0		90	0-200	0.2	200	
2-Methylphenol	43.8	5.0	"	50.0		88	0-200	1	200	
4-Methylphenol	49.4	5.0	"	25.0		198	0-200	3	200	
Naphthalene	45.4	5.0	"	50.0		91	0-200	2	200	
2-Nitroaniline	44.5	10	"	50.0		89	0-200	2	200	
3-Nitroaniline	37.4	100	"	50.0		75	0-200	5	200	
4-Nitroaniline	44.9	50	"	50.0		90	0-200	3	200	
Nitrobenzene	42.8	5.0	"	50.0		86	0-200	2	200	
2-Nitrophenol	43.5	5.0	"	50.0		87	0-200	0.5	200	
4-Nitrophenol	49.3	10	"	50.0		99	11-114	1	40	
N-Nitrosodi-n-propylamine	45.6	5.0	"	50.0		91	41-126	2	40	
N-Nitrosodiphenylamine	54.2	10	"	50.0		108	0-200	0	200	
Pentachlorophenol	46.4	10	"	50.0		93	17-109	9	40	
Phenanthrene	48.1	5.0	"	50.0		96	0-200	0.4	200	
Phenol	44.5	5.0	"	50.0		89	26-90	1	40	
Pyrene	40.7	5.0	"	50.0		81	35-142	2	40	
1,2,4-Trichlorobenzene	41.8	10	"	50.0		84	38-107	1	40	
2,4,5-Trichlorophenol	44.0	5.0	"	50.0		88	0-200	2	200	
2,4,6-Trichlorophenol	43.6	5.0	"	50.0		87	0-200	3	200	
<i>Surrogate: 2-Fluorophenol</i>	83.8		"	100		84	25-121			
<i>Surrogate: Phenol-d6</i>	88.9		"	100		89	24-113			
<i>Surrogate: Nitrobenzene-d5</i>	41.3		"	50.0		83	23-120			
<i>Surrogate: 2-Fluorobiphenyl</i>	43.1		"	50.0		86	30-115			
<i>Surrogate: 2,4,6-Tribromophenol</i>	92.6		"	100		93	19-122			
<i>Surrogate: p-Terphenyl-d14</i>	39.8		"	50.0		80	18-137			

Dept. of Toxic Substances Control-Berkeley 700 Heinz Avenue, Suite 100 Berkeley CA, 94710	Project:OEHHA Playground Study Project Number:- Project Manager:Myrto Petreas	MOF0858 Reported: 08/04/05 16:42
---	---	---

Polynuclear Aromatic Compounds by GC/MS with Selected Ion Monitoring - Quality Control
Sequoia Analytical - Petaluma

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5060042 - EPA 3580A Waste Dil / GCMS-SIM
Blank (5060042-BLK1)

Prepared: 06/30/05 Analyzed: 08/03/05

Naphthalene	ND	66	ug/Wipe							
Acenaphthylene	ND	66	"							
Acenaphthene	ND	66	"							
Fluorene	ND	66	"							
Phenanthrene	ND	66	"							
Anthracene	ND	66	"							
Fluoranthene	ND	66	"							
Pyrene	ND	66	"							
Benzo (a) anthracene	ND	66	"							
Chrysene	ND	66	"							
Benzo (b+k) fluoranthene (total)	ND	130	"							
Benzo (b) fluoranthene	ND	66	"							
Benzo (k) fluoranthene	ND	66	"							
Benzo (a) pyrene	ND	66	"							
Indeno (1,2,3-cd) pyrene	ND	66	"							
Benzo (g,h,i) perylene	ND	66	"							
Dibenz (a,h) anthracene	ND	66	"							
<i>Surrogate: Nitrobenzene-d5</i>	36.0		"	100		36	50-150			S02
<i>Surrogate: 2-Fluorobiphenyl</i>	34.6		"	100		35	50-150			S02
<i>Surrogate: Terphenyl-d14</i>	46.6		"	100		47	50-150			S02

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:-
Project Manager:Myrto Petreas

MOF0858
Reported:
08/04/05 16:42

Notes and Definitions

S02 The surrogate recovery was below control limits.

QL06 Laboratory Control Sample and/or Laboratory Control Sample Duplicate recovery was above the acceptance limits. Analyte not detected, data not impacted.

QB02 The method blank contains this analyte at a concentration above the method reporting limit.

DET Analyte DETECTED

ND Analyte NOT DETECTED at or above the reporting limit or MDL, if MDL is specified

NR Not Reported

dry Sample results reported on a dry weight basis

RPD Relative Percent Difference

MOF 0858

HAZARDOUS MATERIALS
SAMPLE ANALYSIS REQUEST

1. Authorization Number:

HML No.
To

2. Page
1 of 2

3. REQUESTOR: VIDAIR/PETREAS
4. Phone: (510) 540-3003
5. ADDRESS (To Receive Results):
700 HEINZ AVE SUITE 100
BERKELEY CA 94710
5. FAX: () -2305

7. TAT Level: (check one)
 1 2 3 4

8. DATE SAMPLED: 6/21/05
10. ACTIVITY: SCD SRPD CIB SMB FPB SPPT Others

* Unit Chief's Signature
9. Codes (fill in all applicable codes)
a. Office
b. INDEX
c. PCA
d. MPC
e. SITE
f. County

11. SAMPLING LOCATION
b. Site: OEHHA PLAYGROUND STUDY
c. Address
Number Street City ZIP

12. SAMPLES:

a. ID	b. Collector's No.	c. HML No.	d. Type	Sample		g. Field Information
				e. Type	f. Size	
A			POLYESTER WIPES WETTED	WITH WATER	IN 8 OZ GLASS JAR	
B						
C						
D						
E						
F						

13. ANALYSIS REQUESTED: (X desired analysis and enter IDs from 12.a.)

INORGANIC ANALYSIS

Sample(s) ID
<input checked="" type="checkbox"/> Metals Scan (9940) 6020 A, B, C
<input type="checkbox"/> Metal(s) Specific
<input type="checkbox"/> WET
<input checked="" type="checkbox"/> Cyanides Hg 2471 (others, write in) D, E, F
<input type="checkbox"/> TCLP Analysis (only if necessary) (do TCLP regardless)
<input type="checkbox"/> Metals
<input type="checkbox"/> Mercury
<input type="checkbox"/> Volatiles
<input type="checkbox"/> Semivolatiles (others, write in)

ORGANIC ANALYSIS

Sample(s) ID
<input type="checkbox"/> CL-Pesticides (8081)
<input type="checkbox"/> OP-Pesticides (8141)
<input type="checkbox"/> PCBs (8082)
<input type="checkbox"/> GRO (8015B)
<input type="checkbox"/> DRO / Motor Oil / Both (circle one)
<input type="checkbox"/> n-Hexane Extractables (1664)
<input type="checkbox"/> Flash Point (1020)
<input type="checkbox"/> VOCs including BTEX (8253)
<input type="checkbox"/> VOCs - LO Level (5035)
<input type="checkbox"/> VOCs - HI Level (5035)
<input type="checkbox"/> SVOCs (8270)
<input type="checkbox"/> PAHs (8270)
(others, write in)

14. ANALYSIS OBJECTIVE: (check a box)
 Waste Characterization
 Drinking H₂O Standards (applies to DW only)
 Treatment Standards
 Others (contact Lab supervisors first)

15. DETECTION LIMIT REQUIREMENTS: AS LOW AS POSSIBLE (specify if known and contact lab)

16. SUPPLEMENTAL REQUESTS: Initials: Date:

17. LAB REMARKS: POLYESTER WIPES WETTED WITH WATER IN GLASS CONTAINERS

18. CHAIN OF CUSTODY:

a.	b.	c.	d.
Charles Vidair	Charles Vidair	06/21/05	to 06/23/05
Dinesh Chand	Dinesh Chand	06/23/05	to 06/23/05
Maurice	Maurice	06/23/05	11:50
APD	APD	06/23/05	to 16:30

SEQUOIA ANALYTICAL SAMPLE RECEIPT LOG

CLIENT NAME: DTSC
 REC. BY (PRINT): ZAY
 WORKORDER: M06858

DATE REC'D AT LAB: 6/23/05
 TIME REC'D AT LAB: 1630
 DATE LOGGED IN: 6-25-05

For Regulatory Purposes?
 DRINKING WATER YES/NO (NO)
 WASTE WATER YES/NO (NO)

(For clients requiring preservation checks at receipt, document here ↓)

CIRCLE THE APPROPRIATE RESPONSE	LAB SAMPLE #	DASH #	CLIENT ID	CONTAINER DESCRIPTION	PRESERVATIVE	pH	SAMPLE MATRIX	DATE SAMPLED	REMARKS: CONDITION (ETC.)
1. Custody Seal(s) Present / Absent Intact / Broken*	01		A	8oz jar	—	—	Water	6/21/05	
2. Chain-of-Custody Present / Absent*	02		B	↓	↓	↓	↓	↓	
3. Traffic Reports or Packing List: Present / Absent	03		C						
4. Airbill: Airbill / Sticker Present / Absent	04		D						
	05		E						
5. Airbill #: Present / Absent	06		F						
	07		G						
6. Sample Labels: Present / Absent	08		H						
	09		I						
7. Sample IDs: Listed / Not Listed on Chain-of-Custody	10		J						
	11		K						
8. Sample Condition: Intact / Broken* / Leaking*	12		L						
9. Does information on chain-of-custody, traffic reports and sample labels agree? Yes / No*									
10. Sample received within hold time? Yes / No*									
11. Adequate sample volume received? Yes / No*									
12. Proper Preservatives used? Yes / No*									
13. Trip Blank / Temp Blank Received? (circle which, if yes) Yes / No*									
14. Temp Rec. at Lab: Is temp 4 +/-2°C? Yes/No*									

6/23/05 ZAY

(Acceptance range for samples requiring thermal pres.)
 **Exception (if any): METALS / DFF ON ICE
 or Problem COC

*IF CIRCLED, CONTACT PROJECT MANAGER AND ATTACH RECORD OF RESOLUTION.



4 August, 2005

Myrto Petreas
Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley, CA 94710

RE: OEHHA Playground Study
Work Order: MOF0960

Enclosed are the results of analyses for samples received by the laboratory on 06/28/05 16:22. If you have any questions concerning this report, please feel free to contact me.

Sincerely,

Theresa Allen
Project Manager

CA ELAP Certificate #1210

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5734
Project Manager:Myrto Petreas

MOF0960
Reported:
08/04/05 16:47

ANALYTICAL REPORT FOR SAMPLES

Sample ID	Laboratory ID	Matrix	Date Sampled	Date Received
A	MOF0960-01	Wipe	06/27/05 00:00	06/28/05 16:22
B	MOF0960-02	Wipe	06/27/05 00:00	06/28/05 16:22
C	MOF0960-03	Wipe	06/27/05 00:00	06/28/05 16:22
D	MOF0960-04	Wipe	06/27/05 00:00	06/28/05 16:22
E	MOF0960-05	Wipe	06/27/05 00:00	06/28/05 16:22
F	MOF0960-06	Wipe	06/27/05 00:00	06/28/05 16:22
G	MOF0960-07	Wipe	06/27/05 00:00	06/28/05 16:22
H	MOF0960-08	Wipe	06/27/05 00:00	06/28/05 16:22
I	MOF0960-09	Wipe	06/27/05 00:00	06/28/05 16:22
J	MOF0960-10	Wipe	06/27/05 00:00	06/28/05 16:22
K	MOF0960-11	Wipe	06/27/05 00:00	06/28/05 16:22
L	MOF0960-12	Wipe	06/27/05 00:00	06/28/05 16:22

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5734
Project Manager:Myrto Petreas

MOF0960
Reported:
08/04/05 16:47

**Total Metals by EPA 6020 ICPMS
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
A (MOF0960-01) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Aluminum	46	2.0	ug/Wipe	20	5G07010	07/06/05	07/07/05	EPA 6020	
B (MOF0960-02) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Aluminum	56	2.0	ug/Wipe	20	5G07010	07/06/05	07/07/05	EPA 6020	
C (MOF0960-03) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Aluminum	840	10	ug/Wipe	100	5G07010	07/06/05	07/07/05	EPA 6020	

Dept. of Toxic Substances Control-Berkeley 700 Heinz Avenue, Suite 100 Berkeley CA, 94710	Project:OEHHA Playground Study Project Number:SAU5734 Project Manager:Myrto Petreas	MOF0960 Reported: 08/04/05 16:47
---	---	---

**Total Metals by EPA 6000/7000 Series Methods
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
---------	--------	-----------------	-------	----------	-------	----------	----------	--------	-------

A (MOF0960-01) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22

Calcium	1200	12	ug/Wipe	1	5G06014	07/06/05	07/08/05	EPA 6010B	
Iron	130	5.0	"	"	"	"	"	"	
Potassium	ND	100	"	"	"	"	"	"	
Antimony	96	1.0	"	20	5G07010	"	07/07/05	EPA 6020	
Arsenic	ND	1.0	"	"	"	"	"	"	
Barium	6.9	5.0	"	"	"	"	"	"	
Beryllium	ND	0.20	"	"	"	"	"	"	
Cadmium	ND	0.60	"	"	"	"	"	"	
Chromium	ND	10	"	"	"	"	"	"	
Cobalt	ND	2.0	"	"	"	"	"	"	
Copper	ND	5.0	"	"	"	"	"	"	
Lead	ND	5.0	"	"	"	"	"	"	
Molybdenum	ND	2.0	"	"	"	"	"	"	
Nickel	ND	8.0	"	"	"	"	"	"	
Selenium	ND	1.0	"	"	"	"	"	"	
Silver	ND	1.0	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	ND	2.0	"	"	"	"	"	"	
Zinc	45	10	"	"	"	"	"	"	
Magnesium	31	2.5	"	1	5G06014	"	07/08/05	EPA 6010B	

B (MOF0960-02) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22

Calcium	1700	12	ug/Wipe	1	5G06014	07/06/05	07/08/05	EPA 6010B	
Iron	130	5.0	"	"	"	"	"	"	
Potassium	ND	100	"	"	"	"	"	"	
Antimony	110	1.0	"	20	5G07010	"	07/07/05	EPA 6020	
Arsenic	ND	1.0	"	"	"	"	"	"	
Barium	9.8	5.0	"	"	"	"	"	"	
Beryllium	ND	0.20	"	"	"	"	"	"	
Cadmium	ND	0.60	"	"	"	"	"	"	
Chromium	ND	10	"	"	"	"	"	"	
Cobalt	ND	2.0	"	"	"	"	"	"	
Copper	ND	5.0	"	"	"	"	"	"	
Lead	ND	5.0	"	"	"	"	"	"	
Molybdenum	ND	2.0	"	"	"	"	"	"	
Nickel	ND	8.0	"	"	"	"	"	"	
Selenium	ND	1.0	"	"	"	"	"	"	
Silver	ND	1.0	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	ND	2.0	"	"	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
Reported:
 08/04/05 16:47

Total Metals by EPA 6000/7000 Series Methods
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
B (MOF0960-02) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Zinc	61	10	ug/Wipe	20	5G07010	07/06/05	07/07/05	EPA 6020	
Magnesium	40	2.5	"	1	5G06014	"	07/08/05	EPA 6010B	
C (MOF0960-03) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Calcium	1800	12	ug/Wipe	1	5G06014	07/06/05	07/08/05	EPA 6010B	
Iron	1300	5.0	"	"	"	"	"	"	
Potassium	110	100	"	"	"	"	07/11/05	"	
Antimony	140	1.0	"	20	5G07010	"	07/07/05	EPA 6020	
Arsenic	ND	1.0	"	"	"	"	"	"	
Barium	20	5.0	"	"	"	"	"	"	
Beryllium	ND	0.20	"	"	"	"	"	"	
Cadmium	ND	0.60	"	"	"	"	"	"	
Chromium	ND	10	"	"	"	"	"	"	
Cobalt	ND	2.0	"	"	"	"	"	"	
Copper	ND	5.0	"	"	"	"	"	"	
Lead	ND	5.0	"	"	"	"	"	"	
Molybdenum	ND	2.0	"	"	"	"	"	"	
Nickel	ND	8.0	"	"	"	"	"	"	
Selenium	ND	1.0	"	"	"	"	"	"	
Silver	ND	1.0	"	"	"	"	"	"	
Thallium	ND	1.0	"	"	"	"	"	"	
Vanadium	ND	2.0	"	"	"	"	"	"	
Zinc	56	10	"	"	"	"	"	"	
Magnesium	340	2.5	"	1	5G06014	"	07/08/05	EPA 6010B	

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5734
Project Manager:Myrto Petreas

MOF0960
Reported:
08/04/05 16:47

**Total Metals by EPA 6000/7000 Series Methods
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
D (MOF0960-04) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Mercury	ND	0.0050	ug/Wipe	1	5G13012	07/13/05	07/13/05	EPA 7471A	
E (MOF0960-05) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Mercury	ND	0.0050	ug/Wipe	1	5G13012	07/13/05	07/13/05	EPA 7471A	
F (MOF0960-06) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Mercury	0.0068	0.0050	ug/Wipe	1	5G13012	07/13/05	07/13/05	EPA 7471A	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
Reported:
 08/04/05 16:47

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
G (MOF0960-07) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Acenaphthene	ND	5.0	ug/Wipe	1	5F29033	06/29/05	06/30/05	EPA 8270C	
Acenaphthylene	ND	5.0	"	"	"	"	"	"	
Anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) pyrene	ND	5.0	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzoic acid	ND	10	"	"	"	"	"	"	
Benzyl alcohol	ND	10	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	5.0	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	10	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	5.0	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	10	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	5.0	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	5.0	"	"	"	"	"	"	
4-Chloroaniline	ND	50	"	"	"	"	"	"	
2-Chloronaphthalene	ND	5.0	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	5.0	"	"	"	"	"	"	
2-Chlorophenol	ND	5.0	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	10	"	"	"	"	"	"	
Chrysene	ND	5.0	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	5.0	"	"	"	"	"	"	
Dibenzofuran	ND	5.0	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	5.0	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	10	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	50	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	5.0	"	"	"	"	"	"	
Diethyl phthalate	ND	5.0	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	10	"	"	"	"	"	"	
Dimethyl phthalate	ND	5.0	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	5.0	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	10	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	10	"	"	"	"	"	"	
Fluoranthene	ND	5.0	"	"	"	"	"	"	
Fluorene	ND	5.0	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHHA Playground Study
Project Number:SAU5734
Project Manager:Myrto Petreas

MOF0960
Reported:
08/04/05 16:47

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
G (MOF0960-07) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Hexachlorobenzene	ND	5.0	ug/Wipe	1	5F29033	06/29/05	06/30/05	EPA 8270C	
Hexachlorobutadiene	ND	10	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	10	"	"	"	"	"	"	
Hexachloroethane	ND	10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	10	"	"	"	"	"	"	
Isophorone	ND	5.0	"	"	"	"	"	"	
2-Methylnaphthalene	ND	5.0	"	"	"	"	"	"	
2-Methylphenol	ND	5.0	"	"	"	"	"	"	
4-Methylphenol	ND	5.0	"	"	"	"	"	"	
Naphthalene	ND	5.0	"	"	"	"	"	"	
2-Nitroaniline	ND	10	"	"	"	"	"	"	
3-Nitroaniline	ND	100	"	"	"	"	"	"	
4-Nitroaniline	ND	50	"	"	"	"	"	"	
Nitrobenzene	ND	5.0	"	"	"	"	"	"	
2-Nitrophenol	ND	5.0	"	"	"	"	"	"	
4-Nitrophenol	ND	10	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	5.0	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	10	"	"	"	"	"	"	
Pentachlorophenol	ND	10	"	"	"	"	"	"	
Phenanthrene	ND	5.0	"	"	"	"	"	"	
Phenol	ND	5.0	"	"	"	"	"	"	
Pyrene	ND	5.0	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	10	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		80 %		25-121	"	"	"	"	
<i>Surrogate: Phenol-d6</i>		93 %		24-113	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		82 %		23-120	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		86 %		30-115	"	"	"	"	
<i>Surrogate: 2,4,6-Tribromophenol</i>		95 %		19-122	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		80 %		18-137	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
 Reported:
 08/04/05 16:47

Semivolatile Organic Compounds by EPA Method 8270C

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
H (MOF0960-08) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Acenaphthene	ND	5.0	ug/Wipe	1	5F29033	06/29/05	06/30/05	EPA 8270C	
Acenaphthylene	ND	5.0	"	"	"	"	"	"	
Anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) pyrene	ND	5.0	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzoic acid	ND	10	"	"	"	"	"	"	
Benzyl alcohol	ND	10	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	5.0	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	10	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	5.0	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	10	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	5.0	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	5.0	"	"	"	"	"	"	
4-Chloroaniline	ND	50	"	"	"	"	"	"	
2-Chloronaphthalene	ND	5.0	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	5.0	"	"	"	"	"	"	
2-Chlorophenol	ND	5.0	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	10	"	"	"	"	"	"	
Chrysene	ND	5.0	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	5.0	"	"	"	"	"	"	
Dibenzofuran	ND	5.0	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	5.0	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	10	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	50	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	5.0	"	"	"	"	"	"	
Diethyl phthalate	ND	5.0	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	10	"	"	"	"	"	"	
Dimethyl phthalate	ND	5.0	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	5.0	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	10	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	10	"	"	"	"	"	"	
Fluoranthene	ND	5.0	"	"	"	"	"	"	
Fluorene	ND	5.0	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
Reported:
 08/04/05 16:47

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
H (MOF0960-08) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Hexachlorobenzene	ND	5.0	ug/Wipe	1	5F29033	06/29/05	06/30/05	EPA 8270C	
Hexachlorobutadiene	ND	10	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	10	"	"	"	"	"	"	
Hexachloroethane	ND	10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	10	"	"	"	"	"	"	
Isophorone	ND	5.0	"	"	"	"	"	"	
2-Methylnaphthalene	ND	5.0	"	"	"	"	"	"	
2-Methylphenol	ND	5.0	"	"	"	"	"	"	
4-Methylphenol	ND	5.0	"	"	"	"	"	"	
Naphthalene	ND	5.0	"	"	"	"	"	"	
2-Nitroaniline	ND	10	"	"	"	"	"	"	
3-Nitroaniline	ND	100	"	"	"	"	"	"	
4-Nitroaniline	ND	50	"	"	"	"	"	"	
Nitrobenzene	ND	5.0	"	"	"	"	"	"	
2-Nitrophenol	ND	5.0	"	"	"	"	"	"	
4-Nitrophenol	ND	10	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	5.0	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	10	"	"	"	"	"	"	
Pentachlorophenol	ND	10	"	"	"	"	"	"	
Phenanthrene	ND	5.0	"	"	"	"	"	"	
Phenol	ND	5.0	"	"	"	"	"	"	
Pyrene	ND	5.0	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	10	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		78 %		25-121	"	"	"	"	
<i>Surrogate: Phenol-d6</i>		88 %		24-113	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		80 %		23-120	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		85 %		30-115	"	"	"	"	
<i>Surrogate: 2,4,6-Tribromophenol</i>		89 %		19-122	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		80 %		18-137	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHHA Playground Study
Project Number:SAU5734
Project Manager:Myrto Petreas

MOF0960
Reported:
08/04/05 16:47

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
I (MOF0960-09) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Acenaphthene	ND	5.0	ug/Wipe	1	5F29033	06/29/05	06/30/05	EPA 8270C	
Acenaphthylene	ND	5.0	"	"	"	"	"	"	
Anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) anthracene	ND	5.0	"	"	"	"	"	"	
Benzo (a) pyrene	ND	5.0	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	5.0	"	"	"	"	"	"	
Benzoic acid	ND	10	"	"	"	"	"	"	
Benzyl alcohol	ND	10	"	"	"	"	"	"	
Bis(2-chloroethoxy)methane	ND	5.0	"	"	"	"	"	"	
Bis(2-chloroethyl)ether	ND	10	"	"	"	"	"	"	
Bis(2-chloroisopropyl)ether	ND	5.0	"	"	"	"	"	"	
Bis(2-ethylhexyl)phthalate	ND	10	"	"	"	"	"	"	
4-Bromophenyl phenyl ether	ND	5.0	"	"	"	"	"	"	
Butyl benzyl phthalate	ND	5.0	"	"	"	"	"	"	
4-Chloroaniline	ND	50	"	"	"	"	"	"	
2-Chloronaphthalene	ND	5.0	"	"	"	"	"	"	
4-Chloro-3-methylphenol	ND	5.0	"	"	"	"	"	"	
2-Chlorophenol	ND	5.0	"	"	"	"	"	"	
4-Chlorophenyl phenyl ether	ND	10	"	"	"	"	"	"	
Chrysene	ND	5.0	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	5.0	"	"	"	"	"	"	
Dibenzofuran	ND	5.0	"	"	"	"	"	"	
Di-n-butyl phthalate	ND	5.0	"	"	"	"	"	"	
1,2-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,3-Dichlorobenzene	ND	10	"	"	"	"	"	"	
1,4-Dichlorobenzene	ND	10	"	"	"	"	"	"	
3,3'-Dichlorobenzidine	ND	50	"	"	"	"	"	"	
2,4-Dichlorophenol	ND	5.0	"	"	"	"	"	"	
Diethyl phthalate	ND	5.0	"	"	"	"	"	"	
2,4-Dimethylphenol	ND	10	"	"	"	"	"	"	
Dimethyl phthalate	ND	5.0	"	"	"	"	"	"	
4,6-Dinitro-2-methylphenol	ND	5.0	"	"	"	"	"	"	
2,4-Dinitrophenol	ND	10	"	"	"	"	"	"	
2,4-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
2,6-Dinitrotoluene	ND	5.0	"	"	"	"	"	"	
Di-n-octyl phthalate	ND	10	"	"	"	"	"	"	
Fluoranthene	ND	5.0	"	"	"	"	"	"	
Fluorene	ND	5.0	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
Reported:
 08/04/05 16:47

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
---------	--------	-----------------	-------	----------	-------	----------	----------	--------	-------

I (MOF0960-09) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22

Hexachlorobenzene	ND	5.0	ug/Wipe	1	5F29033	06/29/05	06/30/05	EPA 8270C	
Hexachlorobutadiene	ND	10	"	"	"	"	"	"	
Hexachlorocyclopentadiene	ND	10	"	"	"	"	"	"	
Hexachloroethane	ND	10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	10	"	"	"	"	"	"	
Isophorone	ND	5.0	"	"	"	"	"	"	
2-Methylnaphthalene	ND	5.0	"	"	"	"	"	"	
2-Methylphenol	ND	5.0	"	"	"	"	"	"	
4-Methylphenol	ND	5.0	"	"	"	"	"	"	
Naphthalene	ND	5.0	"	"	"	"	"	"	
2-Nitroaniline	ND	10	"	"	"	"	"	"	
3-Nitroaniline	ND	100	"	"	"	"	"	"	
4-Nitroaniline	ND	50	"	"	"	"	"	"	
Nitrobenzene	ND	5.0	"	"	"	"	"	"	
2-Nitrophenol	ND	5.0	"	"	"	"	"	"	
4-Nitrophenol	ND	10	"	"	"	"	"	"	
N-Nitrosodi-n-propylamine	ND	5.0	"	"	"	"	"	"	
N-Nitrosodiphenylamine	ND	10	"	"	"	"	"	"	
Pentachlorophenol	ND	10	"	"	"	"	"	"	
Phenanthrene	ND	5.0	"	"	"	"	"	"	
Phenol	ND	5.0	"	"	"	"	"	"	
Pyrene	ND	5.0	"	"	"	"	"	"	
1,2,4-Trichlorobenzene	ND	10	"	"	"	"	"	"	
2,4,5-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
2,4,6-Trichlorophenol	ND	5.0	"	"	"	"	"	"	
<i>Surrogate: 2-Fluorophenol</i>		72 %		25-121	"	"	"	"	
<i>Surrogate: Phenol-d6</i>		85 %		24-113	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		77 %		23-120	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		84 %		30-115	"	"	"	"	
<i>Surrogate: 2,4,6-Tribromophenol</i>		85 %		19-122	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		77 %		18-137	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
 Reported:
 08/04/05 16:47

Polynuclear Aromatic Compounds by GC/MS with Selected Ion Monitoring

Sequoia Analytical - Petaluma

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
J (MOF0960-10) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Naphthalene	ND	0.82	ug/Wipe	1	5070002	07/01/05	08/04/05	GCMS-SIM	
Acenaphthylene	ND	0.82	"	"	"	"	"	"	
Acenaphthene	ND	0.82	"	"	"	"	"	"	
Fluorene	ND	0.82	"	"	"	"	"	"	
Phenanthrene	1.6	0.82	"	"	"	"	"	"	
Anthracene	ND	0.82	"	"	"	"	"	"	
Fluoranthene	ND	0.82	"	"	"	"	"	"	
Pyrene	4.3	0.82	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.82	"	"	"	"	"	"	
Chrysene	ND	0.82	"	"	"	"	"	"	
Benzo (b+k) fluoranthene (total)	ND	1.6	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	0.82	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.82	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.82	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.82	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.82	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.82	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		51 %		50-150	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		55 %		50-150	"	"	"	"	
<i>Surrogate: Terphenyl-d14</i>		69 %		50-150	"	"	"	"	
K (MOF0960-11) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Naphthalene	ND	0.82	ug/Wipe	1	5070002	07/01/05	08/04/05	GCMS-SIM	
Acenaphthylene	ND	0.82	"	"	"	"	"	"	
Acenaphthene	ND	0.82	"	"	"	"	"	"	
Fluorene	ND	0.82	"	"	"	"	"	"	
Phenanthrene	1.7	0.82	"	"	"	"	"	"	
Anthracene	ND	0.82	"	"	"	"	"	"	
Fluoranthene	ND	0.82	"	"	"	"	"	"	
Pyrene	4.7	0.82	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.82	"	"	"	"	"	"	
Chrysene	ND	0.82	"	"	"	"	"	"	
Benzo (b+k) fluoranthene (total)	ND	1.6	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	0.82	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.82	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.82	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.82	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.82	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.82	"	"	"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
Reported:
 08/04/05 16:47

Polynuclear Aromatic Compounds by GC/MS with Selected Ion Monitoring
Sequoia Analytical - Petaluma

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
K (MOF0960-11) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Surrogate: Nitrobenzene-d5		43 %	50-150		5070002	07/01/05	08/04/05	GCMS-SIM	S02
Surrogate: 2-Fluorobiphenyl		46 %	50-150		"	"	"	"	S02
Surrogate: Terphenyl-d14		73 %	50-150		"	"	"	"	
L (MOF0960-12) Wipe Sampled: 06/27/05 00:00 Received: 06/28/05 16:22									
Naphthalene	ND	0.82	ug/Wipe	1	5070002	07/01/05	08/04/05	GCMS-SIM	
Acenaphthylene	ND	0.82	"	"	"	"	"	"	
Acenaphthene	ND	0.82	"	"	"	"	"	"	
Fluorene	ND	0.82	"	"	"	"	"	"	
Phenanthrene	ND	0.82	"	"	"	"	"	"	
Anthracene	ND	0.82	"	"	"	"	"	"	
Fluoranthene	ND	0.82	"	"	"	"	"	"	
Pyrene	1.8	0.82	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.82	"	"	"	"	"	"	
Chrysene	ND	0.82	"	"	"	"	"	"	
Benzo (b+k) fluoranthene (total)	ND	1.6	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	0.82	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.82	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.82	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.82	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.82	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.82	"	"	"	"	"	"	
Surrogate: Nitrobenzene-d5		41 %	50-150		"	"	"	"	S02
Surrogate: 2-Fluorobiphenyl		47 %	50-150		"	"	"	"	S02
Surrogate: Terphenyl-d14		72 %	50-150		"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
Reported:
 08/04/05 16:47

Total Metals by EPA 6020 ICPMS - Quality Control
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5G07010 - EPA 3050B / EPA 6020
Blank (5G07010-BLK1)

Prepared: 07/06/05 Analyzed: 07/07/05

Aluminum ND 2.0 ug/Wipe

Laboratory Control Sample (5G07010-BS1)

Prepared: 07/06/05 Analyzed: 07/07/05

Aluminum 47.4 2.0 ug/Wipe 50.0 95 80-120

Laboratory Control Sample (5G07010-BS2)

Prepared: 07/06/05 Analyzed: 07/07/05

Aluminum 46.9 2.0 ug/Wipe 50.0 94 80-120

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
 Reported:
 08/04/05 16:47

Total Metals by EPA 6000/7000 Series Methods - Quality Control
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5G06014 - EPA 3050B / EPA 6010B
Blank (5G06014-BLK1)

Prepared: 07/06/05 Analyzed: 07/08/05

Magnesium	ND	2.5	ug/Wipe							
Calcium	ND	12	"							
Iron	ND	5.0	"							
Potassium	ND	100	"							

Laboratory Control Sample (5G06014-BS1)

Prepared: 07/06/05 Analyzed: 07/08/05

Magnesium	528	2.5	ug/Wipe	500		106	85-115			
Calcium	538	12	"	500		108	85-115			
Potassium	586	100	"	500		117	70-125			
Iron	52.5	5.0	"	50.0		105	85-115			

Laboratory Control Sample (5G06014-BS2)

Prepared: 07/06/05 Analyzed: 07/08/05

Magnesium	522	2.5	ug/Wipe	500		104	85-115			
Calcium	535	12	"	500		107	85-115			
Potassium	531	100	"	500		106	70-125			
Iron	52.0	5.0	"	50.0		104	85-115			

Batch 5G07010 - EPA 3050B / EPA 6020
Blank (5G07010-BLK1)

Prepared: 07/06/05 Analyzed: 07/07/05

Antimony	ND	1.0	ug/Wipe							
Arsenic	ND	1.0	"							
Barium	ND	5.0	"							
Beryllium	ND	0.20	"							
Cadmium	ND	0.60	"							
Chromium	ND	10	"							
Cobalt	ND	2.0	"							
Copper	ND	5.0	"							
Lead	ND	5.0	"							
Molybdenum	ND	2.0	"							
Nickel	ND	8.0	"							
Selenium	ND	1.0	"							
Silver	ND	1.0	"							
Thallium	ND	1.0	"							
Vanadium	ND	2.0	"							
Zinc	ND	10	"							

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
Reported:
 08/04/05 16:47

Total Metals by EPA 6000/7000 Series Methods - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5G07010 - EPA 3050B / EPA 6020
Laboratory Control Sample (5G07010-BS1)

Prepared: 07/06/05 Analyzed: 07/07/05

Antimony	48.4	1.0	ug/Wipe	50.0		97	80-120			
Arsenic	47.9	1.0	"	50.0		96	80-120			
Barium	47.6	5.0	"	50.0		95	80-120			
Beryllium	45.7	0.20	"	50.0		91	80-120			
Cadmium	48.3	0.60	"	50.0		97	80-120			
Chromium	52.1	10	"	50.0		104	80-120			
Cobalt	51.2	2.0	"	50.0		102	80-120			
Copper	51.5	5.0	"	50.0		103	80-120			
Lead	52.4	5.0	"	50.0		105	80-120			
Molybdenum	48.9	2.0	"	50.0		98	80-120			
Nickel	51.1	8.0	"	50.0		102	80-120			
Selenium	47.0	1.0	"	50.0		94	80-120			
Silver	49.5	1.0	"	50.0		99	80-120			
Thallium	52.4	1.0	"	50.0		105	80-120			
Vanadium	49.2	2.0	"	50.0		98	80-120			
Zinc	52.0	10	"	50.0		104	80-120			

Laboratory Control Sample (5G07010-BS2)

Prepared: 07/06/05 Analyzed: 07/07/05

Antimony	48.3	1.0	ug/Wipe	50.0		97	80-120			
Arsenic	47.1	1.0	"	50.0		94	80-120			
Barium	46.1	5.0	"	50.0		92	80-120			
Beryllium	44.6	0.20	"	50.0		89	80-120			
Cadmium	48.1	0.60	"	50.0		96	80-120			
Chromium	51.6	10	"	50.0		103	80-120			
Cobalt	50.9	2.0	"	50.0		102	80-120			
Copper	50.7	5.0	"	50.0		101	80-120			
Lead	51.9	5.0	"	50.0		104	80-120			
Molybdenum	48.3	2.0	"	50.0		97	80-120			
Nickel	50.0	8.0	"	50.0		100	80-120			
Selenium	45.5	1.0	"	50.0		91	80-120			
Silver	49.8	1.0	"	50.0		100	80-120			
Thallium	51.6	1.0	"	50.0		103	80-120			
Vanadium	48.2	2.0	"	50.0		96	80-120			
Zinc	51.9	10	"	50.0		104	80-120			

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5734
Project Manager:Myrto Petreas

MOF0960
Reported:
08/04/05 16:47

**Total Metals by EPA 6000/7000 Series Methods - Quality Control
Sequoia Analytical - Morgan Hill**

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5G13012 - EPA 7471A / EPA 7471A

Blank (5G13012-BLK1)

Prepared & Analyzed: 07/13/05

Mercury ND 0.0050 ug/Wipe

Laboratory Control Sample (5G13012-BS1)

Prepared & Analyzed: 07/13/05

Mercury 0.402 0.0050 ug/Wipe 0.400 100 75-125

Laboratory Control Sample (5G13012-BS2)

Prepared & Analyzed: 07/13/05

Mercury 0.400 0.0050 ug/Wipe 0.400 100 75-125

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
Reported:
 08/04/05 16:47

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5F29033 - EPA 3550 Wipe / EPA 8270C
Blank (5F29033-BLK1)

Prepared: 06/29/05 Analyzed: 06/30/05

Acenaphthene	ND	5.0	ug/Wipe							
Acenaphthylene	ND	5.0	"							
Anthracene	ND	5.0	"							
Benzo (a) anthracene	ND	5.0	"							
Benzo (a) pyrene	ND	5.0	"							
Benzo (b) fluoranthene	ND	5.0	"							
Benzo (g,h,i) perylene	ND	10	"							
Benzo (k) fluoranthene	ND	5.0	"							
Benzoic acid	ND	10	"							
Benzyl alcohol	ND	10	"							
Bis(2-chloroethoxy)methane	ND	5.0	"							
Bis(2-chloroethyl)ether	ND	10	"							
Bis(2-chloroisopropyl)ether	ND	5.0	"							
Bis(2-ethylhexyl)phthalate	ND	10	"							
4-Bromophenyl phenyl ether	ND	5.0	"							
Butyl benzyl phthalate	ND	5.0	"							
4-Chloroaniline	ND	50	"							
2-Chloronaphthalene	ND	5.0	"							
4-Chloro-3-methylphenol	ND	5.0	"							
2-Chlorophenol	ND	5.0	"							
4-Chlorophenyl phenyl ether	ND	10	"							
Chrysene	ND	5.0	"							
Dibenz (a,h) anthracene	ND	5.0	"							
Dibenzofuran	ND	5.0	"							
Di-n-butyl phthalate	ND	5.0	"							
1,2-Dichlorobenzene	ND	10	"							
1,3-Dichlorobenzene	ND	10	"							
1,4-Dichlorobenzene	ND	10	"							
3,3'-Dichlorobenzidine	ND	50	"							
2,4-Dichlorophenol	ND	5.0	"							
Diethyl phthalate	ND	5.0	"							
2,4-Dimethylphenol	ND	10	"							
Dimethyl phthalate	ND	5.0	"							
4,6-Dinitro-2-methylphenol	ND	5.0	"							
2,4-Dinitrophenol	ND	10	"							
2,4-Dinitrotoluene	ND	5.0	"							

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
Reported:
 08/04/05 16:47

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5F29033 - EPA 3550 Wipe / EPA 8270C
Blank (5F29033-BLK1)

Prepared: 06/29/05 Analyzed: 06/30/05

2,6-Dinitrotoluene	ND	5.0	ug/Wipe							
Di-n-octyl phthalate	ND	10	"							
Fluoranthene	ND	5.0	"							
Fluorene	ND	5.0	"							
Hexachlorobenzene	ND	5.0	"							
Hexachlorobutadiene	ND	10	"							
Hexachlorocyclopentadiene	ND	10	"							
Hexachloroethane	ND	10	"							
Indeno (1,2,3-cd) pyrene	ND	10	"							
Isophorone	ND	5.0	"							
2-Methylnaphthalene	ND	5.0	"							
2-Methylphenol	ND	5.0	"							
4-Methylphenol	ND	5.0	"							
Naphthalene	ND	5.0	"							
2-Nitroaniline	ND	10	"							
3-Nitroaniline	ND	100	"							
4-Nitroaniline	ND	50	"							
Nitrobenzene	ND	5.0	"							
2-Nitrophenol	ND	5.0	"							
4-Nitrophenol	ND	10	"							
N-Nitrosodi-n-propylamine	ND	5.0	"							
N-Nitrosodiphenylamine	ND	10	"							
Pentachlorophenol	ND	10	"							
Phenanthrene	ND	5.0	"							
Phenol	ND	5.0	"							
Pyrene	ND	5.0	"							
1,2,4-Trichlorobenzene	ND	10	"							
2,4,5-Trichlorophenol	ND	5.0	"							
2,4,6-Trichlorophenol	ND	5.0	"							
<i>Surrogate: 2-Fluorophenol</i>	85.7		"	100		86	25-121			
<i>Surrogate: Phenol-d6</i>	97.1		"	100		97	24-113			
<i>Surrogate: Nitrobenzene-d5</i>	45.6		"	50.0		91	23-120			
<i>Surrogate: 2-Fluorobiphenyl</i>	47.3		"	50.0		95	30-115			
<i>Surrogate: 2,4,6-Tribromophenol</i>	88.1		"	100		88	19-122			
<i>Surrogate: p-Terphenyl-d14</i>	44.6		"	50.0		89	18-137			

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
 Reported:
 08/04/05 16:47

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F29033 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample (5F29033-BS1)

Prepared: 06/29/05 Analyzed: 06/30/05

Acenaphthene	47.0	5.0	ug/Wipe	50.0	94	31-137
Acenaphthylene	46.3	5.0	"	50.0	93	0-200
Anthracene	48.4	5.0	"	50.0	97	0-200
Benzo (a) anthracene	46.8	5.0	"	50.0	94	0-200
Benzo (a) pyrene	48.5	5.0	"	50.0	97	0-200
Benzo (b) fluoranthene	46.6	5.0	"	50.0	93	0-200
Benzo (g,h,i) perylene	40.1	10	"	50.0	80	0-200
Benzo (k) fluoranthene	46.2	5.0	"	50.0	92	0-200
Benzyl alcohol	46.7	10	"	50.0	93	0-200
Bis(2-chloroethoxy)methane	42.4	5.0	"	50.0	85	0-200
Bis(2-chloroethyl)ether	39.3	10	"	50.0	79	0-200
Bis(2-chloroisopropyl)ether	37.9	5.0	"	50.0	76	0-200
Bis(2-ethylhexyl)phthalate	47.9	10	"	50.0	96	0-200
4-Bromophenyl phenyl ether	44.7	5.0	"	50.0	89	0-200
Butyl benzyl phthalate	46.4	5.0	"	50.0	93	0-200
4-Chloroaniline	36.1	50	"	50.0	72	0-200
2-Chloronaphthalene	43.4	5.0	"	50.0	87	0-200
4-Chloro-3-methylphenol	45.8	5.0	"	50.0	92	26-103
2-Chlorophenol	42.7	5.0	"	50.0	85	25-102
4-Chlorophenyl phenyl ether	45.4	10	"	50.0	91	0-200
Chrysene	48.9	5.0	"	50.0	98	0-200
Dibenz (a,h) anthracene	40.5	5.0	"	50.0	81	0-200
Dibenzofuran	46.0	5.0	"	50.0	92	0-200
Di-n-butyl phthalate	50.3	5.0	"	50.0	101	0-200
1,2-Dichlorobenzene	40.1	10	"	50.0	80	0-200
1,3-Dichlorobenzene	39.7	10	"	50.0	79	0-200
1,4-Dichlorobenzene	40.4	10	"	50.0	81	28-104
2,4-Dichlorophenol	45.1	5.0	"	50.0	90	0-200
Diethyl phthalate	47.3	5.0	"	50.0	95	0-200
2,4-Dimethylphenol	36.0	10	"	50.0	72	0-200
Dimethyl phthalate	44.4	5.0	"	50.0	89	0-200
4,6-Dinitro-2-methylphenol	43.4	5.0	"	50.0	87	0-200
2,4-Dinitrophenol	50.0	10	"	50.0	100	0-200
2,4-Dinitrotoluene	46.4	5.0	"	50.0	93	28-89
2,6-Dinitrotoluene	46.9	5.0	"	50.0	94	0-200
Di-n-octyl phthalate	48.0	10	"	50.0	96	0-200

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
 Reported:
 08/04/05 16:47

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F29033 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample (5F29033-BS1)

Prepared: 06/29/05 Analyzed: 06/30/05

Fluoranthene	51.9	5.0	ug/Wipe	50.0		104	0-200			
Fluorene	49.2	5.0	"	50.0		98	0-200			
Hexachlorobenzene	45.1	5.0	"	50.0		90	0-200			
Hexachlorobutadiene	41.2	10	"	50.0		82	0-200			
Hexachlorocyclopentadiene	45.1	10	"	50.0		90	0-200			
Hexachloroethane	37.2	10	"	50.0		74	0-200			
Indeno (1,2,3-cd) pyrene	48.9	10	"	50.0		98	0-200			
Isophorone	38.1	5.0	"	50.0		76	0-200			
2-Methylnaphthalene	46.3	5.0	"	50.0		93	0-200			
2-Methylphenol	42.3	5.0	"	50.0		85	0-200			
4-Methylphenol	48.3	5.0	"	25.0		193	0-200			
Naphthalene	45.9	5.0	"	50.0		92	0-200			
2-Nitroaniline	42.8	10	"	50.0		86	0-200			
3-Nitroaniline	34.9	100	"	50.0		70	0-200			
4-Nitroaniline	39.8	50	"	50.0		80	0-200			
Nitrobenzene	41.8	5.0	"	50.0		84	0-200			
2-Nitrophenol	43.4	5.0	"	50.0		87	0-200			
4-Nitrophenol	44.7	10	"	50.0		89	11-114			
N-Nitrosodi-n-propylamine	44.1	5.0	"	50.0		88	41-126			
N-Nitrosodiphenylamine	54.1	10	"	50.0		108	0-200			
Pentachlorophenol	47.2	10	"	50.0		94	17-109			
Phenanthrene	48.9	5.0	"	50.0		98	0-200			
Phenol	45.8	5.0	"	50.0		92	26-90			QL01
Pyrene	43.4	5.0	"	50.0		87	35-142			
1,2,4-Trichlorobenzene	41.8	10	"	50.0		84	38-107			
2,4,5-Trichlorophenol	44.6	5.0	"	50.0		89	0-200			
2,4,6-Trichlorophenol	45.0	5.0	"	50.0		90	0-200			
<i>Surrogate: 2-Fluorophenol</i>	<i>87.8</i>		<i>"</i>	<i>100</i>		<i>88</i>	<i>25-121</i>			
<i>Surrogate: Phenol-d6</i>	<i>94.4</i>		<i>"</i>	<i>100</i>		<i>94</i>	<i>24-113</i>			
<i>Surrogate: Nitrobenzene-d5</i>	<i>43.5</i>		<i>"</i>	<i>50.0</i>		<i>87</i>	<i>23-120</i>			
<i>Surrogate: 2-Fluorobiphenyl</i>	<i>46.8</i>		<i>"</i>	<i>50.0</i>		<i>94</i>	<i>30-115</i>			
<i>Surrogate: 2,4,6-Tribromophenol</i>	<i>97.0</i>		<i>"</i>	<i>100</i>		<i>97</i>	<i>19-122</i>			
<i>Surrogate: p-Terphenyl-d14</i>	<i>45.4</i>		<i>"</i>	<i>50.0</i>		<i>91</i>	<i>18-137</i>			

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
 Reported:
 08/04/05 16:47

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	--------------------	-------	----------------	------------------	------	----------------	-----	--------------	-------

Batch 5F29033 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample Dup (5F29033-BSD1)

Prepared: 06/29/05 Analyzed: 06/30/05

Acenaphthene	47.9	5.0	ug/Wipe	50.0		96	31-137	2	40	
Acenaphthylene	47.7	5.0	"	50.0		95	0-200	3	200	
Anthracene	49.3	5.0	"	50.0		99	0-200	2	200	
Benzo (a) anthracene	47.6	5.0	"	50.0		95	0-200	2	200	
Benzo (a) pyrene	48.9	5.0	"	50.0		98	0-200	0.8	200	
Benzo (b) fluoranthene	47.4	5.0	"	50.0		95	0-200	2	200	
Benzo (g,h,i) perylene	42.3	10	"	50.0		85	0-200	5	200	
Benzo (k) fluoranthene	45.8	5.0	"	50.0		92	0-200	0.9	200	
Benzyl alcohol	48.9	10	"	50.0		98	0-200	5	200	
Bis(2-chloroethoxy)methane	43.9	5.0	"	50.0		88	0-200	3	200	
Bis(2-chloroethyl)ether	41.7	10	"	50.0		83	0-200	6	200	
Bis(2-chloroisopropyl)ether	39.8	5.0	"	50.0		80	0-200	5	200	
Bis(2-ethylhexyl)phthalate	47.8	10	"	50.0		96	0-200	0.2	200	
4-Bromophenyl phenyl ether	46.7	5.0	"	50.0		93	0-200	4	200	
Butyl benzyl phthalate	46.7	5.0	"	50.0		93	0-200	0.6	200	
4-Chloroaniline	36.0	50	"	50.0		72	0-200	0.3	200	
2-Chloronaphthalene	45.0	5.0	"	50.0		90	0-200	4	200	
4-Chloro-3-methylphenol	46.9	5.0	"	50.0		94	26-103	2	40	
2-Chlorophenol	43.7	5.0	"	50.0		87	25-102	2	40	
4-Chlorophenyl phenyl ether	45.8	10	"	50.0		92	0-200	0.9	200	
Chrysene	48.8	5.0	"	50.0		98	0-200	0.2	200	
Dibenz (a,h) anthracene	41.7	5.0	"	50.0		83	0-200	3	200	
Dibenzofuran	46.6	5.0	"	50.0		93	0-200	1	200	
Di-n-butyl phthalate	49.7	5.0	"	50.0		99	0-200	1	200	
1,2-Dichlorobenzene	42.3	10	"	50.0		85	0-200	5	200	
1,3-Dichlorobenzene	42.1	10	"	50.0		84	0-200	6	200	
1,4-Dichlorobenzene	42.5	10	"	50.0		85	28-104	5	40	
2,4-Dichlorophenol	47.0	5.0	"	50.0		94	0-200	4	200	
Diethyl phthalate	47.3	5.0	"	50.0		95	0-200	0	200	
2,4-Dimethylphenol	34.8	10	"	50.0		70	0-200	3	200	
Dimethyl phthalate	44.9	5.0	"	50.0		90	0-200	1	200	
4,6-Dinitro-2-methylphenol	43.5	5.0	"	50.0		87	0-200	0.2	200	
2,4-Dinitrophenol	49.8	10	"	50.0		100	0-200	0.4	200	
2,4-Dinitrotoluene	46.0	5.0	"	50.0		92	28-89	0.9	40	QL01a
2,6-Dinitrotoluene	46.4	5.0	"	50.0		93	0-200	1	200	
Di-n-octyl phthalate	47.6	10	"	50.0		95	0-200	0.8	200	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
 Reported:
 08/04/05 16:47

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5F29033 - EPA 3550 Wipe / EPA 8270C
Laboratory Control Sample Dup (5F29033-BSD1)

Prepared: 06/29/05 Analyzed: 06/30/05

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
Fluoranthene	51.3	5.0	ug/Wipe	50.0		103	0-200	1	200	
Fluorene	49.2	5.0	"	50.0		98	0-200	0	200	
Hexachlorobenzene	46.7	5.0	"	50.0		93	0-200	3	200	
Hexachlorobutadiene	44.0	10	"	50.0		88	0-200	7	200	
Hexachlorocyclopentadiene	46.5	10	"	50.0		93	0-200	3	200	
Hexachloroethane	40.2	10	"	50.0		80	0-200	8	200	
Indeno (1,2,3-cd) pyrene	50.8	10	"	50.0		102	0-200	4	200	
Isophorone	39.6	5.0	"	50.0		79	0-200	4	200	
2-Methylnaphthalene	47.4	5.0	"	50.0		95	0-200	2	200	
2-Methylphenol	43.8	5.0	"	50.0		88	0-200	3	200	
4-Methylphenol	50.8	5.0	"	25.0		203	0-200	5	200	QL01a
Naphthalene	47.1	5.0	"	50.0		94	0-200	3	200	
2-Nitroaniline	42.7	10	"	50.0		85	0-200	0.2	200	
3-Nitroaniline	35.1	100	"	50.0		70	0-200	0.6	200	
4-Nitroaniline	39.0	50	"	50.0		78	0-200	2	200	
Nitrobenzene	44.2	5.0	"	50.0		88	0-200	6	200	
2-Nitrophenol	45.2	5.0	"	50.0		90	0-200	4	200	
4-Nitrophenol	43.6	10	"	50.0		87	11-114	2	40	
N-Nitrosodi-n-propylamine	45.9	5.0	"	50.0		92	41-126	4	40	
N-Nitrosodiphenylamine	54.9	10	"	50.0		110	0-200	1	200	
Pentachlorophenol	47.4	10	"	50.0		95	17-109	0.4	40	
Phenanthrene	49.2	5.0	"	50.0		98	0-200	0.6	200	
Phenol	48.3	5.0	"	50.0		97	26-90	5	40	QL01b
Pyrene	44.1	5.0	"	50.0		88	35-142	2	40	
1,2,4-Trichlorobenzene	44.3	10	"	50.0		89	38-107	6	40	
2,4,5-Trichlorophenol	45.0	5.0	"	50.0		90	0-200	0.9	200	
2,4,6-Trichlorophenol	45.5	5.0	"	50.0		91	0-200	1	200	
<i>Surrogate: 2-Fluorophenol</i>	90.6		"	100		91	25-121			
<i>Surrogate: Phenol-d6</i>	98.1		"	100		98	24-113			
<i>Surrogate: Nitrobenzene-d5</i>	45.0		"	50.0		90	23-120			
<i>Surrogate: 2-Fluorobiphenyl</i>	47.8		"	50.0		96	30-115			
<i>Surrogate: 2,4,6-Tribromophenol</i>	99.6		"	100		100	19-122			
<i>Surrogate: p-Terphenyl-d14</i>	45.6		"	50.0		91	18-137			

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAU5734
 Project Manager:Myrto Petreas

 MOF0960
Reported:
 08/04/05 16:47

Polynuclear Aromatic Compounds by GC/MS with Selected Ion Monitoring - Quality Control
Sequoia Analytical - Petaluma

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5070002 - EPA 3580A Waste Dil / GCMS-SIM
Blank (5070002-BLK1)

Prepared: 07/01/05 Analyzed: 08/04/05

Naphthalene	ND	0.82	ug/Wipe							
Acenaphthylene	ND	0.82	"							
Acenaphthene	ND	0.82	"							
Fluorene	ND	0.82	"							
Phenanthrene	ND	0.82	"							
Anthracene	ND	0.82	"							
Fluoranthene	ND	0.82	"							
Pyrene	ND	0.82	"							
Benzo (a) anthracene	ND	0.82	"							
Chrysene	ND	0.82	"							
Benzo (b+k) fluoranthene (total)	ND	1.6	"							
Benzo (b) fluoranthene	ND	0.82	"							
Benzo (k) fluoranthene	ND	0.82	"							
Benzo (a) pyrene	ND	0.82	"							
Indeno (1,2,3-cd) pyrene	ND	0.82	"							
Benzo (g,h,i) perylene	ND	0.82	"							
Dibenz (a,h) anthracene	ND	0.82	"							
<i>Surrogate: Nitrobenzene-d5</i>	<i>76.4</i>		<i>"</i>	<i>100</i>		<i>76</i>	<i>50-150</i>			
<i>Surrogate: 2-Fluorobiphenyl</i>	<i>70.8</i>		<i>"</i>	<i>100</i>		<i>71</i>	<i>50-150</i>			
<i>Surrogate: Terphenyl-d14</i>	<i>101</i>		<i>"</i>	<i>100</i>		<i>101</i>	<i>50-150</i>			

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAU5734
Project Manager:Myrto Petreas

MOF0960
Reported:
08/04/05 16:47

Notes and Definitions

S02 The surrogate recovery was below control limits.

QL01b The LCS recovery was above the control limit by 7%.

QL01a The LCS recovery was above the control limit by 3%.

QL01 The LCS recovery was above the control limit by 2%.

DET Analyte DETECTED

ND Analyte NOT DETECTED at or above the reporting limit or MDL, if MDL is specified

NR Not Reported

dry Sample results reported on a dry weight basis

RPD Relative Percent Difference

MDF 6960

**HAZARDOUS MATERIALS
SAMPLE ANALYSIS REQUEST**

1. Authorization Number:
SAL 5734

HML No. _____
To _____
2. Page: **1** of **2**

3. REQUESTOR: **VIDAIR/PETREAS**
4. Phone: **(510) 540-3003**
5. ADDRESS (To Receive Results):
**700 HEINZ AVE, SUITE 100
BERKELEY, CA 94710**
6. FAX: () **2305**

7. TAT Level: (check one)
 1 2 3 4

8. DATE SAMPLED: **6/27/05**

* Lab Chief's signature: _____
9. Codes (fill in all applicable codes)

10. ACTIVITY: SCID SRPD CIB SMB FPB SPPT Others

a. Office _____
b. INDI X _____
c. PCA _____
d. MPC _____
e. SITE _____
f. County _____

11. SAMPLING LOCATION
a. FPA ID No. _____
b. Site: **DEHHA TRACK STUDY**
c. Address:
Number _____ Street _____ City _____ ZIP _____

12. SAMPLES:		Sample	Container
a. ID	b. Collector's No.	c. HML No.	d. Type
01 A	A		POLYESTER WIFE WETTED WITH WATER IN 8 OZ GLASS JAR
02 B	B		"
03 C	C		"
04 D	D		"
05 E	E		"
06 F	F		"

13. ANALYSIS REQUESTED: (X desired analysis and enter IDs from 12.a.)

INORGANIC ANALYSIS		Sample(s) ID
<input checked="" type="checkbox"/> pH		
<input checked="" type="checkbox"/> Metals Scan (8010)	6020	A, B, C
Metal(s) Specific		
WTT		
Cyanides		
<input checked="" type="checkbox"/> Hg	7471 (others, write in)	D, E, F
TCLP Analysis (only if necessary) (do TCLP regardless)		
Metals		
Mercury		
Volatiles		
Semivolatiles		

ORGANIC ANALYSIS		Sample(s) ID
Cl-Pesticides (8081)		
OP-Pesticides (8141)		
PCBs (8082)		
GRO (8015B)		
DRD / Motor Oil / Both (8015A)		
n-Hexane Extractables (1554)		
Flash Point (1020)		
VOCs including BTEX (8260)		
VOCs - LO Level (5035)		
VOCs - HI Level (5036)		
SVOCs (8270)		
PAHs (8270)		

14. ANALYSIS OBJECTIVE:
 Waste Characterization
 Drinking H₂O Standards (applies to DW only)
 Others (contact Lab supervisors first)

15. DETECTION LIMIT REQUIREMENTS: **AS LOW AS POSSIBLE**
(specify if known and contact lab)

16. SUPPLEMENTAL REQUESTS: _____
Initials: _____
Date: _____

17. LAB REMARKS:

18. CHAIN OF CUSTODY:			
a. <i>Charles Vidair</i>	CHARLES VIDAIR	6/27/05	to 6/22/05
b. <i>M. Petreas</i>	M. PETREAS	6/27/05	to 06/28/05
c. <i>D. Chand</i>	D. Chand	06/28/05	to 06/28/05
d. <i>Fletcher</i>	FLETCHER	6/28/05	to _____
_____	ARMON	6/27/05	to _____

MDF 0960

HAZARDOUS MATERIALS
SAMPLE ANALYSIS REQUEST

1. Authorization Number
SAU 5734

HML No. 10
2. Page 2 of 2

3. REQUESTOR: VIDAIR/PETREAS
4. Phone (510) 540-3003
5. ADDRESS (To Receive Results): 700 HEINZ AVE, SUITE 100, BERKELEY, CA 94710
6. FAX () -2305

7. TAI Level: (check one)
 1 2 3 4

8. DATE SAMPLED: 6/27/05
10. ACTIVITY SCD SRPD CID SMD FMB SPPT Others

9. Codes (fill in all applicable codes)

11. SAMPLING LOCATION
a. EPA ID No.
b. Site: DEHNA TRACK STUDY
c. Address: Number Street City ZIP

a. Office
b. INDEX
c. PCA
d. MPC
e. SITE
f. County

12. SAMPLES:		Sample	Container
a. ID	b. Collector's No.	c. HML No.	d. Type
A	G		POLYESTER WIPES WETTED WITH WATER IN 8OZ JAR
B	H		"
C	I		"
D	J		POLYESTER WIPES WETTED WITH ISOPROPYL ALCOHOL IN 8OZ JAR
E	K		"
F	L		"

13. ANALYSIS REQUESTED: (X desired analysis and enter IDs from 12.a)

INORGANIC ANALYSIS	Sample(s) ID
pH	
Metals Scan (6010)	
Metal(s) Specific	
WLF	
Cyanides	
(others, write in)	
(others, write in)	
TCIP Analysis <input type="checkbox"/>	
(only if necessary) (no TCIP reagents)	
Metals	
Mercury	
Volatiles	
Semivolatiles	
(others, write in)	

ORGANIC ANALYSIS	Sample(s) ID
Cl-Pesticides (8041)	
OP-Pesticides (8141)	
PCBs (8082)	
GR0 (8015B)	
DRO/Motor Oil/Both (8015C)	
n-Hexane Extractables (1664)	
Flash Point (1020)	
VOCs including BTEX (8250)	
VOCs LO Level (5035)	
VOCs HI Level (5035)	
X SVOCs (8270)	G, H, I
X PAHs (8270) / SIM	J, K, L
(others, write in)	

14. ANALYSIS OBJECTIVE: (check a box)
 Waste Characterization
 Drinking H₂O Standards (applies to DW only)
 Treatment Standards
 Others (contact Lab supervisors first)

15. DETECTION LIMIT REQUIREMENTS: (specify if known and contact lab) AS LOW AS POSSIBLE

16. SUPPLEMENTAL REQUESTS: Initials Date

17. LAB REMARKS:

18. CHAIN OF CUSTODY:		Inclusive Dates	Signature
a.	Charles Vidair	6/27/05 to 6/27/05	CHARLES VIDAIR
b.	M. Petreas	6/27/05 to 6/28/05	M. PETREAS
c.	D. Chand	6/28/05 to 6/28/05	D. Chand
d.	Gregory Fultchev	6/28/05 to 6/28/05	GREGORY FULTCHEV

SEQUOIA ANALYTICAL SAMPLE RECEIPT LOG

CLIENT NAME: DTSC
 REC. BY (PRINT): TA
 WORKORDER: MOP 6940

DATE REC'D AT LAB: 6/28/05
 TIME REC'D AT LAB: 1622
 DATE LOGGED IN: 6-28-05

For Regulatory Purposes?
 DRINKING WATER YES/NO
 WASTE WATER YES/NO

(For clients requiring preservation checks at receipt, document here ↓)

CIRCLE THE APPROPRIATE RESPONSE		LAB SAMPLE #	DASH #	CLIENT ID	CONTAINER DESCRIPTION	PRESERVATIVE	pH	SAMPLE MATRIX	DATE SAMPLED	REMARKS: CONDITION (ETC.)
1. Custody Seal(s)	Present / <u>Absent</u> Intact / Broken*	01	A	A	Par jar	—	—	Wipe	6/28/05	
2. Chain-of-Custody	<u>Present</u> / Absent*	02		B	↓	↓	↓	↓	↓	
3. Traffic Reports or Packing List:	Present / <u>Absent</u>	03		C						
4. Airbill:	Airbill / Sticker Present / <u>Absent</u>	04		D						
5. Airbill #:		05		E						
6. Sample Labels:	<u>Present</u> / Absent	06		F						
7. Sample IDs:	<u>Listed</u> / Not Listed on Chain-of-Custody	07		G						
8. Sample Condition:	<u>Intact</u> / Broken* / Leaking*	08		H						
9. Does information on chain-of-custody, traffic reports and sample labels agree?	<u>Yes</u> / No*	09		I						
10. Sample received within hold time?	Yes / <u>No</u> *	10		J						
11. Adequate sample volume received?	Yes / <u>No</u> *	11		K						
12. Proper Preservatives used?	<u>Yes</u> / No*	12		L						
13. Trip Blank / Temp Blank Received? (circle which, if yes)	Yes / <u>No</u> *									
14. Temp Rec. at Lab: Is temp 4 +/-2°C? <small>(Acceptance range for samples requiring thermal pres.)</small>	<u>25.502</u> Yes / <u>No</u> **									

6/28/05
 TA

*IF CIRCLED, CONTACT PROJECT MANAGER AND ATTACH RECORD OF RESOLUTION.



28 September, 2005

Jarnail Garcha
Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley, CA 94710

RE: OEHHA Playground Study
Work Order: MOI0327

Enclosed are the results of analyses for samples received by the laboratory on 09/09/05 17:25. If you have any questions concerning this report, please feel free to contact me.

Sincerely,

Theresa Allen
Project Manager

CA ELAP Certificate #1210

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAV5795
Project Manager:Jarnail Garcha

MOI0327
Reported:
09/28/05 12:30

ANALYTICAL REPORT FOR SAMPLES

Sample ID	Laboratory ID	Matrix	Date Sampled	Date Received
UC1	MOI0327-01	Wipe	09/06/05 00:00	09/09/05 17:25
UC2	MOI0327-02	Wipe	09/06/05 00:00	09/09/05 17:25
UC3	MOI0327-03	Wipe	09/06/05 00:00	09/09/05 17:25
EC1	MOI0327-04	Wipe	09/06/05 00:00	09/09/05 17:25
EC2	MOI0327-05	Wipe	09/06/05 00:00	09/09/05 17:25
EC3	MOI0327-06	Wipe	09/06/05 00:00	09/09/05 17:25
GR1	MOI0327-07	Wipe	09/06/05 00:00	09/09/05 17:25
GR2	MOI0327-08	Wipe	09/06/05 00:00	09/09/05 17:25
GR3	MOI0327-09	Wipe	09/06/05 00:00	09/09/05 17:25
SM1	MOI0327-10	Wipe	09/06/05 00:00	09/09/05 17:25
SM2	MOI0327-11	Wipe	09/06/05 00:00	09/09/05 17:25
SM3	MOI0327-12	Wipe	09/06/05 00:00	09/09/05 17:25

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHHA Playground Study
 Project Number:SAV5795
 Project Manager:Jarnail Garcha

 MOI0327
Reported:
 09/28/05 12:30

Semivolatile Organic Compounds by EPA Method 8270C

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
UC1 (MOI0327-01) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
Acenaphthene	ND	0.10	ug/Wipe	1	5I15023	09/15/05	09/27/05	GCMS-SIM	
Acenaphthylene	ND	0.10	"	"	"	"	"	"	
Anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.10	"	"	"	"	"	"	
Benzo (b) fluoranthene	0.14	0.10	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.10	"	"	"	"	"	"	
Chrysene	0.27	0.10	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.10	"	"	"	"	"	"	
Fluoranthene	0.27	0.10	"	"	"	"	"	"	
Fluorene	ND	0.10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.10	"	"	"	"	"	"	
Naphthalene	0.11	0.10	"	"	"	"	"	"	
Phenanthrene	0.15	0.10	"	"	"	"	"	"	
Pyrene	0.41	0.10	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		92 %		35-115	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		86 %		35-120	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		99 %		40-130	"	"	"	"	
UC2 (MOI0327-02) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
Acenaphthene	ND	0.10	ug/Wipe	1	5I15023	09/15/05	09/27/05	GCMS-SIM	
Acenaphthylene	ND	0.10	"	"	"	"	"	"	
Anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.10	"	"	"	"	"	"	
Benzo (b) fluoranthene	0.11	0.10	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.10	"	"	"	"	"	"	
Chrysene	0.22	0.10	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.10	"	"	"	"	"	"	
Fluoranthene	0.23	0.10	"	"	"	"	"	"	
Fluorene	ND	0.10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.10	"	"	"	"	"	"	
Naphthalene	ND	0.10	"	"	"	"	"	"	
Phenanthrene	0.12	0.10	"	"	"	"	"	"	
Pyrene	0.37	0.10	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		73 %		35-115	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		70 %		35-120	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAV5795
 Project Manager:Jarnail Garcha

 MOI0327
 Reported:
 09/28/05 12:30

Semivolatile Organic Compounds by EPA Method 8270C

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
UC2 (MOI0327-02) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
<i>Surrogate: p-Terphenyl-d14</i>		78 %	40-130		5I15023	09/15/05	09/27/05	GCMS-SIM	
UC3 (MOI0327-03) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
Acenaphthene	ND	0.10	ug/Wipe	1	5I15023	09/15/05	09/27/05	GCMS-SIM	
Acenaphthylene	ND	0.10	"	"	"	"	"	"	
Anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.10	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	0.10	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.10	"	"	"	"	"	"	
Chrysene	ND	0.10	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.10	"	"	"	"	"	"	
Fluoranthene	ND	0.10	"	"	"	"	"	"	
Fluorene	ND	0.10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.10	"	"	"	"	"	"	
Naphthalene	ND	0.10	"	"	"	"	"	"	
Phenanthrene	ND	0.10	"	"	"	"	"	"	
Pyrene	0.10	0.10	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		87 %	35-115		"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		73 %	35-120		"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		96 %	40-130		"	"	"	"	
EC1 (MOI0327-04) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
Acenaphthene	ND	0.10	ug/Wipe	1	5I15023	09/15/05	09/27/05	GCMS-SIM	
Acenaphthylene	ND	0.10	"	"	"	"	"	"	
Anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.10	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	0.10	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.10	"	"	"	"	"	"	
Chrysene	ND	0.10	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.10	"	"	"	"	"	"	
Fluoranthene	0.14	0.10	"	"	"	"	"	"	
Fluorene	ND	0.10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.10	"	"	"	"	"	"	
Naphthalene	ND	0.10	"	"	"	"	"	"	
Phenanthrene	ND	0.10	"	"	"	"	"	"	
Pyrene	0.27	0.10	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAV5795
 Project Manager:Jarnail Garcha

 MOI0327
Reported:
 09/28/05 12:30

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
EC1 (MOI0327-04) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
<i>Surrogate: Nitrobenzene-d5</i>		81 %	35-115		5115023	09/15/05	09/27/05	GCMS-SIM	
<i>Surrogate: 2-Fluorobiphenyl</i>		75 %	35-120		"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		89 %	40-130		"	"	"	"	
EC2 (MOI0327-05) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
Acenaphthene	ND	0.10	ug/Wipe	1	5115023	09/15/05	09/27/05	GCMS-SIM	
Acenaphthylene	ND	0.10	"	"	"	"	"	"	
Anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.10	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	0.10	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.10	"	"	"	"	"	"	
Chrysene	ND	0.10	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.10	"	"	"	"	"	"	
Fluoranthene	0.13	0.10	"	"	"	"	"	"	
Fluorene	ND	0.10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.10	"	"	"	"	"	"	
Naphthalene	ND	0.10	"	"	"	"	"	"	
Phenanthrene	ND	0.10	"	"	"	"	"	"	
Pyrene	0.28	0.10	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		72 %	35-115		"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		71 %	35-120		"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		100 %	40-130		"	"	"	"	

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAV5795
 Project Manager:Jarnail Garcha

 MOI0327
 Reported:
 09/28/05 12:30

Semivolatile Organic Compounds by EPA Method 8270C Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
EC3 (MOI0327-06) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
Acenaphthene	ND	0.10	ug/Wipe	1	5I15023	09/15/05	09/27/05	GCMS-SIM	
Acenaphthylene	ND	0.10	"	"	"	"	"	"	
Anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.10	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	0.10	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.10	"	"	"	"	"	"	
Chrysene	ND	0.10	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.10	"	"	"	"	"	"	
Fluoranthene	ND	0.10	"	"	"	"	"	"	
Fluorene	ND	0.10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.10	"	"	"	"	"	"	
Naphthalene	0.11	0.10	"	"	"	"	"	"	
Phenanthrene	ND	0.10	"	"	"	"	"	"	
Pyrene	ND	0.10	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		104 %	35-115		"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		84 %	35-120		"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		93 %	40-130		"	"	"	"	
GR1 (MOI0327-07) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
Acenaphthene	ND	0.10	ug/Wipe	1	5I15023	09/15/05	09/27/05	GCMS-SIM	
Acenaphthylene	ND	0.10	"	"	"	"	"	"	
Anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.10	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	0.10	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.10	"	"	"	"	"	"	
Chrysene	ND	0.10	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.10	"	"	"	"	"	"	
Fluoranthene	0.11	0.10	"	"	"	"	"	"	
Fluorene	ND	0.10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.10	"	"	"	"	"	"	
Naphthalene	0.10	0.10	"	"	"	"	"	"	
Phenanthrene	0.30	0.10	"	"	"	"	"	"	
Pyrene	0.40	0.10	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		95 %	35-115		"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		72 %	35-120		"	"	"	"	

Dept. of Toxic Substances Contol-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAV5795
 Project Manager:Jarnail Garcha

 MOI0327
 Reported:
 09/28/05 12:30

Semivolatile Organic Compounds by EPA Method 8270C

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
GR1 (MOI0327-07) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
<i>Surrogate: p-Terphenyl-d14</i>		95 %	40-130		5I15023	09/15/05	09/27/05	GCMS-SIM	
GR2 (MOI0327-08) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
Acenaphthene	ND	0.10	ug/Wipe	1	5I15023	09/15/05	09/27/05	GCMS-SIM	
Acenaphthylene	ND	0.10	"	"	"	"	"	"	
Anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.10	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	0.10	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.10	"	"	"	"	"	"	
Chrysene	ND	0.10	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.10	"	"	"	"	"	"	
Fluoranthene	ND	0.10	"	"	"	"	"	"	
Fluorene	ND	0.10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.10	"	"	"	"	"	"	
Naphthalene	0.13	0.10	"	"	"	"	"	"	
Phenanthrene	0.19	0.10	"	"	"	"	"	"	
Pyrene	0.31	0.10	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		114 %	35-115		"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		88 %	35-120		"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		97 %	40-130		"	"	"	"	
GR3 (MOI0327-09) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
Acenaphthene	ND	0.10	ug/Wipe	1	5I15023	09/15/05	09/27/05	GCMS-SIM	
Acenaphthylene	ND	0.10	"	"	"	"	"	"	
Anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.10	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	0.10	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.10	"	"	"	"	"	"	
Chrysene	ND	0.10	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.10	"	"	"	"	"	"	
Fluoranthene	ND	0.10	"	"	"	"	"	"	
Fluorene	ND	0.10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.10	"	"	"	"	"	"	
Naphthalene	0.11	0.10	"	"	"	"	"	"	
Phenanthrene	ND	0.10	"	"	"	"	"	"	
Pyrene	0.11	0.10	"	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAV5795
 Project Manager:Jarnail Garcha

 MOI0327
Reported:
 09/28/05 12:30

Semivolatile Organic Compounds by EPA Method 8270C
Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
GR3 (MOI0327-09) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
Surrogate: Nitrobenzene-d5		110 %	35-115		5115023	09/15/05	09/27/05	GCMS-SIM	
Surrogate: 2-Fluorobiphenyl		80 %	35-120		"	"	"	"	
Surrogate: p-Terphenyl-d14		93 %	40-130		"	"	"	"	
SM1 (MOI0327-10) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
Acenaphthene	ND	0.10	ug/Wipe	1	5115023	09/15/05	09/27/05	GCMS-SIM	
Acenaphthylene	ND	0.10	"	"	"	"	"	"	
Anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.10	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	0.10	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.10	"	"	"	"	"	"	
Chrysene	0.34	0.10	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.10	"	"	"	"	"	"	
Fluoranthene	0.48	0.10	"	"	"	"	"	"	
Fluorene	ND	0.10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.10	"	"	"	"	"	"	
Naphthalene	0.11	0.10	"	"	"	"	"	"	
Phenanthrene	1.2	0.10	"	"	"	"	"	"	
Pyrene	3.5	0.10	"	"	"	"	"	"	
Surrogate: Nitrobenzene-d5		100 %	35-115		"	"	"	"	
Surrogate: 2-Fluorobiphenyl		82 %	35-120		"	"	"	"	
Surrogate: p-Terphenyl-d14		94 %	40-130		"	"	"	"	

Dept. of Toxic Substances Contol-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAV5795
 Project Manager:Jarnail Garcha

 MOI0327
 Reported:
 09/28/05 12:30

Semivolatile Organic Compounds by EPA Method 8270C

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
SM2 (MOI0327-11) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
Acenaphthene	ND	0.10	ug/Wipe	1	5I15023	09/15/05	09/27/05	GCMS-SIM	
Acenaphthylene	ND	0.10	"	"	"	"	"	"	
Anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.10	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	0.10	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.10	"	"	"	"	"	"	
Chrysene	0.20	0.10	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.10	"	"	"	"	"	"	
Fluoranthene	0.37	0.10	"	"	"	"	"	"	
Fluorene	ND	0.10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.10	"	"	"	"	"	"	
Naphthalene	0.12	0.10	"	"	"	"	"	"	
Phenanthrene	0.86	0.10	"	"	"	"	"	"	
Pyrene	2.7	0.10	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		101 %	35-115	"	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		81 %	35-120	"	"	"	"	"	
<i>Surrogate: p-Terphenyl-d14</i>		95 %	40-130	"	"	"	"	"	
SM3 (MOI0327-12) Wipe Sampled: 09/06/05 00:00 Received: 09/09/05 17:25									
Acenaphthene	ND	0.10	ug/Wipe	1	5I15023	09/15/05	09/27/05	GCMS-SIM	
Acenaphthylene	ND	0.10	"	"	"	"	"	"	
Anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) anthracene	ND	0.10	"	"	"	"	"	"	
Benzo (a) pyrene	ND	0.10	"	"	"	"	"	"	
Benzo (b) fluoranthene	ND	0.10	"	"	"	"	"	"	
Benzo (g,h,i) perylene	ND	0.10	"	"	"	"	"	"	
Benzo (k) fluoranthene	ND	0.10	"	"	"	"	"	"	
Chrysene	ND	0.10	"	"	"	"	"	"	
Dibenz (a,h) anthracene	ND	0.10	"	"	"	"	"	"	
Fluoranthene	0.11	0.10	"	"	"	"	"	"	
Fluorene	0.22	0.10	"	"	"	"	"	"	
Indeno (1,2,3-cd) pyrene	ND	0.10	"	"	"	"	"	"	
Naphthalene	0.10	0.10	"	"	"	"	"	"	
Phenanthrene	0.15	0.10	"	"	"	"	"	"	
Pyrene	0.26	0.10	"	"	"	"	"	"	
<i>Surrogate: Nitrobenzene-d5</i>		92 %	35-115	"	"	"	"	"	
<i>Surrogate: 2-Fluorobiphenyl</i>		73 %	35-120	"	"	"	"	"	

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley 700 Heinz Avenue, Suite 100 Berkeley CA, 94710	Project:OEHHA Playground Study Project Number:SAV5795 Project Manager:Jarnail Garcha	MOI0327 Reported: 09/28/05 12:30
---	--	---

Semivolatile Organic Compounds by EPA Method 8270C

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Dilution	Batch	Prepared	Analyzed	Method	Notes
---------	--------	--------------------	-------	----------	-------	----------	----------	--------	-------

SM3 (MOI0327-12) Wipe **Sampled: 09/06/05 00:00** **Received: 09/09/05 17:25**

<i>Surrogate: p-Terphenyl-d14</i>		95 %	40-130		5115023	09/15/05	09/27/05	GCMS-SIM	
-----------------------------------	--	------	--------	--	---------	----------	----------	----------	--

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAV5795
 Project Manager:Jarnail Garcha

 MOI0327
 Reported:
 09/28/05 12:30

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control

Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5I15023 - EPA 3550 Wipe / GCMS-SIM
Blank (5I15023-BLK1)

Prepared: 09/15/05 Analyzed: 09/27/05

Acenaphthene	ND	0.10	ug/Wipe							
Acenaphthylene	ND	0.10	"							
Anthracene	ND	0.10	"							
Benzo (a) anthracene	ND	0.10	"							
Benzo (a) pyrene	ND	0.10	"							
Benzo (b) fluoranthene	ND	0.10	"							
Benzo (g,h,i) perylene	ND	0.10	"							
Benzo (k) fluoranthene	ND	0.10	"							
Chrysene	ND	0.10	"							
Dibenz (a,h) anthracene	ND	0.10	"							
Fluoranthene	ND	0.10	"							
Fluorene	ND	0.10	"							
Indeno (1,2,3-cd) pyrene	ND	0.10	"							
Naphthalene	ND	0.10	"							
Phenanthrene	ND	0.10	"							
Pyrene	ND	0.10	"							
<i>Surrogate: Nitrobenzene-d5</i>	1.20		"	5.00		24	35-115			S02
<i>Surrogate: 2-Fluorobiphenyl</i>	1.60		"	5.00		32	35-120			S02
<i>Surrogate: p-Terphenyl-d14</i>	4.36		"	5.00		87	40-130			

Laboratory Control Sample (5I15023-BS1)

Prepared: 09/15/05 Analyzed: 09/27/05

Acenaphthene	8.51	0.10	ug/Wipe	10.0		85	65-110			
Acenaphthylene	9.61	0.10	"	10.0		96	30-145			
Anthracene	9.99	0.10	"	10.0		100	25-130			
Benzo (a) anthracene	10.9	0.10	"	10.0		109	30-140			
Benzo (a) pyrene	11.0	0.10	"	10.0		110	15-150			
Benzo (b) fluoranthene	11.0	0.10	"	10.0		110	25-150			
Benzo (g,h,i) perylene	9.75	0.10	"	10.0		98	10-150			
Benzo (k) fluoranthene	11.2	0.10	"	10.0		112	10-150			
Chrysene	10.6	0.10	"	10.0		106	15-150			
Dibenz (a,h) anthracene	11.5	0.10	"	10.0		115	10-150			
Fluoranthene	10.5	0.10	"	10.0		105	25-135			
Fluorene	9.31	0.10	"	10.0		93	60-120			
Indeno (1,2,3-cd) pyrene	11.0	0.10	"	10.0		110	10-150			
Naphthalene	5.52	0.10	"	10.0		55	20-130			
Phenanthrene	9.71	0.10	"	10.0		97	50-150			

Sequoia Analytical - Morgan Hill

The results in this report apply to the samples analyzed in accordance with the chain of custody document. Unless otherwise stated, results are reported on a wet weight basis. This analytical report must be reproduced in its entirety.

Dept. of Toxic Substances Control-Berkeley
 700 Heinz Avenue, Suite 100
 Berkeley CA, 94710

 Project:OEHHA Playground Study
 Project Number:SAV5795
 Project Manager:Jarnail Garcha

 MOI0327
 Reported:
 09/28/05 12:30

Semivolatile Organic Compounds by EPA Method 8270C - Quality Control Sequoia Analytical - Morgan Hill

Analyte	Result	Reporting Limit	Units	Spike Level	Source Result	%REC	%REC Limits	RPD	RPD Limit	Notes
---------	--------	-----------------	-------	-------------	---------------	------	-------------	-----	-----------	-------

Batch 5I15023 - EPA 3550 Wipe / GCMS-SIM
Laboratory Control Sample (5I15023-BS1)

Prepared: 09/15/05 Analyzed: 09/27/05

Pyrene	10.5	0.10	ug/Wipe	10.0		105	60-120			
Surrogate: Nitrobenzene-d5	1.99		"	5.00		40	35-115			
Surrogate: 2-Fluorobiphenyl	2.75		"	5.00		55	35-120			
Surrogate: p-Terphenyl-d14	4.50		"	5.00		90	40-130			

Laboratory Control Sample Dup (5I15023-BSD1)

Prepared: 09/15/05 Analyzed: 09/27/05

Acenaphthene	9.14	0.10	ug/Wipe	10.0		91	65-110	7	20	
Acenaphthylene	10.5	0.10	"	10.0		105	30-145	9	20	
Anthracene	9.72	0.10	"	10.0		97	25-130	3	20	
Benzo (a) anthracene	9.76	0.10	"	10.0		98	30-140	11	20	
Benzo (a) pyrene	9.97	0.10	"	10.0		100	15-150	10	20	
Benzo (b) fluoranthene	10.2	0.10	"	10.0		102	25-150	8	20	
Benzo (g,h,i) perylene	7.73	0.10	"	10.0		77	10-150	23	20	QC21
Benzo (k) fluoranthene	10.3	0.10	"	10.0		103	10-150	8	20	
Chrysene	9.64	0.10	"	10.0		96	15-150	9	20	
Dibenz (a,h) anthracene	9.28	0.10	"	10.0		93	10-150	21	20	QC21
Fluoranthene	9.41	0.10	"	10.0		94	25-135	11	20	
Fluorene	9.66	0.10	"	10.0		97	60-120	4	20	
Indeno (1,2,3-cd) pyrene	8.88	0.10	"	10.0		89	10-150	21	20	QC21
Naphthalene	7.67	0.10	"	10.0		77	20-130	33	20	QC21
Phenanthrene	9.46	0.10	"	10.0		95	50-150	3	20	
Pyrene	9.60	0.10	"	10.0		96	60-120	9	20	
Surrogate: Nitrobenzene-d5	0.456		"	5.00		9	35-115			S02
Surrogate: 2-Fluorobiphenyl	0.494		"	5.00		10	35-120			S02
Surrogate: p-Terphenyl-d14	4.02		"	5.00		80	40-130			

Dept. of Toxic Substances Control-Berkeley
700 Heinz Avenue, Suite 100
Berkeley CA, 94710

Project:OEHHA Playground Study
Project Number:SAV5795
Project Manager:Jarnail Garcha

MOI0327
Reported:
09/28/05 12:30

Notes and Definitions

S02 The surrogate recovery was below control limits.

QC21 The RPD result exceeded the control limits; however, both percent recoveries were acceptable. Sample results for the QC batch were accepted based on percent recoveries and completeness of QC data.

DET Analyte DETECTED

ND Analyte NOT DETECTED at or above the reporting limit or MDL, if MDL is specified

NR Not Reported

dry Sample results reported on a dry weight basis

RPD Relative Percent Difference

14016327

HAZARDOUS MATERIALS

1. Authorization Number

HML No.

2. Page

1 of 2

SAMPLE ANALYSIS REQUEST

3. REQUESTOR: VIDAIR/PETREAS 4. Phone (510) 540 3003

7. TAT Level: (check one)

5. ADDRESS (To Receive Results) 6. FAX () 2305

700 HEINZ AVE, SUITE 100
BERKELEY, CA 94710

1 2 3 4

8. DATE SAMPLED: ~~9/7~~ UC-9/7 EC-9/6

* Unit Chief's Signature

10. ACTIVITY: SCQ SHPD CIB SMB CPB SPP1 Others:

9. Codes (fill in all applicable codes)

11. SAMPLING LOCATION

a. Office

b. INDEX

c. PCA

d. MPC

e. SIIT

f. County

b. Site OEHHA PLAYGROUND STUDY

c. Address

Number Street City ZIP

12. SAMPLES.

a. ID	b. Collector's No.	c. HML No.	d. Type	e. Type	f. Size	g. Field Information
A	UC 1		POLYESTER WIFE WETTED WITH			ISOPROPYL ALCOHOL IN GLASS JAR
B	UC 2		"			"
C	UC 3		"			"
D	UC 1		"			"
E	UC 2		"			"
F	UC 3		"			"

13. ANALYSIS REQUESTED: (X desired analysis and enter IDs from 12.a.)

INORGANIC ANALYSIS	Sample(s) ID	ORGANIC ANALYSIS	Sample(s) ID
pH		Cl Pesticides (8081)	
Metals Screen (E010)		OP-Pesticides (8141)	
Metal(s) Specific		PCBs (8082)	
WFT		G.P.O. (801513)	
Cyanides		D.R.O. / Motor Oil / Both (write one)	
(others, write in)		n-Hexane Extractables (1664)	
(others, write in)		Flash Point (1070)	
TCLP Analysis <input type="checkbox"/>	<input type="checkbox"/>	VOCs including STEK (8260)	
(only if necessary)	(do TCLP regardless)	VOCs - LC Level (5035)	
Metals		VOCs - HI Level (5035)	
Mercury		SVOCs (8270)	
Volatiles		PAHs (8270) / SIM	ABCDEF
Semivolatiles		(others, write in)	

14. ANALYSIS OBJECTIVE: (check a box) Waste Characterization Treatment Standards Drinking H₂O Standards (applies to DW only) Others (contact Lab supervisors first)

15. DETECTION LIMIT REQUIREMENTS: (specify if known and contact lab) AS LOW AS POSSIBLE

16. SUPPLEMENTAL REQUESTS Initials _____ Date _____

17. LAB REMARKS: PLEASE ANALYZE ALL 12 SAMPLES AT SIMILAR REPORTING LEVELS

18. CHAIN OF CUSTODY: a. Charles Vidair CHARLES VIDAIR 9/6/05 to 9/7/05
b. [Signature] [Signature] 9/7/05 to 9/9/05
c. [Signature] [Signature] 9/9/05 1300-1725
d. _____ to _____

Signature(s)

Name(s) / Title(s)

Inclusive Dates of Custody

MOI6327

HAZARDOUS MATERIALS SAMPLE ANALYSIS REQUEST
1. Authorization Number
HML No. To
2. Page 2 of 2

3. REQUESTOR: VIDAIR/PETREAS
4. Phone (510) 540-3003
5. ADDRESS (To Receive Results): 700 HEINZ AVE, SUITE 100, BERKELEY, CA 94710
6. FAX () -2305

7. TAT Level: (check one)
 1 2 3 4
* Unit Chief's Signature

8. DATE SAMPLED: ~~9/7/05~~ GR-9/6 SM-9/7
10. ACTIVITY: SCD SRPD CIB SMB FPB SPP7 Others

9. Codes (fill in all applicable codes)
a. Office
b. INDEX
c. PCA
d. MPC
e. SITE
f. County

11. SAMPLING LOCATION
a. EPA ID No.
b. Site: OEHHA PLAYGROUND STUDY
c. Address
Number Street City ZIP

12. SAMPLES:

a. ID	b. Collector's No.	c. HML No.	d. Type	e. Type	f. Size	g. Field Information
A	GR 1	POLYESTER	WIFE WETTED			WITH ISOPROPYL ALCOHOL IN GLASS JAR
B	GR 2		"			"
C	GR 3		"			"
D	SM 1		"			"
E	SM 2		"			"
F	SM 3		"			"

13. ANALYSIS REQUESTED: (X desired analysis and enter I.D.s from 12.a.)

INORGANIC ANALYSIS

Sample(s) ID
pH
Metals Scan (6010)
Metal(s) Specific
WET
Cyanides
(others, write in)
(others, write in)
TCLP Analysis <input type="checkbox"/> (only if necessary) <input type="checkbox"/> (do TCLP regardless)
Metals
Mercury
Volatiles
Semivolatiles
(others, write in)

ORGANIC ANALYSIS

Sample(s) ID
CL-Pesticides (8081)
OP-Pesticides (8141)
PCBs (8082)
GRO (8015B)
DRO / Motor Oil / Both (circle one)
n-Hexane Extractables (1664)
Flash Point (1020)
VOCs including BTEX (8260)
VOCs - LO Level (5035)
VOCs - HI Level (5035)
SVOCs (8270)
X PAHs (8270) ISIM ABCDEF
(others, write in)

14. ANALYSIS OBJECTIVE: (check a box)
Waste Characterization
Drinking H₂O Standards (applies to D/W only)
Treatment Standards
X Others (contact Lab supervisors first)

15. DETECTION LIMIT REQUIREMENTS: (specify if known and contact lab) AS LOW AS POSSIBLE

16. SUPPLEMENTAL REQUESTS
Initials
Date

17. LAB REMARKS:

18. CHAIN OF CUSTODY:
Charles Vidair
COM
MAURICE
9/6/05 to 9/7/05
9/7/05 to 9/9/05 dnd
9/9/05 1300-1725

SEQUOIA ANALYTICAL SAMPLE RECEIPT LOG

CLIENT NAME: California Department of Pesticide Regulation **DATE REC'D AT LAB:** 9/9/05
REC. BY (PRINT): Phuc **TIME REC'D AT LAB:** 17:25
WORKORDER: MOE 0327 **DATE LOGGED IN:** 9-12-05

For Regulatory Purposes?
 DRINKING WATER YES/NO
 WASTE WATER YES/NO

CIRCLE THE APPROPRIATE RESPONSE	LAB SAMPLE #	DASH #	CLIENT ID	CONTAINER DESCRIPTION	PRESERVATIVE	PH	SAMPLE MATRIX	DATE SAMPLED	REMARKS: CONDITION (ETC.)
1. Custody Seal(s) Present / <input checked="" type="radio"/> Absent Intact / Broken*	01	A	UC1	250ml Glass Jar	—	—	W	9/9/05	→ 9/6/05
	02		UC2						
2. Chain-of-Custody Present / <input checked="" type="radio"/> Absent*	03		UC3						
3. Traffic Reports or Packing List: Present / <input checked="" type="radio"/> Absent	04		EC1						
	05		2						
4. Airbill: Airbill / Sticker Present / <input checked="" type="radio"/> Absent	06		3						
	07		FR1						
5. Airbill #:	08		2						
6. Sample Labels: Present / <input checked="" type="radio"/> Absent	09		3						
7. Sample IDs: Labeled / Not Listed on Chain-of-Custody	10		SM1						
	11		2						
8. Sample Condition: Intact / Broken* / Leaking*	12		3						
9. Does information on chain-of-custody, traffic reports and sample labels agree? <input checked="" type="radio"/> Yes / No*									
10. Sample received within hold time? <input checked="" type="radio"/> Yes / No*									
11. Adequate sample volume received? <input checked="" type="radio"/> Yes / No*									
12. Proper preservatives used? <input checked="" type="radio"/> Yes / No*									
13. Trip Blank / Temp Blank Received? (circle which, if yes) Yes / <input checked="" type="radio"/> No*									
14. Read Temp: <u>8.9°C</u> Corrected Temp: <u>↓</u> Is corrected temp 4 ± 2°C? Yes / <input checked="" type="radio"/> No* (acceptance range for samples requiring thermal pres.) Exception (if any): METALS / <input checked="" type="radio"/> DFF ON ICE Problem COC									

*IF CIRCLED, CONTACT PROJECT MANAGER AND ATTACH RECORD OF RESOLUTION.

Contractor's Report to the Board

Evaluation of Health Effects of Recycled Waste Tires in Playground and Track Products

(Publication #622-06-013)

Produced under contract by:



January 2007

Appendix C: Raw Data From Skin Sensitization Testing



PRODUCT

Rubber Tiles, EPDM Tiles, High Density Polyethylene, and Rubber Crumb

STUDY TITLE

Delayed Contact Dermal Sensitization Test - Modified Buehler Method for Solid Materials

DATA REQUIREMENT

U.S. EPA Health Effects Test Guidelines, OPPTS 870.2600 (2003)

AUTHOR

Daniel J. Merkel, B.S.

STUDY COMPLETED ON

PERFORMING LABORATORY

Product Safety Laboratories
2394 Highway 130
Dayton, New Jersey 08810

LABORATORY STUDY NUMBER

17608

STATEMENT OF NO DATA CONFIDENTIALITY CLAIMS

No claim of confidentiality is made for any information contained in this study on the basis of its falling within the scope of FIFRA 10 (d) (1) (A), (B) or (C).

Company: **CALIFORNIA EPA,
OFFICE OF ENVIRONMENTAL HEALTH HAZARD ASSESSMENT**

Company Agent:

Name

Title

Signature

Date



GOOD LABORATORY PRACTICE STATEMENT

Rubber Tiles, EPDM Tiles, High Density Polyethylene, and Rubber Crumb

This study meets the requirements of 40 CFR Part 160: U.S. EPA (FIFRA) with the following exceptions:

1. Specific information related to the determination of the stability, identity, strength, purity, and composition of the test substance as received and the concentration as tested is the responsibility of the study Sponsor (see Test Substance section).
2. The stability, uniformity of mixture and verification of concentration of alpha-Hexyleinnamaldehyde Technical (HCA) in its carriers during Product Safety Laboratories historical positive control study were not determined.

Study Director:

D. J. Merkel
 Daniel J. Merkel, B.S.
 Product Safety Laboratories

4/20/06
 Date

Submitter:

Charles Vidarin
 Signature

6/9/06
 Date

Sponsor:

Signature

Date

QUALITY ASSURANCE STATEMENT

The Product Safety Laboratories' Quality Assurance Unit reviewed this study for adherence to PSL's Standard Operating Procedures, the study protocol, and all applicable GLP standards. This final report was found to be an accurate representation of the work conducted. Records of QA findings are kept on file. The summary below provides verification of statements made in the final report section that addresses Quality Assurance audits.

QA activities for this study:

QA Activity	Date Conducted	Date Findings Reported To Study Director And Management
Protocol review	6/7/05 ¹ ; 8/10/05	6/7/05; 8/10/05
In-process inspection: <i>24 hour scoring (2nd induction); Day 29 in-life food consumption observations</i>	6/17/05; 7/8/05	8/10/05
Raw data audit	8/10/05	8/10/05
Draft report review	8/10/05	8/10/05
Final report review		

Rhonda S. Krick, B.S.
 Quality Assurance Director
 Product Safety Laboratories

¹ PSL's "generic" protocol used for this study was reviewed by the Quality Assurance group on this date.

TABLE OF CONTENTS

STATEMENT OF NO DATA CONFIDENTIALITY CLAIMS.....	2
GOOD LABORATORY PRACTICE STATEMENT.....	3
QUALITY ASSURANCE STATEMENT.....	4
TABLE OF CONTENTS.....	5
DELAYED CONTACT DERMAL SENSITIZATION TEST - MODIFIED BUEHLER METHOD FOR SOLID MATERIALS.....	6
1. PURPOSE.....	6
2. SUMMARY.....	7
3. MATERIALS.....	9
4. METHODS.....	10
5. PROCEDURE.....	11
6. EVALUATION.....	13
7. POSITIVE CONTROL VALIDATION STUDY.....	13
8. STUDY CONDUCT.....	14
9. REFERENCES.....	14
10. QUALITY ASSURANCE.....	14
11. DEVIATIONS FROM FINAL PROTOCOL.....	14
12. FINAL REPORT AND RECORDS TO BE MAINTAINED.....	14
13. RESULTS.....	14
14. CONCLUSION.....	17
SIGNATURE.....	18
TABLE 1: INDIVIDUAL BODY WEIGHTS (TEST SUBSTANCE).....	19
TABLE 2: INDIVIDUAL BODY WEIGHTS (POSITIVE CONTROL).....	23
TABLE 3: PRE-DOSE AND INDUCTION PHASE SKIN REACTION SCORES (TEST SUBSTANCE).....	24
TABLE 4: PRE-DOSE AND INDUCTION PHASE SKIN REACTION SCORES (POSITIVE CONTROL).....	31
TABLE 5: PRE-DOSE AND CHALLENGE PHASE SKIN REACTION SCORES (TEST SUBSTANCE).....	32
TABLE 6: PRE-DOSE AND CHALLENGE PHASE SKIN REACTION SCORES (POSITIVE CONTROL).....	36
TABLE 7: PRE-DOSE AND RECHALLENGE PHASE SKIN REACTION SCORES (TEST SUBSTANCE).....	37
TABLE 8: PRE-DOSE AND RECHALLENGE PHASE SKIN REACTION SCORES (POSITIVE CONTROL).....	41

DELAYED CONTACT DERMAL SENSITIZATION TEST - MODIFIED BUEHLER METHOD FOR SOLID MATERIALS

PROTOCOL NO.: P328.OEHHA

AGENCY: EPA (FIFRA)

STUDY NUMBER: 17608

SPONSOR: CALIFORNIA EPA,
OFFICE OF ENVIRONMENTAL HEALTH
HAZARD ASSESSMENT
1515 Clay Street, 16th Floor
Oakland, CA 94612

TEST SUBSTANCE IDENTIFICATION: Rubber Tiles, EPDM Tiles, High Density Polyethylene, and Rubber Crumb

PRODUCT IDENTIFICATION	PSL REFERENCE NUMBER
Rubber Tiles	041215-2D
EPDM Tiles	041215-3D
High Density Polyethylene	041215-4D
Rubber Crumb	050110-3D

TEST SUBSTANCE DESCRIPTION: Rubber tiles with cylindrical "feet", rust-colored tiles, a white sheet, and black rubber pieces

DATES RECEIVED: December 15, 2004 and January 10, 2005

STUDY INITIATION DATE: June 8, 2005

DATES OF TEST: June 9 - July 16, 2005

NOTEBOOK NO.: 05-49: pages 55-99

1. PURPOSE

To determine the potential for Rubber Tiles, EPDM Tiles, High Density Polyethylene, and Rubber Crumb to elicit a skin sensitization reaction.

2. SUMMARY

A dermal sensitization test was conducted with guinea pigs to determine the potential for Rubber Tiles, EPDM Tiles, High Density Polyethylene, and Rubber Crumb to produce sensitization after repeated topical applications.

The appropriate test substances were each topically applied to a group of ten healthy test guinea pigs, once each week for a three-week induction period. Twenty-eight days after the first induction dose, a challenge dose of the appropriate test substance was applied to a naive site on each guinea pig. Approximately 24 and 48 hours after each induction and challenge dose, the animals were scored for erythema.

A separate positive control study was conducted concurrently as PSL #17608. Due to the absence of a clear positive response at challenge, it was necessary to conduct a rechallenge in that study. Therefore, seven days after the primary challenge, a rechallenge was also conducted in this study using the original test animals. Approximately 24 and 48 hours after rechallenge patch removal the animals were scored for a sensitization response (erythema).

A table summarizing the incidence and severity of the sensitization response noted after challenge and rechallenge is found below:

Group 1

	Sensitization Response Indices			
	Incidence of Positive Response ¹		Severity ²	
	Hours		Hours	
	24	48	24	48
Test Animals	0/10	0/10	0.10	0.0
Test Animals – Rechallenge	0/10	0/10	0.05	0.0

Group 2

	Sensitization Response Indices			
	Incidence of Positive Response ¹		Severity ²	
	Hours		Hours	
	24	48	24	48
Test Animals	0/10	0/10	0.05	0.0
Test Animals – Rechallenge	0/10	0/10	0.10	0.0

¹ Animals with scores greater than 0.5.

² Sum of the erythema scores divided by the number of animals evaluated.

Group 3

	Sensitization Response Indices			
	Incidence of Positive Response ¹		Severity ²	
	Hours		Hours	
	24	48	24	48
Test Animals	0/10	0/10	0.10	0.0
Test Animals – Rechallenge	0/10	0/10	0.05	0.0

Group 4

	Sensitization Response Indices			
	Incidence of Positive Response ¹		Severity ²	
	Hours		Hours	
	24	48	24	48
Test Animals	0/9 ³	0/9	0.17	0.0
Test Animals – Rechallenge	0/9	0/9	0.0	0.0

Group 5

	Sensitization Response Indices			
	Incidence of Positive Response ¹		Severity ²	
	Hours		Hours	
	24	48	24	48
Test Animals	0/10	0/10	0.20	0.0
Test Animals – Rechallenge	0/10	0/10	0.05	0.0

Group 6

	Sensitization Response Indices			
	Incidence of Positive Response ¹		Severity ²	
	Hours		Hours	
	24	48	24	48
Test Animals	0/10	0/10	0.10	0.0
Test Animals – Rechallenge	0/10	0/10	0.15	0.0

¹ Animals with scores greater than 0.5.

² Sum of the erythema scores divided by the number of animals evaluated.

³ Animal #25768 was euthanized for humane reasons.

Group 7

	Sensitization Response Indices			
	Incidence of Positive Response ¹		Severity ²	
	Hours		Hours	
	24	48	24	48
Test Animals	0/10	0/10	0.15	0.0
Test Animals – Rechallenge	0/10	0/10	0.10	0.0

Based on the results of this study, the test substances are not considered to be contact sensitizers. The positive response observed in the positive control validation study validates the test system used in this study (see Section 7).

3. MATERIALS

A. Test Substance

The test substances were identified as follows:

Material	Rubber Tiles	EPDM Tiles	High Density Polyethylene	Rubber Crumb
PSL Ref. #	041215-2D	041215-3D	041215-4D	050110-3D
Receipt Date	12/15/04	12/15/04	12/15/04	1/10/05
Composition	Shredded automobile tires held together with a polyurethane binder	Ethylene propylene diene monomer granules held together with a polyurethane binder	High density polyethylene	Shredded automobile tires
Description	Rubber tires with cylindrical “feet”	Rust-colored tiles	White sheet	Black rubber pieces
Documentation of the methods of synthesis, fabrication, or derivation of the test article is retained by:				
	Unity Surfacing Systems 56 Bloomingdale Rd. Hicksville, NY 11801	All About Play 3844 Presidio St. Sacramento, CA 95838	TOLAS Health Care Packaging 905 Pennsylvania Blvd. Feasterville, PA 19053	West Coast Rubber Recycling 105 Leavesly Rd., #7B Gilroy, CA 95020
The test substances were expected to be stable for the duration of testing.				

¹ Animals with scores greater than 0.5.

² Sum of the erythema scores divided by the number of animals evaluated.

B. Animals

Ten test animals were indiscriminately assigned to each of the following test groups:

ANIMAL GROUP ASSIGNMENT

Group #	Induction Exposure	Challenge Exposure
1	High Density Polyethylene, 041215-4D (negative control)	High Density Polyethylene, 041215-4D (negative control)
2	High Density Polyethylene, 041215-4D (negative control)	Rubber Crumb, 050110-3D (test substance)
3	Rubber Crumb, 050110-3D (test substance)	Rubber Crumb, 050110-3D (test substance)
4	High Density Polyethylene, 041215-4D (negative control)	Rubber Tiles, 041215-2D (test substance)
5	Rubber Tiles, 041215-2D (test substance)	Rubber Tiles, 041215-2D (test substance)
6	High Density Polyethylene, 041215-4D (negative control)	EPDM Tiles, 041215-3D (test substance)
7	EPDM Tiles, 041215-3D (test substance)	EPDM Tiles, 041215-3D (test substance)

3.B.1 Number of Animals: 70

3.B.2 Sex: Male

3.B.3 Species/Strain: Guinea pigs/Hartley albino.

3.B.4 Age/Body weight: Test and Challenge/Rechallenge Groups: Young adult/males
319-418 grams at experimental start.

3.B.5 Source: Received from Elm Hill Breeding Labs, Chelmsford, MA on June 1, 2005 (Test Group).

4. METHODS

A. Husbandry

4.A.1 Housing: The animals were group housed in suspended stainless steel caging with mesh floors or plastic perforated bottom caging which conform to the size recommendations in the most recent *Guide for the Care and Use of Laboratory Animals DHEW (NIH)*. Litter paper was placed beneath the cage and was changed at least three times per week.

4.A.2 Animal Room Temperature Range: 18-23 °C



- 4.A.3 Photoperiod: 12-hour light/dark cycle
- 4.A.4 Acclimation Period: 8 days
- 4.A.5 Food: Pelleted Purina Guinea Pig Chow #5025
- 4.A.6 Water: Filtered tap water was supplied *ad-libitum* by an automatic water dispensing system.
- 4.A.7 Contaminants: There were no known contaminants reasonably expected to be found in the food or water at levels which would have interfered with the results of this study. Analyses of the food and water are conducted at least once a year and the records are kept on file at Product Safety Laboratories.

B. Identification

- 4.B.1 Cage: Each cage was identified with a cage card indicating at least the study number and identification and sex of the animal.
- 4.B.2 Animal: Each guinea pig was marked with a color code and given a sequential animal number assigned to study 17608, which constituted unique identification.

5. PROCEDURE

A. Preparation and Selection of Animals

On the day before initiation, the fur of a group of animals was removed by clipping the dorsal area and flanks. After clipping and prior to initiation, the animals were weighed and the skin was checked for any abnormalities. Only healthy animals without pre-existing skin irritation were selected for test. Animals were re-clipped prior to each dose.

B. Pre-Dose Scoring

Prior to each application, the dose sites were scored according to the scoring system described in Section 5.F.

C. Induction Phase

Once each week for three weeks, the appropriate test substance was moistened with distilled water (0.1 ml) and applied to the left side of each test animal using a 2 x 2-inch, 4-ply gauze patch. The sites were covered with dental dam and then wrapped with non-allergenic surgical tape to avoid dislocation of the patches and to minimize loss of the test substance. The High Density Polyethylene (Groups 1, 2, 4, and 6) and EPDM Tiles (Group 7) were applied as 1 x 1-inch squares. The Rubber Crumb (Group 3) and Rubber Tiles (Group 5) were applied using 0.4 g of Rubber Crumb and 1-inch diameter circles of the tiles, respectively. After the 6-hour exposure period, the patches were removed and the test sites were gently cleansed of any residual test substance. Approximately 24 and 48 hours after each induction application, readings were made of local reactions (erythema) according to the scoring system described in Section 5.F.

D. Challenge Phase

Twenty-eight days after the first induction dose, the appropriate test substance was moistened with distilled water (0.1 ml) and applied to the left side of each test animal using a 2 x 2-inch, 4-ply gauze patch to a naive site on the right side of each animal as a challenge dose, using the procedures described above. These sites were evaluated for a sensitization response (erythema) approximately 24 and 48 hours after the challenge application according to the system described in Section 5.F.

E. Rechallenge Phase

Due to the absence of a positive response in animals at the challenge dose in the positive control study, the Study Director, in consultation with the Sponsor, elected to conduct a rechallenge. Seven days after the primary challenge, a rechallenge was conducted using the original test animals. Approximately 24 and 48 hours after rechallenge patch removal, the animals were scored for a sensitization response (erythema). The test substance, as received, was applied to a naive site on each test animal, using the procedures described in 5.C. Approximately 24 and 48 hours after rechallenge patch removal the animals were scored for a sensitization response (erythema). These sites were evaluated for a sensitization response (erythema) approximately 24 and 48 hours after the rechallenge application according to the system described in Section 5.F.

F. Scoring System

- 0 - no reaction
- 0.5 - very faint erythema, usually non-confluent*
- 1 - faint erythema, usually confluent
- 2 - moderate erythema
- 3 - severe erythema with or without edema

*Very faint erythema is not considered a positive reaction.

G. Body Weights

Individual body weights of the animals were recorded prior to initiation and again on the day after challenge.

H. Clinical Observations and Food Consumption

Clinical observations were made daily on all animals during the study. Food consumption was qualitatively evaluated daily, during clinical observations.

The results for the observations for all animals #'s 25730-25799 are as follows:

Day	Observations	
	Clinical Observations	Food Consumption
0		
1, 3-38	Active and healthy	Normal
2	Animal #25768 – Gasping, moribund, ano-genital staining, death imminent, euthanized for humane reasons. All other were active and healthy.	Normal

6. EVALUATION

In order to evaluate the sensitization response at challenge, two indices were used: one for incidence and one for severity (Ritz, H. and Buehler, E., 1980) in the test and vehicle control animals.

The incidence index is the ratio of animals with erythema scores greater than 0.5 per number of animals evaluated, and is presented for both the 24 and 48-hour intervals after challenge evaluation as follows:

Incidence Index = Number of erythema scores greater than 0.5 / Number of animals evaluated

The severity index is the mean erythema score, and is calculated for both the 24 and 48-hour intervals after challenge evaluation according to the following formula:

$$\text{Severity Index} = \frac{\text{Sum of erythema scores}}{\text{Number of animals evaluated}}$$

The following criteria were used to classify the test substance as a potential contact sensitizer (Robinson, et al., 1990):

At the 24-hour and/or 48-hour scoring interval, 15% or more of the test animals exhibit a positive response (scores > 0.5) in the absence of similar results in the vehicle control group.

The positive reaction at the 24-hour interval must persist to 48 hours in at least one test animal.

7. POSITIVE CONTROL VALIDATION STUDY

The procedures used in this study were validated using alpha-Hexylcinnamaldehyde Technical, 85% (HCA) as a positive control substance. The validation study, PSL Study #17609, was performed concurrent with this study by Product Safety Laboratories and testing was completed on July 16, 2005. The raw data and report for this study are archived in Product Safety Laboratories Data Notebook No. 05-49: pages 100-113. This test was conducted at the Dayton Facility with Hartley strain albino guinea pigs from Elm Hill Breeding Labs following induction and challenge procedures similar to those described in Section 5. The results obtained from this testing are presented in Section 13.



8. STUDY CONDUCT

This study was conducted at Product Safety Laboratories, 2394 Highway 130, Dayton, New Jersey 08810. The primary scientist for this study was Anselmo Villagran, B.S. This study was conducted to comply with the Good Laboratory Practice (GLP) regulations as defined in:

- 40 CFR 160: U.S. EPA GLP Standards: Pesticide Programs (FIFRA)

and in accordance with:

- U.S. EPA Health Effects Test Guidelines, OPPTS 870.2600 (2003)

9. REFERENCES

Robinson, M., Nusair, T., Fletcher, E., and Ritz, H., A Review of the Buehler Guinea Pig Skin Sensitization Test And Its Use in a Risk Assessment Process for Human Skin Sensitization. *Toxicology*, 61, 91-107, 1990.

Ritz, H., and Buehler, E., Planning, Conduct, and Interpretation Of Guinea Pig Sensitization Patch Tests. *Current Concepts in Cutaneous Toxicity*, V.A. Drill and P. Lazar (Eds.), Academic Press, New York, 1980, page 25.

10. QUALITY ASSURANCE

The final report was audited for agreement with the raw data records and for compliance with the protocol, Product Safety Laboratories Standard Operating Procedures and appropriate Good Laboratory Practice Standards. Dates of inspections and audits performed during the study, and the dates of reporting of the inspection and audit findings to the Study Director and Facility Management are presented in the Quality Assurance Statement.

11. DEVIATIONS FROM FINAL PROTOCOL

None.

12. FINAL REPORT AND RECORDS TO BE MAINTAINED

The original, signed final report will be forwarded to the Sponsor. A copy of this signed report, together with the protocol and all raw data generated at Product Safety Laboratories, is maintained in the Product Safety Laboratories Archives. PSL will maintain these records for a period of at least five years. After this time, the Sponsor will be offered the opportunity to take possession of the records or will be charged an archiving fee for continued archiving by PSL.

13. RESULTS

Individual body weights for test and positive control animals are presented in Tables 1 and 2. Pre-Dose, Induction, Challenge, and Rechallenge Phase skin reaction scores for test and positive control animals are presented in Tables 3 through 8.

Due to the fact that death appeared imminent, one test animal was euthanized for humane reasons within the initial 48 hours during the first induction. Toxic signs noted prior to death included gasping, hypoactivity, ano-genital staining, and moribund appearance. Gross necropsy of the decedent revealed discoloration of the lungs, intestines, and entire area of the reproductive organs. However, all other animals appeared active and healthy during the entire observation period.

Induction Phase

Test Animal Groups 1, 2, 4, and 6 - (100% High Density Polyethylene, as received): Very faint erythema (0.5) was noted for some test sites during the induction phase.

Test Animal Group 3 - (100% Rubber Crumb, as received): Very faint erythema (0.5) was noted for some test sites during the induction phase.

Test Animal Group 5 - (100% Rubber Tiles, as received): Very faint erythema (0.5) was noted for some test sites during the induction phase.

Test Animal Group 7 - (100% EPDM Tiles, as received): Very faint erythema (0.5) was noted for some test sites during the induction phase.

Positive Control Animals (HCA applied undiluted): Very faint erythema (0.5) was noted for most test sites during the induction phase.

Challenge Phase

Test Animal Group 1 - (100% High Density Polyethylene): Very faint erythema (0.5) was noted for two of ten test sites 24 hours following the challenge application. Irritation cleared from all sites by 48 hours.

Test Animal Group 2 - (100% Rubber Crumb): Very faint erythema (0.5) was noted for one of ten test sites 24 hours following the challenge application. Irritation cleared from all sites by 48 hours.

Test Animal Group 3 - (100% Rubber Crumb): Very faint erythema (0.5) was noted for two of ten test sites 24 hours following the challenge application. Irritation cleared from all sites by 48 hours.

Test Animal Group 4 - (100% Rubber Tiles): Very faint erythema (0.5) was noted for three of nine test sites 24 hours following the challenge application. Irritation cleared from all sites by 48 hours.

Test Animal Group 5 - Test Animals (100% Rubber Tiles): Very faint erythema (0.5) was noted for four of ten test sites 24 hours following the challenge application. Irritation cleared from all sites by 48 hours.



Test Animal Group 6 - Test Animals (100% EPDM Tiles): Very faint erythema (0.5) was noted for two of ten test sites 24 hours following the challenge application. Irritation cleared from all sites by 48 hours.

Test Animal Group 7- Test Animals (100% EPDM Tiles): Very faint erythema (0.5) was noted for three of nine test sites 24 hours following the challenge application. Irritation cleared from all sites by 48 hours.

Positive Control Animals (HCA applied undiluted): Very faint erythema (0.5) was noted for three of ten test sites 24 hours following the challenge application. Irritation cleared from all sites by 48 hours.

Naive Control Animals (HCA applied undiluted): Very faint erythema (0.5) was noted for one of five naive control sites 24 hours after challenge. Irritation cleared from all sites by 48 hours.

Rechallenge Phase

Test Animal Group 1 - (100% High Density Polyethylene): Very faint erythema (0.5) was noted for one of ten test sites 24 hours following the rechallenge application. Irritation cleared from all sites by 48 hours.

Test Animal Group 2 - (100% Rubber Crumb): Very faint erythema (0.5) was noted for two of ten test sites 24 hours following the rechallenge application. Irritation cleared from all sites by 48 hours.

Test Animal Group 3 - (100% Rubber Crumb): Very faint erythema (0.5) was noted for one of ten test sites 24 hours following the rechallenge application. Irritation cleared from all sites by 48 hours.

Test Animal Group 4 - (100% Rubber Tiles): Very faint erythema (0.5) was noted for two of nine test sites 24 hours following the rechallenge application. Irritation cleared from all sites by 48 hours.

Test Animal Group 5 - Test Animals (100% Rubber Tiles): Very faint erythema (0.5) was noted for one of ten test sites 24 hours following the rechallenge application. Irritation cleared from all sites by 48 hours.

Test Animal Group 6 - Test Animals (100% EPDM Tiles): Very faint erythema (0.5) was noted for three of ten test sites 24 hours following the rechallenge application. Irritation cleared from all sites by 48 hours.

Test Animal Group 7- Test Animals (100% EPDM Tiles): Very faint erythema (0.5) was noted for two of ten test sites 24 hours following the rechallenge application. Irritation cleared from all sites by 48 hours.



Positive Control Animals (HCA applied undiluted): Five of ten animals exhibited signs of a sensitization response [faint to severe erythema (1-3)] 24 hours after rechallenge. Similar irritation persisted for four sites through 48 hours. Very faint erythema (0.5) was observed at two test sites.

Naive Control Animals (HCA applied undiluted): Very faint erythema (0.5) was noted at two of five naive control sites 24 hours after challenge. Irritation cleared from all sites by 48 hours.

14. **CONCLUSION**

Based on these findings and on the evaluation system used, Rubber Tiles, EPDM Tiles, High Density Polyethylene, and Rubber Crumb are not considered to be contact sensitizers.

The positive response observed in the positive control validation study with alpha-Hexylcinnamaldehyde Technical (HCA) validates the test system used in this study (see Section 7).

SIGNATURE

Rubber Tiles, EPDM Tiles, High Density Polyethylene, and Rubber Crumb

I, the undersigned, declare that the methods, results and data contained in this report faithfully reflect the procedures used and raw data collected during the study.

Daniel J. Merkel, B.S.
Study Director
Product Safety Laboratories

Date

TABLE 1: INDIVIDUAL BODY WEIGHTS (TEST SUBSTANCE)

Test Substance

Group 1

Animal No.	Sex	Initial (g)	Day After Challenge (g)
25730	M	383	596
25731	M	385	550
25732	M	389	629
25733	M	387	617
25734	M	374	565
25735	M	387	564
25736	M	355	566
25737	M	361	574
25738	M	347	601
25739	M	406	633

Group 2

Animal No.	Sex	Initial (g)	Day After Challenge (g)
25740	M	369	622
25741	M	360	618
25742	M	368	572
25743	M	363	515
25744	M	364	571
25745	M	351	568
25746	M	355	556
25747	M	351	563
25748	M	373	608
25749	M	414	625

TABLE 1 (cont.): INDIVIDUAL BODY WEIGHTS (TEST SUBSTANCE)

Test Substance

Group 3

Animal No.	Sex	Initial (g)	Day After Challenge (g)
25750	M	365	561
25751	M	412	696
25752	M	375	583
25753	M	372	639
25754	M	381	545
25755	M	375	527
25756	M	366	526
25757	M	369	487
25758	M	357	508
25759	M	369	575

Group 4

Animal No.	Sex	Initial (g)	Day After Challenge (g)
25760	M	377	551
25761	M	362	548
25762	M	371	684
25763	M	417	565
25764	M	375	611
25765	M	355	533
25766	M	376	558
25767	M	399	584
25768	M	319	- ¹
25769	M	366	489

¹ Animal #25768 was euthanized for humane reasons, body weight was taken prior to euthanasia (315 g).

TABLE 1 (cont.): INDIVIDUAL BODY WEIGHTS (TEST SUBSTANCE)

Test Substance

Group 5

Animal No.	Sex	Initial (g)	Day After Challenge (g)
25770	M	361	633
25771	M	368	607
25772	M	378	633
25773	M	375	686
25774	M	370	591
25775	M	379	664
25776	M	384	674
25777	M	354	623
25778	M	346	562
25779	M	386	655

Group 6

Animal No.	Sex	Initial (g)	Day After Challenge (g)
25780	M	418	606
25781	M	361	548
25782	M	372	571
25783	M	381	615
25784	M	363	491
25785	M	370	520
25786	M	371	597
25787	M	382	652
25788	M	365	598
25789	M	382	648

TABLE 1 (cont.): INDIVIDUAL BODY WEIGHTS (TEST SUBSTANCE)

Test Substance

Group 7

Animal No.	Sex	Initial (g)	Day After Challenge (g)
25790	M	374	574
25791	M	358	589
25792	M	371	615
25793	M	409	707
25794	M	385	557
25795	M	387	545
25796	M	368	553
25797	M	391	597
25798	M	368	581
25799	M	385	575

TABLE 2: INDIVIDUAL BODY WEIGHTS (POSITIVE CONTROL)

Positive Control Validation Study¹

Positive Control Group

Animal No.	Sex	Initial (g)	Day After Challenge (g)
25800	M	426	656
25801	M	373	658
25802	M	356	679
25803	M	367	621
25804	M	404	684
25805	M	381	612
25806	M	389	605
25807	M	399	657
25808	M	387	668
25809	M	381	560

Naive Control Group

Animal No.	Sex	Initial (g)	Day After Challenge (g)
25810	M	357	614
25811	M	384	631
25812	M	347	573
25813	M	383	661
25814	M	358	530

¹ PSL Study #17609, performed by PSL, concurrent with this study. Testing was completed on July 16, 2005.

TABLE 3: PRE-DOSE AND INDUCTION PHASE SKIN REACTION SCORES (TEST SUBSTANCE)

Test Substance

Group 1

PRE-DOSE

Induction Number	1	2	3
Concentration	100%	100%	100%
Amount Applied¹	N/A	N/A	N/A
Hours²	Pre-Dose Scoring		
Animal No.			
25730	0	0	0
25731	0	0	0
25732	0	0	0
25733	0	0	0
25734	0	0	0
25735	0	0	0
25736	0	0	0
25737	0	0	0
25738	0	0	0
25739	0	0	0

INDUCTION

Induction Number	1		2		3	
Concentration	100%		100%		100%	
Amount Applied¹	N/A		N/A		N/A	
Hours²	24	48	24	48	24	48
Animal No.						
25730	0	0	0	0	0	0
25731	0	0	0	0	0	0
25732	0	0	0.5	0	0	0
25733	0.5	0	0	0	0	0
25734	0	0	0	0	0	0
25735	0	0	0.5	0	0	0
25736	0	0	0	0	0	0
25737	0	0	0	0	0	0
25738	0	0	0	0	0	0
25739	0	0	0.5	0	0	0

¹ The test substance was moistened with distilled water and applied as 1 x 1-inch squares.

² Hours after induction dose.

**TABLE 3 (cont.): PRE-DOSE AND INDUCTION PHASE SKIN REACTION SCORES
(TEST SUBSTANCE)**

Test Substance

Group 2

PRE-DOSE

Induction Number	1	2	3
Concentration	100%	100%	100%
Amount Applied¹	N/A	N/A	N/A
Hours²	Pre-Dose Scoring		
Animal No.			
25740	0	0	0
25741	0	0	0
25742	0	0	0
25743	0	0	0
25744	0	0	0
25745	0	0	0
25746	0	0	0
25747	0	0	0
25748	0	0	0
25749	0	0	0

INDUCTION

Induction Number	1		2		3	
Concentration	100%		100%		100%	
Amount Applied¹	N/A		N/A		N/A	
Hours²	24	48	24	48	24	48
Animal No.						
25740	0	0	0	0	0	0
25741	0	0	0.5	0	0	0
25742	0	0	0.5	0.5	0.5	0
25743	0	0	0	0	0	0
25744	0	0	0	0	0	0
25745	0	0	0	0	0	0
25746	0	0	0	0	0	0
25747	0	0	0	0	0	0
25748	0	0	0	0	0	0
25749	0	0	0	0	0	0

¹ The test substance was moistened with distilled water and applied as 1 x 1-inch squares.

² Hours after induction dose.

**TABLE 3 (cont.): PRE-DOSE AND INDUCTION PHASE SKIN REACTION SCORES
(TEST SUBSTANCE)**

Test Substance

Group 3

PRE-DOSE

Induction Number	1	2	3
Concentration ¹	100%	100%	100%
Amount Applied (g)	0.4	0.4	0.4
Hours ²	Pre-Dose Scoring		
Animal No.			
25750	0	0	0
25751	0	0	0
25752	0	0	0
25753	0	0	0
25754	0	0	0
25755	0	0	0
25756	0	0	0
25757	0	0	0
25758	0	0	0
25759	0	0	0

INDUCTION

Induction Number	1		2		3	
Concentration ¹	100%		100%		100%	
Amount Applied (g)	0.4		0.4		0.4	
Hours ²	24	48	24	48	24	48
Animal No.						
25750	0.5	0.5	0	0	0	0
25751	0	0	0	0	0	0
25752	0	0	0.5	0	0	0
25753	0	0	0	0	0.5	0
25754	0.5	0	0	0	0	0
25755	0	0	0	0	0	0
25756	0	0	0.5	0	0	0
25757	0	0	0	0	0	0
25758	0	0	0	0	0	0
25759	0	0	0	0	0	0

¹ The test substance was moistened with distilled water and applied

² Hours after induction dose.

**TABLE 3 (cont.): PRE-DOSE AND INDUCTION PHASE SKIN REACTION SCORES
(TEST SUBSTANCE)**

Test Substance

Group 4

PRE-DOSE

Induction Number	1	2	3
Concentration ¹	100%	100%	100%
Amount Applied	N/A	N/A	N/A
Hours ²	Pre-Dose Scoring		
Animal No.			
25760	0	0	0
25761	0	0	0
25762	0	0	0
25763	0	0	0
25764	0	0	0
25765	0	0	0
25766	0	0	0
25767	0	0	0
25768	0	- ³	-
25769	0	0	0

INDUCTION

Induction Number	1		2		3	
Concentration ¹	100%		100%		100%	
Amount Applied	N/A		N/A		N/A	
Hours ²	24	48	24	48	24	48
Animal No.						
25760	0.5	0.5	0	0	0	0
25761	0	0	0	0	0	0
25762	0	0	0	0	0	0
25763	0	0	0.5	0	0	0
25764	0	0	0	0	0	0
25765	0	0	0	0	0	0
25766	0	0	0.5	0	0	0
25767	0	0	0	0	0	0
25768	0	- ³	-	-	-	-
25769	0	0	0.5	0	0	0

¹ The test substance was moistened with distilled water and applied as 1 x 1-inch squares.

² Hours after induction dose.

³ Animal #25768 was euthanized for humane reasons.

**TABLE 3 (cont.): PRE-DOSE AND INDUCTION PHASE SKIN REACTION SCORES
(TEST SUBSTANCE)**

Test Substance

Group 5

PRE-DOSE

Induction Number	1	2	3
Concentration ¹	100%	100%	100%
Amount Applied	N/A	N/A	N/A
Hours ²	Pre-Dose Scoring		
Animal No.			
25770	0	0	0
25771	0	0	0
25772	0	0	0
25773	0	0	0
25774	0	0	0
25775	0	0	0
25776	0	0	0
25777	0	0	0
25778	0	0	0
25779	0	0	0

INDUCTION

Induction Number	1		2		3	
Concentration ¹	100%		100%		100%	
Amount Applied	N/A		N/A		N/A	
Hours ²	24	48	24	48	24	48
Animal No.						
25770	0.5	0	0	0	0	0
25771	0	0	0	0	0	0
25772	0.5	0.5	0.5	0	0	0
25773	0	0	0	0	0	0
25774	0	0	0	0	0	0
25775	0	0	0	0	0	0
25776	0.5	0.5	0.5	0	0	0
25777	0	0	0	0	0	0
25778	0.5	0.5	0.5	0	0	0
25779	0	0	0.5	0	0	0

¹ The test substance was moistened with distilled water and applied as one-inch diameter circles.

² Hours after induction dose.

**TABLE 3 (cont.): PRE-DOSE AND INDUCTION PHASE SKIN REACTION SCORES
(TEST SUBSTANCE)**

Test Substance

Group 6

PRE-DOSE

Induction Number	1	2	3
Concentration¹	100%	100%	100%
Amount Applied	N/A	N/A	N/A
Hours²	Pre-Dose Scoring		
Animal No.			
25780	0	0	0
25781	0	0	0
25782	0	0	0
25783	0	0	0
25784	0	0	0
25785	0	0	0
25786	0	0	0
25787	0	0	0
25788	0	0	0
25789	0	0	0

INDUCTION

Induction Number	1		2		3	
Concentration¹	100%		100%		100%	
Amount Applied	N/A		N/A		N/A	
Hours²	24	48	24	48	24	48
Animal No.						
25780	0	0	0	0	0	0
25781	0	0	0.5	0	0	0
25782	0	0	0.5	0	0	0
25783	0	0	0	0	0	0
25784	0	0	0	0	0	0
25785	0	0	0	0	0.5	0
25786	0.5	0.5	0	0	0	0
25787	0	0	0	0	0	0
25788	0	0	0	0	0	0
25789	0	0	0	0	0	0

¹ The test substance was moistened with distilled water and applied as 1 x 1-inch squares.

² Hours after induction dose.

**TABLE 3 (cont.): PRE-DOSE AND INDUCTION PHASE SKIN REACTION SCORES
(TEST SUBSTANCE)**

Test Substance

Group 7

PRE-DOSE

Induction Number	1	2	3
Concentration ¹	100%	100%	100%
Amount Applied	N/A	N/A	N/A
Hours ²	Pre-Dose Scoring		
Animal No.			
25790	0	0	0
25791	0	0	0
25792	0	0	0
25793	0	0	0
25794	0	0	0
25795	0	0	0
25796	0	0	0
25797	0	0	0
25798	0	0	0
25799	0	0	0

INDUCTION

Induction Number	1		2		3	
Concentration ¹	100%		100%		100%	
Amount Applied	N/A		N/A		N/A	
Hours ²	24	48	24	48	24	48
Animal No.						
25790	0	0	0.5	0	0.5	0
25791	0	0	0	0	0	0
25792	0.5	0	0.5	0	0	0
25793	0	0	0	0	0	0
25794	0	0	0	0	0	0
25795	0	0	0.5	0	0	0
25796	0.5	0	0	0	0	0
25797	0	0	0	0	0	0
25798	0	0	0	0	0	0
25799	0	0	0	0	0.5	0

¹ The test substance was moistened with distilled water and applied as 1 x 1-inch squares.

² Hours after induction dose.

TABLE 4: PRE-DOSE AND INDUCTION PHASE SKIN REACTION SCORES (POSITIVE CONTROL)

Positive Control Validation Study¹

Positive Control Group

PRE-DOSE

Induction Number	1	2	3
Concentration	Undiluted	Undiluted	Undiluted
Amount Applied (ml)	0.4	0.4	0.4
Hours²	Pre-Dose Scoring		
Animal No.			
25800	0	0	0
25801	0	0	0
25802	0	0	0
25803	0	0	0
25804	0	0	0
25805	0	0	0
25806	0	0	0
25807	0	0	0
25808	0	0	0
25809	0	0	0

INDUCTION

Induction Number	1		2		3	
Concentration	Undiluted		Undiluted		Undiluted	
Amount Applied (ml)	0.4		0.4		0.4	
Hours²	24	48	24	48	24	48
Animal No.						
25800	0	0	0	0	0.5	0.5
25801	0	0	0	0	0	0
25802	0.5	0	0.5	0	0	0
25803	0	0	0.5	0	0.5	0
25804	0	0	0	0	0	0
25805	0.5	0	0.5	0	0.5	0.5
25806	0	0	0	0	0	0
25807	0	0	0	0	0.5	0.5
25808	0	0	0.5	0	0.5	0
25809	0	0	0	0	0	0

¹ PSL Study #17609, performed by PSL, concurrent with this study. Testing was completed on July 16, 2005.

² Hours after induction dose.

TABLE 5: PRE-DOSE AND CHALLENGE PHASE SKIN REACTION SCORES (TEST SUBSTANCE)

Test Substance

Group 1¹

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25730	0	0	0
25731	0	0	0
25732	0	0.5	0
25733	0	0	0
25734	0	0	0
25735	0	0	0
25736	0	0	0
25737	0	0	0
25738	0	0.5	0
25739	0	0	0

Group 2²

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25740	0	0	0
25741	0	0	0
25742	0	0	0
25743	0	0	0
25744	0	0	0
25745	0	0.5	0
25746	0	0	0
25747	0	0	0
25748	0	0	0
25749	0	0	0

¹ The test substance was moistened with distilled water and applied as 1 x 1-inch squares.

² The test substance was moistened with distilled water and applied.

**TABLE 5 (cont.): PRE-DOSE AND CHALLENGE PHASE SKIN REACTION SCORES
(TEST SUBSTANCE)**

Test Substance

Group 3¹

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25750	0	0	0
25751	0	0.5	0
25752	0	0	0
25753	0	0.5	0
25754	0	0	0
25755	0	0	0
25756	0	0	0
25757	0	0	0
25758	0	0	0
25759	0	0	0

Group 4²

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25760	0	0	0
25761	0	0	0
25762	0	0	0
25763	0	0	0
25764	0	0	0
25765	0	0.5	0
25766	0	0.5	0
25767	0	0.5	0
25768 ³	0	-	-
25769	0	0	0

¹ The test substance was moistened with distilled water and applied.

² The test substance was moistened with distilled water and applied as one-inch diameter circles.

³ Animal #25768 was euthanized for humane reasons.

**TABLE 5 (cont.): PRE-DOSE AND CHALLENGE PHASE SKIN REACTION SCORES
(TEST SUBSTANCE)**

Test Substance Group

Group 5¹

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25770	0	0.5	0
25771	0	0	0
25772	0	0	0
25773	0	0.5	0
25774	0	0	0
25775	0	0.5	0
25776	0	0	0
25777	0	0	0
25778	0	0	0
25779	0	0.5	0

Group 6²

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25780	0	0.5	0
25781	0	0	0
25782	0	0	0
25783	0	0	0
25784	0	0	0
25785	0	0	0
25786	0	0	0
25787	0	0	0
25788	0	0.5	0
25789	0	0	0

¹ The test substance was moistened with distilled water and applied as one-inch diameter circles.

² The test substance was moistened with distilled water and applied as 1 x 1-inch squares.

**TABLE 5 (cont.): PRE-DOSE AND CHALLENGE PHASE SKIN REACTION SCORES
(TEST SUBSTANCE)**

Test Substance Group¹

Group 7

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25790	0	0	0
25791	0	0	0
25792	0	0.5	0
25793	0	0	0
25794	0	0.5	0
25795	0	0	0
25796	0	0	0
25797	0	0	0
25798	0	0.5	0
25799	0	0	0

¹The test substance was moistened with distilled water and applied as 1 x 1-inch squares.

TABLE 6: PRE-DOSE AND CHALLENGE PHASE SKIN REACTION SCORES (POSITIVE CONTROL)

Positive Control Validation Study¹

Positive Control Group²

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25800	0	0	0
25801	0	0	0
25802	0	0.5	0
25803	0	0	0
25804	0	0	0
25805	0	0	0
25806	0	0.5	0
25807	0	0	0
25808	0	0.5	0
25809	0	0	0

Naive Control Group²

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25810	0	0	0
25811	0	0	0
25812	0	0.5	0
25813	0	0	0
25814	0	0	0

¹ PSL Study #17609, performed by PSL, concurrent with this study. Testing was completed on July 16, 2005.

² Four-tenths of a milliliter of the test substance was applied undiluted.

**TABLE 7: PRE-DOSE AND RECHALLENGE PHASE SKIN REACTION SCORES
(TEST SUBSTANCE)**

Test Substance

Group 1¹

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25730	0	0	0
25731	0	0	0
25732	0	0	0
25733	0	0	0
25734	0	0	0
25735	0	0	0
25736	0	0	0
25737	0	0	0
25738	0	0.5	0
25739	0	0	0

Group 2²

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25740	0	0.5	0
25741	0	0	0
25742	0	0	0
25743	0	0	0
25744	0	0	0
25745	0	0	0
25746	0	0.5	0
25747	0	0	0
25748	0	0	0
25749	0	0	0

¹The test substance was moistened with distilled water and applied as 1 x 1-inch squares.

²The test substance was moistened with distilled water and applied.

**TABLE 7 (cont.): PRE-DOSE AND RECHALLENGE PHASE SKIN REACTION SCORES
(TEST SUBSTANCE)**

Test Substance

Group 3¹

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25750	0	0	0
25751	0	0	0
25752	0	0	0
25753	0	0	0
25754	0	0	0
25755	0	0	0
25756	0	0	0
25757	0	0.5	0
25758	0	0	0
25759	0	0	0

Group 4²

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25760	0	0	0
25761	0	0	0
25762	0	0	0
25763	0	0	0
25764	0	0	0
25765	0	0	0
25766	0	0	0
25767	0	0	0
25768 ³	0	-	-
25769	0	0	0

¹ The test substance was moistened with distilled water and applied.

² The test substance was moistened with distilled water and applied as one-inch diameter circles.

³ Animal #25768 was euthanized for humane reasons.

**TABLE 7 (cont.): PRE-DOSE AND RECHALLENGE PHASE SKIN REACTION SCORES
(TEST SUBSTANCE)**

Test Substance

Group 5¹

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25770	0	0	0
25771	0	0	0
25772	0	0	0
25773	0	0	0
25774	0	0	0
25775	0	0	0
25776	0	0.5	0
25777	0	0	0
25778	0	0	0
25779	0	0	0

Group 6²

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25780	0	0	0
25781	0	0	0
25782	0	0	0
25783	0	0.5	0
25784	0	0	0
25785	0	0.5	0
25786	0	0	0
25787	0	0	0
25788	0	0.5	0
25789	0	0	0

¹The test substance was moistened with distilled water and applied as one-inch diameter circles.

²The test substance was moistened with distilled water and applied as 1 x 1-inch squares.

**TABLE 7 (cont.): PRE-DOSE AND RECHALLENGE PHASE SKIN REACTION SCORES
(TEST SUBSTANCE)**

Test Substance

Group 7¹

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25790	0	0	0
25791	0	0	0
25792	0	0	0
25793	0	0	0
25794	0	0.5	0
25795	0	0	0
25796	0	0	0
25797	0	0.5	0
25798	0	0	0
25799	0	0	0

¹The test substance was moistened with distilled water and applied as 1 x 1-inch squares.

**TABLE 8: PRE-DOSE AND RECHALLENGE PHASE SKIN REACTION SCORES
(POSITIVE CONTROL)**

Positive Control Validation Study¹

Positive Control Group²

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
25800	0	1	0.5
25801	0	0.5	0
25802	0	2	1
25803	0	0.5	0
25804	0	3	2
25805	0	2	2
25806	0	0	0
25807	0	3	3
25808	0	0	0
25809	0	0	0

Naive Control Group²

Animal No.	Pre-Dose	Hours after Dosing	
		24	48
26548	0	0	0
26549	0	0.5	0
26550	0	0.5	0
26551	0	0	0
26552	0	0	0

¹ PSL Study #17609, performed by PSL, concurrent with this study. Testing was completed on July 16, 2005.

² Four-tenths of a milliliter of the test substance was applied undiluted.